

PNNL-36963, Rev 0

Materials Characterization, Prediction, and Control Project

Summary Report on Material Characterization, Part 2
September 2024

DR Todd	A Guzman
K Nwe	A Ortiz
M Pole	MJ Olszta
Y Guo	O Linsuain

With contributions from:

DM Brown	H Das
C Minerich	KA Ross
JD Escobar Atehortua	EI Barker
D Garcia	LE Smith
T Wang	

DISCLAIMER

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor Battelle Memorial Institute, nor any of their employees, makes **any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights.** Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or Battelle Memorial Institute. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

PACIFIC NORTHWEST NATIONAL LABORATORY
operated by
BATTELLE
for the
UNITED STATES DEPARTMENT OF ENERGY
under Contract DE-AC05-76RL01830

Printed in the United States of America

Available to DOE and DOE contractors from
the Office of Scientific and Technical Information,
P.O. Box 62, Oak Ridge, TN 37831-0062
www.osti.gov
ph: (865) 576-8401
fox: (865) 576-5728
email: reports@osti.gov

Available to the public from the National Technical Information Service
5301 Shawnee Rd., Alexandria, VA 22312
ph: (800) 553-NTIS (6847)
or (703) 605-6000
email: info@ntis.gov
Online ordering: <http://www.ntis.gov>

Materials Characterization, Prediction, and Control Project

Summary Report on Material Characterization, Part 2

September 2024

DR Todd	A Guzman
K Nwe	A Ortiz
M Pole	MJ Olszta
Y Guo	O Linsuain

With contributions from:

DM Brown	H Das
C Minerich	KA Ross
JD Escobar Atehortua	EI Barker
D Garcia	LE Smith
T Wang	

Prepared for
the U.S. Department of Energy
under Contract DE-AC05-76RL01830

Pacific Northwest National Laboratory
Richland, Washington 99354

Acknowledgments

This research was supported by the Materials Characterization, Prediction, and Control (MCPC) investment, under the Laboratory Directed Research and Development (LDRD) Program at Pacific Northwest National Laboratory (PNNL). PNNL is a multi-program national laboratory operated for the Department of Energy (DOE) by Battelle Memorial Institute under Contract No. DE-AC05-76RL01830.

Authorship for this report reflects substantial contributions in collecting, curating, interpreting, and/or technical leadership of MCPC Material Characterization Vertex activities throughout the duration of the project. Those responsible for specific characterization activities are identified in report attachments that describe that data.

Acronyms and Abbreviations

DOI	Digital Object Identifier – also doi
EBSD	Electron Backscatter Diffraction
FOM	Figure-of-Merit
FSP	friction stir processing
MCPC	Materials Characterization, Prediction, and Control
PNNL	Pacific Northwest National Laboratory
SEM	scanning electron microscopy
SHA1	Secure Hash Algorithm 1
UT	ultrasonic testing

Contents

Acknowledgments	ii
Acronyms and Abbreviations	ii
1.0 Introduction and Background	1
2.0 Scope	3
3.0 Sample Identification and Naming	4
4.0 Material Characterization Modalities	6
5.0 Example Product Metrics from Material Characterization	8
5.1 Tabulations of Example Product Metrics	8
5.2 Graphical Representations of Product Metrics	10
6.0 Structure of Electronic Modality Data	14
6.1 Approach	14
6.2 Structure of Data	14
7.0 References	18

Figures

Figure 1. Example FSP specimens.	4
Figure 2. Example SEM and EBSD measurement locations.....	7
Figure 3. Circle-equivalent mean grain diameter versus nominal processing temperature.	10
Figure 4. Hardness versus nominal processing temperature.	11
Figure 5. UT FOM nominal processing temperature.	11
Figure 6. Hardness and mean grain size relationship.	12
Figure 7. UT FOM versus intercept-based grain diameter.	13
Figure 8. Illustration of typical file structure.	15
Figure 9. Example YAML metadata parameter file.....	17

Tables

Table 1. Nominal process conditions for FSP experiments.....	1
Table 2. Condition, Sample, and Specimen ID matrix for each modality.	5
Table 3. FSP conditions per sample (sorted by Sample ID).....	9
Table 4. Tabulated modality data per sample.	9

Attachments


- Attachment A. MCPC Round 2 Material Characterization Results for Modality EBSD
- Attachment B. MCPC Round 2 Material Characterization Results for Modality HARDNESS
- Attachment C. MCPC Round 2 Material Characterization Results for Modality OPTICAL
- Attachment D. MCPC Round 2 Material Characterization Results for Modality SEM
- Attachment E. MCPC Round 2 Material Characterization Results for Modality ULTRASONIC

1.0 Introduction and Background

The Pacific Northwest National Laboratory (PNNL) undertook the Materials Characterization, Prediction, and Control (MCPC) Laboratory Directed Research and Development Project to advance understanding of nuclear material processing and enable multifold acceleration in the development and qualification of new material systems in national security and advanced energy applications (Smith 2021). The MCPC Project executed research across three scientific vertices—material characterization, predictive modeling, and data analytics—with extensive support by a data curation and management team.

The central technical objective in the MCPC Project was to improve the prediction and characterization of the process-structure-property relationships within the microstructurally refined region of stainless-steel samples prepared utilizing friction stir processing (FSP). Application of the FSP technique is well established at PNNL within the Solid Phase Processing capability through many years of investment across a range of materials and applications (PNNL 2024).

Three distinct rounds of FSP experiments were performed by the experimental team, producing replicate samples across eleven different nominal processing conditions (Condition IDs) listed in Table 1. The starting material on which FSP was applied was commercially available unprocessed stainless-steel type 316L material. Chosen processing conditions were very diverse, and some were intentionally chosen to produce defects. Several samples experienced tool breakage during experimentation, so a full set of three replicates was not produced for every nominal processing condition.

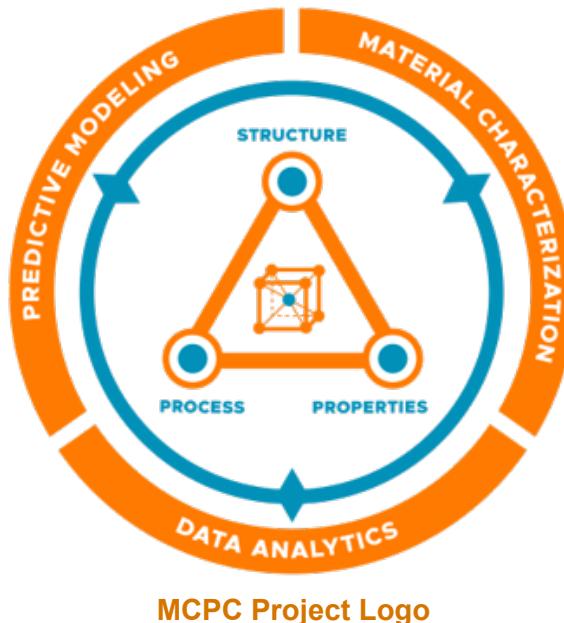

MCPC Project Logo

Table 1. Nominal process conditions for FSP experiments.

Condition ID	Temperature (°C)	Tool traverse (in/min)	Tool traverse (mm/min)	Force (lbs)	Force (kN)
C00	N/A	N/A	N/A	N/A	N/A
C01	720	0.5	12.7	9000	40.0
C02	720	0.5	12.7	10500	46.7
C03	720	1.0	25.4	10500	46.7
C04	720	1.0	25.4	9000	40.0
C05	720	3.0	76.2	10500	46.7
C06	750	1.0	25.4	10500	46.7
C07	750	3.0	76.2	10500	46.7
C08	800	1.0	25.4	10500	46.7

Condition ID	Temperature (°C)	Tool traverse (in/min)	Tool traverse (mm/min)	Force (lbs)	Force (kN)
C09	800	3.0	76.2	10500	46.7
C10	850	1.0	25.4	10500	46.7
C11	850	3.0	76.2	10500	46.7

Condition ID “C00” represents the unprocessed starting material in the form of a control sample. “Temperature” is the sensed value within the FSP tool and not the working temperature at the tool/steel interface.

The Material Characterization task within the MCPC Project was tasked with delivering results from two primary characterization approaches: 1) destructive characterization modalities utilizing traditional forms of microstructure and property evaluation, and 2) a nondestructive ultrasonic testing modality capable of full-volume interrogation for defects and microstructure characteristics. Material characterization data was obtained via five characterization modalities across the destructive and nondestructive approaches. The modalities are listed below alphabetically based on the names used with the curated datasets:

- Electron Backscatter Diffraction (EBSD): *Data for this modality is curated and archived with the identifying name “EBSD” in curated datasets.*
- Hardness testing via microscopic indentation method: *Data for this modality is curated and archived with the identifying name “HARDNESS” in curated datasets.*
- Optical Microscopy: *Data for this modality is curated and archived with the identifying name “OPTICAL” in curated datasets.*
- Scanning electron microscopy (SEM): *Data for this modality is curated and archived with the identifying name “SEM” in curated datasets.*
- Ultrasonic testing (UT) is referred to as nondestructive examination in some project documentation: *Data for this modality is curated and archived with the identifying name “ULTRASONIC” in curated datasets.*

Background information on these and other material characterization modalities relevant to FSP can be found in Glass et al. (2024).

As described in this report, material characterization data from each round and modality was carefully curated and key metadata collected to ensure traceability, reproducibility, and explainability of the MCPC datasets. Implementation of modern data management and curation was a central theme in MCPC, which facilitated efficient uptake and utilization, including in the calculation of example metrics via predictive modeling and data analytics methods for each nominal process condition. It is anticipated that the significant body of curated material characterization data developed under MCPC will be utilized for other research at PNNL and beyond in the future.

2.0 Scope

This report summarizes key data from material characterization Round 2 of the MCPC Project. It is one in a series of summary reports¹ that describe material characterization data obtained in the project. Each summary report captures data from a distinct round of experimentation and characterization and contains results for up to eleven different FSP nominal processing conditions for each of the five characterization modalities (see Table 1). Electronic versions of the materials described here, along with a large volume of similar data for the round, are made available via the PNNL DataHub (<https://data.pnnl.gov>) platform. Associated Digital Object Identifiers (doi) will be minted upon publication of the data. This report is structured as follows:

- Section 3: Sample identification and naming
- Section 4: Material characterization modalities
- Section 5: Example product metrics from material characterization
- Section 6: Structure of electronic modality data
- Attachment A: Material Characterization Results for Modality EBSD
- Attachment B: Material Characterization Results for Modality HARDNESS
- Attachment C: Material Characterization Results for Modality OPTICAL
- Attachment D: Material Characterization Results for Modality SEM
- Attachment E: Material Characterization Results for Modality ULTRASONIC

¹ A project bibliography is available in other MCPC Project publications. The report establishes a baseline reference for future reports, conference papers, and journal articles produced by the MCPC Project to build upon.

3.0 Sample Identification and Naming

Samples were produced from FSP experimentation at each nominal process condition¹, where processing conditions were programmed to be constant across the entire length of a sample. Samples were identified with a unique *Sample ID*, and replicate application of the same Condition ID on multiple sets of similar starting material produced distinct Sample IDs.

Several individual specimens were sectioned for measurement in the various modalities from each unique sample. Example specimens are shown in Figure 1. Each specimen was marked with a unique *Specimen ID* on the top surface, such as MCPC0079 (top) and MCPC0073 (bottom) for the specimens shown in Figure 1(a).² These specimens represented the actual test articles for testing in the material characterization rounds, and the Specimen ID provided traceability of a test article for a characterization modality to specimens from the same sample characterized by other modalities. The Specimen IDs also provided traceability to the nominal process conditions. Figure 1(b) shows the front surface of a microscopy specimen mounted in acrylic after etching in preparation for optical microscopy.

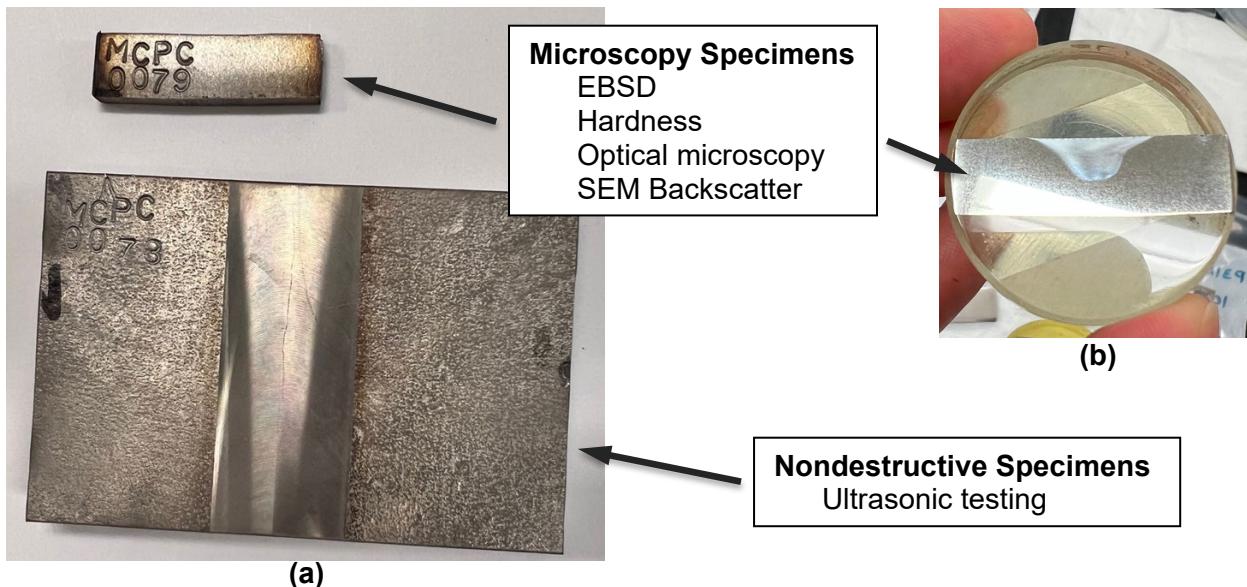


Figure 1. Example FSP specimens.

Table 2 provides a cross-reference table between Condition ID, Sample ID, and Specimen ID for each test article of the five material characterization modalities allocated to this round. The Sample ID and Specimen ID were directly used in file-naming structures as part of the traceability to individual microscopy and ultrasonic samples (see Figure 1), making this cross-reference table important for how to traverse datasets. Note that not all control specimens were measured in every modality.

¹ Actual process conditions from successful FSP experiments only deviated slightly from nominal (planned conditions).

² The top surface of UT specimens required light machining and sanding to smooth the surface for reliable penetration of the ultrasonic signal. The resulting specimens had a polished finish that is not present in Figure 1. The Specimen ID was reapplied after surface treatment.

Table 2. Condition, Sample, and Specimen ID matrix for each modality.

Condition ID	Sample ID	Hardness Specimen ID	Optical, SEM, and EBSD Specimen ID	UT Specimen ID
C00	SS36	MCPC0181	N/A	N/A
C01	SS33	MCPC0161	MCPC0162	MCPC0163
C02	SS24	MCPC0116	MCPC0117	MCPC0118
C03	SS09	MCPC0041	MCPC0042	MCPC0043
C04	N/A	N/A	N/A	N/A
C05	SS10	MCPC0046	MCPC0047	MCPC0048
C06	SS11	MCPC0051	MCPC0052	MCPC0053
C07	SS12	MCPC0056	MCPC0057	MCPC0058
C08	SS13	MCPC0061	MCPC0062	MCPC0063
C09	SS14	MCPC0066	MCPC0067	MCPC0068
C10	SS15	MCPC0071	MCPC0072	MCPC0073
C11	SS16	MCPC0076	MCPC0077	MCPC0078

Condition ID "C00" represents the unprocessed control sample.

As noted earlier, samples were prepared by FSP for eleven different process conditions (plus control) to produce samples with different microstructural characteristics. The nominal process conditions and unique Condition IDs were previously listed in Table 1. Subject matter experts evaluated the resulting sample quality and time series data obtained from the FSP machinery during FSP experiments (including the actual process conditions that were compared to nominal conditions) to assess the quality of each experiment and identify if upsets occurred, such as a broken tool. Invalid samples were flagged, and samples were not tested for these FSP experiments. If this occurred, they are shown as N/A above in Table 2.

At least one successful sample was produced for each nominal process condition. The MCPC Project elected not to perform additional experimentation to replace failed experiments, as the failed experiments were for challenging conditions that risked the tool and equipment.

Assignment of samples to a characterization round was performed independently of the characterization effort, and samples were traceable to a particular date/time of experimentation and the original unprocessed material.

4.0 Material Characterization Modalities

Material characterization measurements were performed for each sample. The characterization approach evolved over the rounds as lessons were learned and the desired and most useful data came into focus. This mainly involved refining the spatial sampling approach and refinement in the choice of magnification levels for the microscopy. At the operational level (not affecting data quality), preparation of samples for EBSD was refined over the rounds to reduce polishing times and to facilitate easier orientation of samples within the instrument. The characterization approach is summarized in this section for the current round to facilitate comparison to other rounds of data.

The characterization plan for Round 2 was based on obtaining focused EBSD and SEM data within a small window of the stir region. The characterization approach for other modalities was performed consistent with past practice. The approach for each modality is summarized below, roughly following the order of the data that was collected. See the attachments for each modality for more information, where available.

- The optical microscopy result was obtained for etched samples using a combined ocular and magnification level of 100x that focused on the FSP-affected region. Other magnification and contrast methods were not performed.
- Microhardness testing was performed for all available samples. Measurements were performed on a 0.5×0.5 mm grid for all samples.
- Measurements with SEM were performed on a high magnification that revealed microstructural details of the friction stir processed region. Multiple individual tiles were collected to yield a total montage of 0.5×0.5 mm area. An example of the location is shown in Figure 2.
- Three different measurements (e.g., panels) labeled as L01-L03 were obtained for EBSD. The three locations coincided with the upper left, center, and lower right corner of the SEM montage. An example of the locations is shown in Figure 2. Little variation in grain size was noted for specimens across locations and so Location L02 (in the middle of the SEM montage) was used to report most data. EBSD for several specimens was re-measured with lower magnification levels to obtain panels with more grains present in the results. These re-measurements were performed at L01 because it was easier to locate and there was no appreciable special variation in the earlier results. See Attachment A for more details. Reported tabular values in the next section are from the most appropriate magnification for the specimen.
- The approach for UT was invariant across all measurements and rounds in the MCPC Project in terms of spatial extent (i.e., full volume of each UT sample), spatial resolution, transducer frequency, etc. See Guo et al. (2024) describing this work for details.

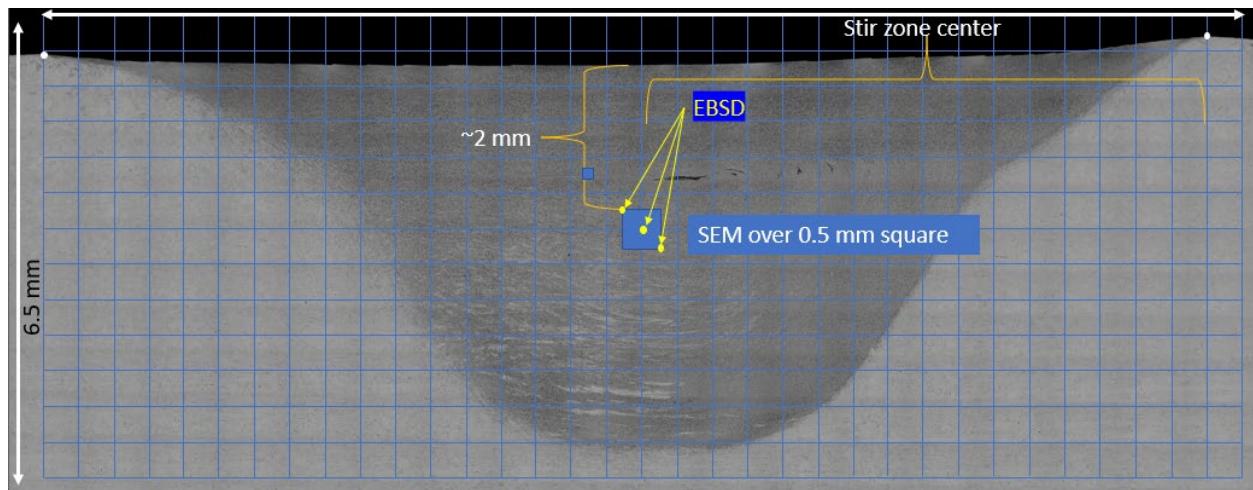


Figure 2. Example SEM and EBSD measurement locations.

5.0 Example Product Metrics from Material Characterization

The modality data (i.e., from microscopy and UT instruments) described in the prior sections was analyzed, individually and in combination, to produce a wide range of metrics for characterizing the FSP product corresponding to each nominal condition. Example product metrics typically used in production environments include grain-size distribution, grain-orientation distribution, hardness, and tensile strength. The MCPC Project elected to focus on a selected subset of these metrics. This section provides tabular and graphical representations of the product metrics that were of primary interest during the MCPC Project, but they represent just a few examples of the product metrics that can be generated from the destructive and nondestructive approaches.

5.1 Tabulations of Example Product Metrics

This section provides a tabulation of selected metric results drawn from across the modalities. First, Table 3 is a re-listing of the processing-parameter data found in Table 1, but sorted by Sample ID¹ instead of Condition ID. Table 4 provides a tabulation of the example product metrics. Brief descriptions of each example product metric are given below. Additional information can be found in the associated appendices and references.

- The “circle equivalent” mean grain diameter² was obtained from data described in Attachment A at location L02 (except where noted in the Attachment). The data was obtained using the AZtecCrystal EBSD analysis software package (Nanoanalysis 2024)
- The intercept-based grain diameter was obtained based on the application of linear paths through the grain boundaries obtained from EBSD data in general conformance with ASTM Standard E112-13 (ASTM E112-13 2021). This metric aligns with the way in which the UT method measures grain characteristics. See technical references associated with UT data analysis for more details.
- The hardness value was obtained in conformance with the Vickers hardness test method, and the listed data was from a small window near the L02 location associated with EBSD.
- The UT Figure-of-Merit (FOM) value was extracted from analysis of UT data using a frequency-domain analysis of sheer wave UT data with special treatments for transducer effects. See technical references associated with UT data analysis for more details.

¹ Data maintained in electronic repositories is sorted by Sample ID. Therefore, data in this section is displayed in the same order.

² The circle equivalent diameter gives a value for area that is equivalent to the area of a segmented grain obtained by calculating the number of steps or pixels within the grain.

Table 3. FSP conditions per sample (sorted by Sample ID).

Condition ID	Sample ID	Temperature (°C)	Tool Traverse (in/min)	Tool Traverse (mm/min)	Force (lbs)	Force (kN)
C03	SS09	720	1.0	25.4	10500	46.7
C05	SS10	720	3.0	76.2	10500	46.7
C06	SS11	750	1.0	25.4	10500	46.7
C07	SS12	750	3.0	76.2	10500	46.7
C08	SS13	800	1.0	25.4	10500	46.7
C09	SS14	800	3.0	76.2	10500	46.7
C10	SS15	850	1.0	25.4	10500	46.7
C11	SS16	850	3.0	76.2	10500	46.7
C02	SS24	720	0.5	12.7	10500	46.7
C01	SS33	720	0.5	12.7	9000	40.0
C04	SS32	720	1.0	25.4	9000	40.0
C00	SS36	N/A	N/A	N/A	N/A	N/A

Table 4. Tabulated modality data per sample.

Condition ID	Sample ID	Mean Grain Diameter (µm)	Intercept-based Grain Diameter (µm)	Hardness Value	UT FOM Value
C03	SS09	0.9	1.58	273.51	0.1038
C05	SS10	1.2	1.86	265.19	0.0650
C06	SS11	0.8	1.52	276.08	0.0946
C07	SS12	0.8	1.30	275.13	0.0950
C08	SS13	2.023	4.14	228.28	0.2752
C09	SS14	2.3	3.29	227.65	0.2441
C10	SS15	3.1	4.87	215.34	0.4417
C11	SS16	3.3	4.86	211.78	0.3746
C02	SS24	0.8	1.48	292.48	0.0610
C01	SS33	0.8	1.42	290.87	0.0551
C04	N/A	N/A	N/A	N/A	N/A
C00	SS36	N/A	N/A	N/A	N/A

- Sample ID SS11 and SS12 are highlighted in **Bold**. Inspection of this data suggests the FSP tool has broken—but was not dispositioned as such by the FSP experts after the experiment.
- A tool break was noted for Condition ID C04 by FSP experts after the experiment.
- More values after the decimal point were reported from EBSD for Mean Grain Diameter in some cases. The precision listed here is consistent with reported values.
- No data is collected for the control sample, C00.

5.2 Graphical Representations of Product Metrics

Graphical representations of example product metrics are provided in this section to visually illustrate trends and to identify outlier and/or suspect data from the instrument modalities. Interpretation of the trends is not provided in this report; please consult other MCPC Project publications for that information.

Figure 3 through Figure 5 illustrate the trend of mean grain diameter, hardness, and UT FOM as a function of nominal processing temperature for the process conditions. With two exceptions, subject matter expert assessment judges the illustrated trends reflect valid data with respect to the nominal processing conditions. As noted in the last section, the exception is related to Sample ID SS11 and SS12 that is highlighted in bold in Table 3. This sample should be used with caution as a tool break may have occurred, resulting in different processing conditions than the nominal (planned) values.

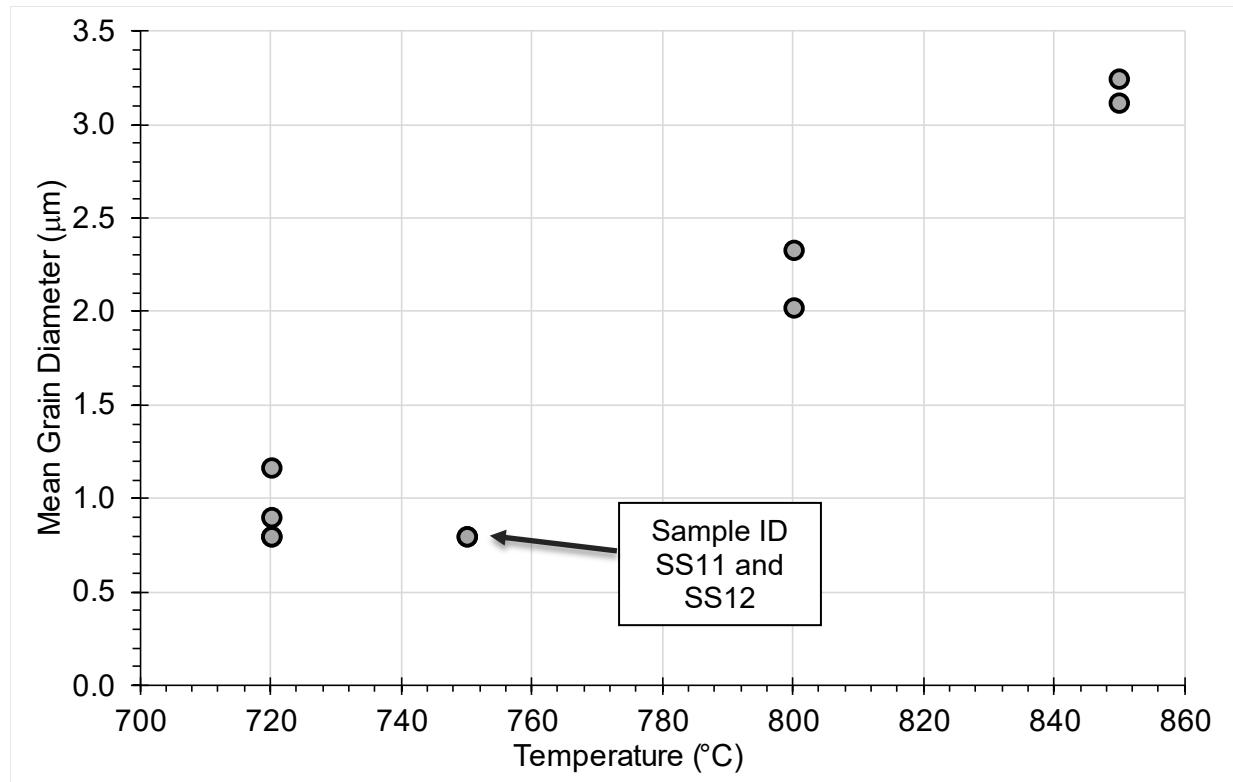


Figure 3. Circle-equivalent mean grain diameter versus nominal processing temperature.

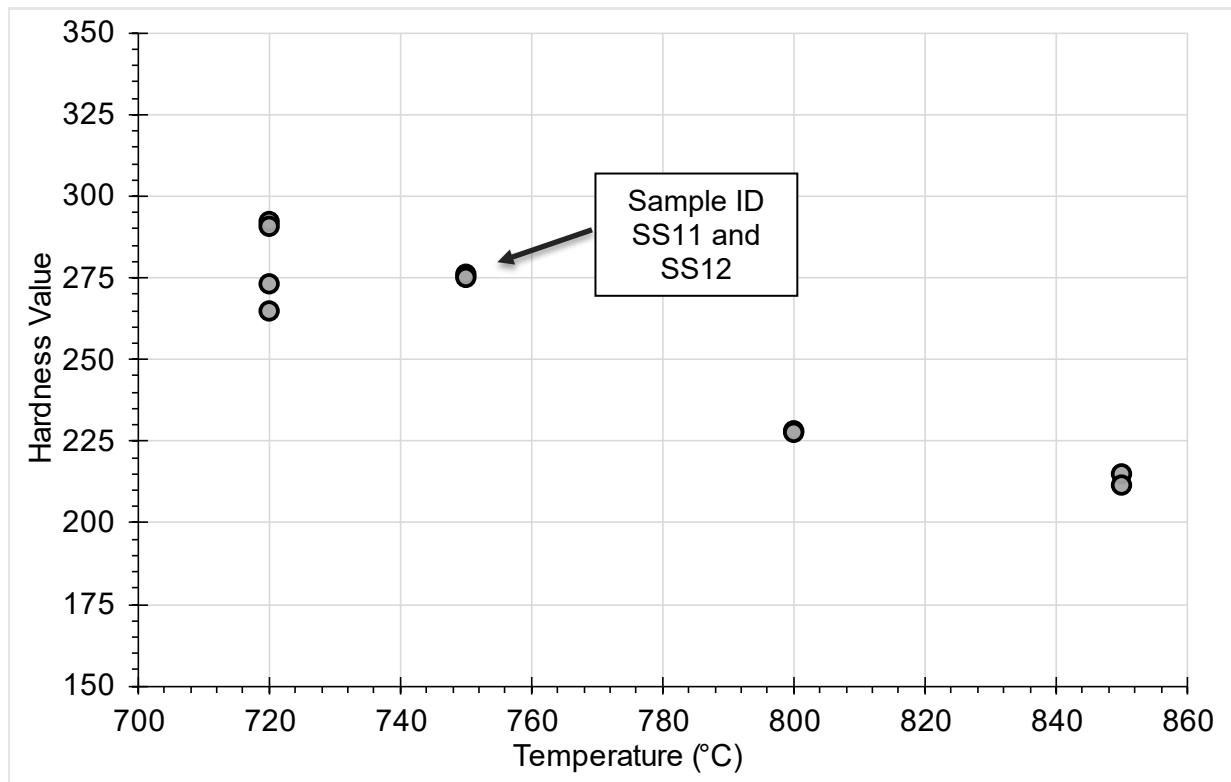


Figure 4. Hardness versus nominal processing temperature.

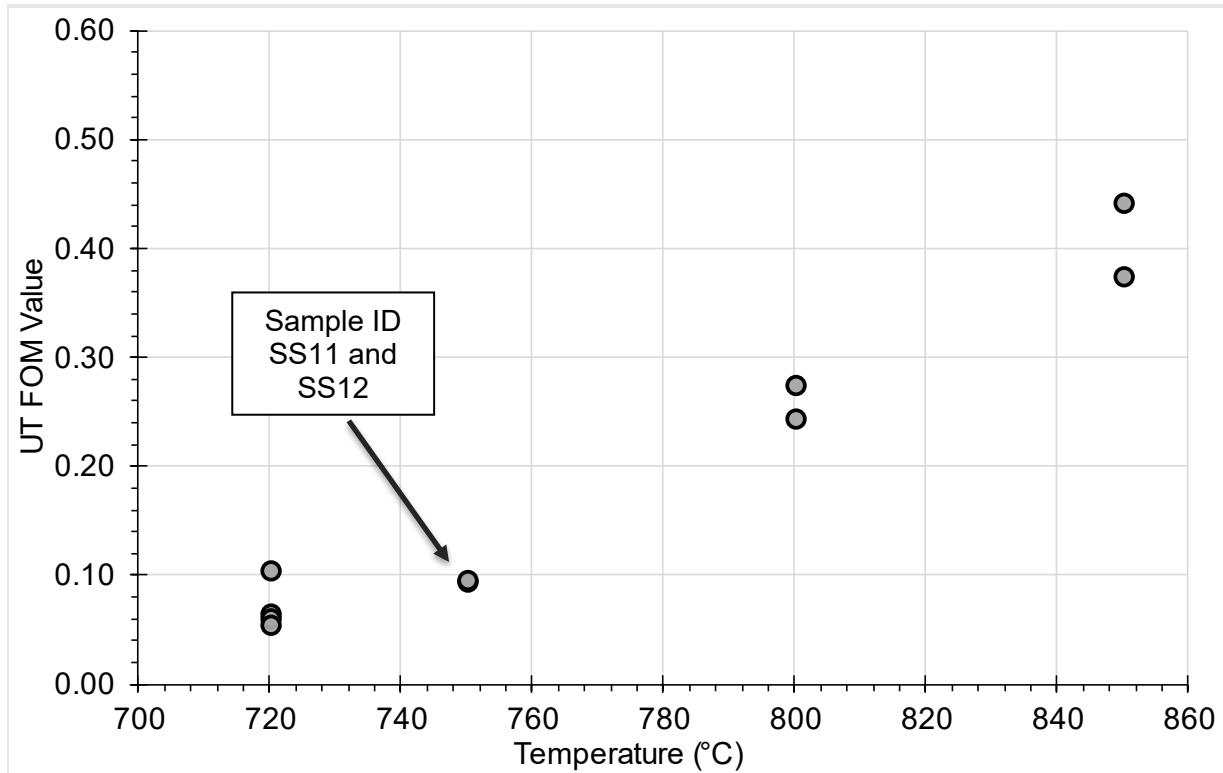


Figure 5. UT FOM nominal processing temperature.

A classical means for evaluating the structure-property relationship is to compare hardness versus the inverse square root of mean grain diameter (i.e., $1/\sqrt{d}$). This relationship is shown in Figure 6 and validates the overall consistency of the mean grain size versus hardness data. Note that Sample ID SS28 is not an outlier in this relationship, suggesting that the hardness and grain size for that sample are consistent with each other, but as shown in prior figures, neither metric is consistent with the *nominal* (i.e., as-planned but not actual) processing condition. Note, control data was not available for Round 2. Round 1 values of 36.5 μm and 150 for grain size and hardness were used in the figure to generate the trend line.

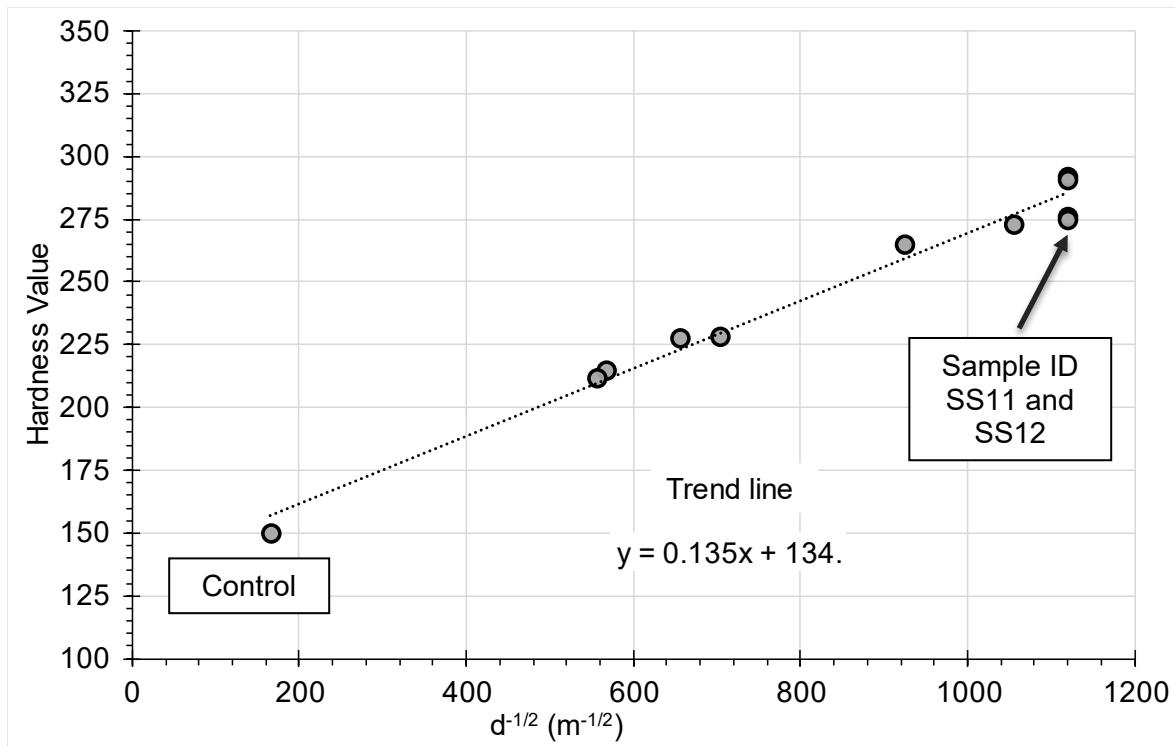


Figure 6. Hardness and mean grain size relationship.

Finally, the relationship between the UT FOM and intercept-based mean grain diameter is shown in Figure 7, fitted with an exponential trend line. The graphical trend is consistent with published work (Guo et al. 2003) for the expected theoretical shape, thus demonstrating validity of the EBSD data obtained by analyzing grain imagery using an intercept method in comparison to the UT FOM data.

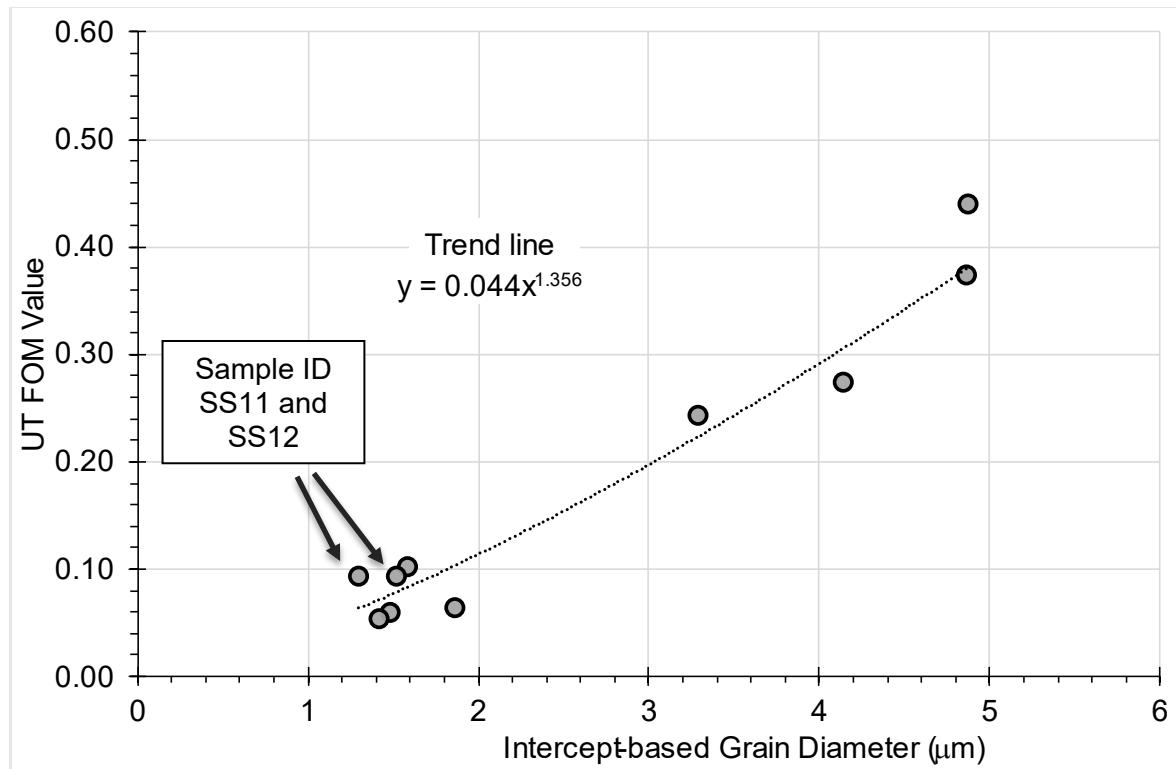


Figure 7. UT FOM versus intercept-based grain diameter.

6.0 Structure of Electronic Modality Data

6.1 Approach

The MCPC Project undertook a robust approach to curation and management of scientific data since the inception of the project. All material characterization data described in this report was managed through workflows and version control processes that are common to software development activities. The final end-product of the curation and management effort is made available via the PNNL DataHub platform.

A key objective in the overall curation and management process was to deliver systematically organized information that is human and computer readable in format and structure. To this end, a naming hierarchy and file structure that was compatible with the project workflows was used. The fundamental element of data was a dataset assigned a Dataset ID that is unique within a modality and round. The Dataset ID for microscopy data was drawn from the unique number assigned during the preparation and mounting within the metallographic preparation lab (i.e., the mount number), as this number was highly visible to the microscopist at the time of data collection. Note that a letter may be added to the end of the mount number in creating the Dataset ID if the same specimen was examined multiple times. For other data, a unique scan or log number was assigned by the data collector. This unique number differs for repeated scans of the same sample.

All information about a dataset was designed to be self-contained within an assigned directory, including raw data, analysis, visualizations, and a summary parameter file containing useful information and metadata. Interpreted results, collages of imagery, and summary data listings found outside a dataset directory were sourced to the original dataset. In case of a discrepancy or inconsistency, refer to information within a dataset directory for the primary source. In using this approach, addition of new datasets and distribution of individual datasets to collaborators were easily achieved by adding or sharing a single directory containing all pertinent information for the dataset.

6.2 Structure of Data

The top file structure of electronic data (and the attachments of this report) reflects the five modalities described at the end of Section 1.0: EBSD, HARDNESS, OPTICAL, SEM, and ULTRASONIC. Data from individual datasets for each modality was placed in a dedicated subdirectory named by a Sample ID and Dataset ID. Furthermore, as noted in the last section, datasets associated with a re-measurement, if present, had a unique letter appended at the end of the name or other means to ensure uniqueness within the modality files.

The key “raw” files from each measurement were placed in the DATA directory of the dataset. These file(s) were typically obtained directly from the instrument. A digital fingerprint was captured in metadata for key files for traceability purposes. Derived visualizations (rescaling or cropping of an optical image, for example), production of numerical data (such as grain size data from EBSD), and interpretation are obtained from these files. The derived information is organized in ANALYSIS or VISUALIZATION directories. See discussion for each modality in the attachments regarding contents.

A metadata parameter file in the human and computer readable YAML¹ file format was created for each dataset. This parameter file contained important information about the individual dataset. It also captured comments related to the validity of the dataset. A dataset may be determined to be invalid because the underlying FSP experiment was determined invalid—see the curated FSP data for the source of which experiments were determined to be invalid. Or the data collection was affected in some manner that affected data quality.

A file named `{modality}_METADATA_LISTING` was produced in several file formats at the root of each modality directory. This file contained a convenient collation of all data in the metadata parameter files described above for the modality and permitted easy inter-comparison and lookup of information across all datasets. In case of discrepancy between the summary file and individual dataset parameter file—data in the individual dataset files takes precedence.

Finally, useful collections of information from across multiple datasets of a modality and relevant summary results files were placed in the `ENSEMBLE_DATA` directory (if present). These files were designed to collect key results from all the datasets into tabular listings for convenience.

An example file structure is illustrated in Figure 8 using example Sample ID, Specimen ID, and Dataset ID values. The arrangement of file naming was carefully designed to assist data generators and data consumers in finding information while reducing the likelihood of unintentional use related to the Condition ID, Sample ID, Specimen ID identification scheme listed in Table 2.

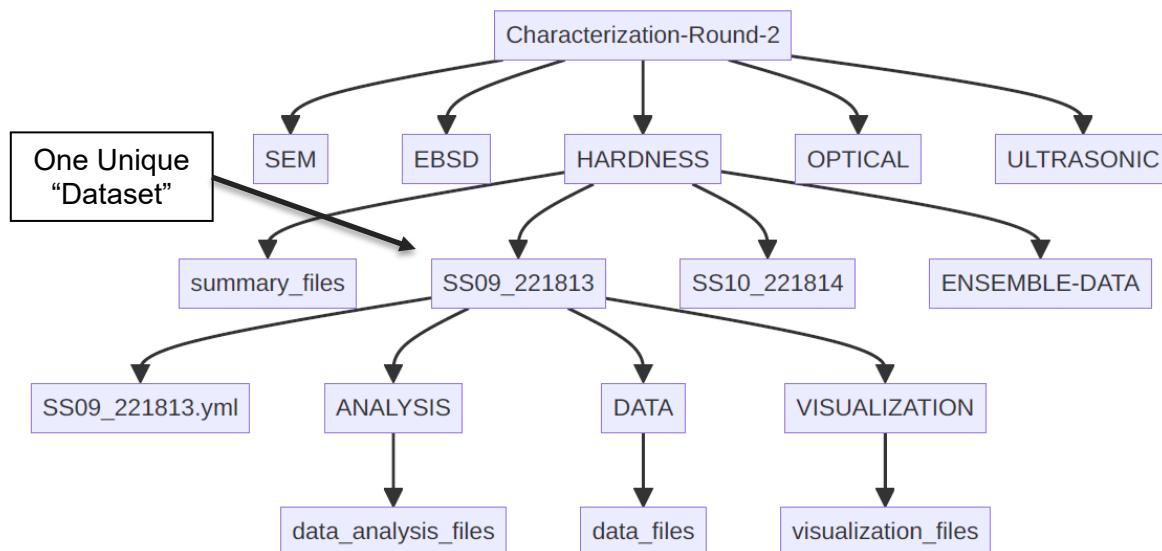


Figure 8. Illustration of typical file structure.

¹ YAML is a widely used text-based file format supported in most modern programming languages for saving and reading data. The YAML is not considered an acronym, though it originated as one.

As shown in the figure, an individual dataset is placed into a directory named `{Sample ID}_{Dataset ID}` (for example `SS09_22813`). The parameter file for the dataset used this same naming. The use of `{Sample ID}` in the name immediately tied a dataset to the same sample found in other modalities—it also yielded a consistent sort order of datasets across modalities. The `{Dataset ID}` was a unique value, but it has no connection to the processing conditions. The modality data files in directory `{Sample ID}_{Dataset ID}/DATA` are given the name `{Specimen ID}_{Dataset ID}`. This naming was used to reduce human-performance mistakes because `{Specimen ID}` is physically stamped on a specimen and is the only visual association with the original experiment. Recall that two specimens from the same sample were expected to be metallurgically identical, and these identical specimens were typically characterized by different modalities to account for different sample preparation requirements. As noted earlier, a unique Dataset ID was defined within the modality if the same specimen is measured multiple times.

A readme in each modality subdirectory provided additional detail and discussion for the data and results for that modality. Much of this readme text is reproduced in the attachments to this report.

An example of a metadata parameter file in YAML file format is shown in Figure 9. As seen in the example, this file contained metadata, the status of the dataset, a listing of key “raw” files that included the first 10 digits of an SHA1¹ digital fingerprint for the file, spatial and geodetic information, and other notes about the individual dataset. This file type was chosen because it is easily loaded into a “dictionary” data type by tools such as Python while also being human readable.

¹ SHA1, or “Secure Hash Algorithm 1”, is a cryptographic hash function that produces a 160-bit message digest from an input that can be used to verify the authenticity of electronic information.

```

Operator: Anthony Guzman
Date: '2022-05-25'
Time: '13:41:51'
Dataset ID: '22742'
Specimen ID: MCPC0006
Sample ID: SS02
Condition ID: C05
Modality: OPTICAL
Instrument ID: 'Olympus, Model: DP74'
Dataset status: Normal
Dataset status notes: Tool pin was chipped after this run. It is unclear
exactly where the chipping occurred from processing conditions
Key data files:
  MCPC0006_22742_10X_Nugget-Region-Etched.jpg: 1aa04623ff
  MCPC0006_22742_5X_Montage-DIC.jpg: 5b2fb1b468
  MCPC0006_22742_5X_Montage-Etched.jpg: eb221906c8
Spatial:
  Stir center:
    Width: '18387.0'
    Height: '5698.0'
  Rotation: '2.1'
  Scale: 1704.5
  Scale units: pix/mm
  Notes: For 10x etched data. Spatial location & rotation data to align the
center
    of the stir region is only approximate at this time.
Notes: NONE

```

Figure 9. Example YAML metadata parameter file.

As noted earlier in this section, “raw” data, interpreted data, and derived visualizations of the data were placed into separate directories. The general principle was that all interpreted data and visualizations could be re-derived and are traceable to the raw data listed in the parameter files. All interpreted results were located within the dataset directory and a comingling of results across datasets or modalities could trace the data source to the individual dataset directory.

7.0 References

ASTM Standard E112-13. 2021. *Standard Test Methods for Determining Average Grain Size*, ASTM Committee E04 on Metallography. doi: <https://www.doi.org/10.1520/E0112-13R21>.

Glass S.W., M.S. Good, Y. Guo, K.A. Ross, D.R. Todd, and T.A. White. 2024. *Materials Characterization: A Primer for Solid Phase Processing Applications*. PNNL-36795. Richland, WA: Pacific Northwest National Laboratory.

Guo, Y., R. B. Thompson, and F. J. Margetan. 2003. "Simultaneous Measurement of Grain Size and Shape from Ultrasonic Backscattering Measurements Made from a Single Surface." In *Review of Progress in QNDE*, Vol. 22, 2003.

Guo Y., D.R. Todd, D.A. Koch, J.D. Escobar, N.A. Conway, M.S. Good, and K. Nwe, et al. 2024. *Materials Characterization, Prediction, and Control Project; Characterization of 316L Stainless Steel after Solid Phase Processing using Ultrasonic NDE Method*. PNNL-36770. Richland, WA: Pacific Northwest National Laboratory.

Nanoanalysis. 2024. "AZtecCrystal." Oxford Instruments. Accessed 17 June 2024. <https://nano.oxinst.com/azteccrystal>.

PNNL. n.d. Solid Phase Processing Demonstration Facility." Pacific Northwest National Laboratory, Richland, Washington. <https://www.pnnl.gov/solid-phase-processing-demonstration-facility>. Accessed 17 June 2024.

Smith, E. L. 2021. LDRD Project 79593 (AGILE) Project Management Plan Lite.

Attachment A: MCPC Round 2 Material Characterization Results for Modality EBSD

M Poole DR Todd
K Nwe A Guzman

Attachment A contains [70](#) pages

Acknowledgments

This research was supported by the Materials Characterization, Prediction, and Control (MCPC) investment, under the Laboratory Directed Research and Development (LDRD) Program at Pacific Northwest National Laboratory (PNNL). PNNL is a multi-program national laboratory operated for the U.S. Department of Energy (DOE) by Battelle Memorial Institute under Contract No. DE-AC05-76RL01830.

Contents

1	Introduction	5
2	Key Information and Results	6
3	Instrumentation and Measurement Locations (Sites)	7
4	Results Files	8
5	Notes and Comments	9
6	Tabular Results	10
7	Graphics	11
7.1	Grain Charts	11
7.2	Band Contrast + Grain Boundaries	20
7.3	Band Contrast + Kernel Average Misorientation	30
7.4	Inverse Pole Function - X direction	40
7.5	Inverse Pole Function - Y direction	50
7.6	Inverse Pole Function - Z direction	60

Figures

7.1	CED Grain Size and Other Data for L02: Condition C03, Sample SS09	12
7.2	CED Grain Size and Other Data for L02: Condition C05, Sample SS10	12
7.3	CED Grain Size and Other Data for L02: Condition C06, Sample SS11	13
7.4	CED Grain Size and Other Data for L02: Condition C07, Sample SS12	13
7.5	CED Grain Size and Other Data for L02: Condition C08, Sample SS13	14
7.6	CED Grain Size and Other Data for L02: Condition C09, Sample SS14	14
7.7	CED Grain Size and Other Data for L02: Condition C10, Sample SS15	15
7.8	CED Grain Size and Other Data for L02: Condition C11, Sample SS16	15
7.9	CED Grain Size and Other Data for L02: Condition C02, Sample SS24	16
7.10	CED Grain Size and Other Data for L02: Condition C01, Sample SS33	16
7.11	CED Grain Size and Other Data for L01b (2500x mag): Condition C05, Sample SS10	17
7.12	CED Grain Size and Other Data for L01b (2500x mag): Condition C09, Sample SS14	17
7.13	CED Grain Size and Other Data for L01b (2500x mag): Condition C10, Sample SS15	18
7.14	CED Grain Size and Other Data for L01b (2500x mag): Condition C11, Sample SS16	18
7.15	CED Grain Size and Other Data for L01b (1000x mag): Condition C09, Sample SS14	19
7.16	CED Grain Size and Other Data for L01b (1000x mag): Condition C10, Sample SS15	19
7.17	CED Grain Size and Other Data for L01b (1000x mag): Condition C11, Sample SS16	20
7.18	Grain Boundary + Band Contrast for L02: Condition C03, Sample SS09	21
7.19	Grain Boundary + Band Contrast for L02: Condition C05, Sample SS10	21
7.20	Grain Boundary + Band Contrast for L02: Condition C06, Sample SS11	22
7.21	Grain Boundary + Band Contrast for L02: Condition C07, Sample SS12	22
7.22	Grain Boundary + Band Contrast for L02: Condition C08, Sample SS13	23
7.23	Grain Boundary + Band Contrast for L02: Condition C09, Sample SS14	23
7.24	Grain Boundary + Band Contrast for L02: Condition C10, Sample SS15	24
7.25	Grain Boundary + Band Contrast for L02: Condition C11, Sample SS16	24
7.26	Grain Boundary + Band Contrast for L02: Condition C02, Sample SS24	25
7.27	Grain Boundary + Band Contrast for L02: Condition C01, Sample SS33	25
7.28	Grain Boundary + Band Contrast for L01b (2500x mag): Condition C05, Sample SS10	26
7.29	Grain Boundary + Band Contrast for L01b (2500x mag): Condition C08, Sample SS13	26
7.30	Grain Boundary + Band Contrast for L01b (2500x mag): Condition C09, Sample SS14	27
7.31	Grain Boundary + Band Contrast for L01b (2500x mag): Condition C10, Sample SS15	27
7.32	Grain Boundary + Band Contrast for L01b (2500x mag): Condition C11, Sample SS16	28
7.33	Grain Boundary + Band Contrast for L01b (1000x mag): Condition C09, Sample SS14	28

7.34	Grain Boundary + Band Contrast for L01b (1000x mag): Condition C10, Sample SS15	29
7.35	Grain Boundary + Band Contrast for L01b (1000x mag): Condition C11, Sample SS16	29
7.36	Grain Boundary + Kernel Average Misorientation for L02: Condition C03, Sample SS09	31
7.37	Grain Boundary + Kernel Average Misorientation for L02: Condition C05, Sample SS10	31
7.38	Grain Boundary + Kernel Average Misorientation for L02: Condition C06, Sample SS11	32
7.39	Grain Boundary + Kernel Average Misorientation for L02: Condition C07, Sample SS12	32
7.40	Grain Boundary + Kernel Average Misorientation for L02: Condition C08, Sample SS13	33
7.41	Grain Boundary + Kernel Average Misorientation for L02: Condition C09, Sample SS14	33
7.42	Grain Boundary + Kernel Average Misorientation for L02: Condition C10, Sample SS15	34
7.43	Grain Boundary + Kernel Average Misorientation for L02: Condition C11, Sample SS16	34
7.44	Grain Boundary + Kernel Average Misorientation for L02: Condition C02, Sample SS24	35
7.45	Grain Boundary + Kernel Average Misorientation for L02: Condition C01, Sample SS33	35
7.46	Grain Boundary + Kernel Average Misorientation for L01b (2500x mag): Condition C05, Sample SS10	36
7.47	Grain Boundary + Kernel Average Misorientation for L01b (2500x mag): Condition C08, Sample SS13	36
7.48	Grain Boundary + Kernel Average Misorientation for L01b (2500x mag): Condition C09, Sample SS14	37
7.49	Grain Boundary + Kernel Average Misorientation for L01b (2500x mag): Condition C10, Sample SS15	37
7.50	Grain Boundary + Kernel Average Misorientation for L01b (2500x mag): Condition C11, Sample SS16	38
7.51	Grain Boundary + Kernel Average Misorientation for L01b (1000x mag): Condition C09, Sample SS14	38
7.52	Grain Boundary + Kernel Average Misorientation for L01b (1000x mag): Condition C10, Sample SS15	39
7.53	Grain Boundary + Kernel Average Misorientation for L01b (1000x mag): Condition C11, Sample SS16	39
7.54	Inverse Pole Function - X Images for L02: Condition C03, Sample SS09	41
7.55	Inverse Pole Function - X Images for L02: Condition C05, Sample SS10	41
7.56	Inverse Pole Function - X Images for L02: Condition C06, Sample SS11	42
7.57	Inverse Pole Function - X Images for L02: Condition C07, Sample SS12	42
7.58	Inverse Pole Function - X Images for L02: Condition C08, Sample SS13	43
7.59	Inverse Pole Function - X Images for L02: Condition C09, Sample SS14	43
7.60	Inverse Pole Function - X Images for L02: Condition C10, Sample SS15	44

7.61	Inverse Pole Function - X Images for L02: Condition C11, Sample SS16	44
7.62	Inverse Pole Function - X Images for L02: Condition C02, Sample SS24	45
7.63	Inverse Pole Function - X Images for L02: Condition C01, Sample SS33	45
7.64	Inverse Pole Function - X Images for L01b (2500x mag): Condition C05, Sample SS10	46
7.65	Inverse Pole Function - X Images for L01b (2500x mag): Condition C08, Sample SS13	46
7.66	Inverse Pole Function - X Images for L01b (2500x mag): Condition C09, Sample SS14	47
7.67	Inverse Pole Function - X Images for L01b (2500x mag): Condition C10, Sample SS15	47
7.68	Inverse Pole Function - X Images for L01b (2500x mag): Condition C11, Sample SS16	48
7.69	Inverse Pole Function - X Images for L01b (1000x mag): Condition C09, Sample SS14	48
7.70	Inverse Pole Function - X Images for L01b (1000x mag): Condition C10, Sample SS15	49
7.71	Inverse Pole Function - X Images for L01b (1000x mag): Condition C11, Sample SS16	49
7.72	Inverse Pole Function - Y Images for L02: Condition C03, Sample SS09	51
7.73	Inverse Pole Function - Y Images for L02: Condition C05, Sample SS10	51
7.74	Inverse Pole Function - Y Images for L02: Condition C06, Sample SS11	52
7.75	Inverse Pole Function - Y Images for L02: Condition C07, Sample SS12	52
7.76	Inverse Pole Function - Y Images for L02: Condition C08, Sample SS13	53
7.77	Inverse Pole Function - Y Images for L02: Condition C09, Sample SS14	53
7.78	Inverse Pole Function - Y Images for L02: Condition C10, Sample SS15	54
7.79	Inverse Pole Function - Y Images for L02: Condition C11, Sample SS16	54
7.80	Inverse Pole Function - Y Images for L02: Condition C02, Sample SS24	55
7.81	Inverse Pole Function - Y Images for L02: Condition C01, Sample SS33	55
7.82	Inverse Pole Function - Y Images for L01b (2500x mag): Condition C05, Sample SS10	56
7.83	Inverse Pole Function - Y Images for L01b (2500x mag): Condition C08, Sample SS13	56
7.84	Inverse Pole Function - Y Images for L01b (2500x mag): Condition C09, Sample SS14	57
7.85	Inverse Pole Function - Y Images for L01b (2500x mag): Condition C10, Sample SS15	57
7.86	Inverse Pole Function - Y Images for L01b (2500x mag): Condition C11, Sample SS16	58
7.87	Inverse Pole Function - Y Images for L01b (1000x mag): Condition C09, Sample SS14	58
7.88	Inverse Pole Function - Y Images for L01b (1000x mag): Condition C10, Sample SS15	59
7.89	Inverse Pole Function - Y Images for L01b (1000x mag): Condition C11, Sample SS16	59
7.90	Inverse Pole Function - Z Images for L02: Condition C03, Sample SS09	61
7.91	Inverse Pole Function - Z Images for L02: Condition C05, Sample SS10	61

7.92	Inverse Pole Function - Z Images for L02: Condition C06, Sample SS11	62
7.93	Inverse Pole Function - Z Images for L02: Condition C07, Sample SS12	62
7.94	Inverse Pole Function - Z Images for L02: Condition C08, Sample SS13	63
7.95	Inverse Pole Function - Z Images for L02: Condition C09, Sample SS14	63
7.96	Inverse Pole Function - Z Images for L02: Condition C10, Sample SS15	64
7.97	Inverse Pole Function - Z Images for L02: Condition C11, Sample SS16	64
7.98	Inverse Pole Function - Z Images for L02: Condition C02, Sample SS24	65
7.99	Inverse Pole Function - Z Images for L02: Condition C01, Sample SS33	65
7.100	Inverse Pole Function - Z Images for L01b (2500X mag): Condition C05, Sample SS10	66
7.101	Inverse Pole Function - Z Images for L01b (2500X mag): Condition C08, Sample SS13	66
7.102	Inverse Pole Function - Z Images for L01b (2500X mag): Condition C09, Sample SS14	67
7.103	Inverse Pole Function - Z Images for L01b (2500X mag): Condition C10, Sample SS15	67
7.104	Inverse Pole Function - Z Images for L01b (2500X mag): Condition C11, Sample SS16	68
7.105	Inverse Pole Function - Z Images for L01b (1000x mag): Condition C09, Sample SS14	68
7.106	Inverse Pole Function - Z Images for L01b (1000x mag): Condition C10, Sample SS15	69
7.107	Inverse Pole Function - Z Images for L01b (1000x mag): Condition C11, Sample SS16	69

Tables

6.1 Listing of mean grain diameter.	10
---	----

1.0 Introduction

Electron Back Scatter Diffraction (EBSD) is a microscopy technique that can measure micro-structural properties such as grain sizes, crystallographic orientations, misorientations, texture, and others. The primary property of interest within the scope of the MCPC Project is circle equivalent mean grain size. Additionally, the grain boundary imagery is utilized for some elements of the project. Phase discrimination, analysis of texture, and other properties is not undertaken even though the information is contained in the results.

The following sections provide a summary of results for this modality to enhance dissemination of the large volume of similar data that are made available via the PNNL DataHub (<https://data.pnnl.gov>) platform.

2.0 Key Information and Results

The main portion of this report provides a summary of key information related to the modality, including processing conditions, sample identification information, and the numerical results retrieved from EBSD data analysis in the project. Where to find the information and results in the main report is described below (Section, Table, and Figure numbers listed below are found in the main report):

- Nominal process conditions for the FSP experiments are defined in Table 1 and Table 3 (data is in two different sorting orders).
- The Condition, Sample, and Specimen ID matrix is defined in Table 2 that is necessary to decode the nominal conditions applied to a particular specimen.
- Details about the modality data collection approach is defined in Section 4.0. This includes information about sites where EBSD is performed.
- Tabulation of the modality results considered most important (mean grain diameter) per Sample ID is listed in Table 3 with discussion of what the particular result means introduced earlier in the section.
- Mean grain diameter value versus nominal processing temperature listed in Table 3 and Table 4 is displayed graphically in Figure 3.
- A classical means for evaluating the structure-property relationship is to compare hardness versus the inverse square root of mean grain diameter. This is shown in Figure 6 to highlight consistency of results across a range of conditions.

AZtecCrystal <https://nano.oxinst.com/azteccrystal> is a comprehensive software package distributed by Oxford Instruments for processing data collected using EBSD. This software package generates numerous visualizations and tabulated results based on user specification. Tabulated results include various grain size statistics, via circle equivalent diameter, which was listed in the main report for location L02. The source of tabulated data can be found in the right-hand side of the "Grain Charts" shown in Section 7.1, below.

3.0 Instrumentation and Measurement Locations (Sites)

The following instrument was utilized in testing of specimens:

Thermoscientific Helios Hydra UX, Plamsa Focused Ion Beam microscope

EBSD results were obtained at multiple locations (sites) for each specimen as described in Section 4.0 and illustrated in Figure 2 in the main report. The distinct locations were labeled L01 through L03 as illustrated in the figure. Each interrogation produced results files labeled with the related location code.

4.0 Results Files

Below is a summary of the unique results files produced for each location where measurements were made for each specimen. Items after the first entry describe derived data files that are provided, where the indicated string is found in the file name.

- h5oina (DATA Directory, Extension): The "HDF5 Oxford Instruments NanoAnalysis" file format contains all data captured during an EBSD measurement session. All subsequent visualizations, data analysis, and information is obtained from this key file. Generally, proprietary software (AZtecCrystal) is needed to extract visualizations and perform data analysis. Data is contained in the HDF5 format. The specification for this file format can be found here: <https://github.com/oinanoanalysis/h5oina>.
- GB+BC (VISUALIZATION Directory, TIF Image): EBSD results image showing the band contrast image overlaid with grain boundaries identified through segmentation.
- GB+KAM (VISUALIZATION Directory, TIF Image): EBSD results image showing the kernel average misorientation overlaid with grain boundaries identified through segmentation.
- IPF-X+GB (VISUALIZATION Directory, TIF Image): EBSD Inverse pole figure (IPF) map in the X-direction with grain boundaries.
- IPF-Y+GB (VISUALIZATION Directory, TIF Image): EBSD IPF map in the Y-direction with grain boundaries.
- IPF-Z+GB (VISUALIZATION Directory, TIF Image): EBSD IPF map in the x-direction with grain boundaries.
- Grain-Chart (ANALYSIS Directory, TIF Image): Distribution chart of grain sizes.
- Grain-Chart-Data (ANALYSIS Directory, CSV file): Text listing of the distribution chart of grain size data.

Note that all visualizations and grain chart analysis were produced with a grain misorientation angle threshold of 10 degrees. A subdirectory in the ANALYSIS directory may contain grain chart data with other threshold settings as indicated in the directory name.

5.0 Notes and Comments

The following observations are made about data and files for this modality:

1. Magnification levels for several datasets were too high for several datasets resulting on too few grains present for reliable analysis. These datasets were repeated in "a" and "b" dataset directories, for example SS10_221803a and SS10_221803b.
2. Review of the "a" datasets determined they should not be used, and so they were redone.
3. The "b" datasets were done with up to two different magnification levels. Note that these were only done at one location, L01, which was easier to relocate on the specimens. As shown in tabular data below, the L01 location results from the initial analysis were very consistent with the L02 location.
4. Reported grain data in Table 4 of the main report listed the recommended most suitable information from available datasets.

6.0 Tabular Results

Mean grain diameter for locations L01-L03 is listed Table 6.1 in units of microns. This data is obtained from the EBSD_Grain-Data-Results.xlsx file described earlier. The file contains additional tabular data transcribed from the right side of each Grain Chart shown in Section 7.1. As noted before, reported grain data in Table 4 of the main report listed the recommended most suitable information from available datasets.

Table 6.1. Listing of mean grain diameter.

Sample ID	L01	L02	L03	L01b (2500X)	L01b (1000X)
SS09	1.2	1.0	1.2		
SS10	1.2	1.2	1.3	1.17	
SS11	1.6	1.6	1.3		
SS12	1.5	1.5	1.2		
SS13	1.6	2.1	1.7	2.023	
SS14	1.8	2.1	2.1	2.143	2.33
SS15	2.8	3.0	2.7	3.117	3.12
SS16	2.1	2.5	2.3	3.106	3.25
SS24	0.9	0.8	0.9		
SS33	1.1	1.2	1.1		

7.0 Graphics

The following sub sections display key graphics obtained from EBSD analysis.

7.1 Grain Charts

The following figures show graphical results for the L02 datasets listed in Table 6.1 along with those at location L01 for the "b" redo of the EBSD at up to two magnification levels reflected in the table. These figures show area-weighted fraction of grains measured for the specimen as a function of equivalent circle diameter in the form of histograms. Grain sizing settings and numerical results are displayed on the right of the figure for grain count (number of grains), mean (circle equivalent) grain diameter, area weighted mean, minimum, maximum, and standard deviation of the grain size distribution, and misorientation angle threshold. The mean grain diameter displayed above in Table 6.1 is transcribed from this figure for each location. The other results are available in file EBSD_Grain-Data-Results.xlsx. The figures show the grain boundaries identified through segmentation at the misorientation angle of 10° as indicated next to "Threshold Angle" in each figure.

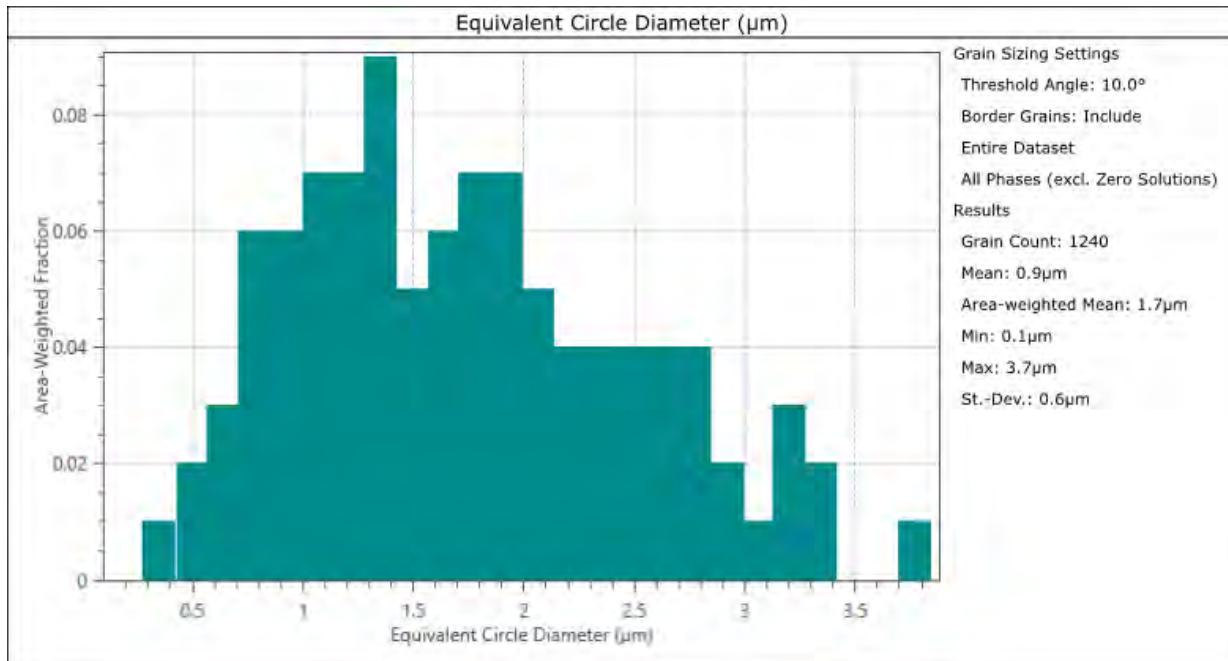


Figure 7.1. CED Grain Size and Other Data for L02: Condition C03, Sample SS09

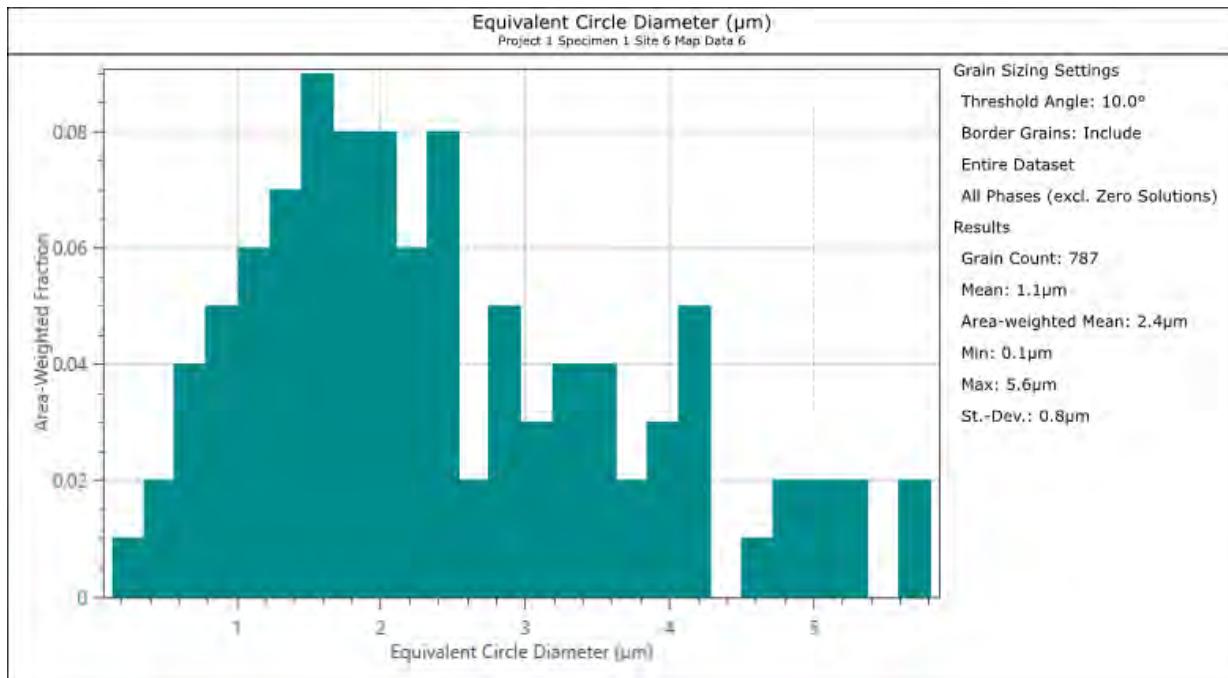


Figure 7.2. CED Grain Size and Other Data for L02: Condition C05, Sample SS10

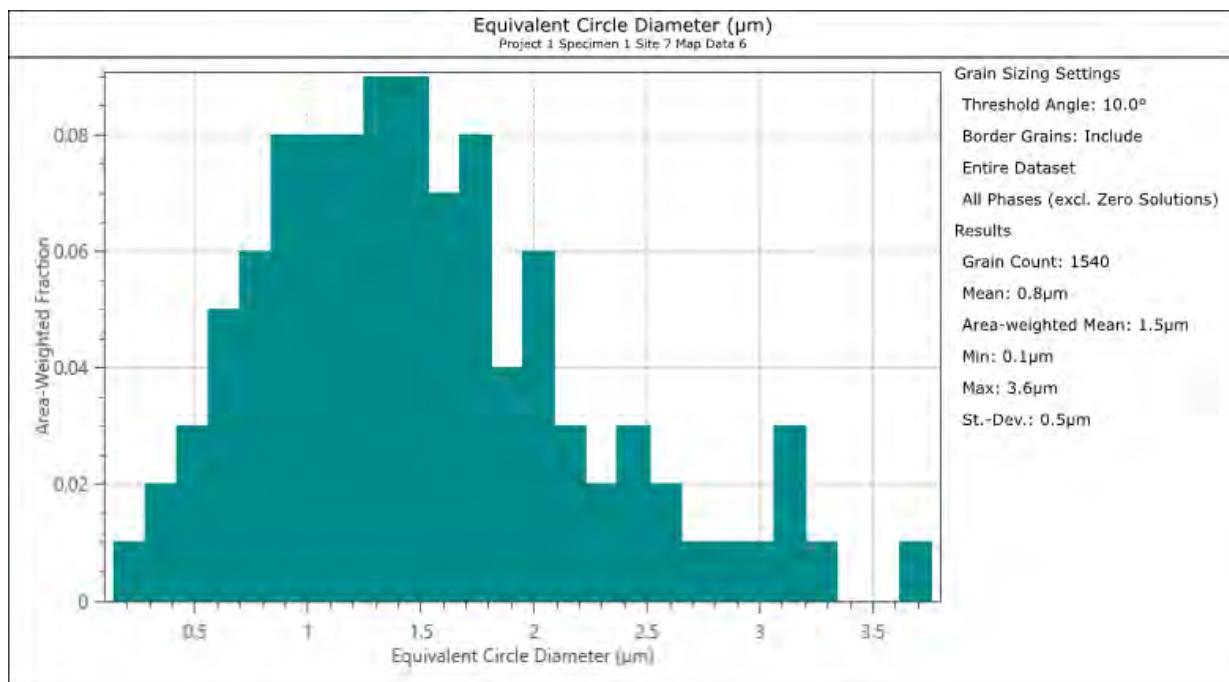


Figure 7.3. CED Grain Size and Other Data for L02: Condition C06, Sample SS11

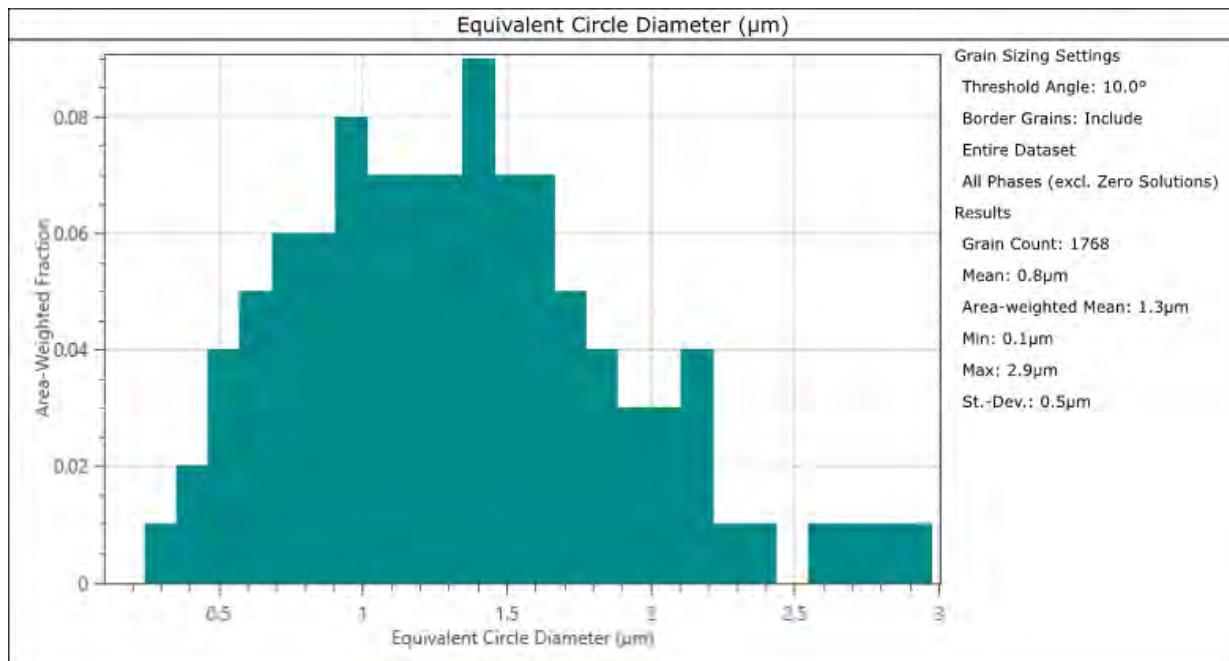


Figure 7.4. CED Grain Size and Other Data for L02: Condition C07, Sample SS12

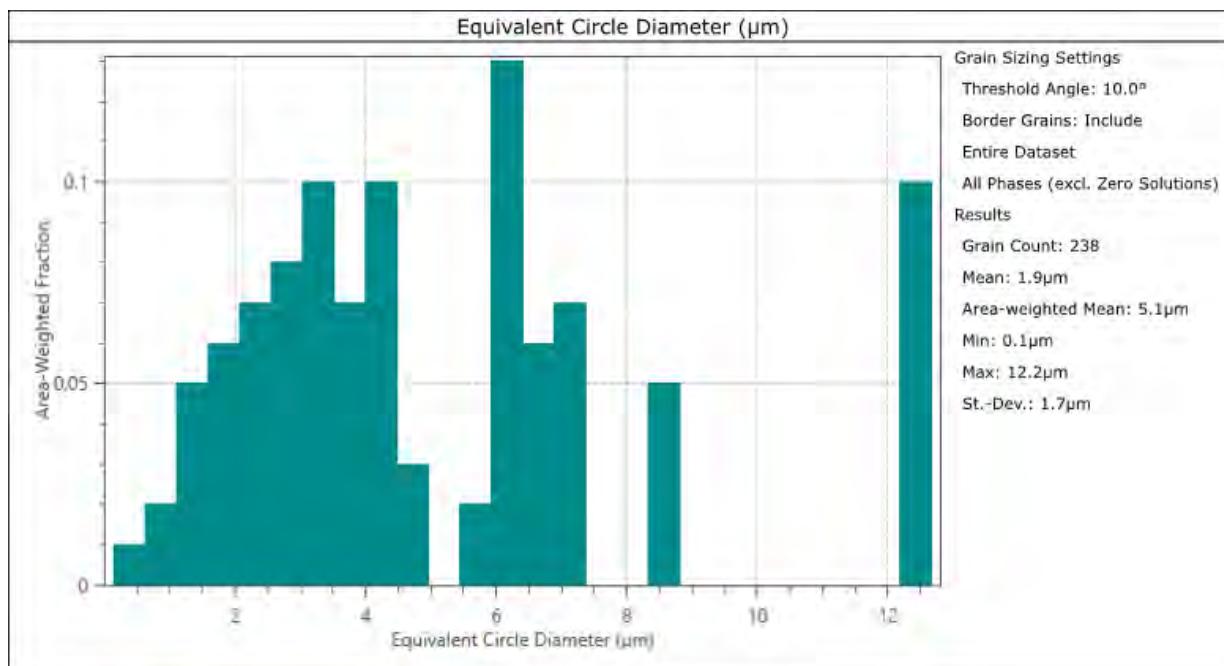


Figure 7.5. CED Grain Size and Other Data for L02: Condition C08, Sample SS13

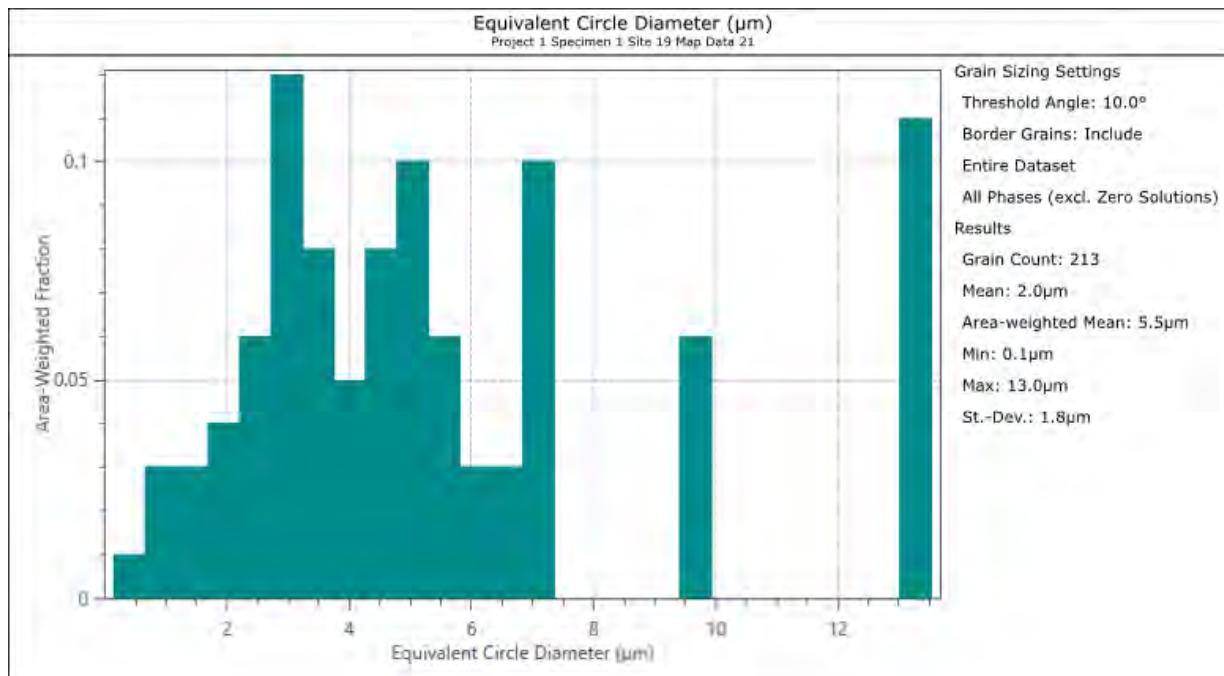


Figure 7.6. CED Grain Size and Other Data for L02: Condition C09, Sample SS14

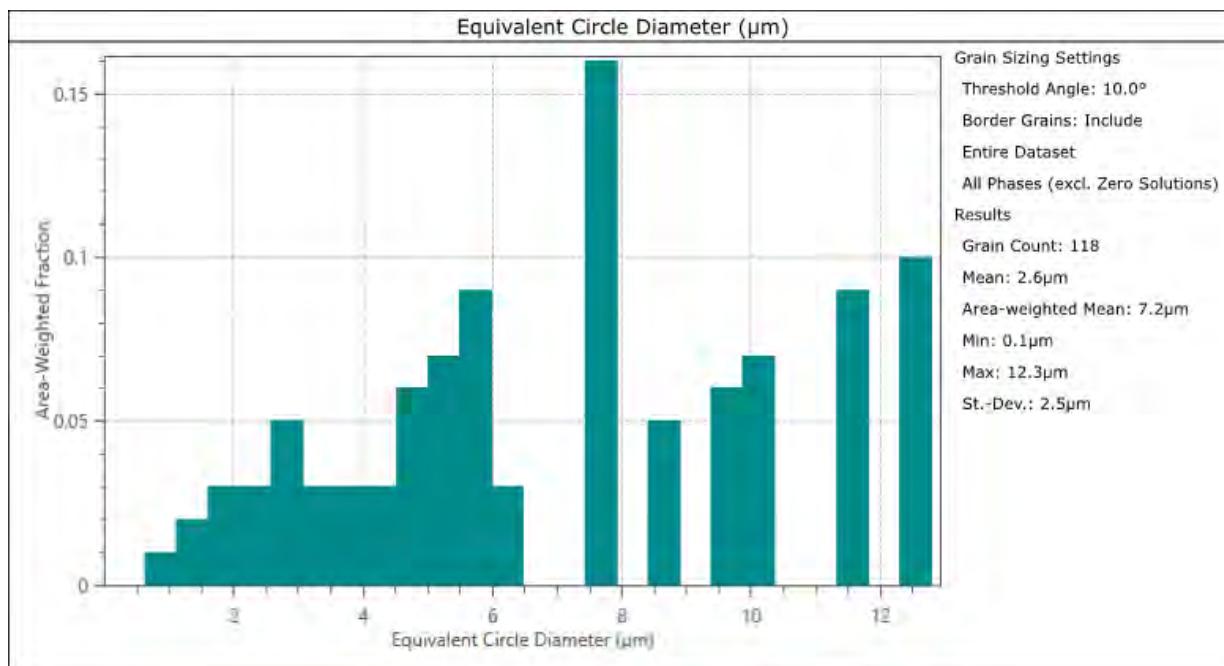


Figure 7.7. CED Grain Size and Other Data for L02: Condition C10, Sample SS15

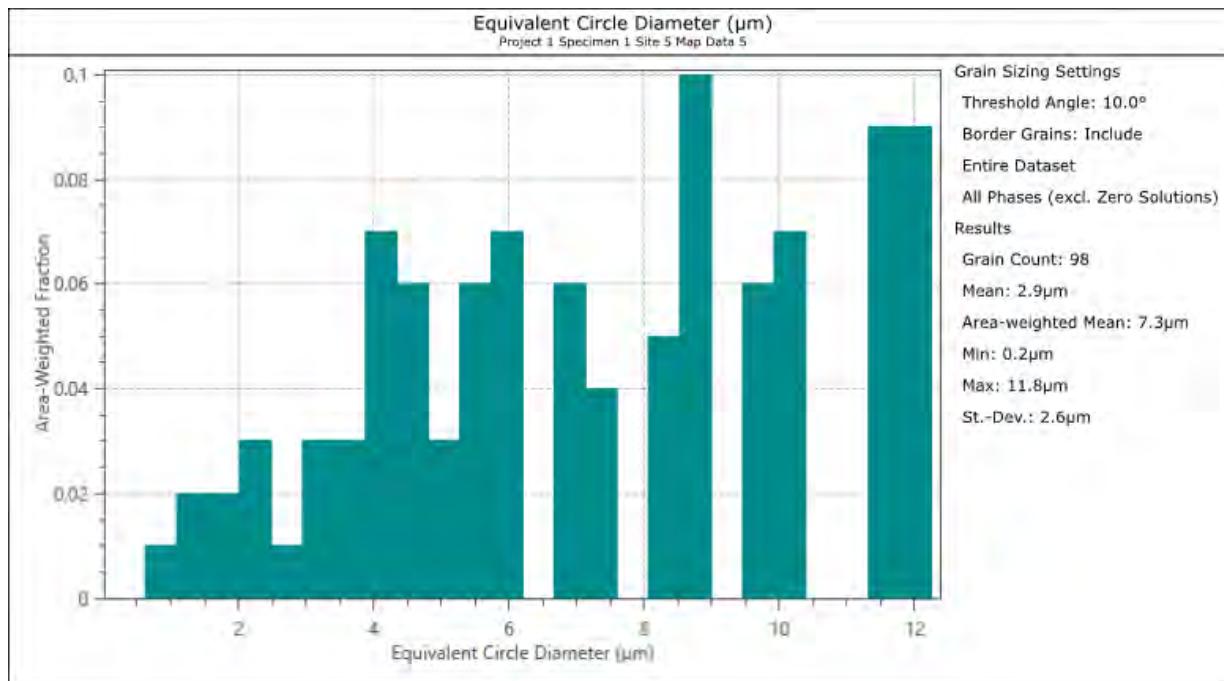


Figure 7.8. CED Grain Size and Other Data for L02: Condition C11, Sample SS16

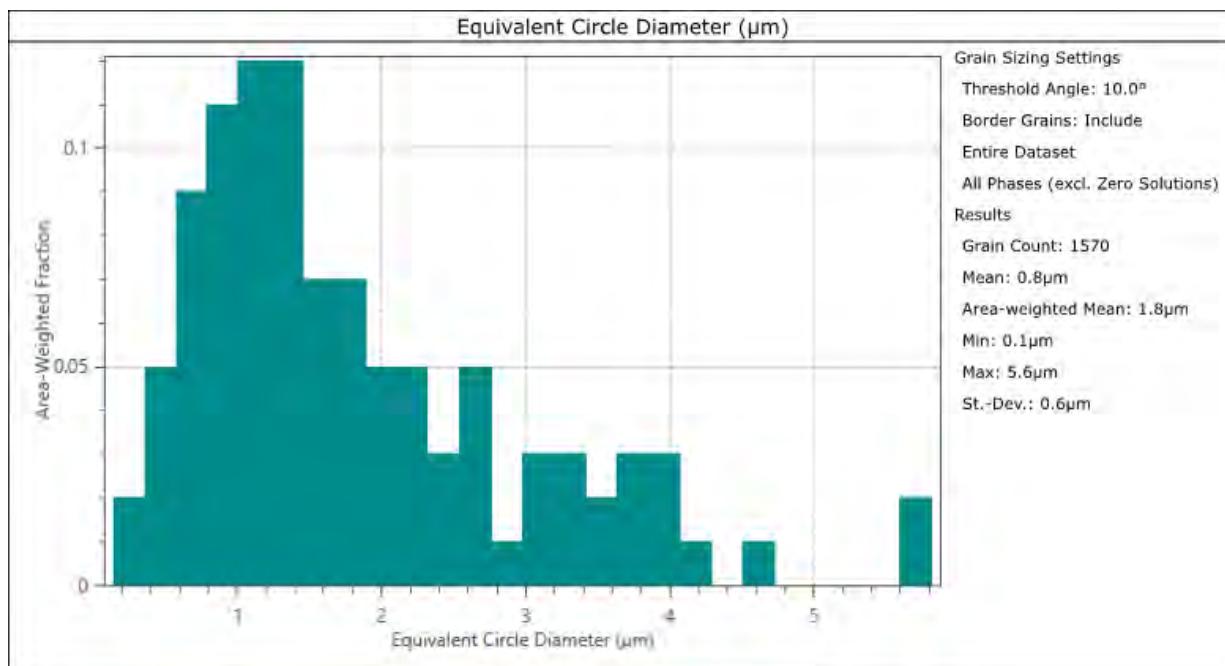


Figure 7.9. CED Grain Size and Other Data for L02: Condition C02, Sample SS24

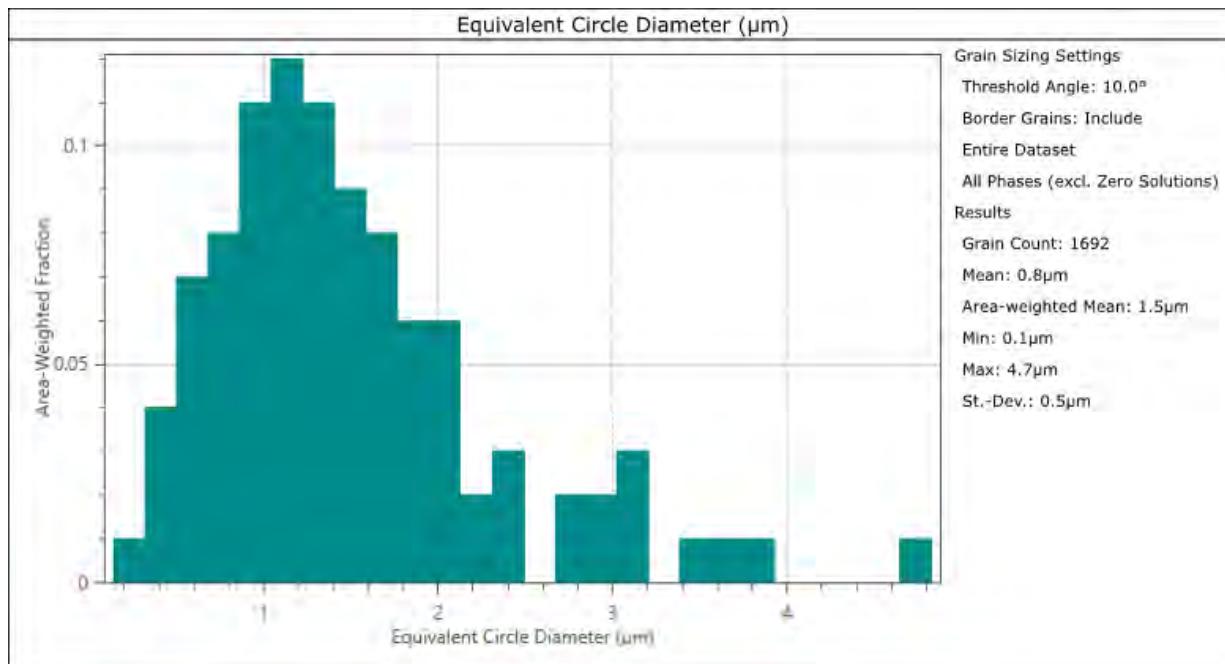


Figure 7.10. CED Grain Size and Other Data for L02: Condition C01, Sample SS33

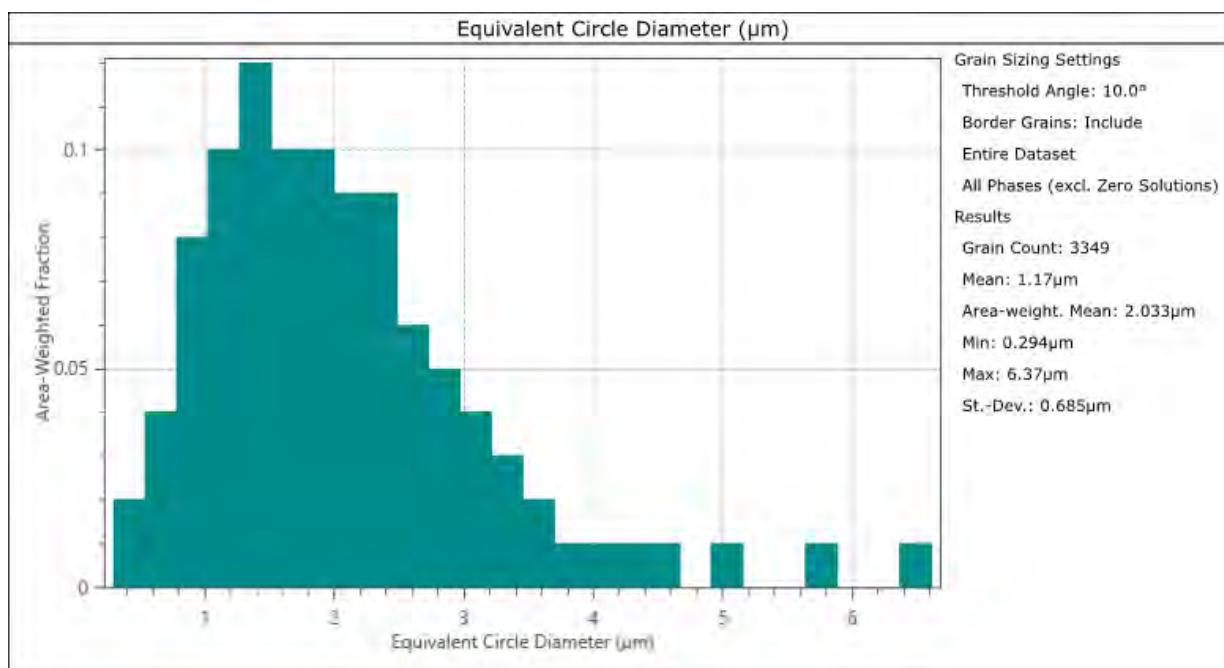


Figure 7.11. CED Grain Size and Other Data for L01b (2500x mag): Condition C05, Sample SS10

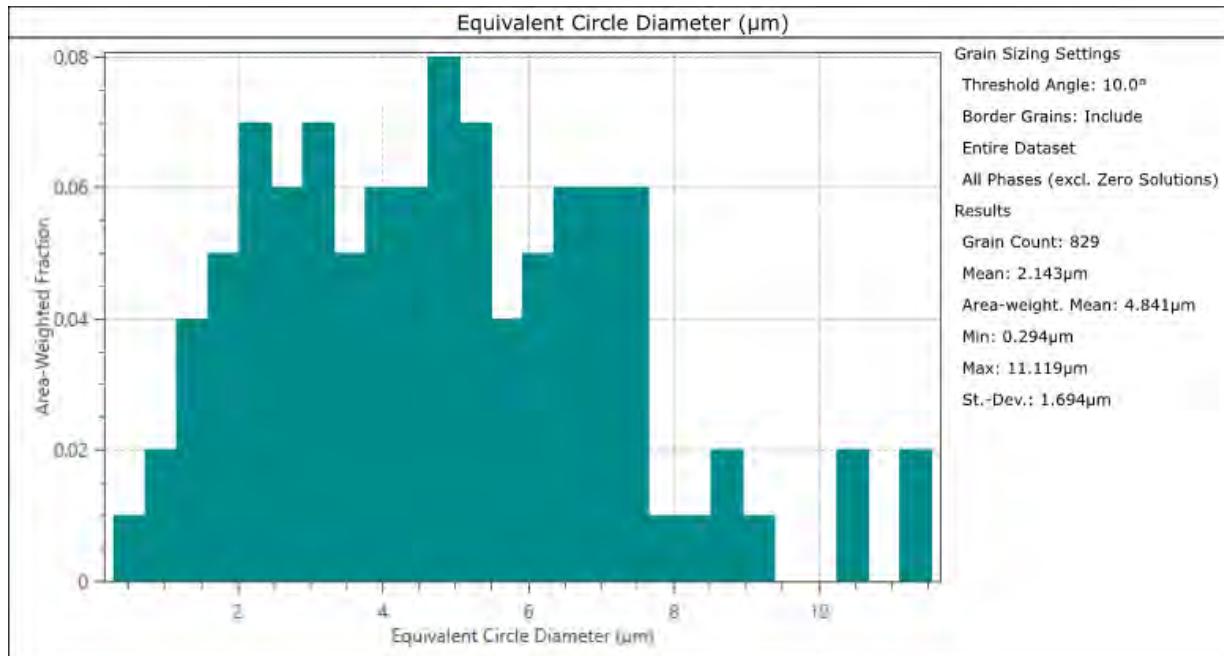


Figure 7.12. CED Grain Size and Other Data for L01b (2500x mag): Condition C09, Sample SS14

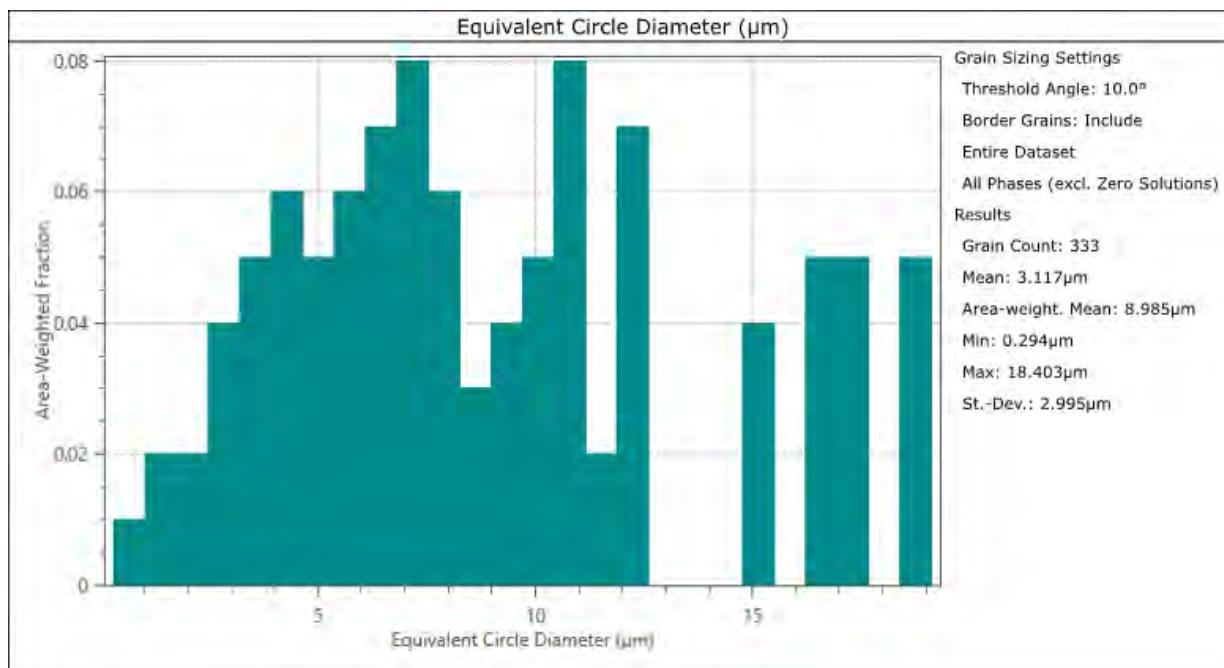


Figure 7.13. CED Grain Size and Other Data for L01b (2500x mag): Condition C10, Sample SS15

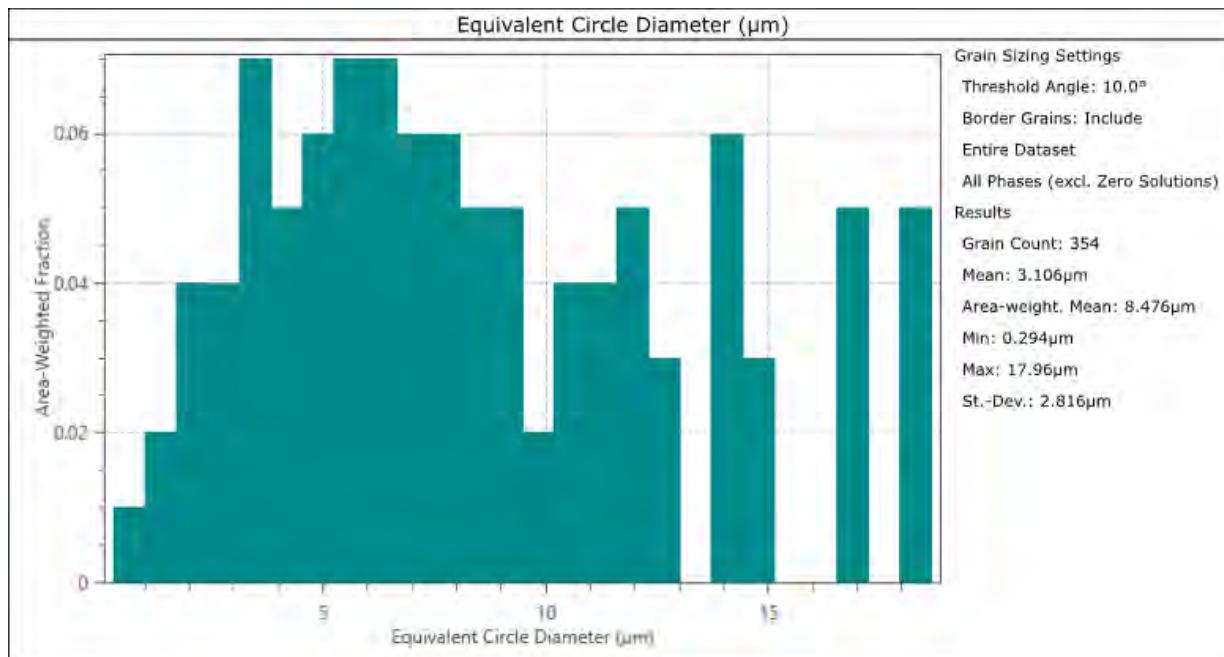


Figure 7.14. CED Grain Size and Other Data for L01b (2500x mag): Condition C11, Sample SS16

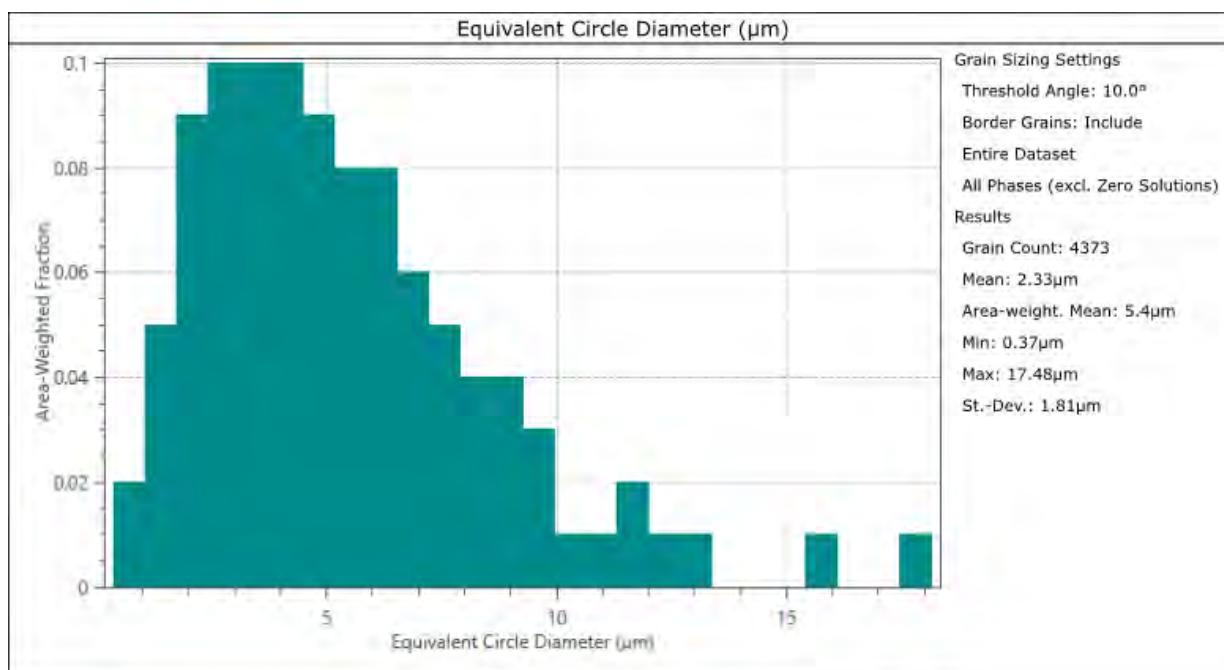


Figure 7.15. CED Grain Size and Other Data for L01b (1000x mag): Condition C09, Sample SS14

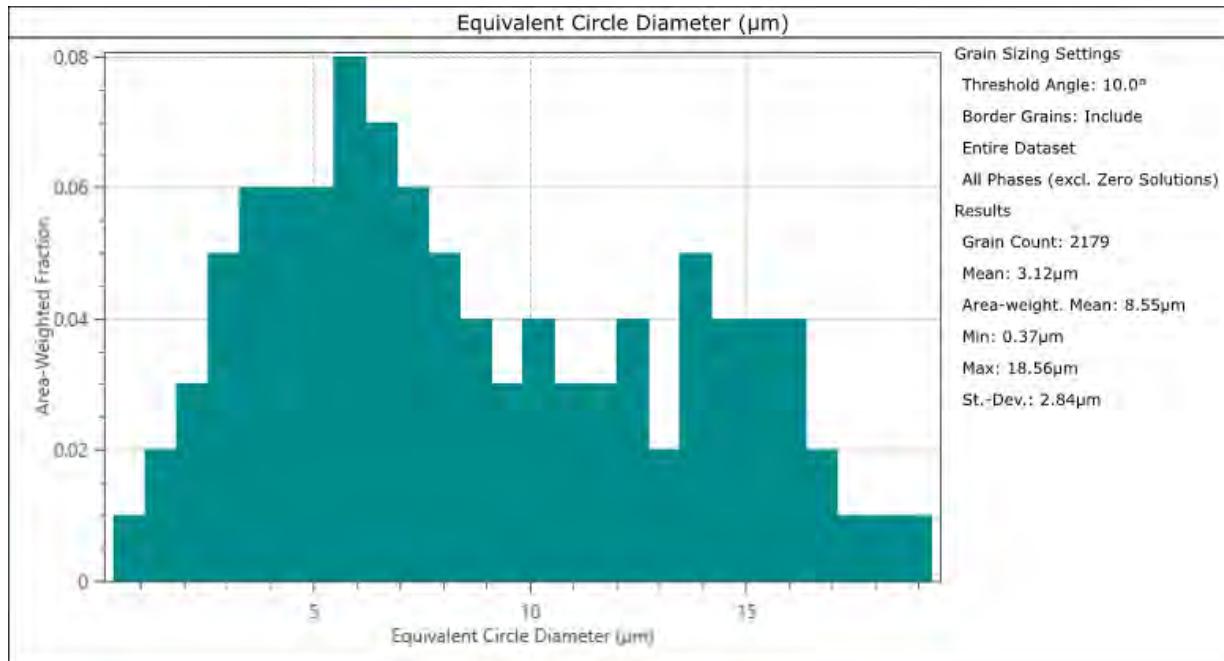


Figure 7.16. CED Grain Size and Other Data for L01b (1000x mag): Condition C10, Sample SS15

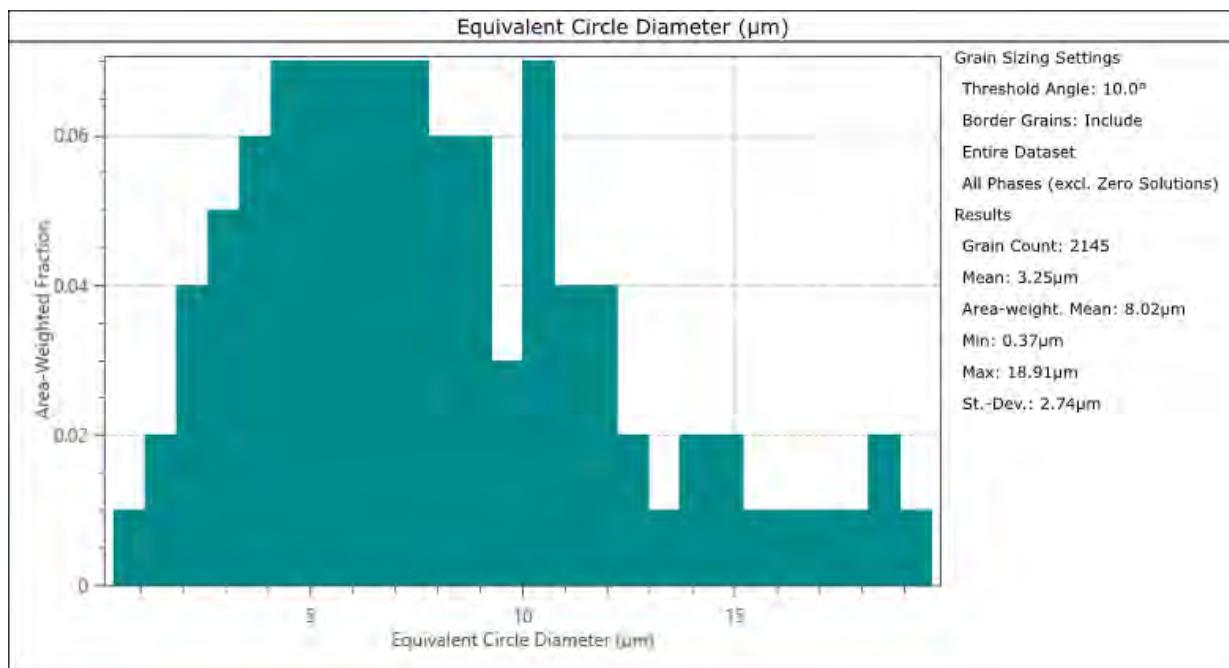


Figure 7.17. CED Grain Size and Other Data for L01b (1000x mag): Condition C11, Sample SS16

7.2 Band Contrast + Grain Boundaries

The following figures show the grain boundaries identified through segmentation with a setting of 10° the misorientation angle, overlaid on the band contrast image of the microstructure. These images are the ones utilized to calculate the intercept-based grain diameter as briefly discussed in the main report.

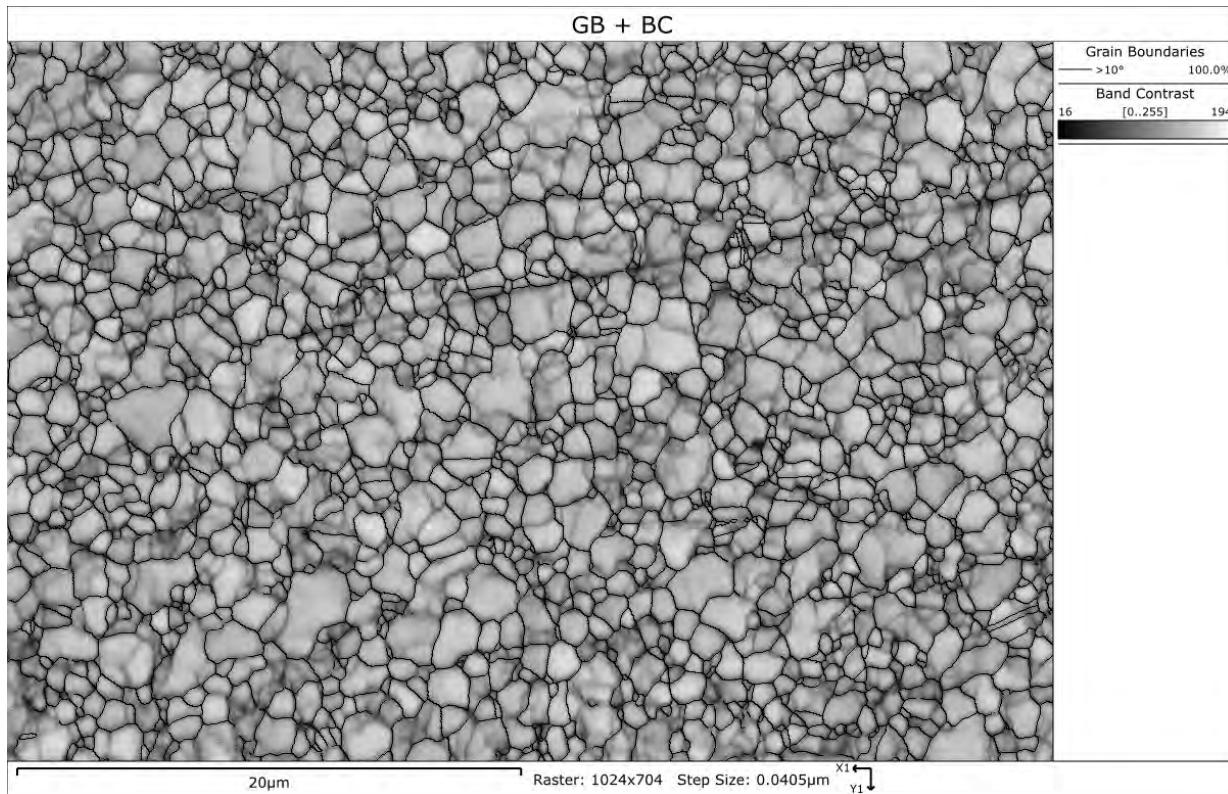


Figure 7.18. Grain Boundary + Band Contrast for L02: Condition C03, Sample SS09

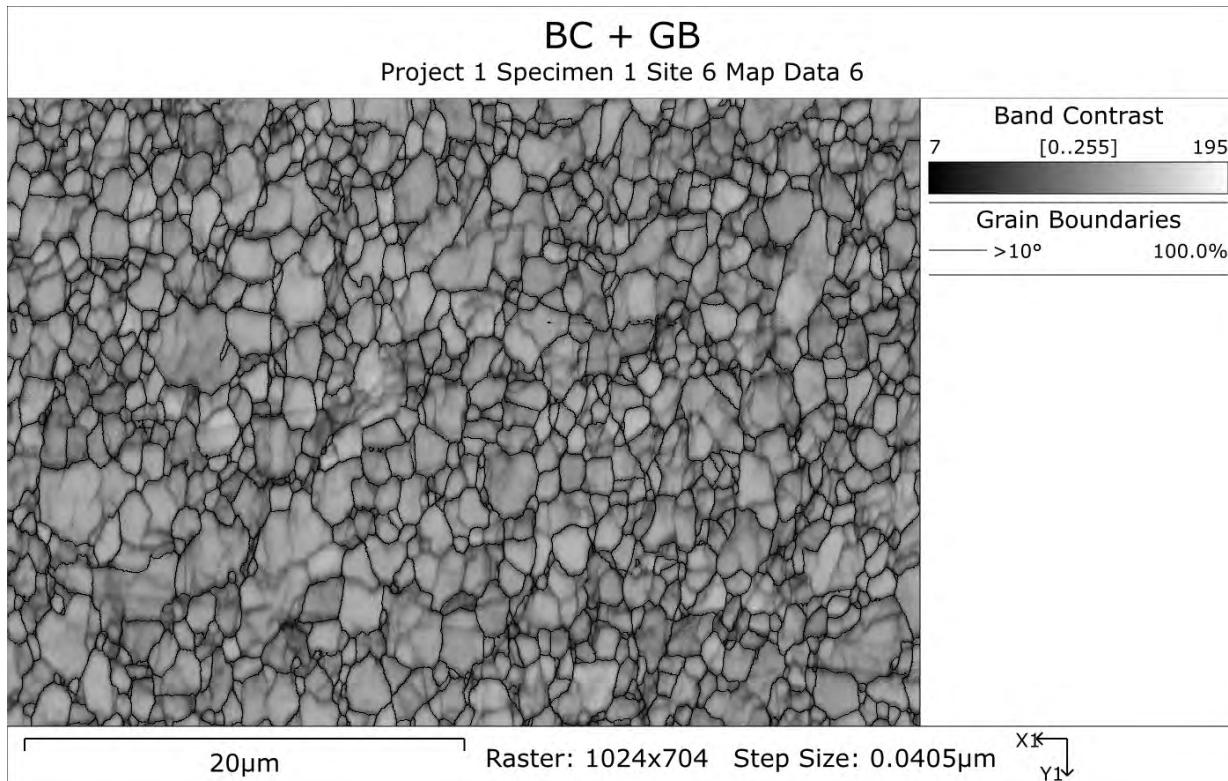


Figure 7.19. Grain Boundary + Band Contrast for L02: Condition C05, Sample SS10

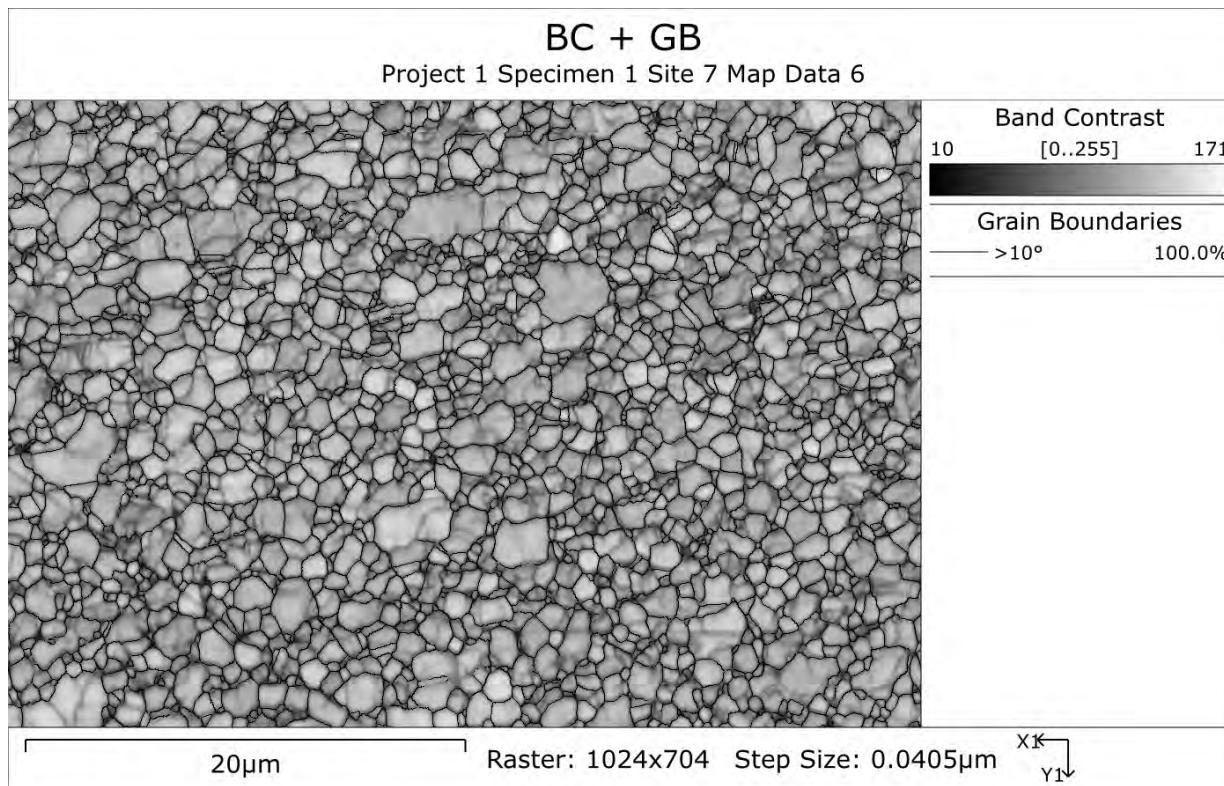


Figure 7.20. Grain Boundary + Band Contrast for L02: Condition C06, Sample SS11

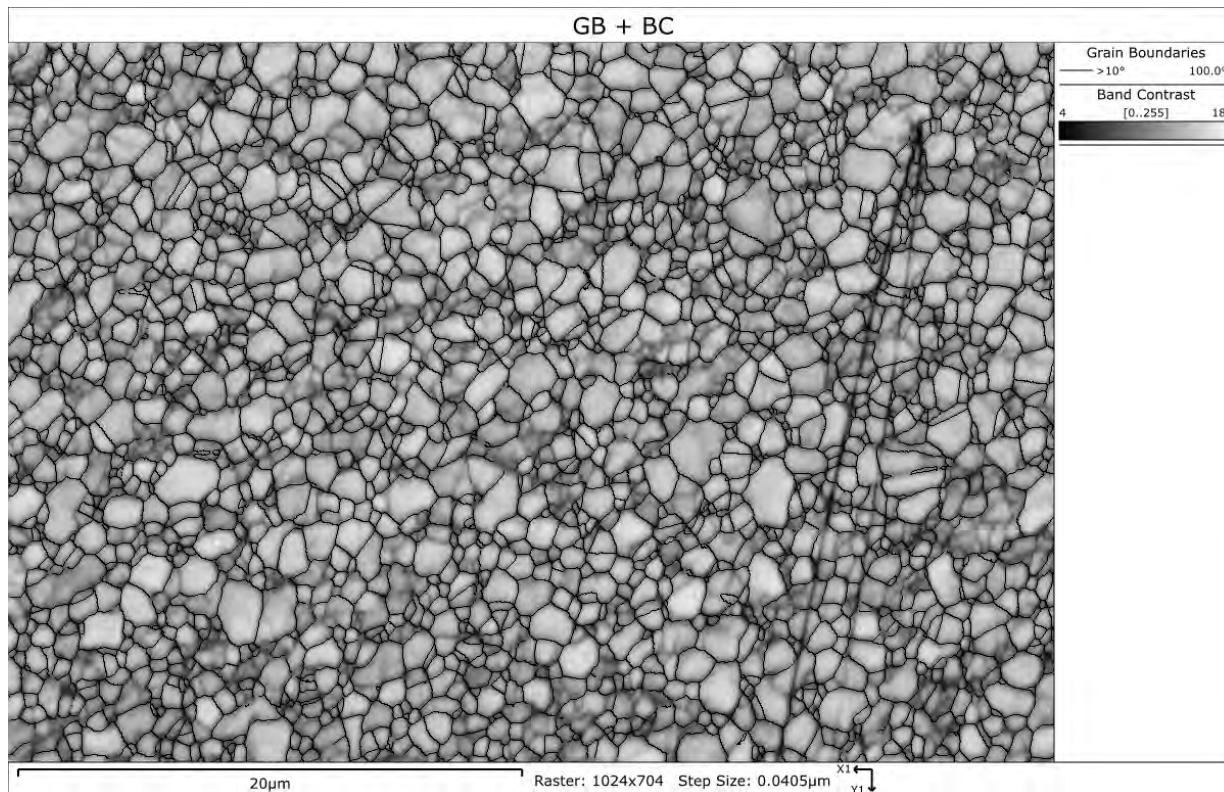


Figure 7.21. Grain Boundary + Band Contrast for L02: Condition C07, Sample SS12

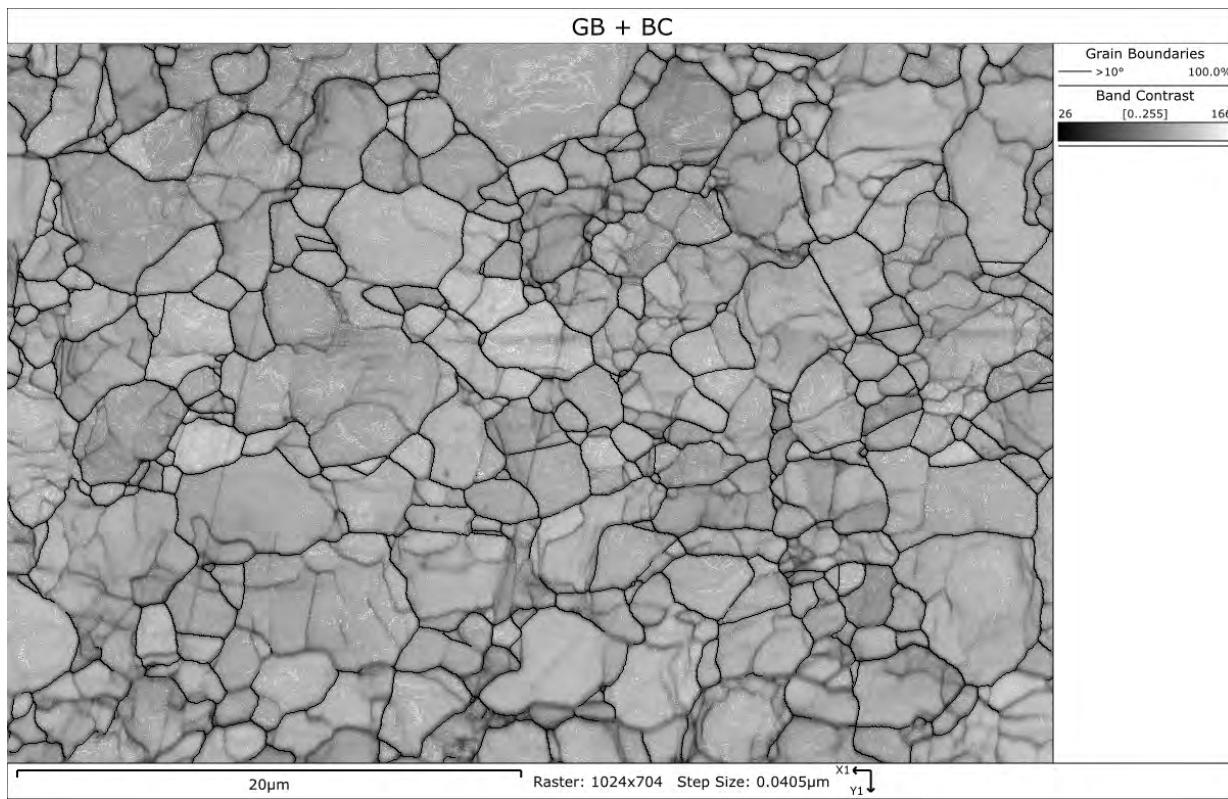


Figure 7.22. Grain Boundary + Band Contrast for L02: Condition C08, Sample SS13

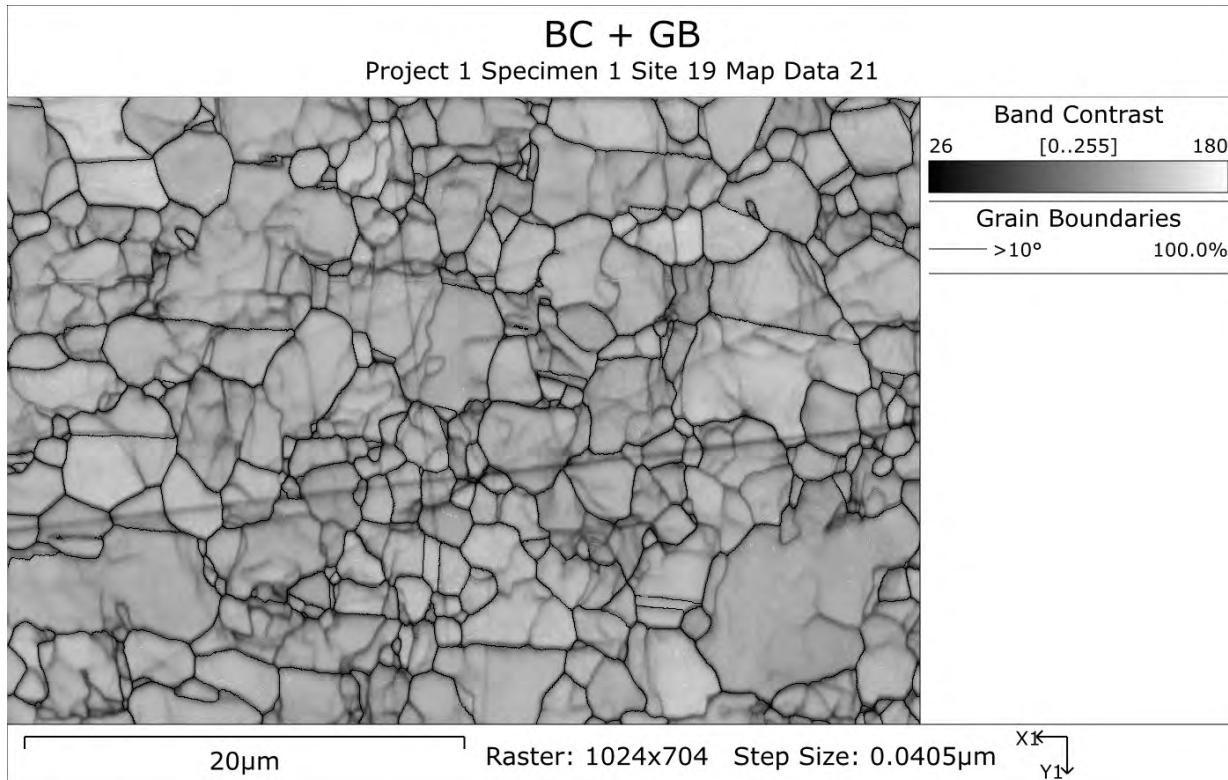


Figure 7.23. Grain Boundary + Band Contrast for L02: Condition C09, Sample SS14

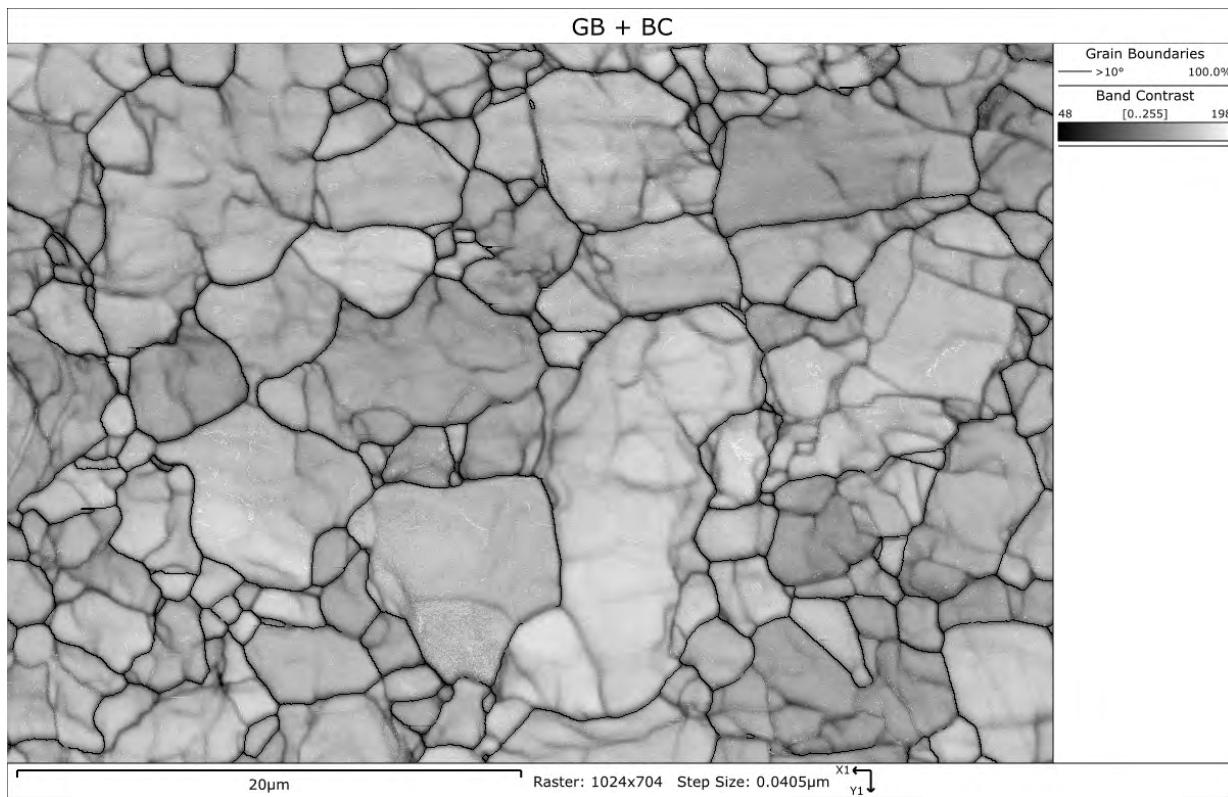


Figure 7.24. Grain Boundary + Band Contrast for L02: Condition C10, Sample SS15

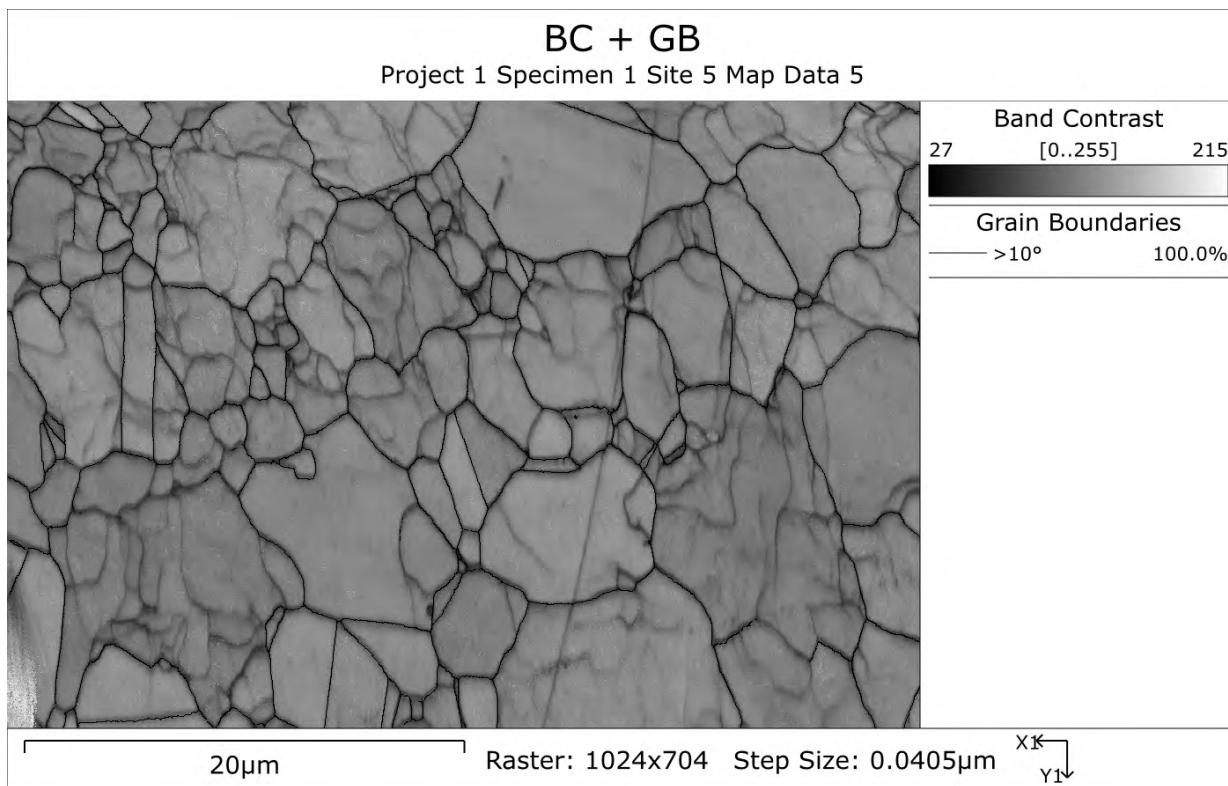


Figure 7.25. Grain Boundary + Band Contrast for L02: Condition C11, Sample SS16

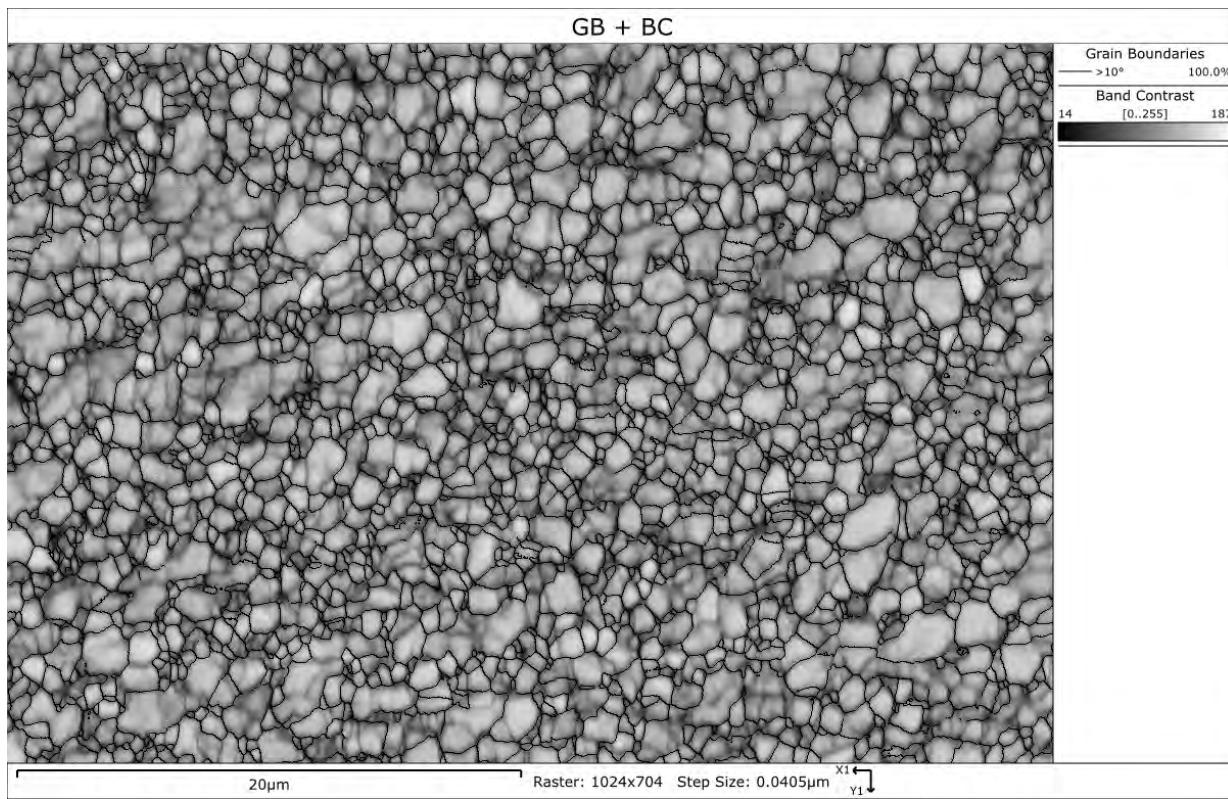


Figure 7.26. Grain Boundary + Band Contrast for L02: Condition C02, Sample SS24

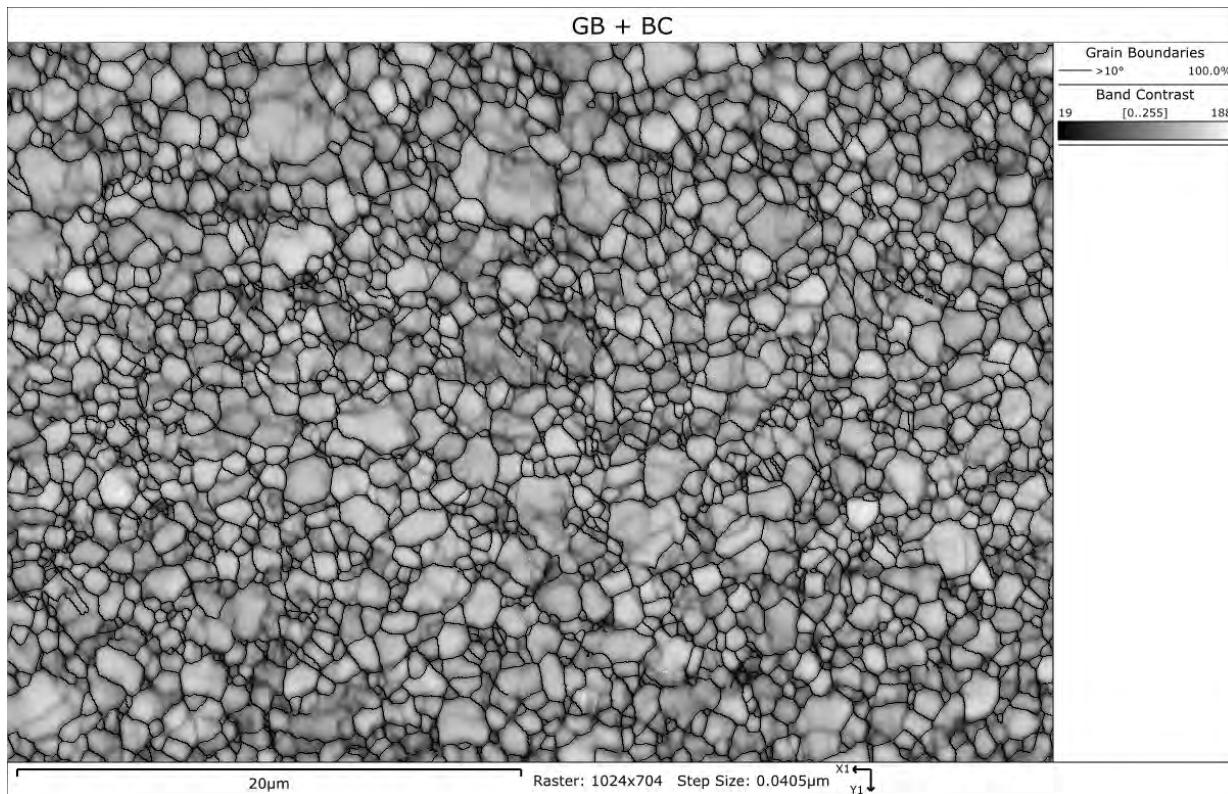


Figure 7.27. Grain Boundary + Band Contrast for L02: Condition C01, Sample SS33

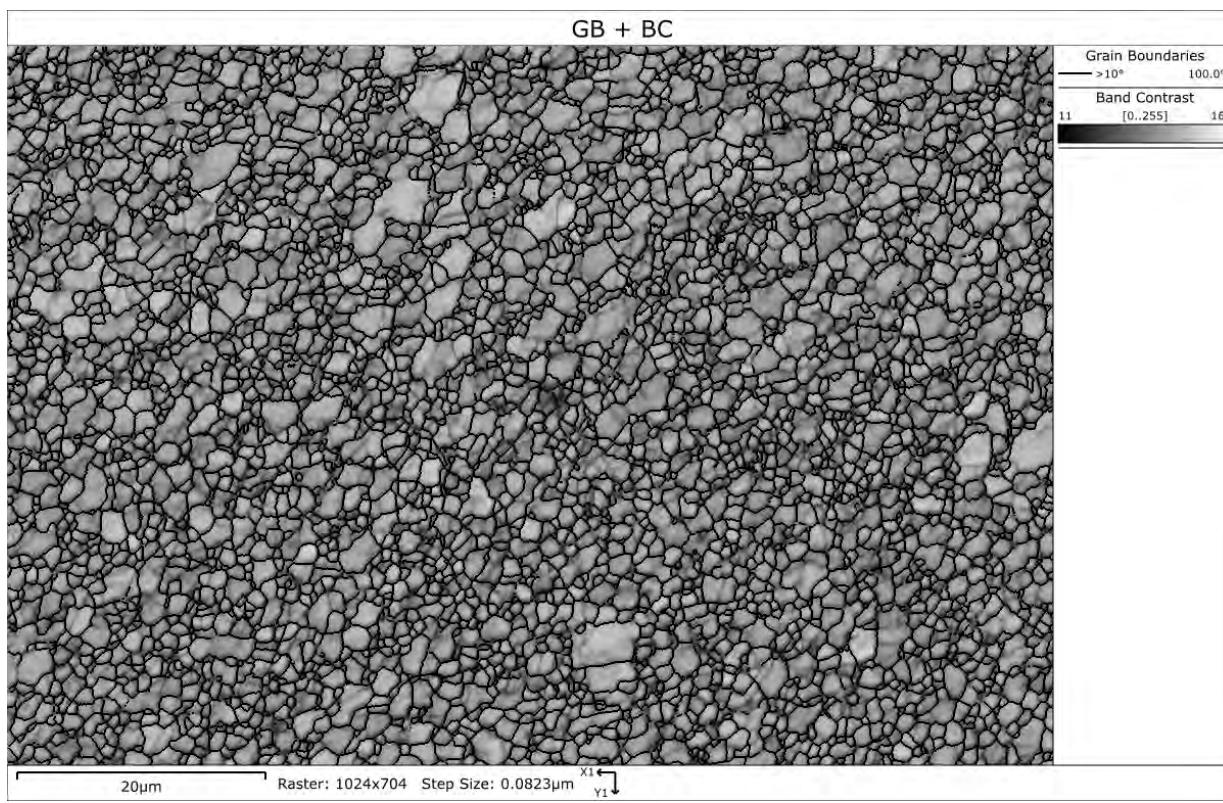


Figure 7.28. Grain Boundary + Band Contrast for L01b (2500x mag): Condition C05, Sample SS10

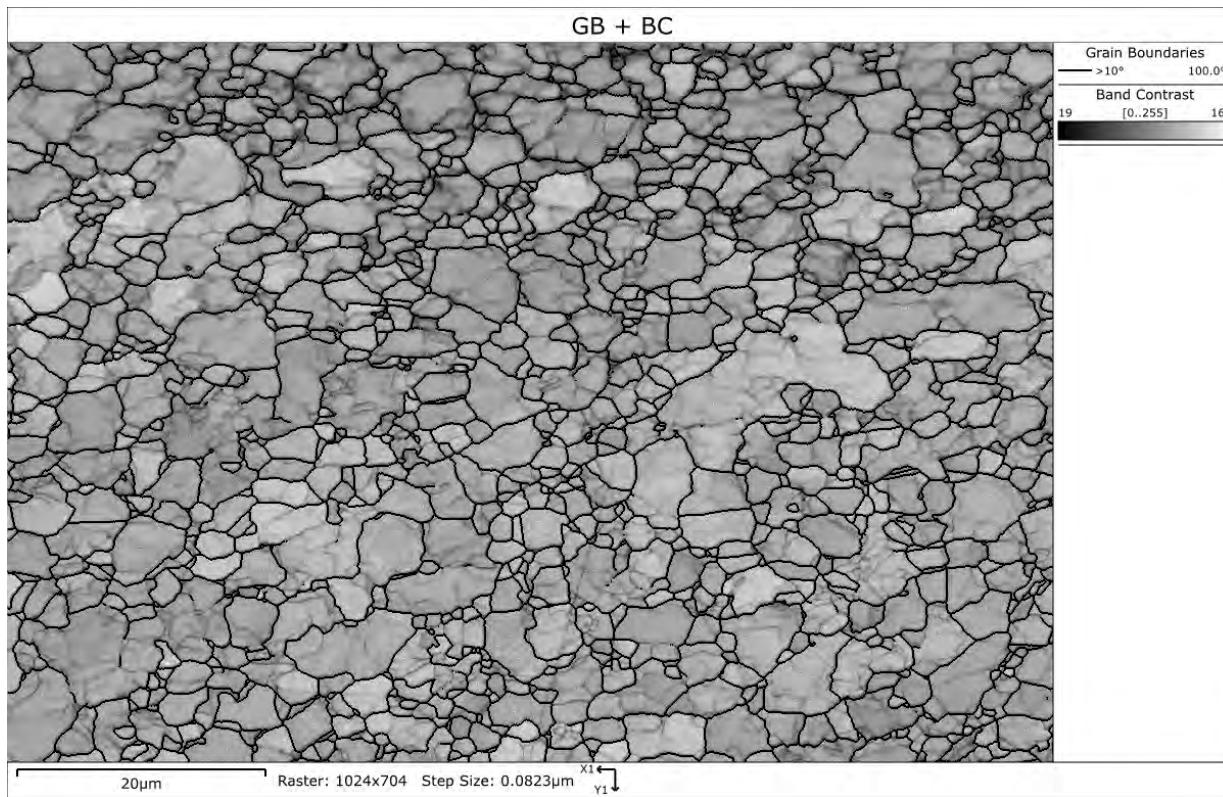


Figure 7.29. Grain Boundary + Band Contrast for L01b (2500x mag): Condition C08, Sample SS13

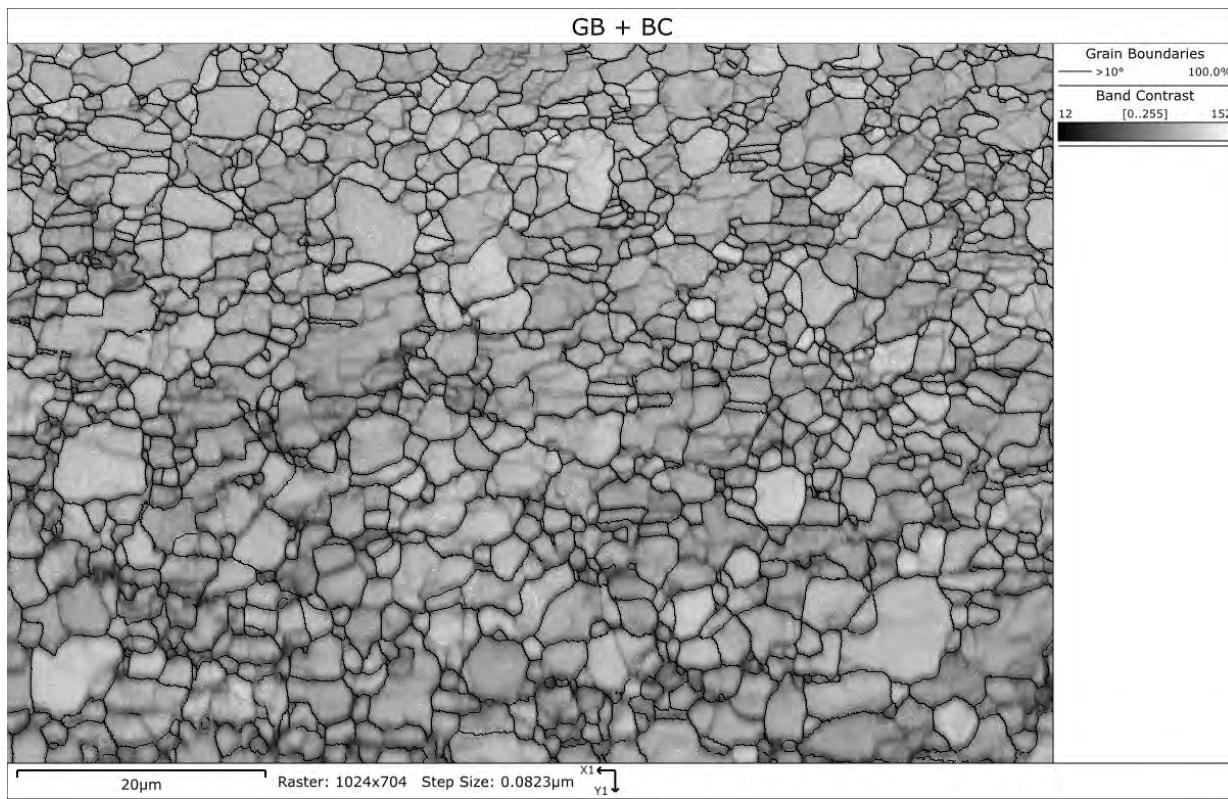


Figure 7.30. Grain Boundary + Band Contrast for L01b (2500x mag): Condition C09, Sample SS14

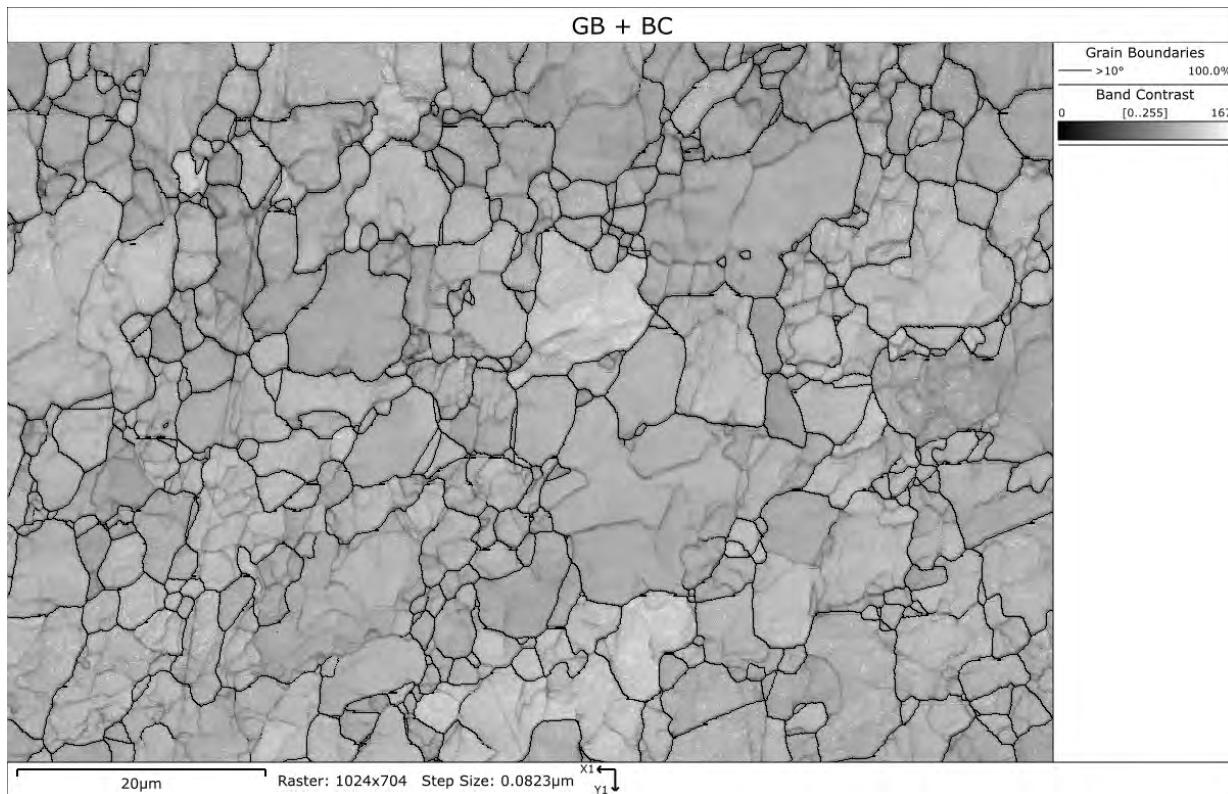


Figure 7.31. Grain Boundary + Band Contrast for L01b (2500x mag): Condition C10, Sample SS15

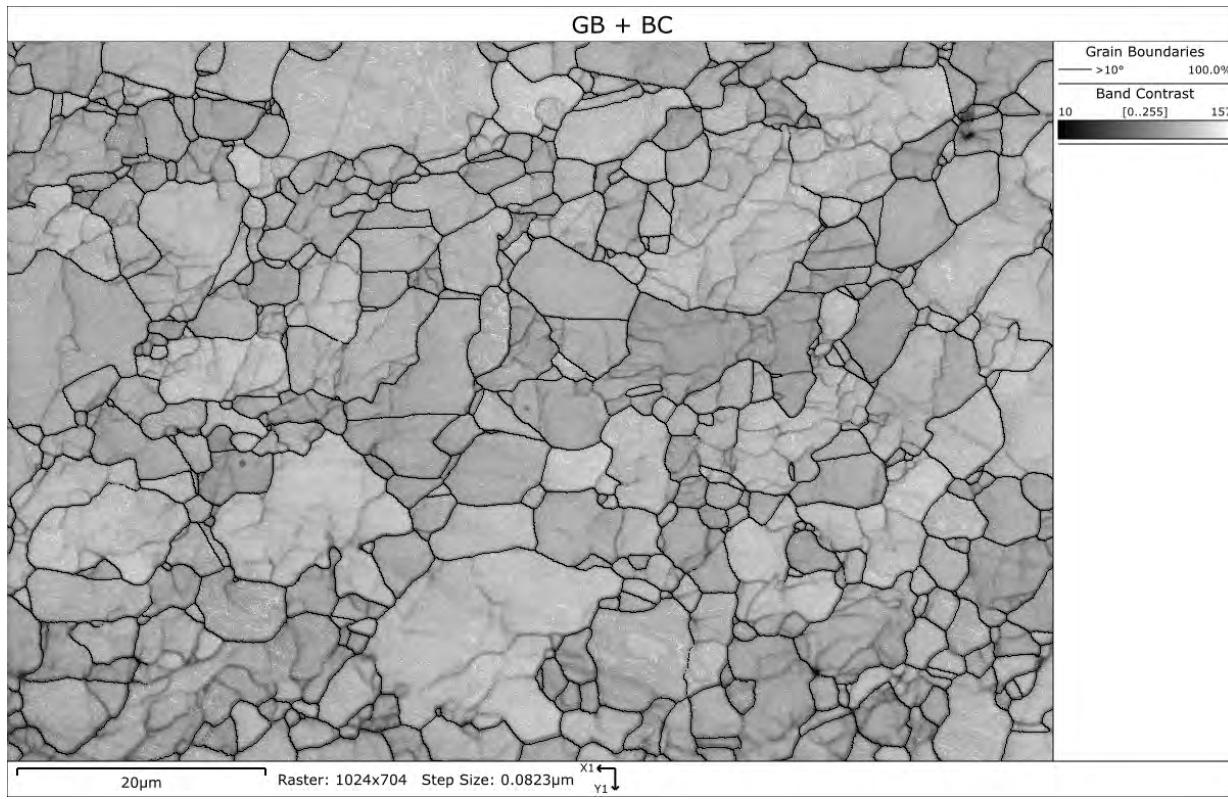


Figure 7.32. Grain Boundary + Band Contrast for L01b (2500x mag): Condition C11, Sample SS16

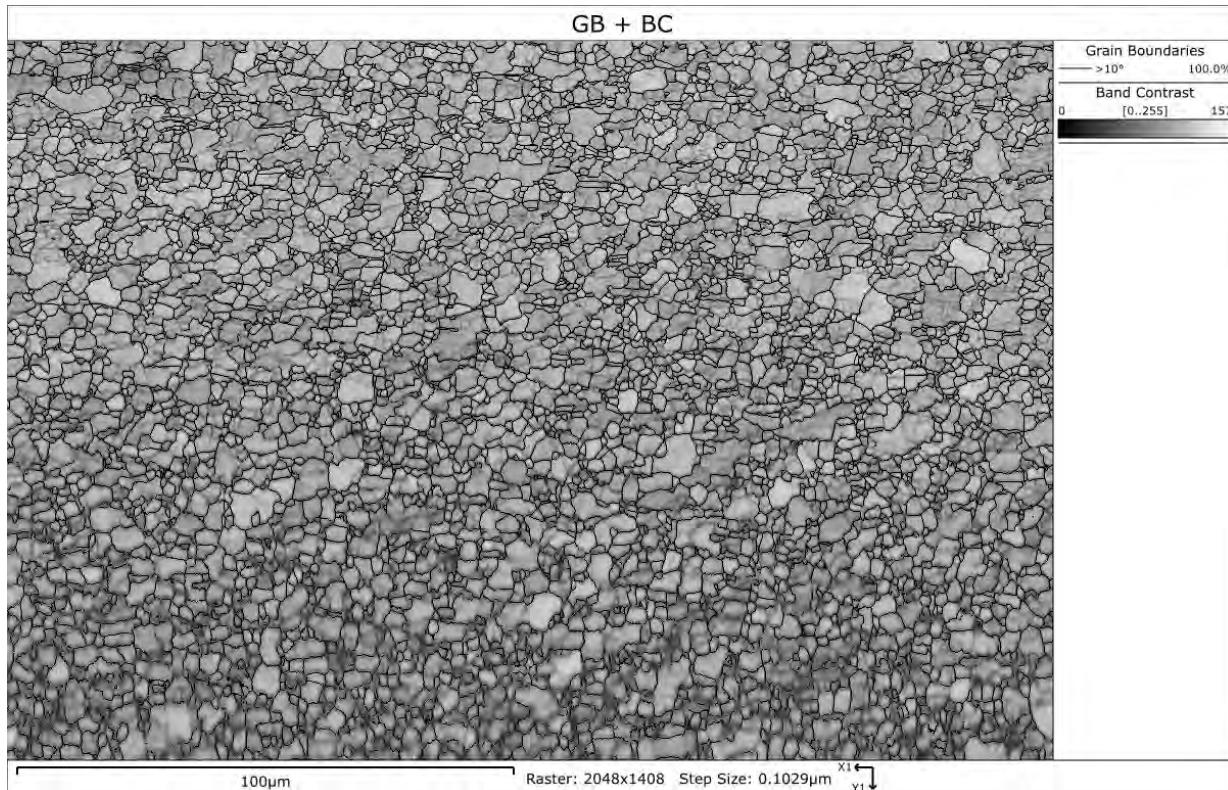


Figure 7.33. Grain Boundary + Band Contrast for L01b (1000x mag): Condition C09, Sample SS14

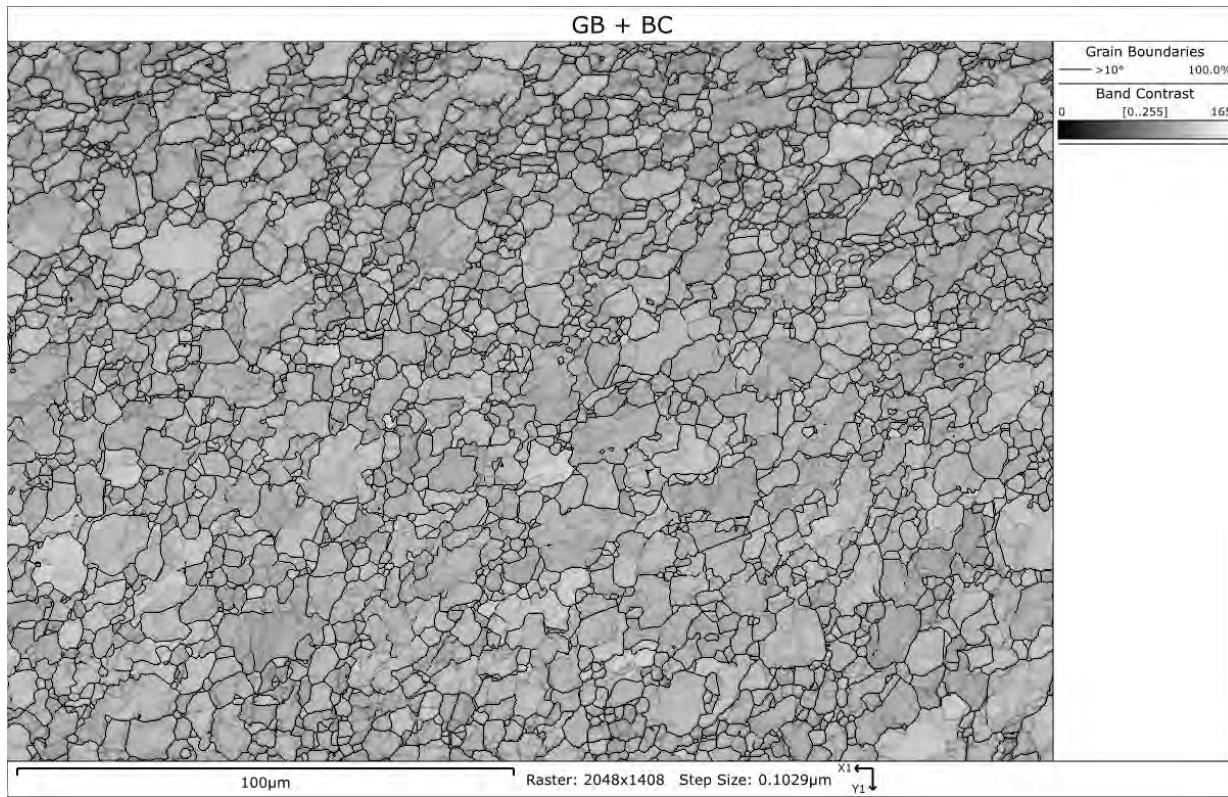


Figure 7.34. Grain Boundary + Band Contrast for L01b (1000x mag): Condition C10, Sample SS15

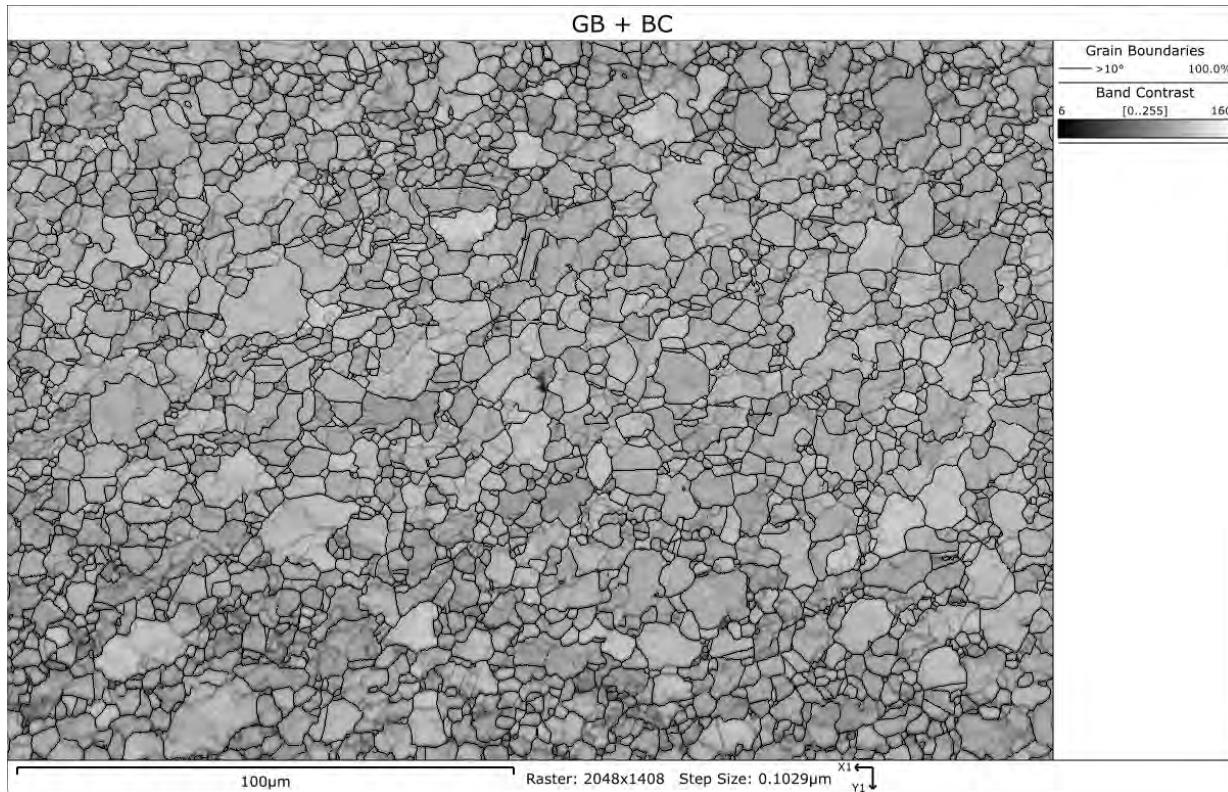


Figure 7.35. Grain Boundary + Band Contrast for L01b (1000x mag): Condition C11, Sample SS16

7.3 Band Contrast + Kernel Average Misorientation

The following figures show the grain boundaries identified through segmentation with a setting of 10° the misorientation angle, overlaid on the kernel average misorientation of the microstructure.

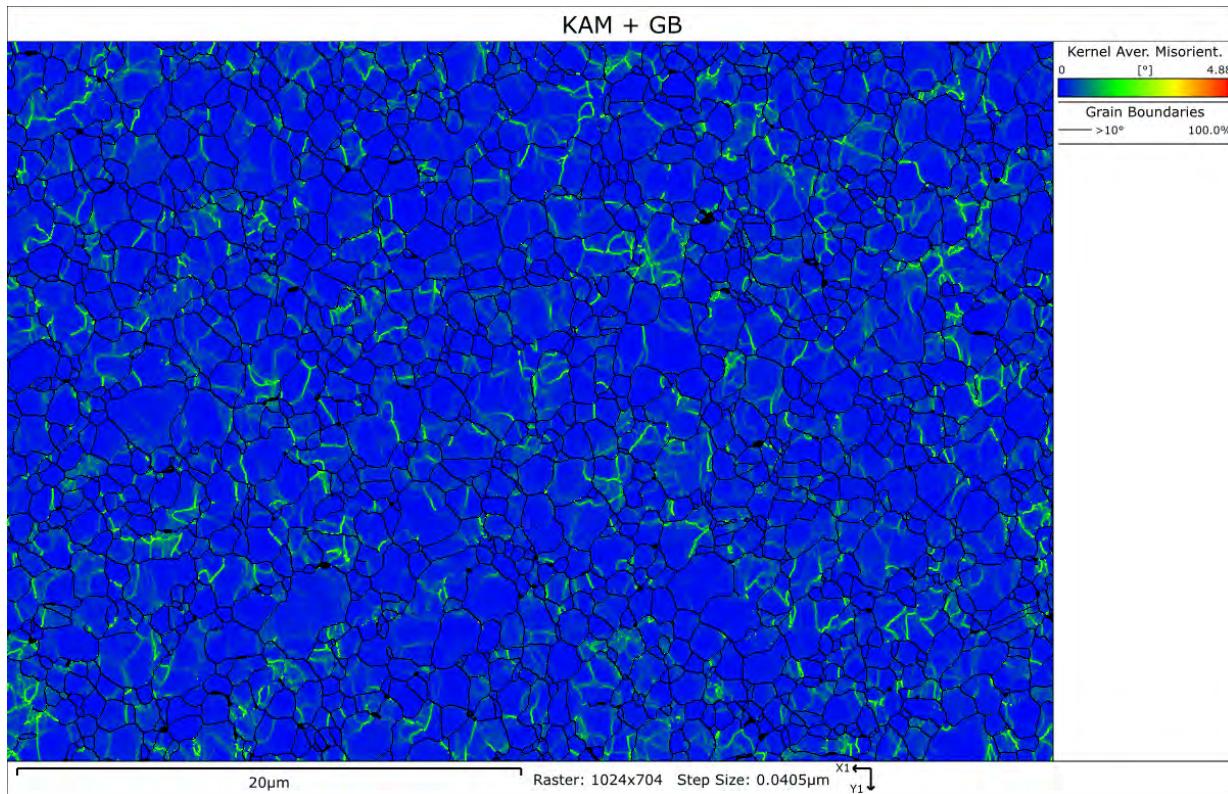


Figure 7.36. Grain Boundary + Kernel Average Misorientation for L02: Condition C03, Sample SS09

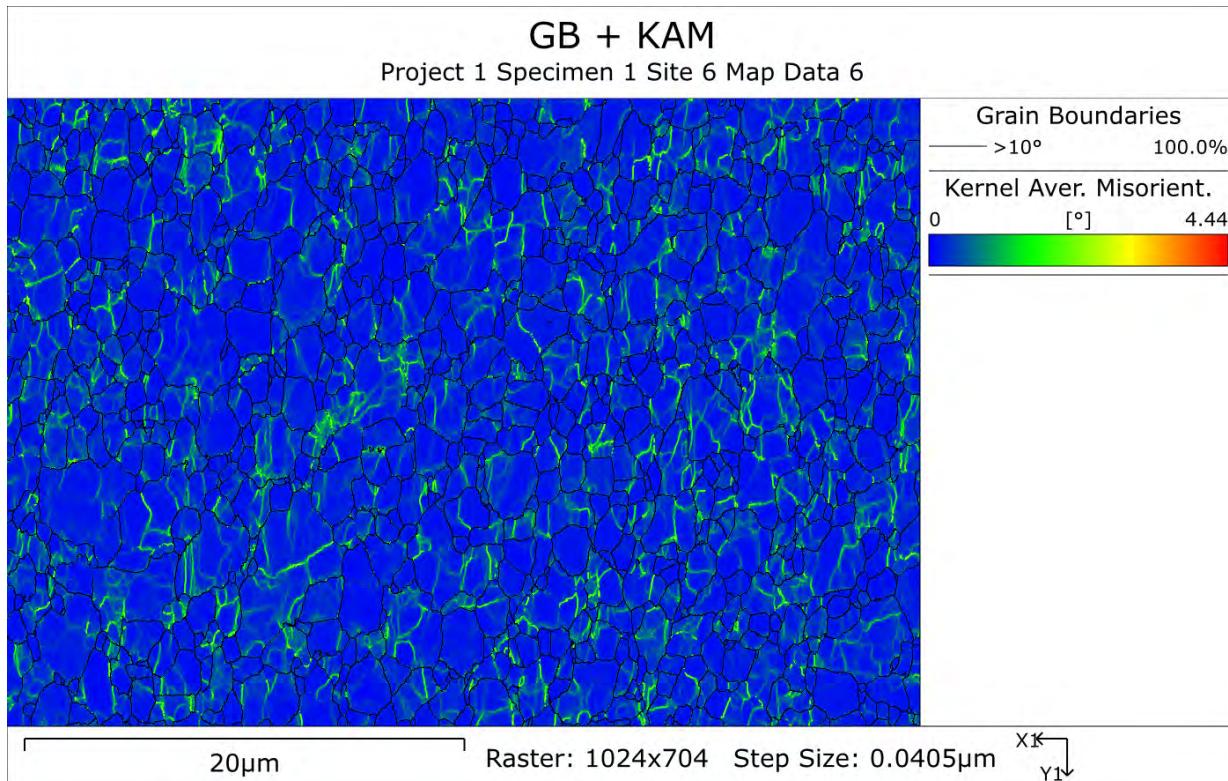


Figure 7.37. Grain Boundary + Kernel Average Misorientation for L02: Condition C05, Sample SS10

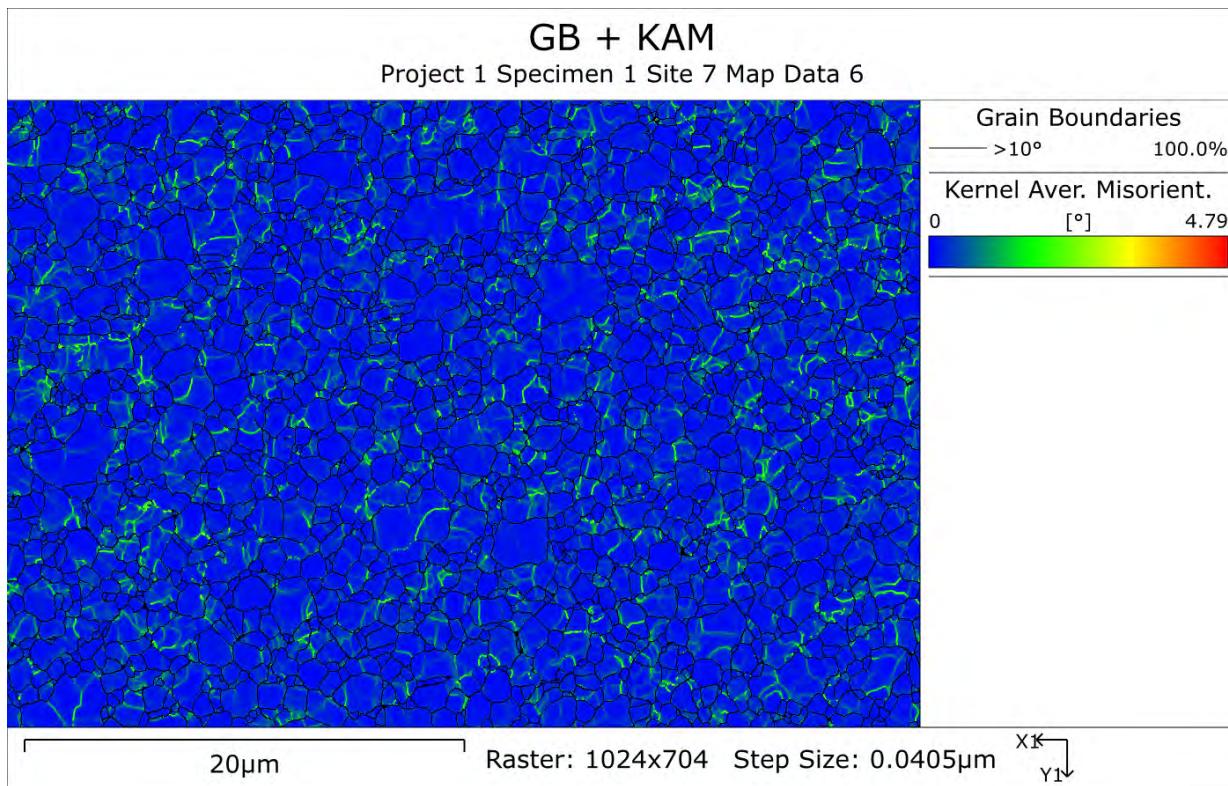


Figure 7.38. Grain Boundary + Kernel Average Misorientation for L02: Condition C06, Sample SS11

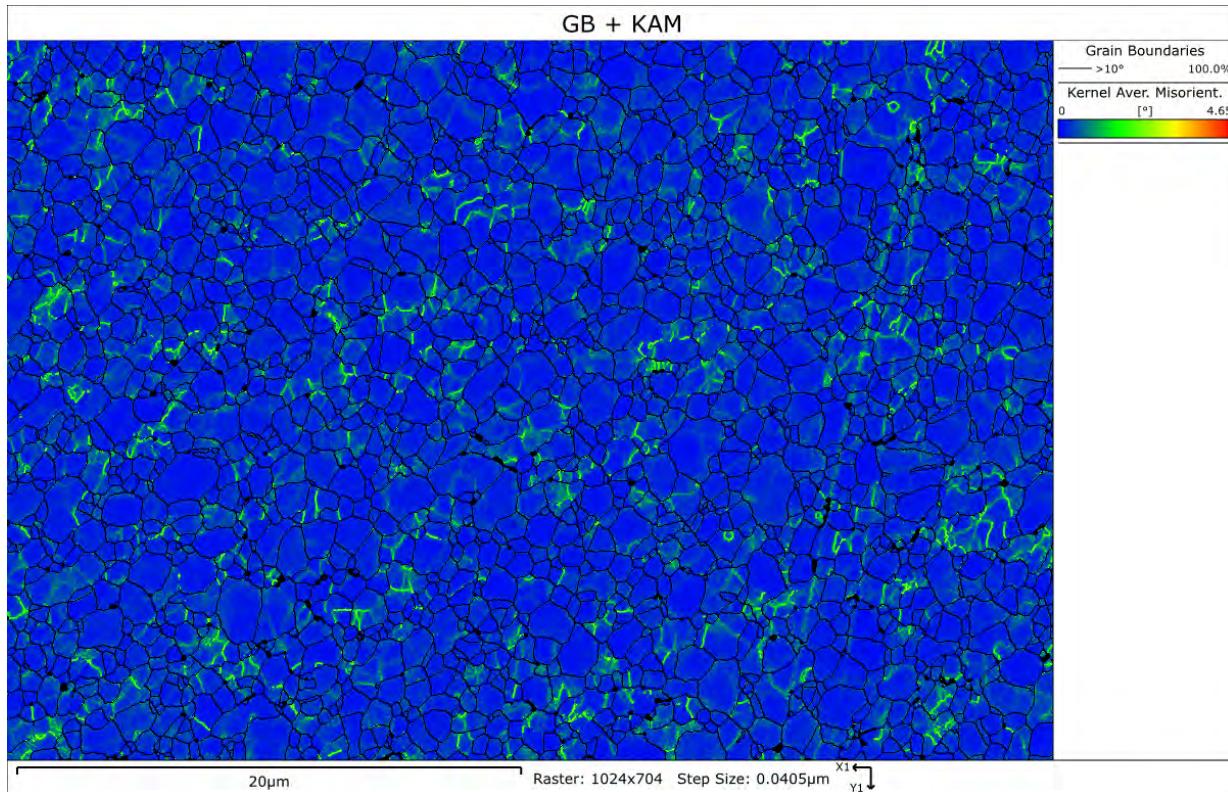


Figure 7.39. Grain Boundary + Kernel Average Misorientation for L02: Condition C07, Sample SS12

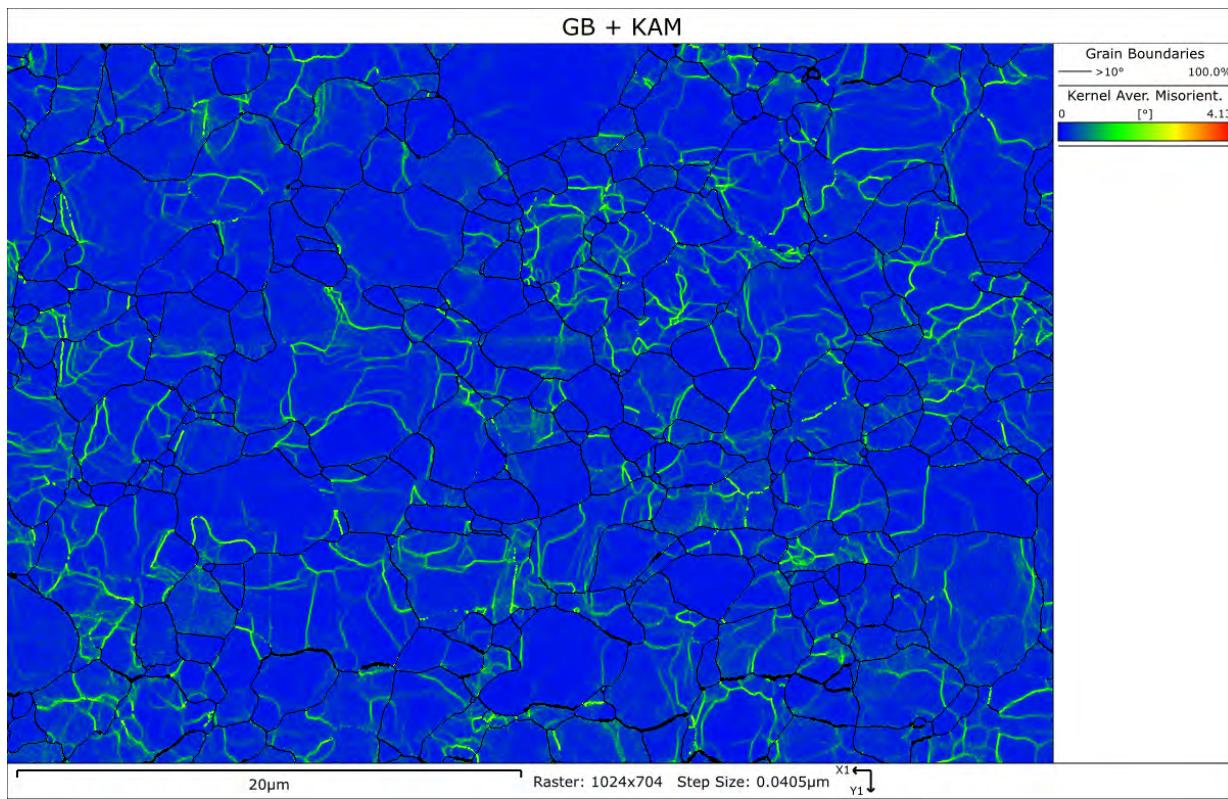


Figure 7.40. Grain Boundary + Kernel Average Misorientation for L02: Condition C08, Sample SS13

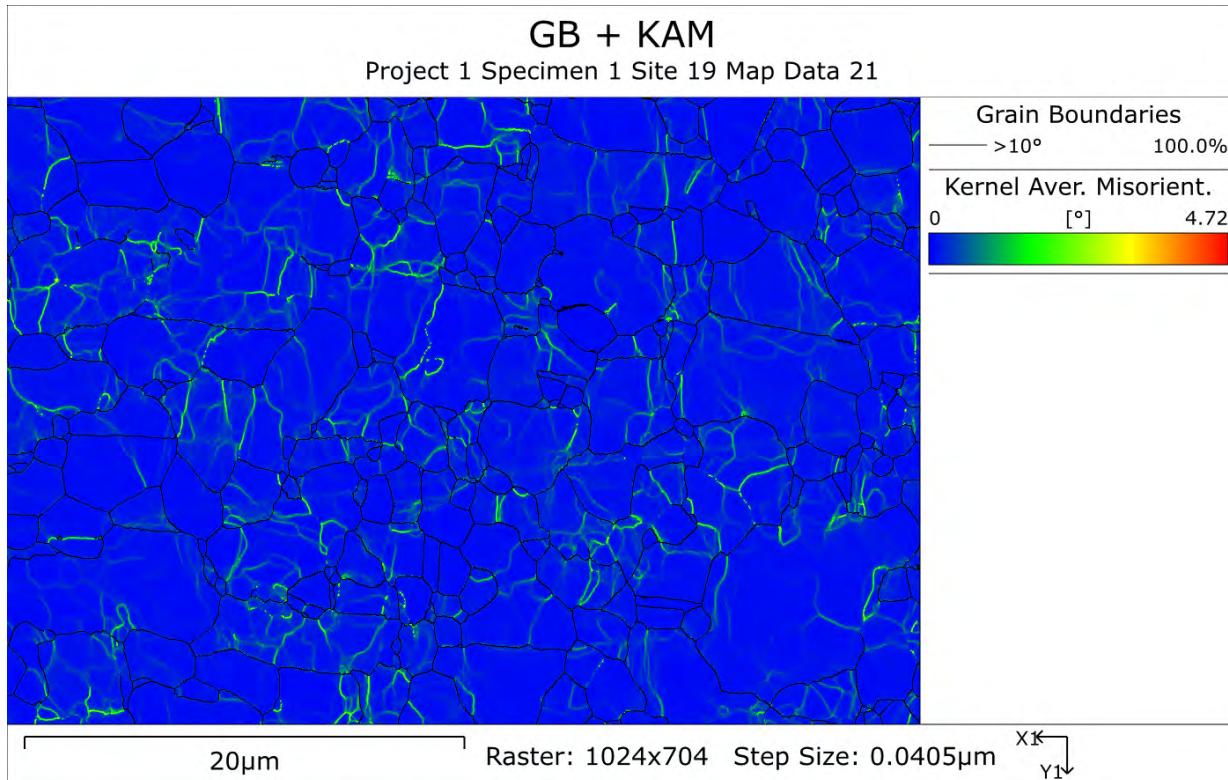


Figure 7.41. Grain Boundary + Kernel Average Misorientation for L02: Condition C09, Sample SS14

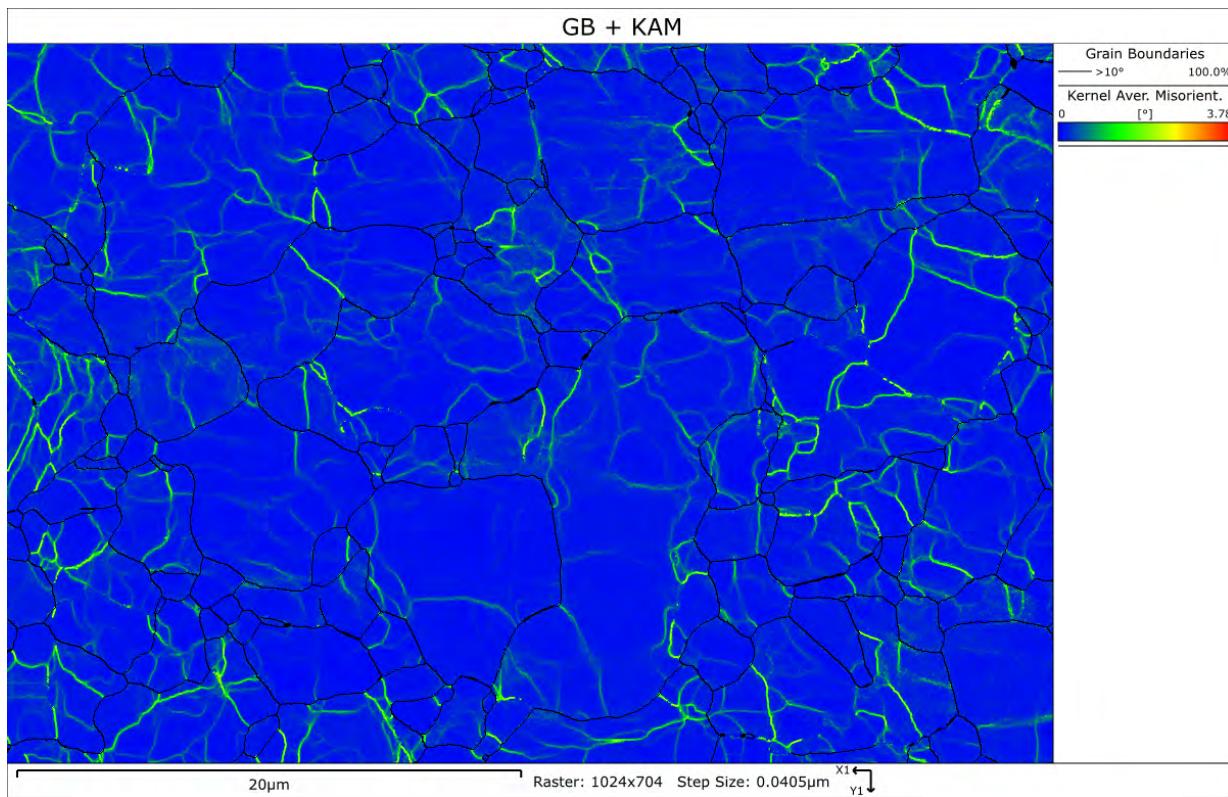


Figure 7.42. Grain Boundary + Kernel Average Misorientation for L02: Condition C10, Sample SS15

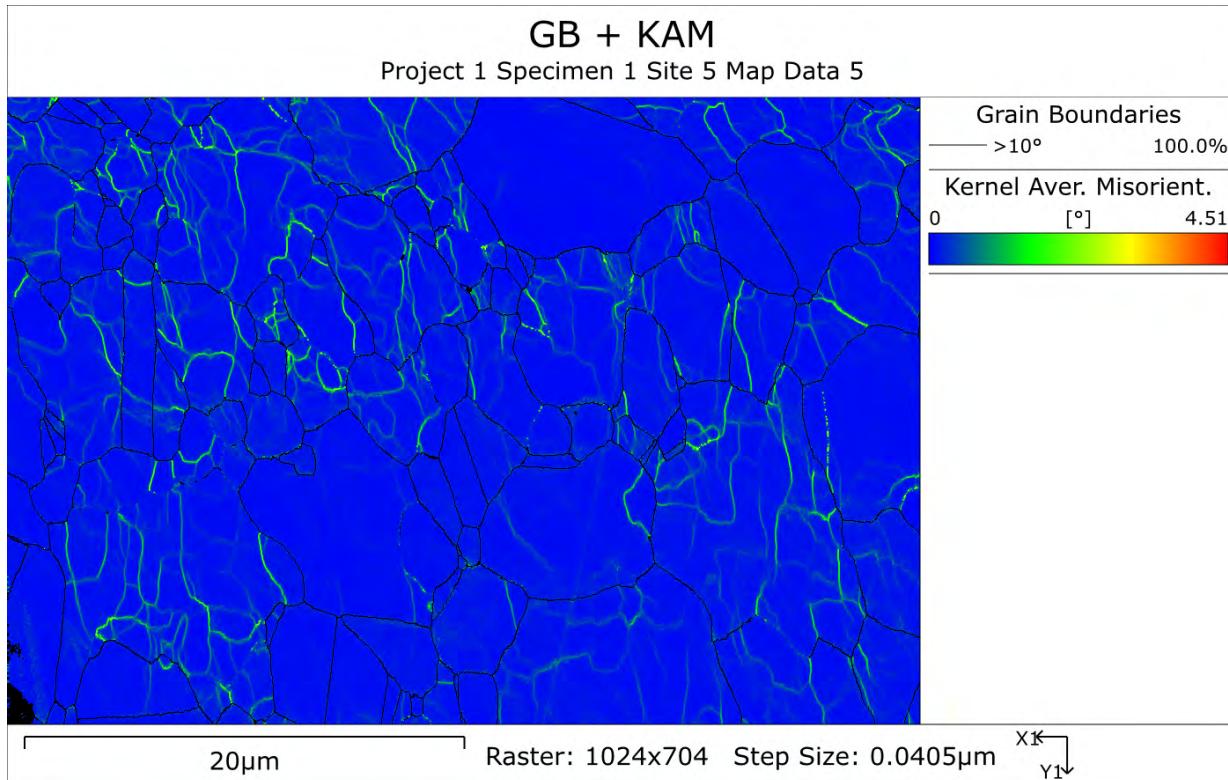


Figure 7.43. Grain Boundary + Kernel Average Misorientation for L02: Condition C11, Sample SS16

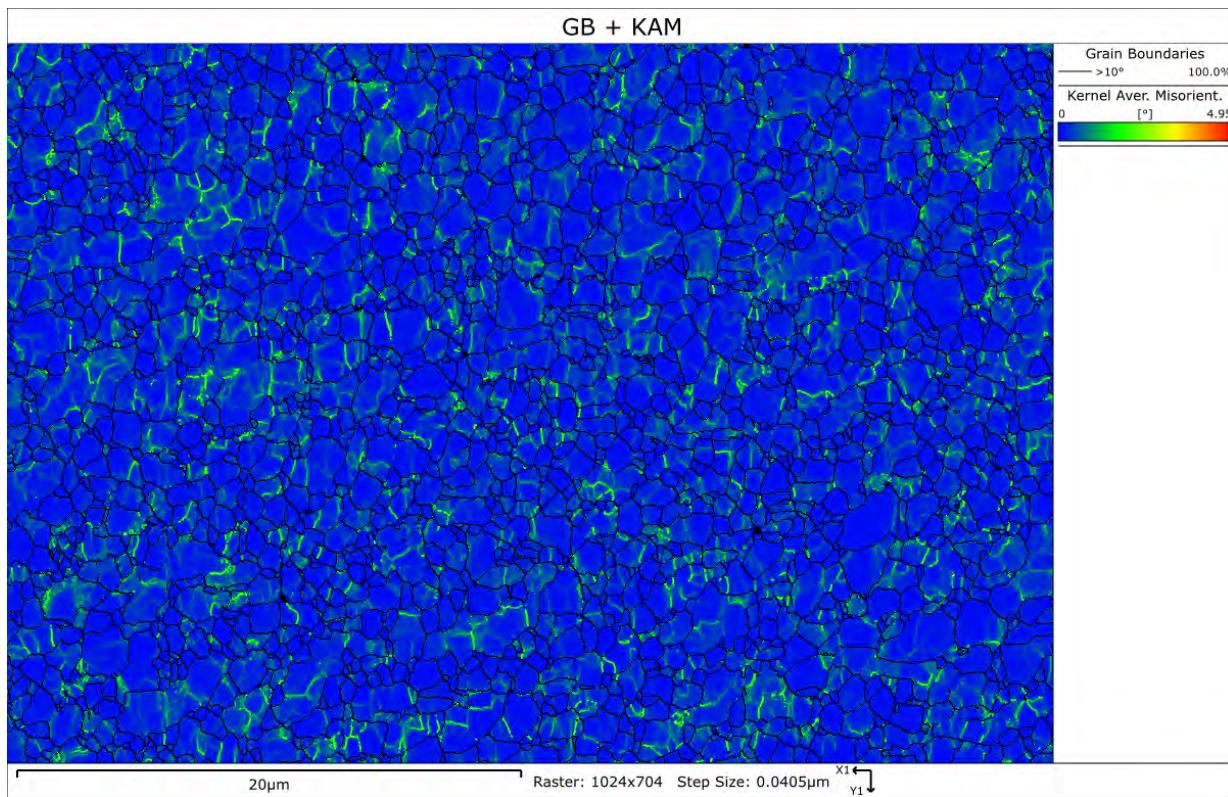


Figure 7.44. Grain Boundary + Kernel Average Misorientation for L02: Condition C02, Sample SS24

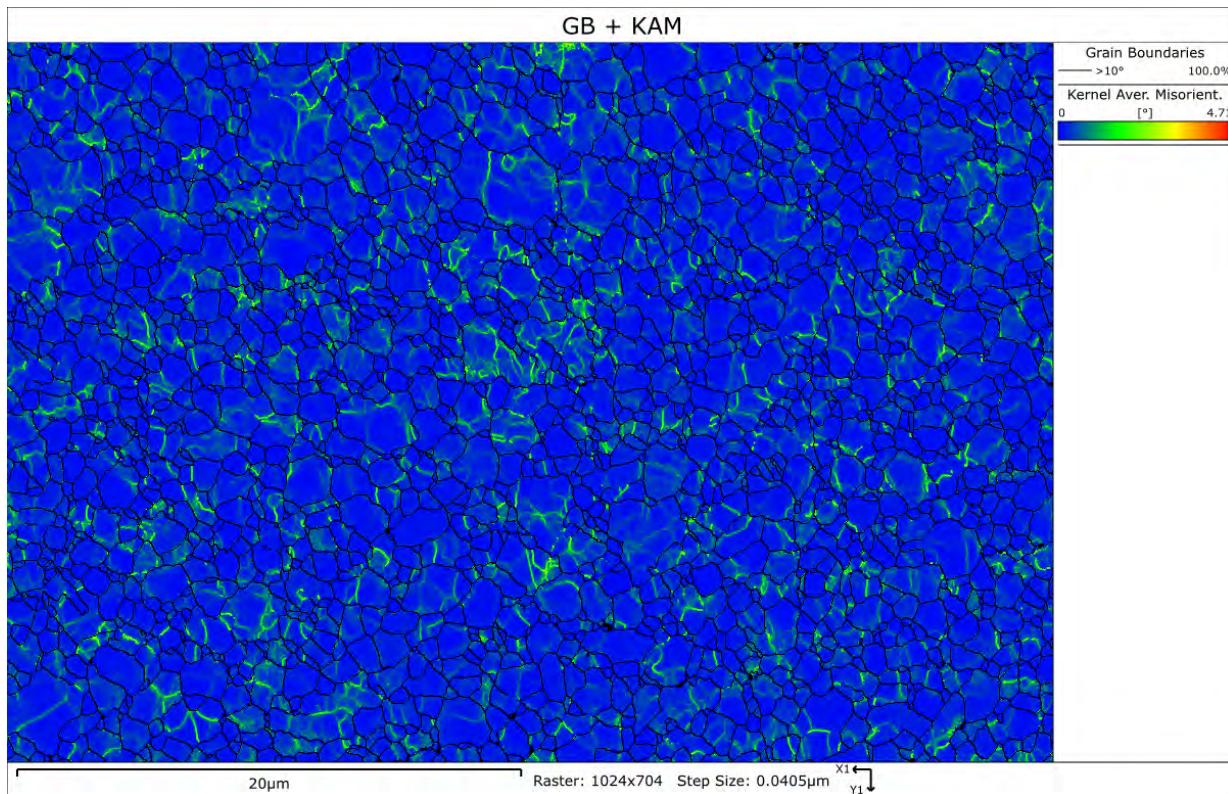


Figure 7.45. Grain Boundary + Kernel Average Misorientation for L02: Condition C01, Sample SS33

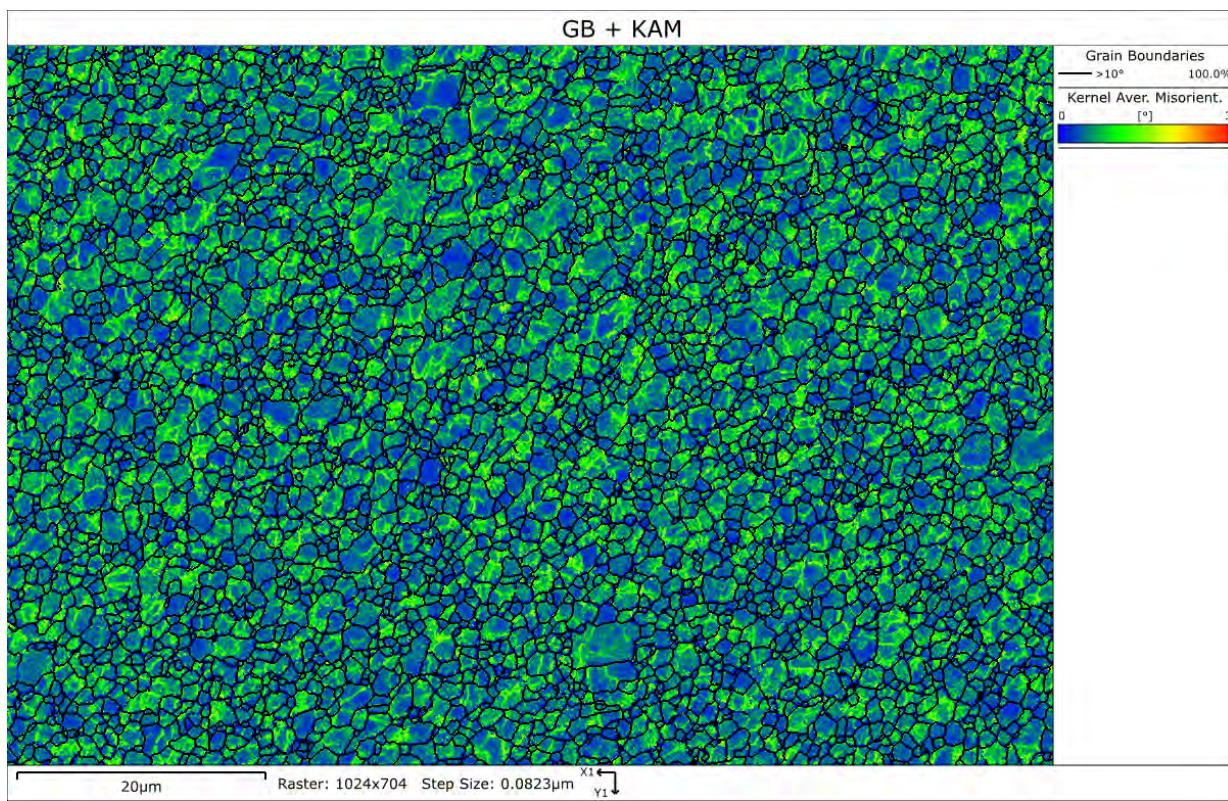


Figure 7.46. Grain Boundary + Kernel Average Misorientation for L01b (2500x mag): Condition C05, Sample SS10

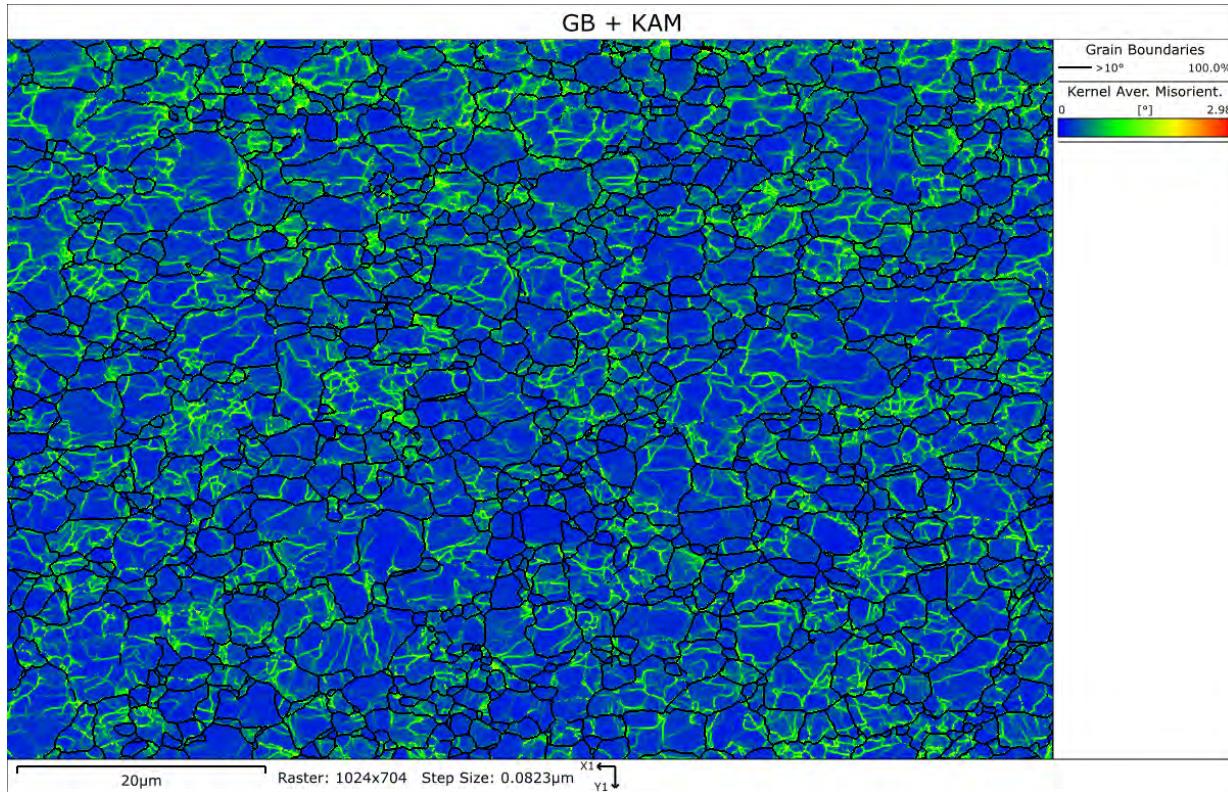


Figure 7.47. Grain Boundary + Kernel Average Misorientation for L01b (2500x mag): Condition C08, Sample SS13

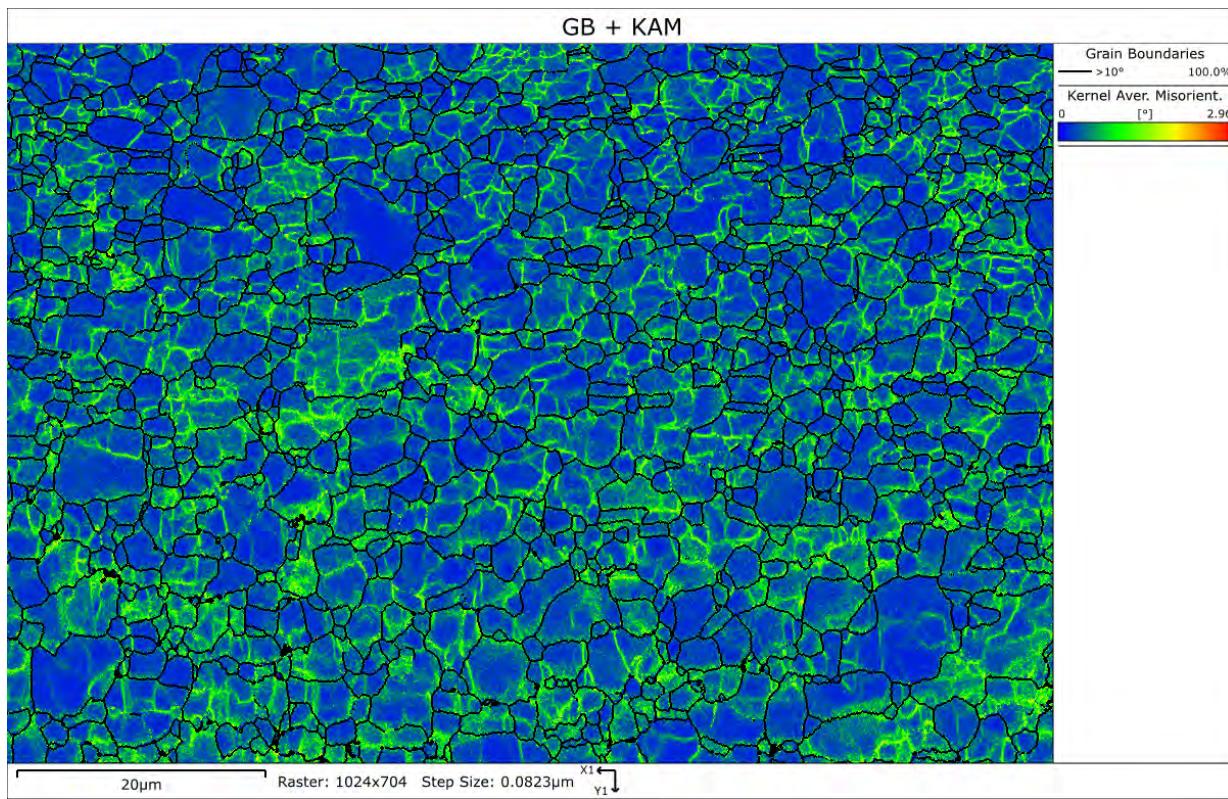


Figure 7.48. Grain Boundary + Kernel Average Misorientation for L01b (2500x mag): Condition C09, Sample SS14

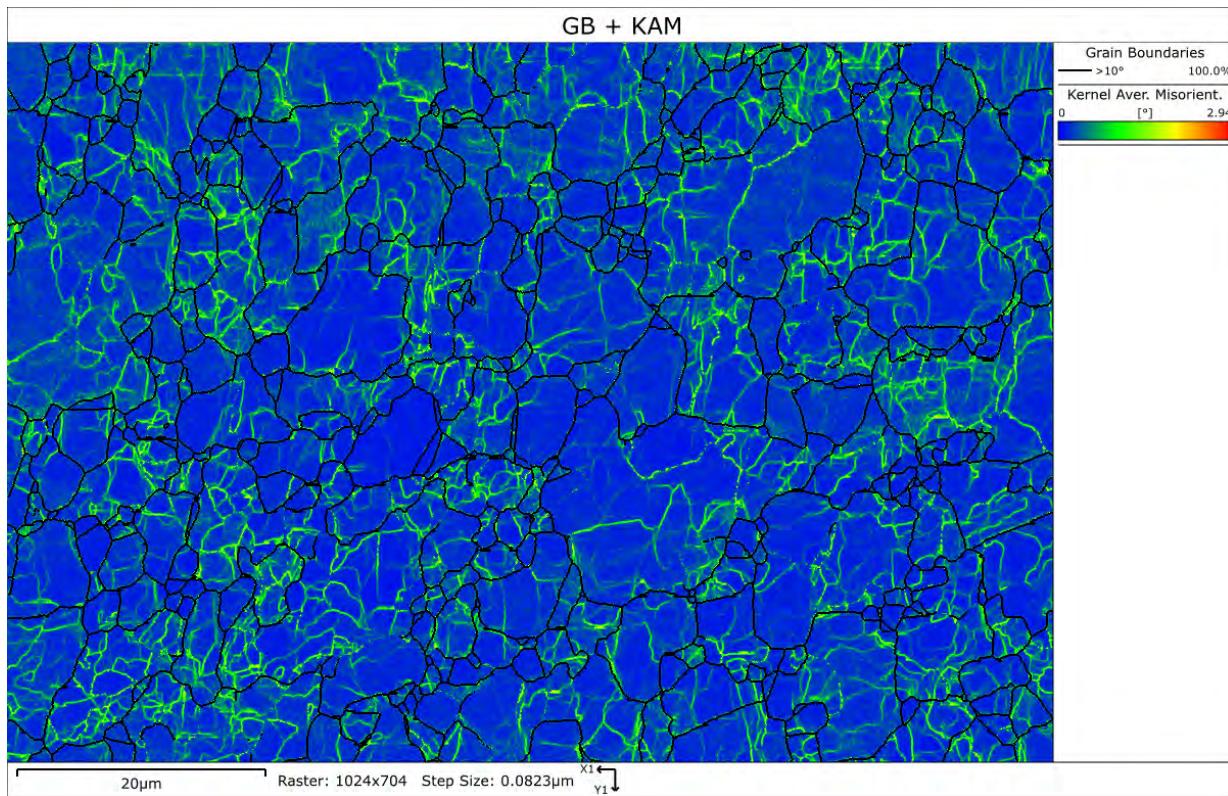


Figure 7.49. Grain Boundary + Kernel Average Misorientation for L01b (2500x mag): Condition C10, Sample SS15

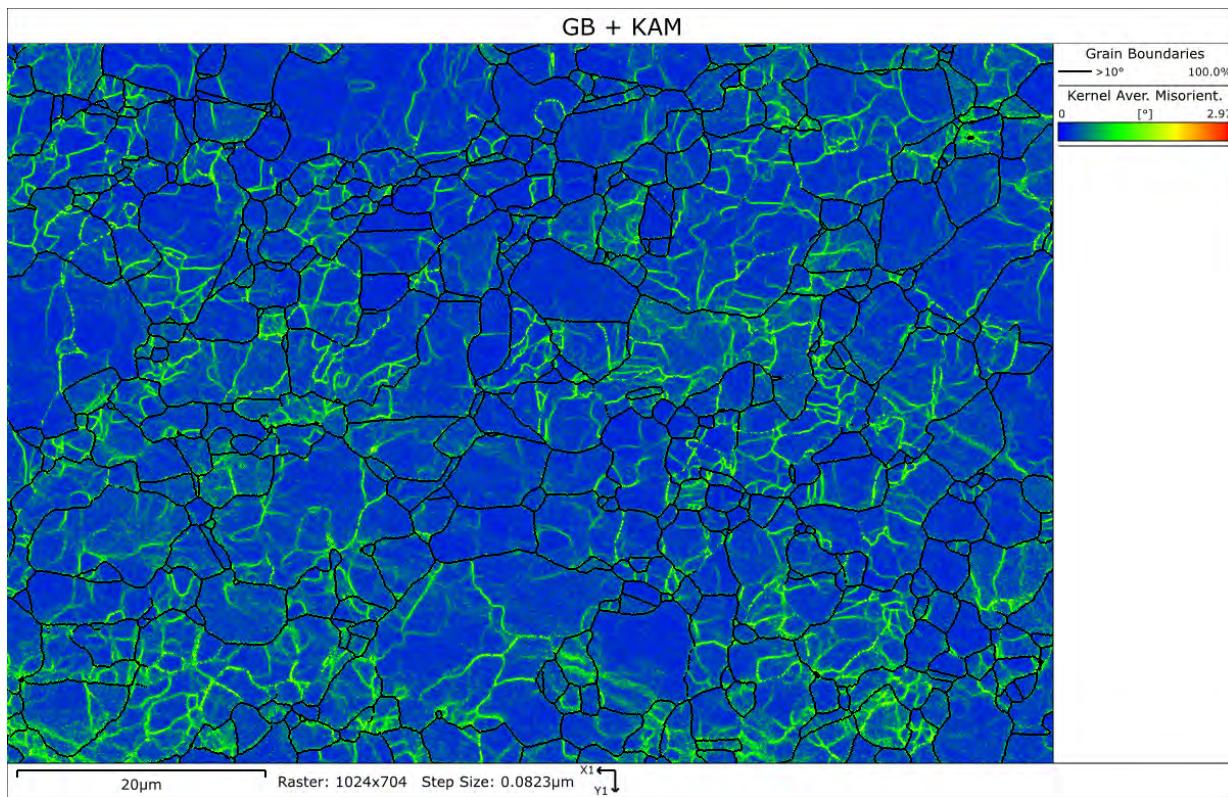


Figure 7.50. Grain Boundary + Kernel Average Misorientation for L01b (2500x mag): Condition C11, Sample SS16

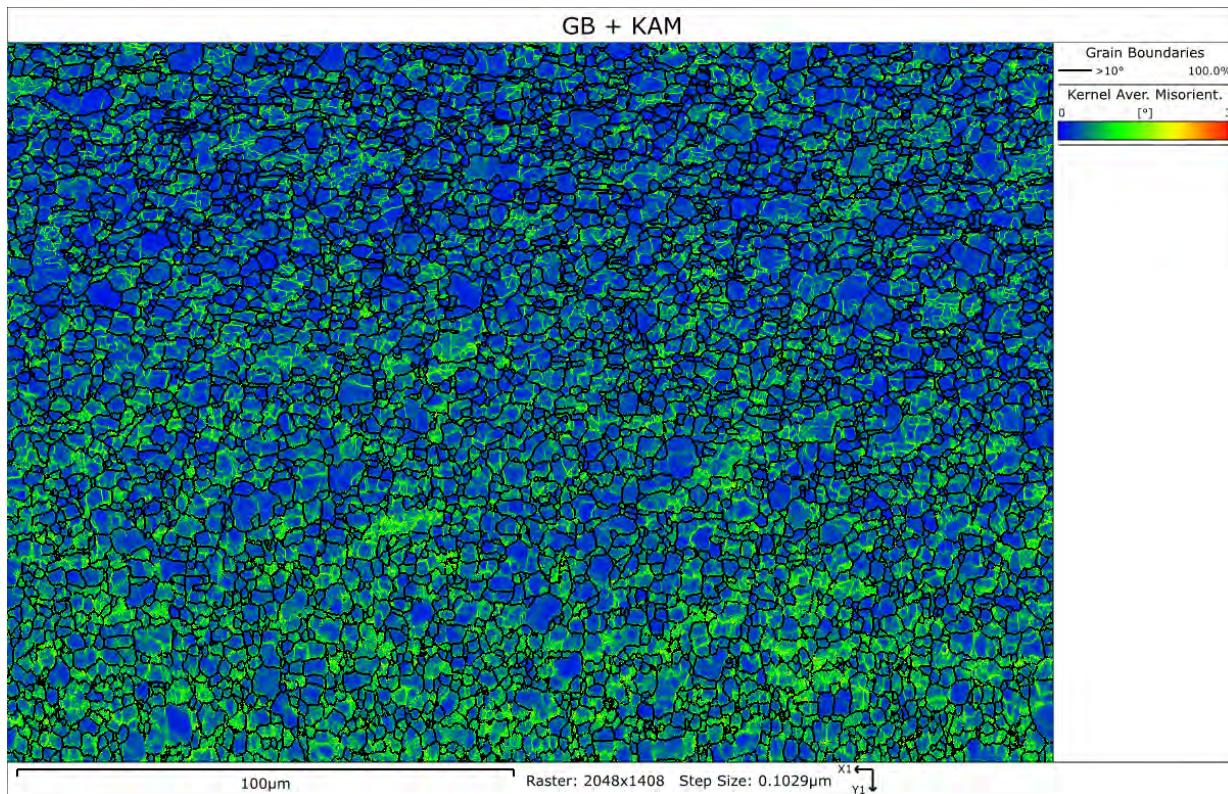


Figure 7.51. Grain Boundary + Kernel Average Misorientation for L01b (1000x mag): Condition C09, Sample SS14

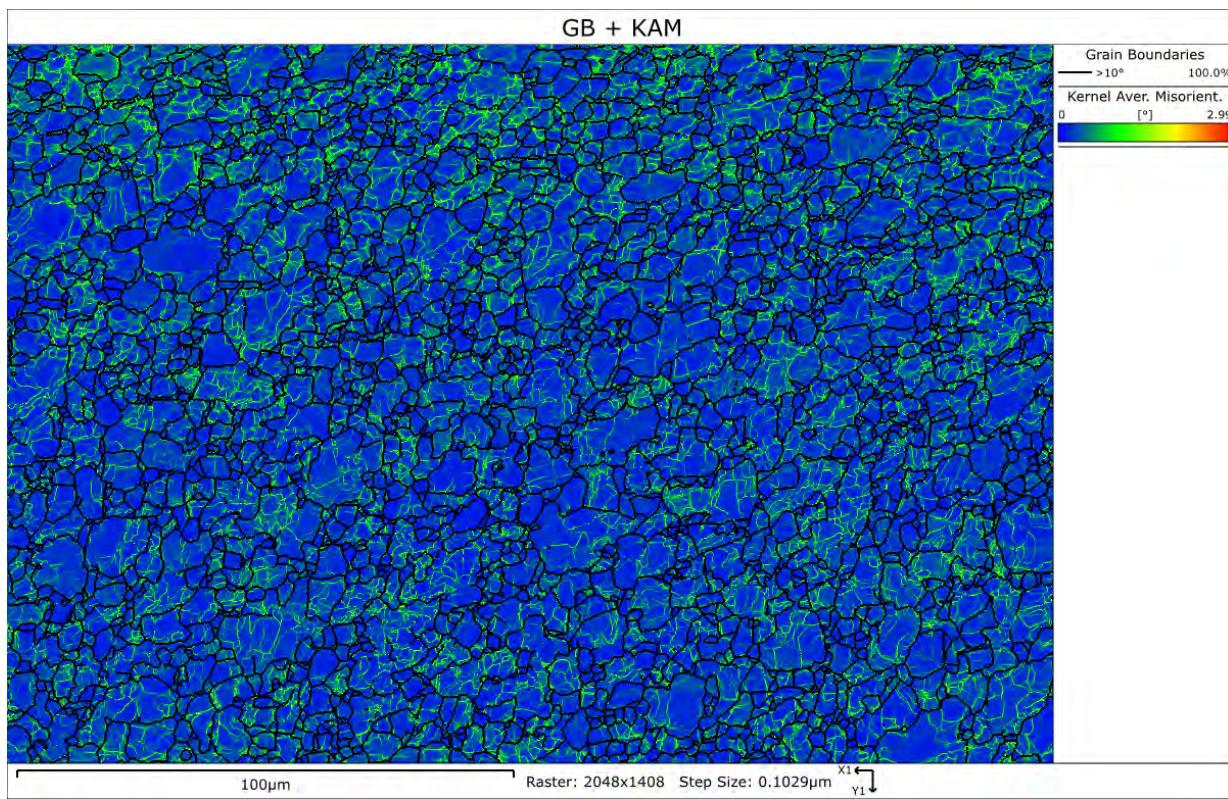


Figure 7.52. Grain Boundary + Kernel Average Misorientation for L01b (1000x mag): Condition C10, Sample SS15

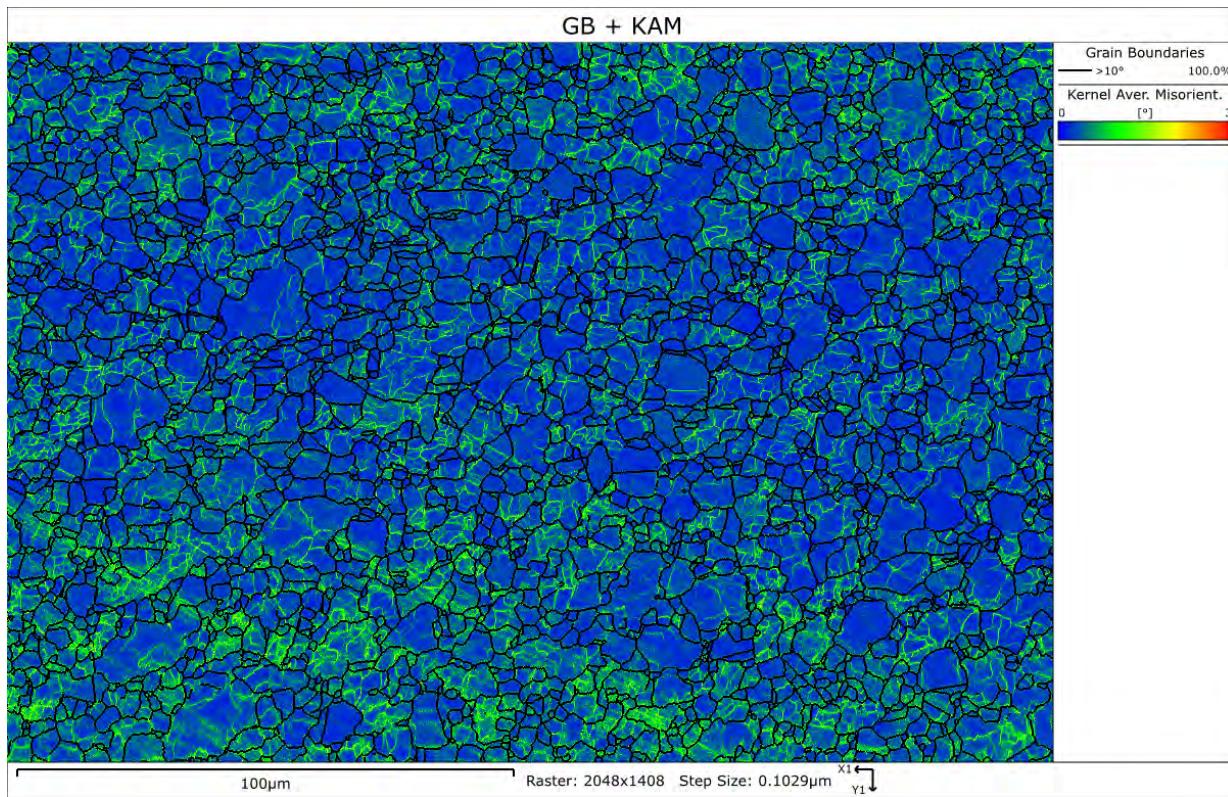


Figure 7.53. Grain Boundary + Kernel Average Misorientation for L01b (1000x mag): Condition C11, Sample SS16

7.4 Inverse Pole Function - X direction

The following figures show the IPF map in the x-direction with grain boundaries identified through segmentation.

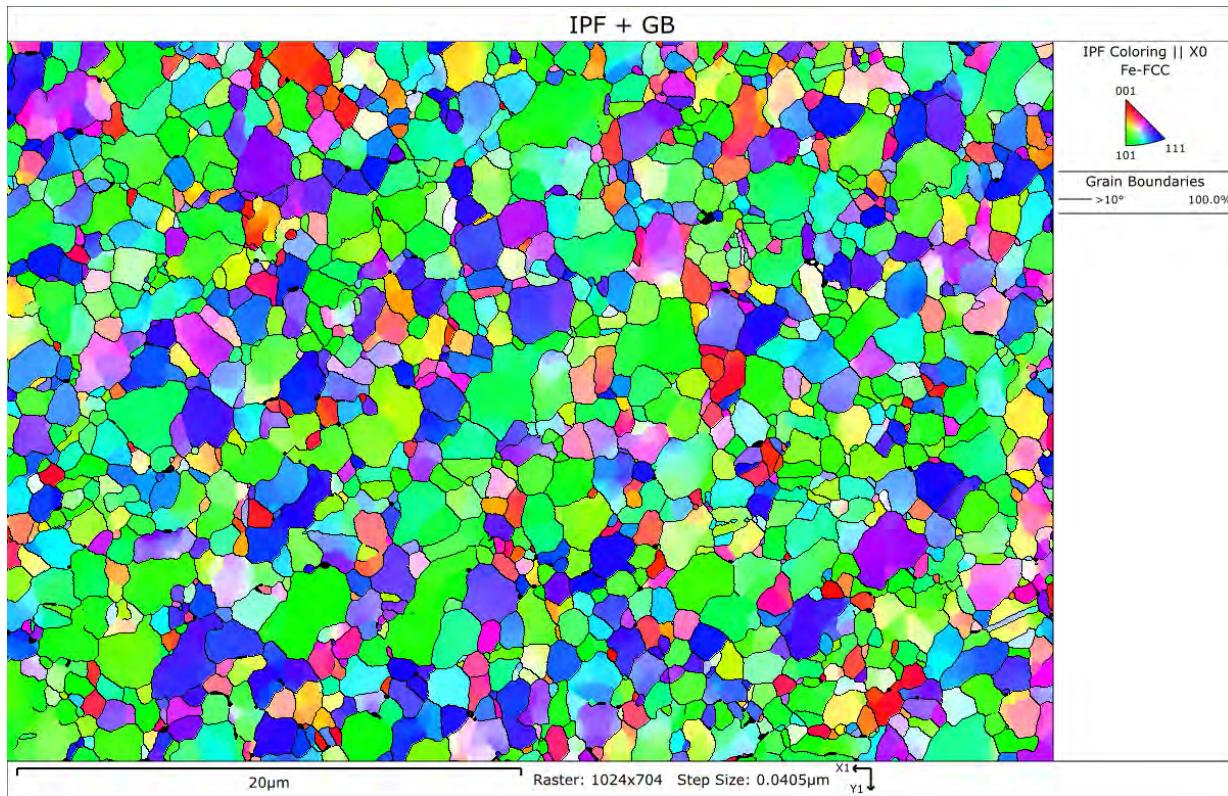


Figure 7.54. Inverse Pole Function - X Images for L02: Condition C03, Sample SS09

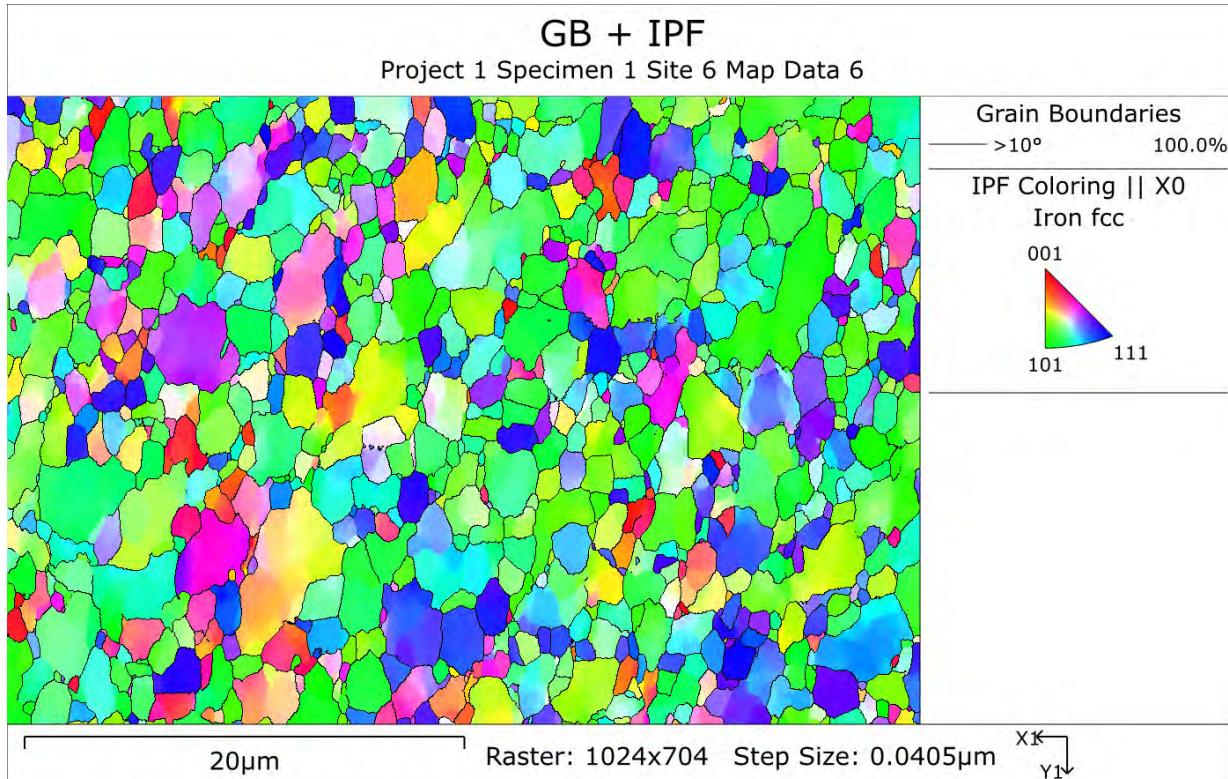


Figure 7.55. Inverse Pole Function - X Images for L02: Condition C05, Sample SS10

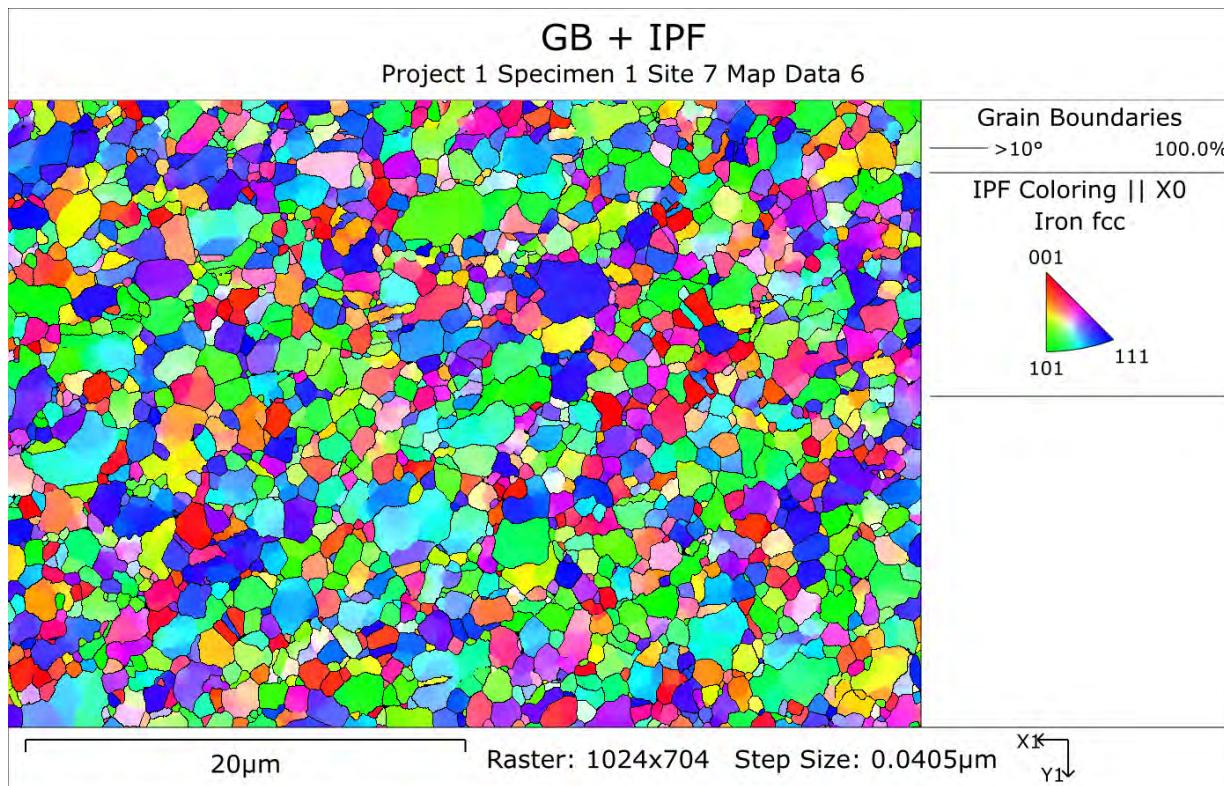


Figure 7.56. Inverse Pole Function - X Images for L02: Condition C06, Sample SS11

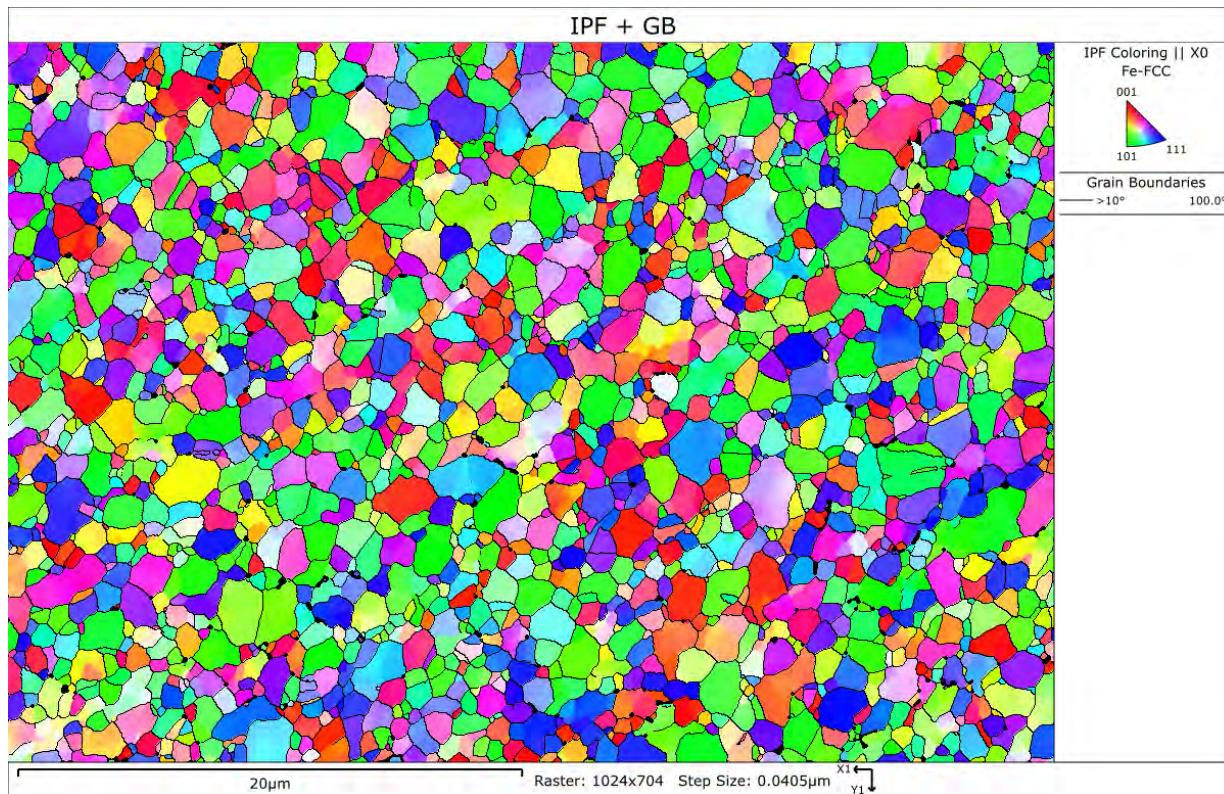


Figure 7.57. Inverse Pole Function - X Images for L02: Condition C07, Sample SS12

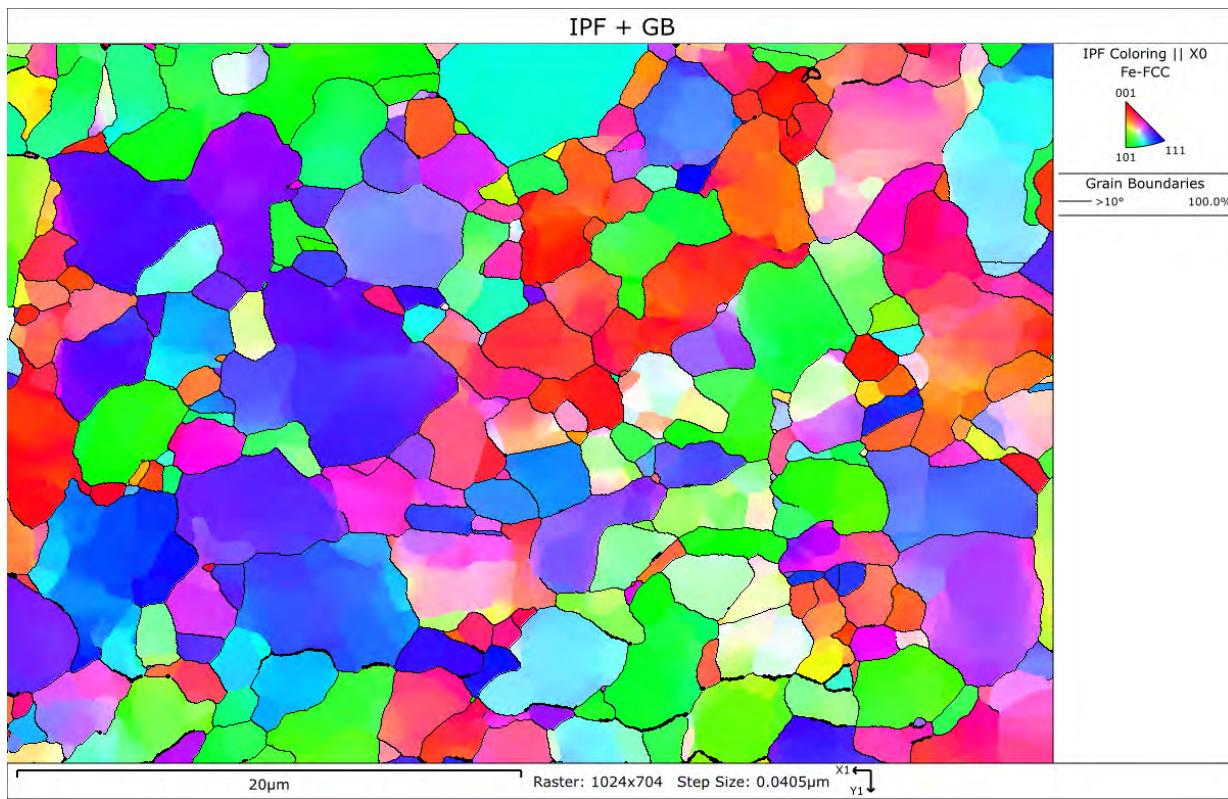


Figure 7.58. Inverse Pole Function - X Images for L02: Condition C08, Sample SS13

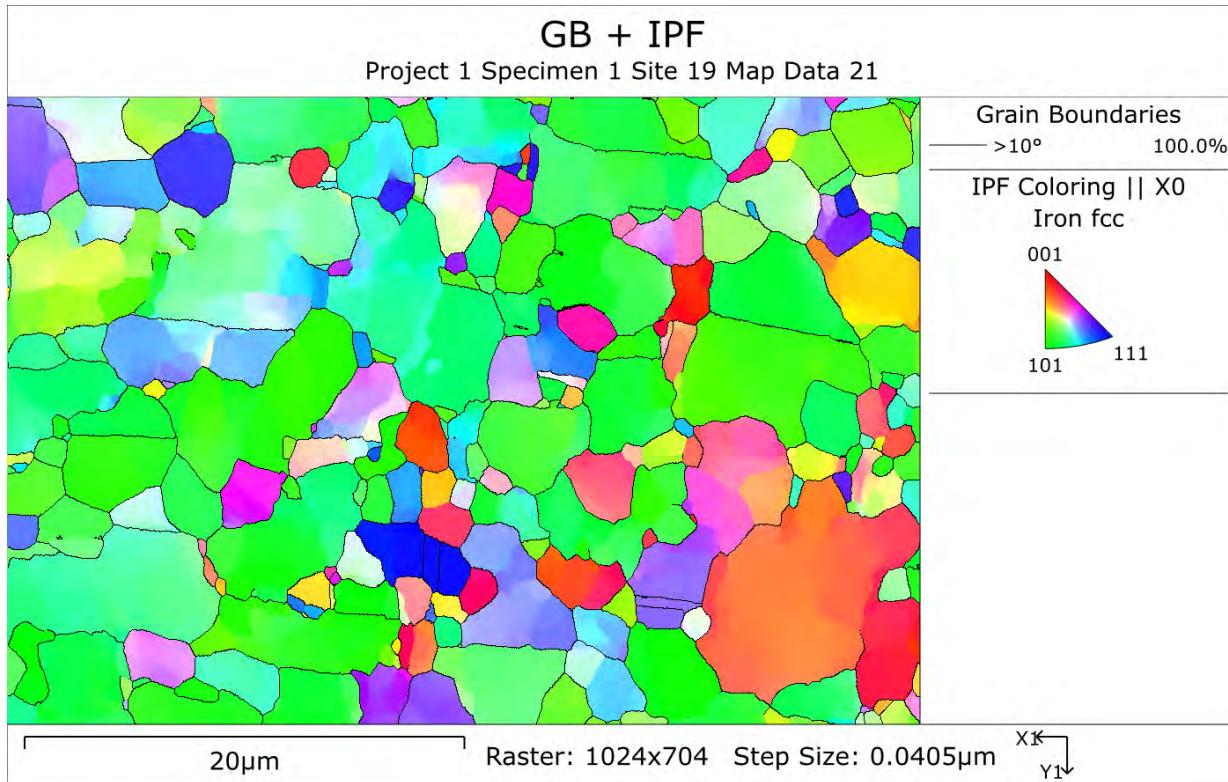


Figure 7.59. Inverse Pole Function - X Images for L02: Condition C09, Sample SS14

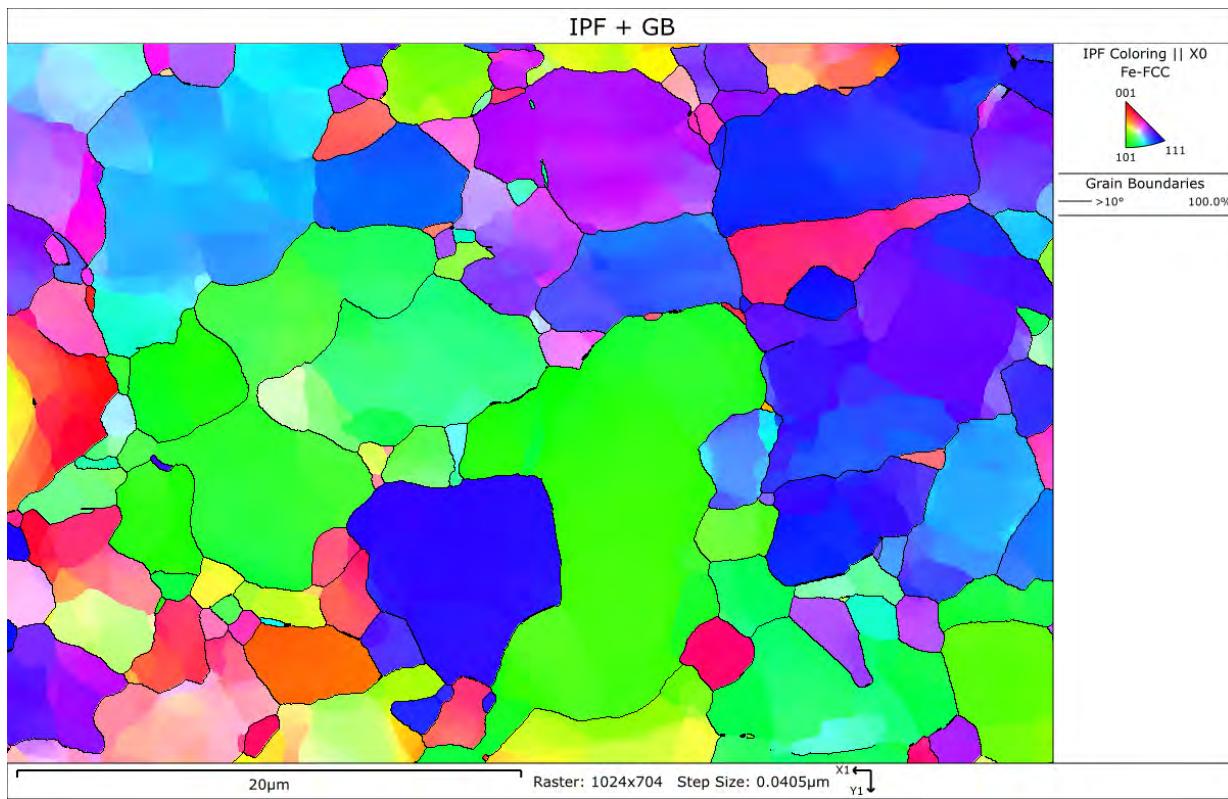


Figure 7.60. Inverse Pole Function - X Images for L02: Condition C10, Sample SS15

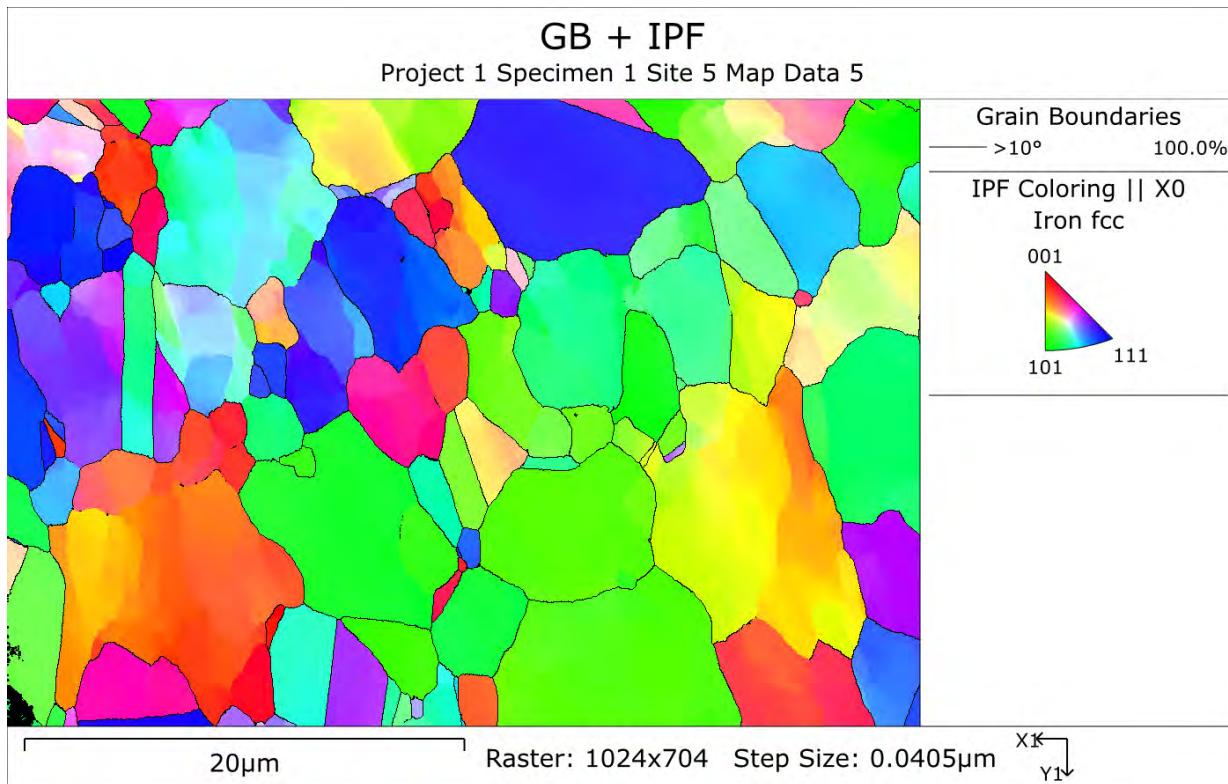


Figure 7.61. Inverse Pole Function - X Images for L02: Condition C11, Sample SS16

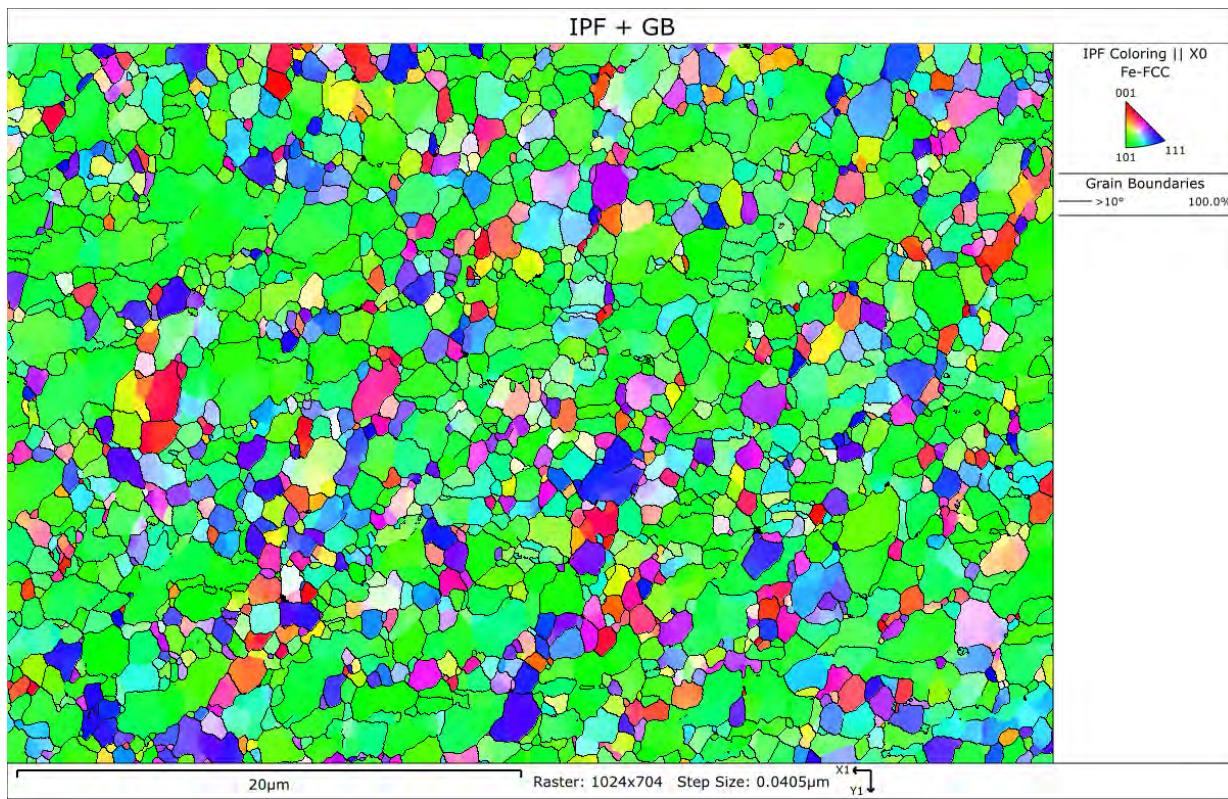


Figure 7.62. Inverse Pole Function - X Images for L02: Condition C02, Sample SS24

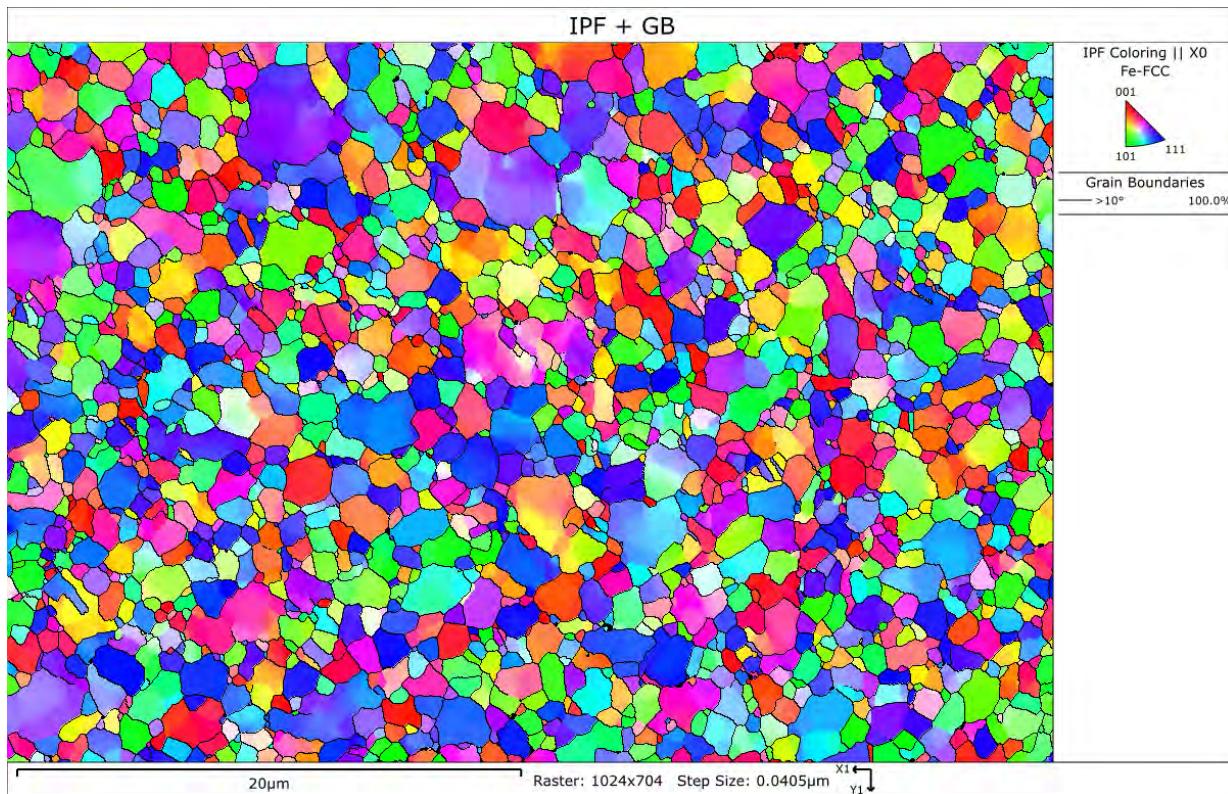


Figure 7.63. Inverse Pole Function - X Images for L02: Condition C01, Sample SS33

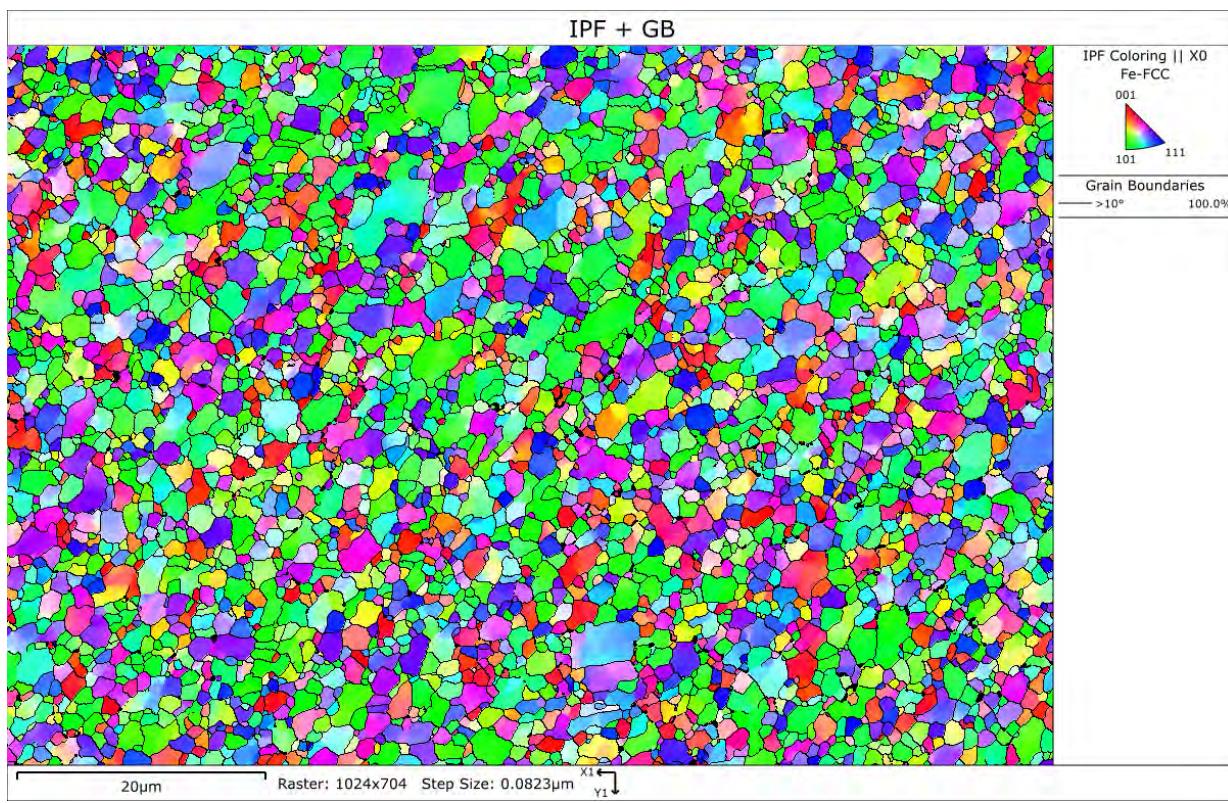


Figure 7.64. Inverse Pole Function - X Images for L01b (2500x mag): Condition C05, Sample SS10

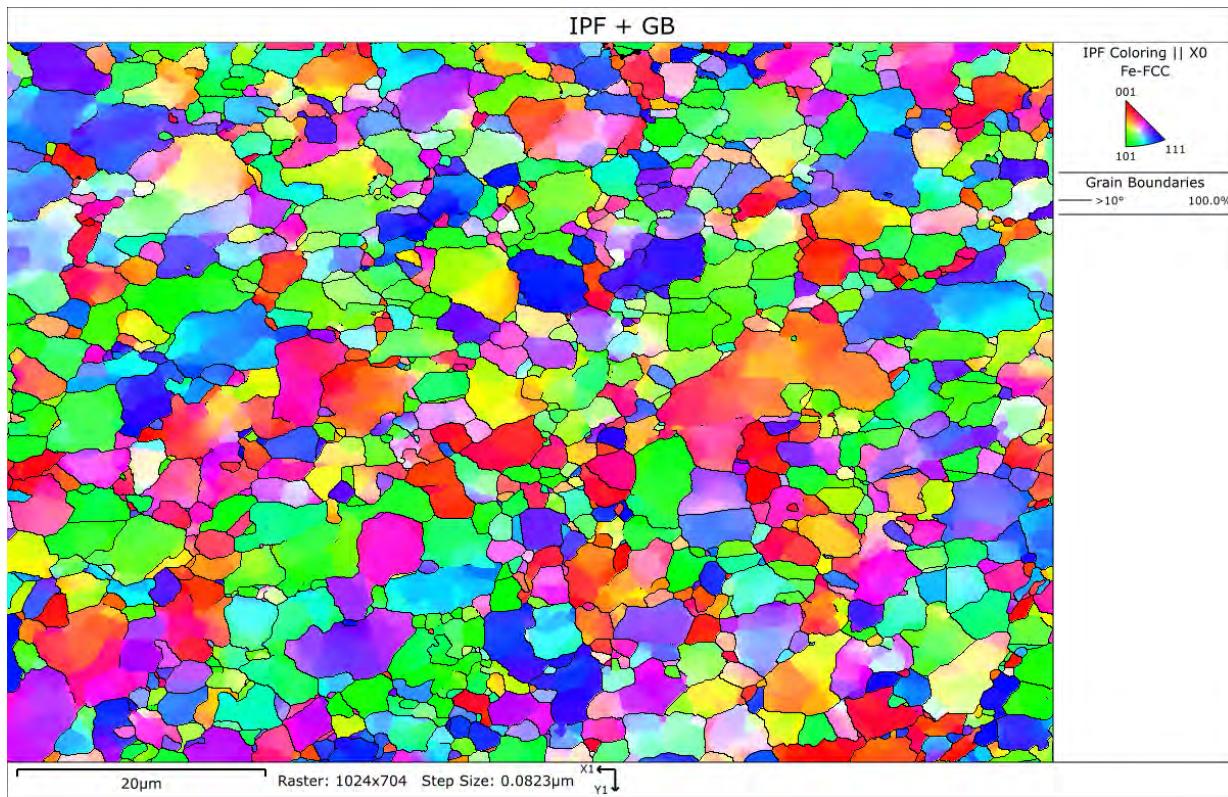


Figure 7.65. Inverse Pole Function - X Images for L01b (2500x mag): Condition C08, Sample SS13

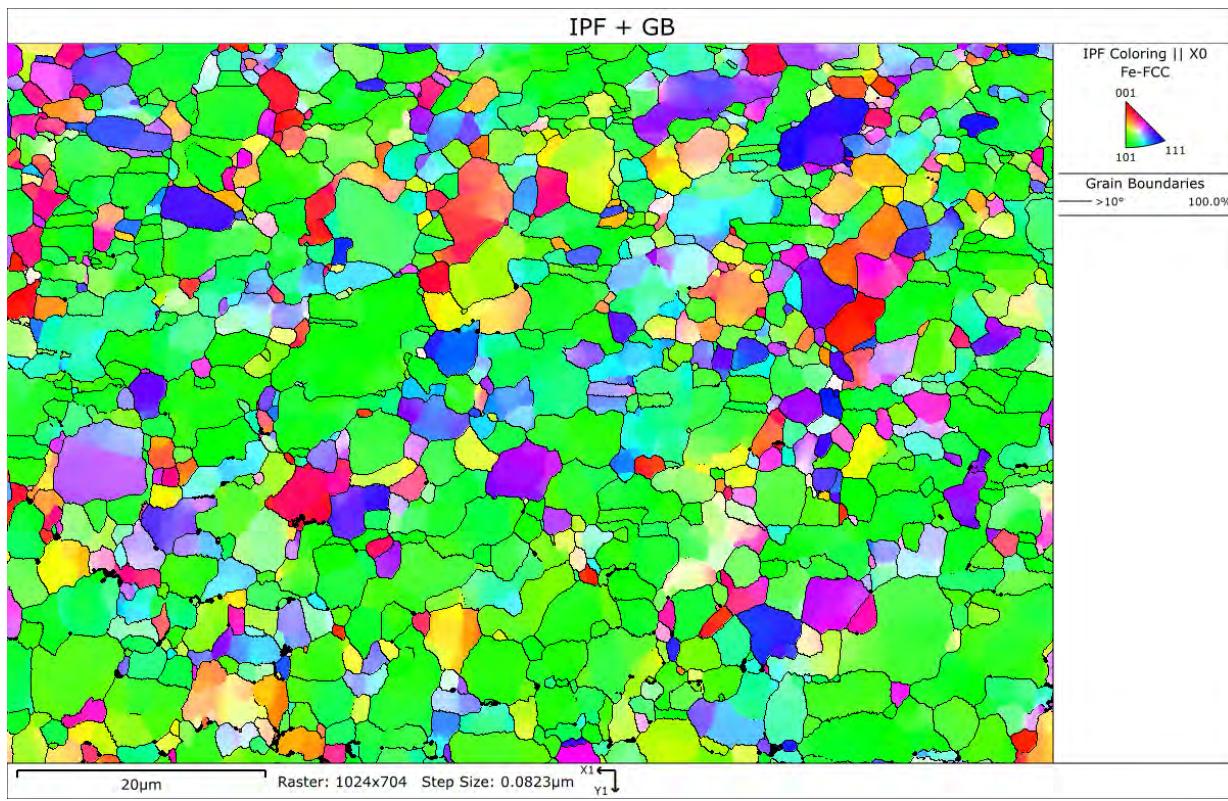


Figure 7.66. Inverse Pole Function - X Images for L01b (2500x mag): Condition C09, Sample SS14

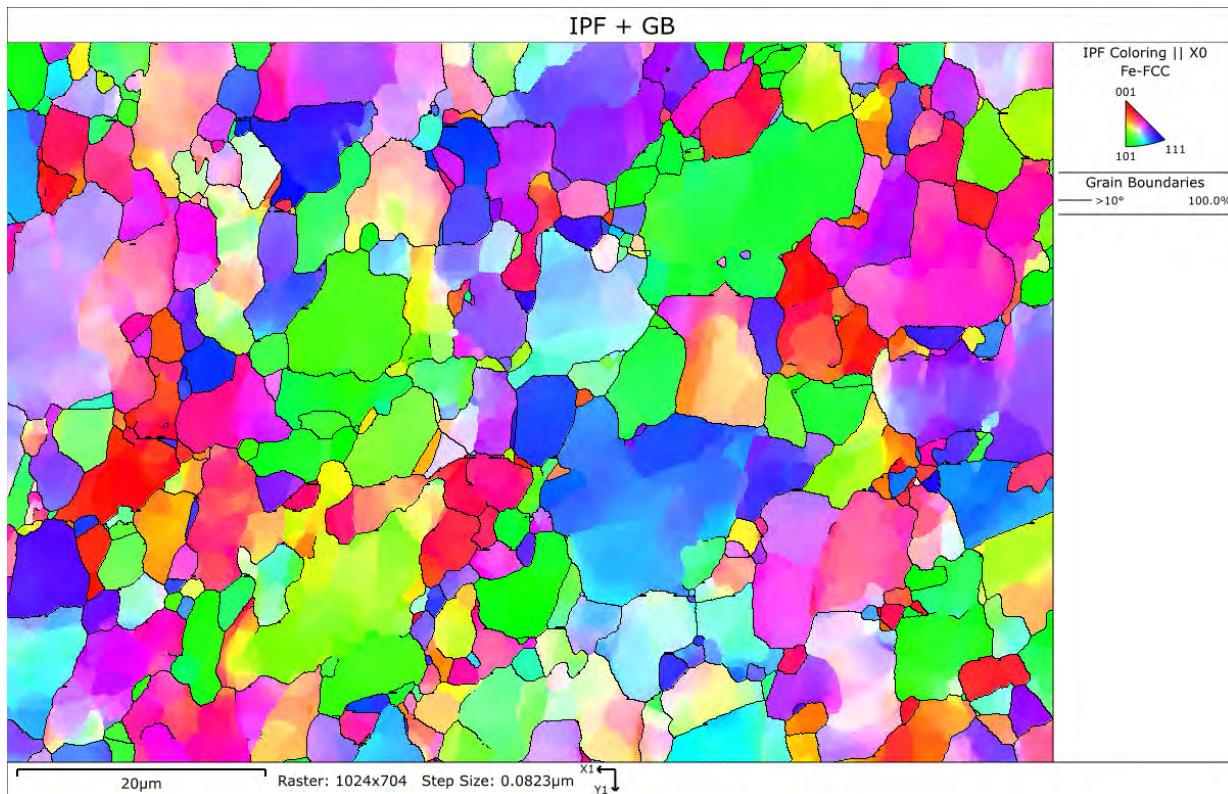


Figure 7.67. Inverse Pole Function - X Images for L01b (2500x mag): Condition C10, Sample SS15

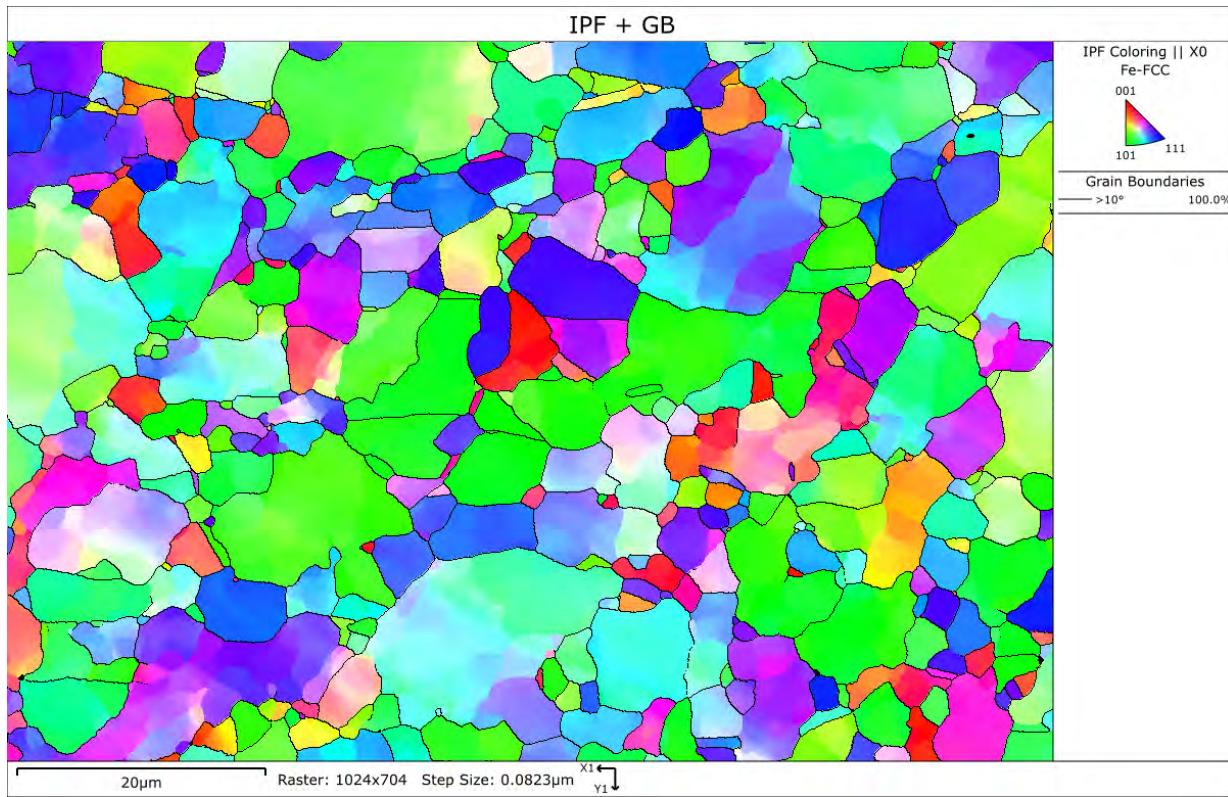


Figure 7.68. Inverse Pole Function - X Images for L01b (2500x mag): Condition C11, Sample SS16

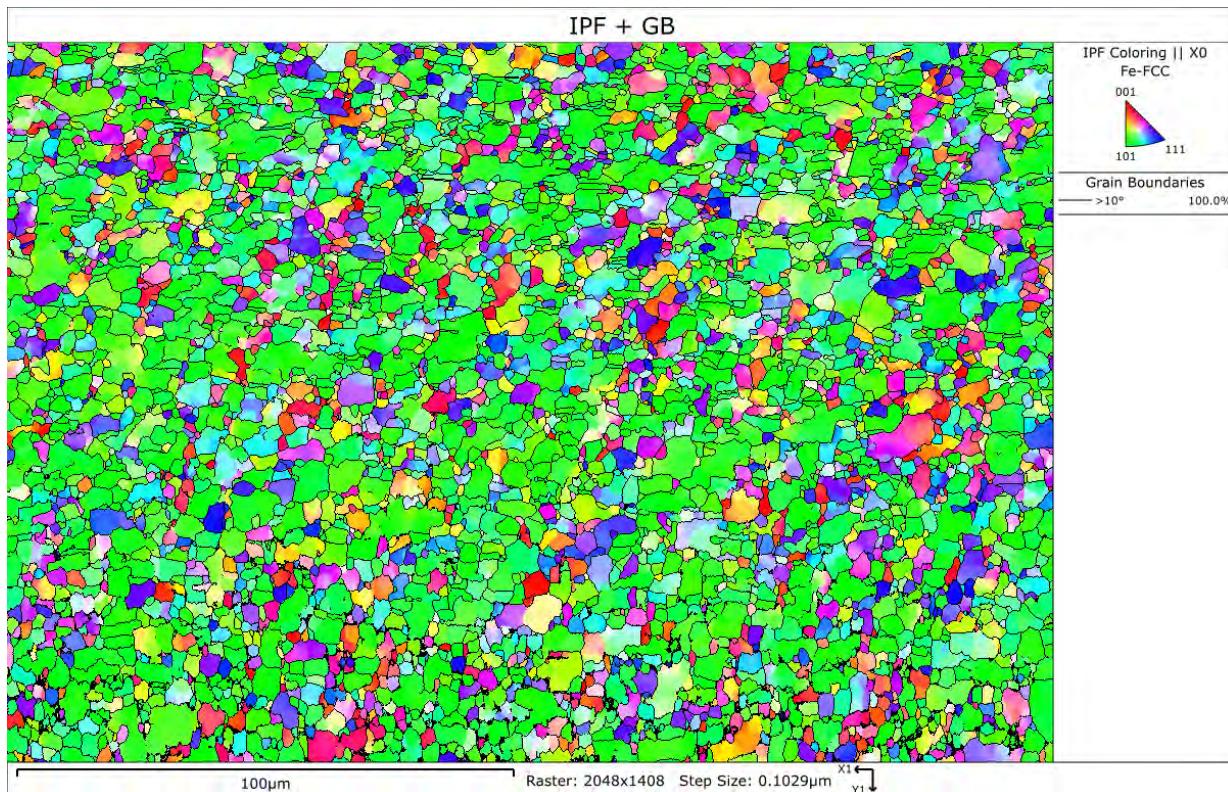


Figure 7.69. Inverse Pole Function - X Images for L01b (1000x mag): Condition C09, Sample SS14

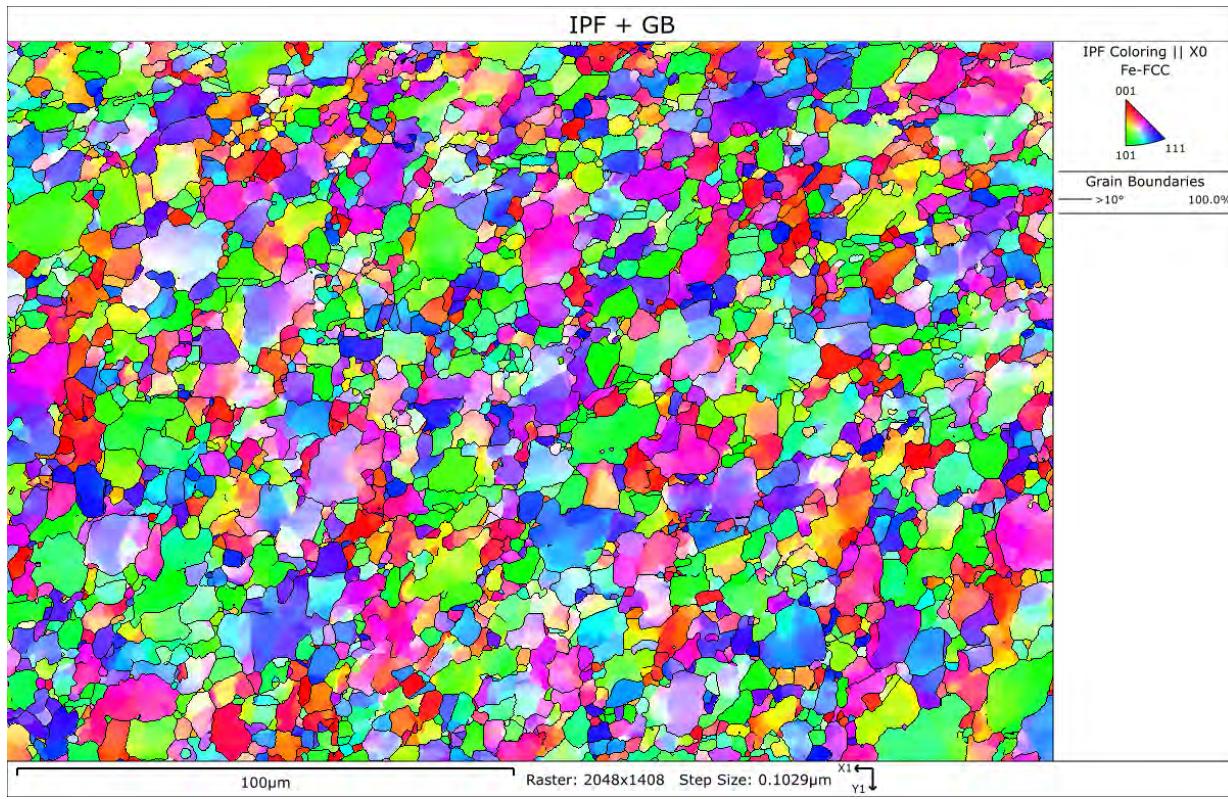


Figure 7.70. Inverse Pole Function - X Images for L01b (1000x mag): Condition C10, Sample SS15

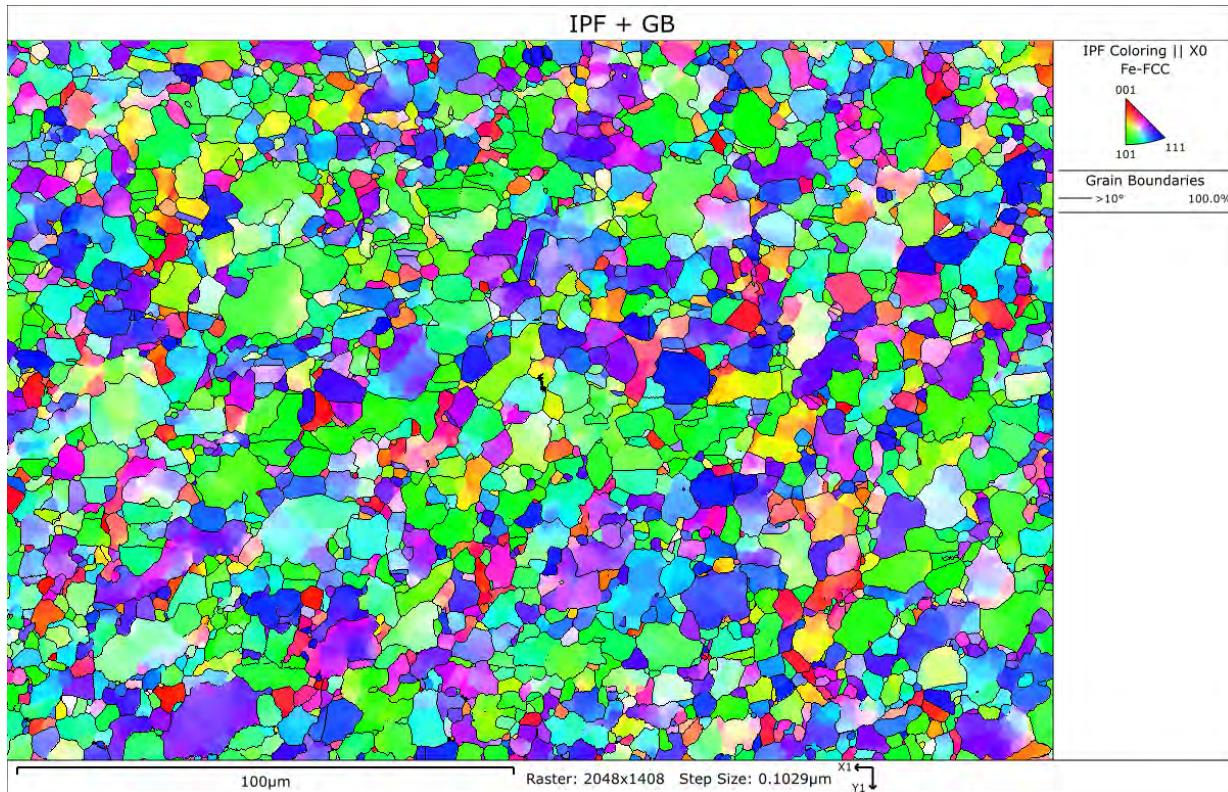


Figure 7.71. Inverse Pole Function - X Images for L01b (1000x mag): Condition C11, Sample SS16

7.5 Inverse Pole Function - Y direction

The following figures show the IPF map in the y-direction with grain boundaries identified through segmentation.

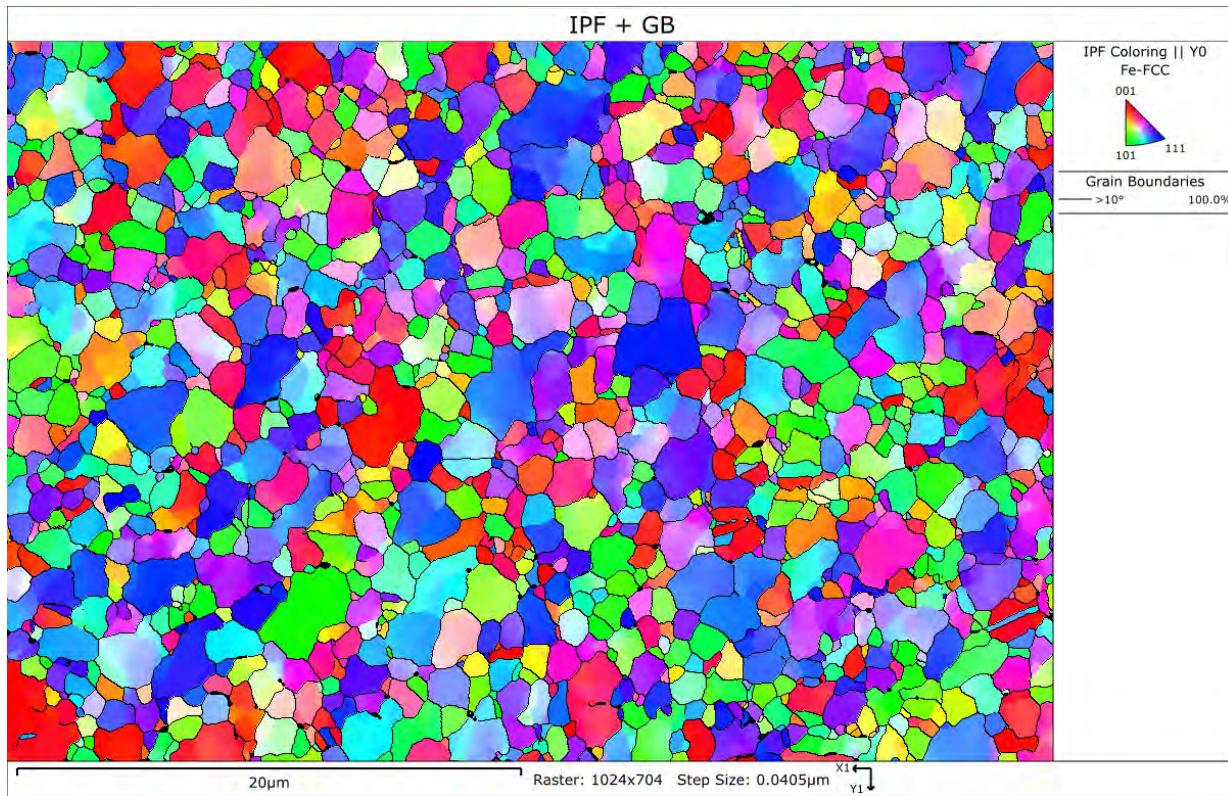


Figure 7.72. Inverse Pole Function - Y Images for L02: Condition C03, Sample SS09

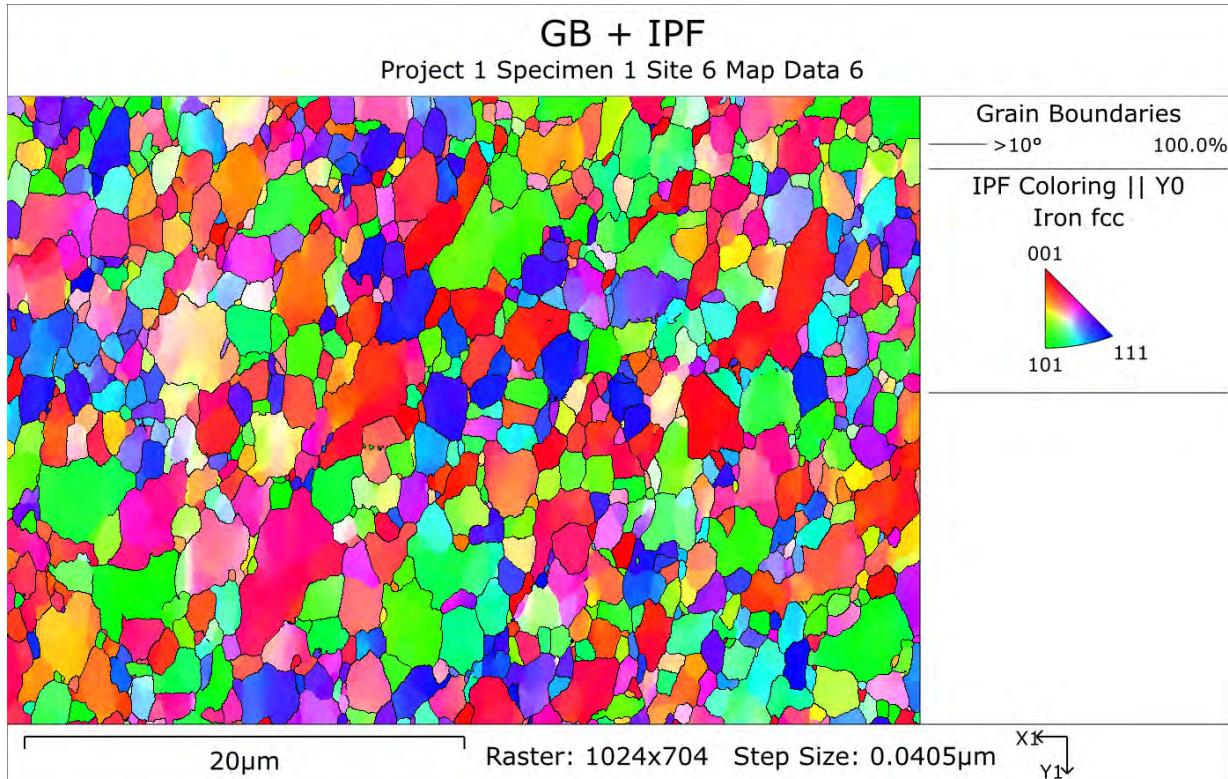


Figure 7.73. Inverse Pole Function - Y Images for L02: Condition C05, Sample SS10

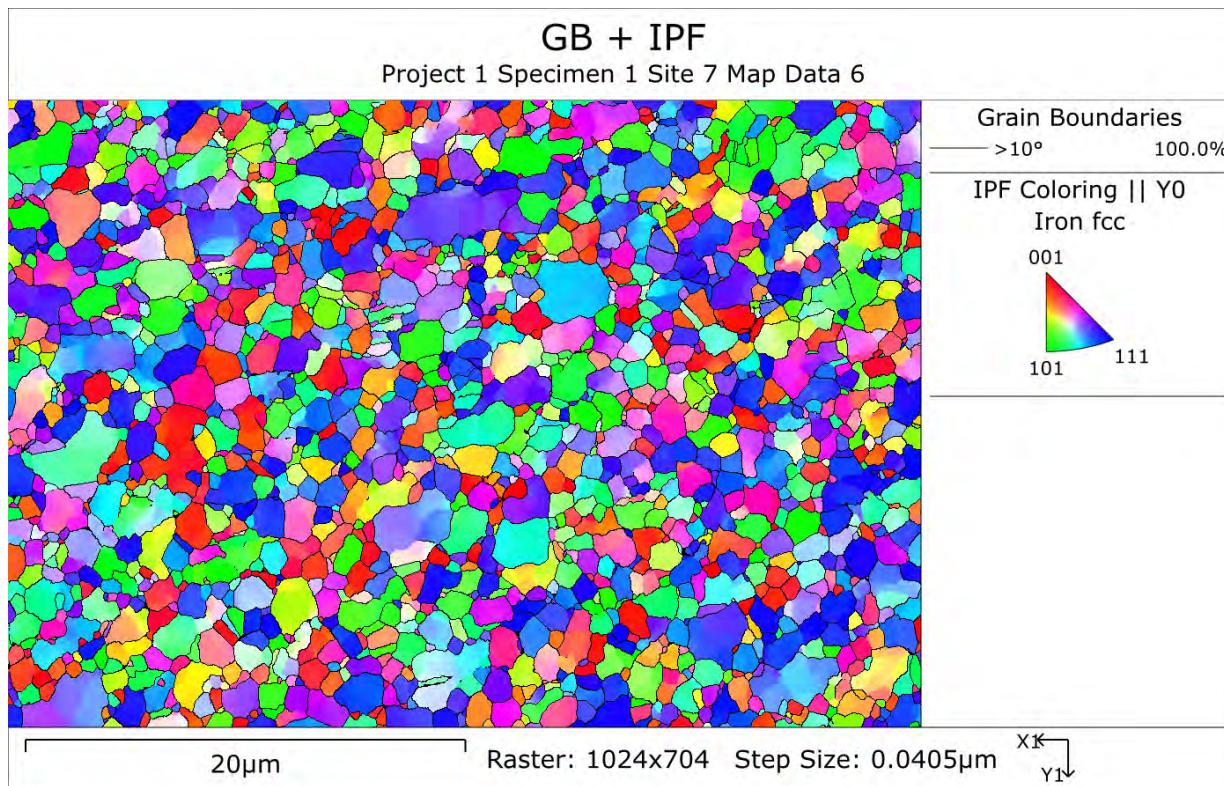


Figure 7.74. Inverse Pole Function - Y Images for L02: Condition C06, Sample SS11

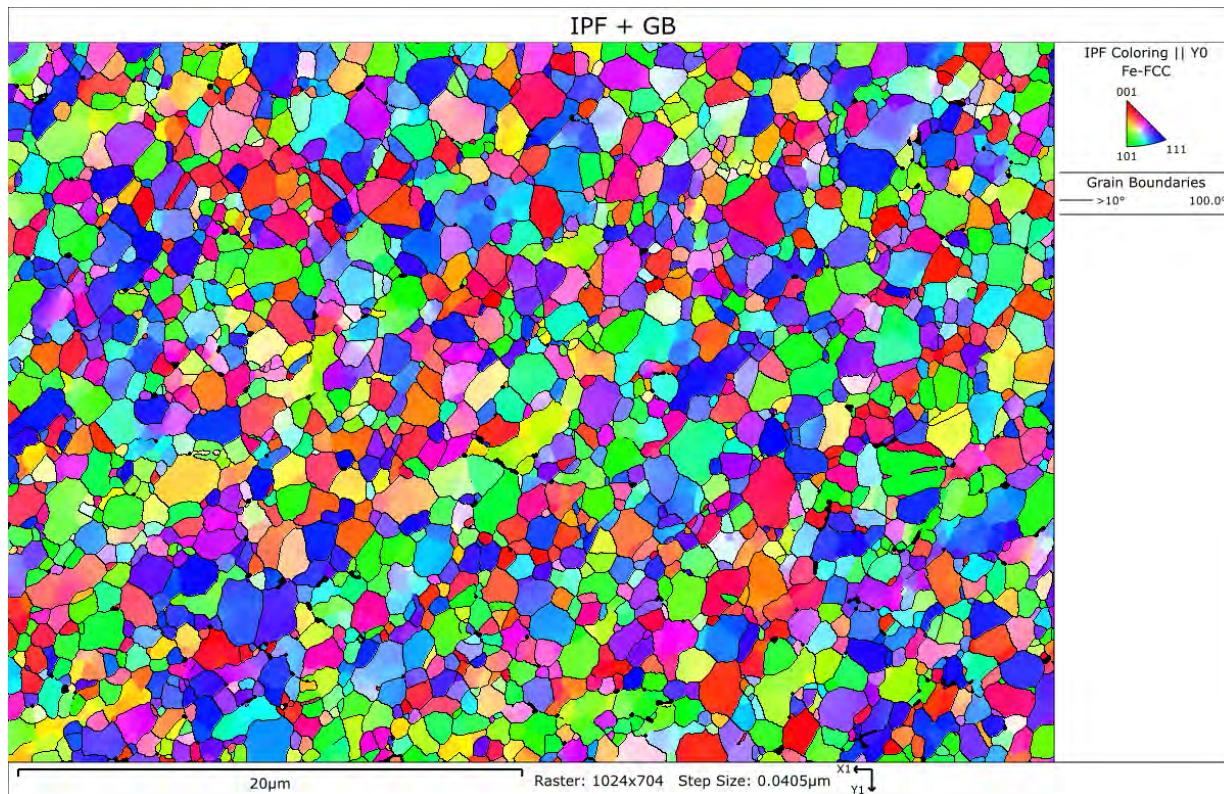


Figure 7.75. Inverse Pole Function - Y Images for L02: Condition C07, Sample SS12

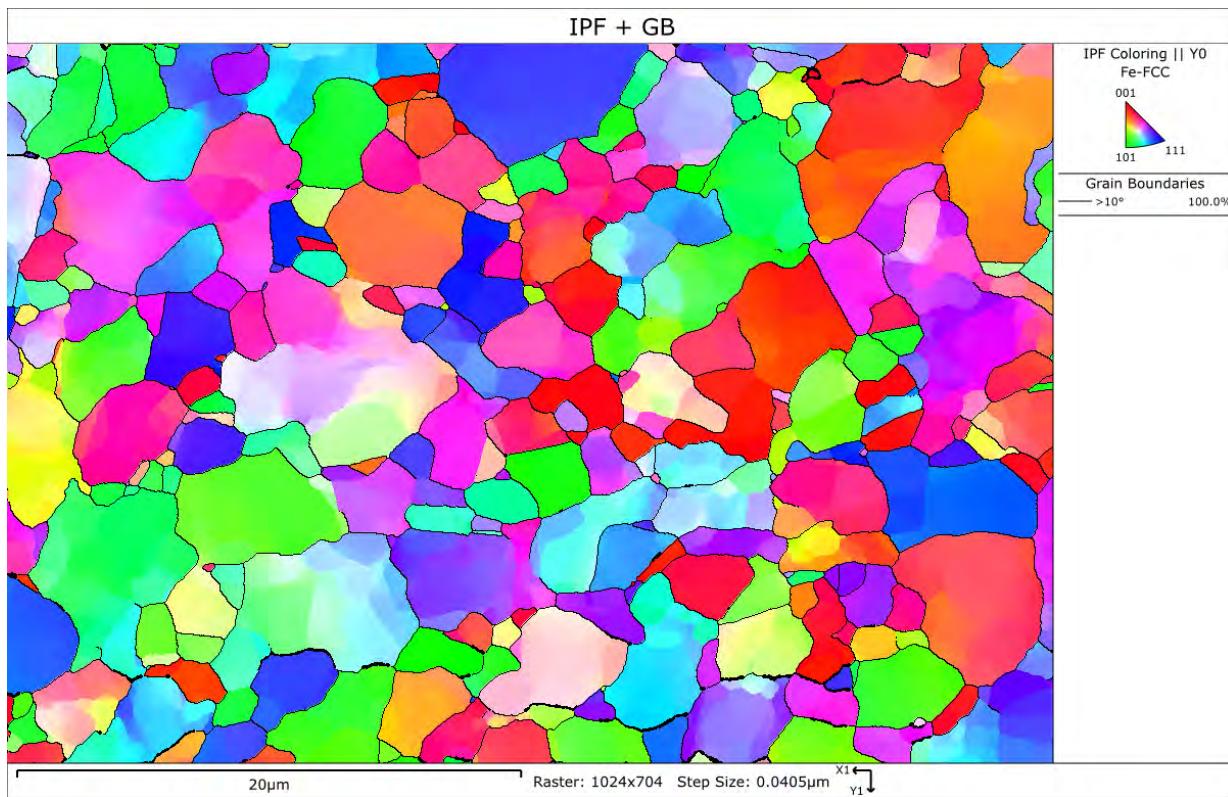


Figure 7.76. Inverse Pole Function - Y Images for L02: Condition C08, Sample SS13

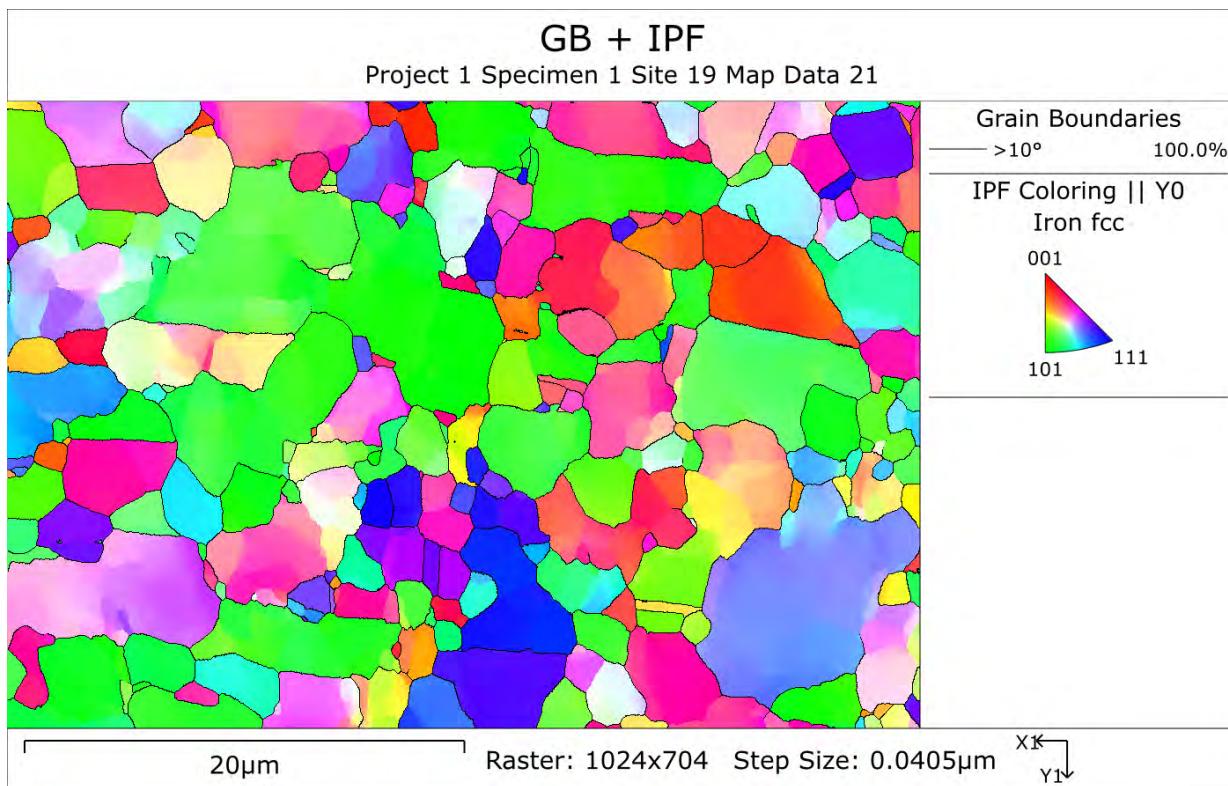


Figure 7.77. Inverse Pole Function - Y Images for L02: Condition C09, Sample SS14

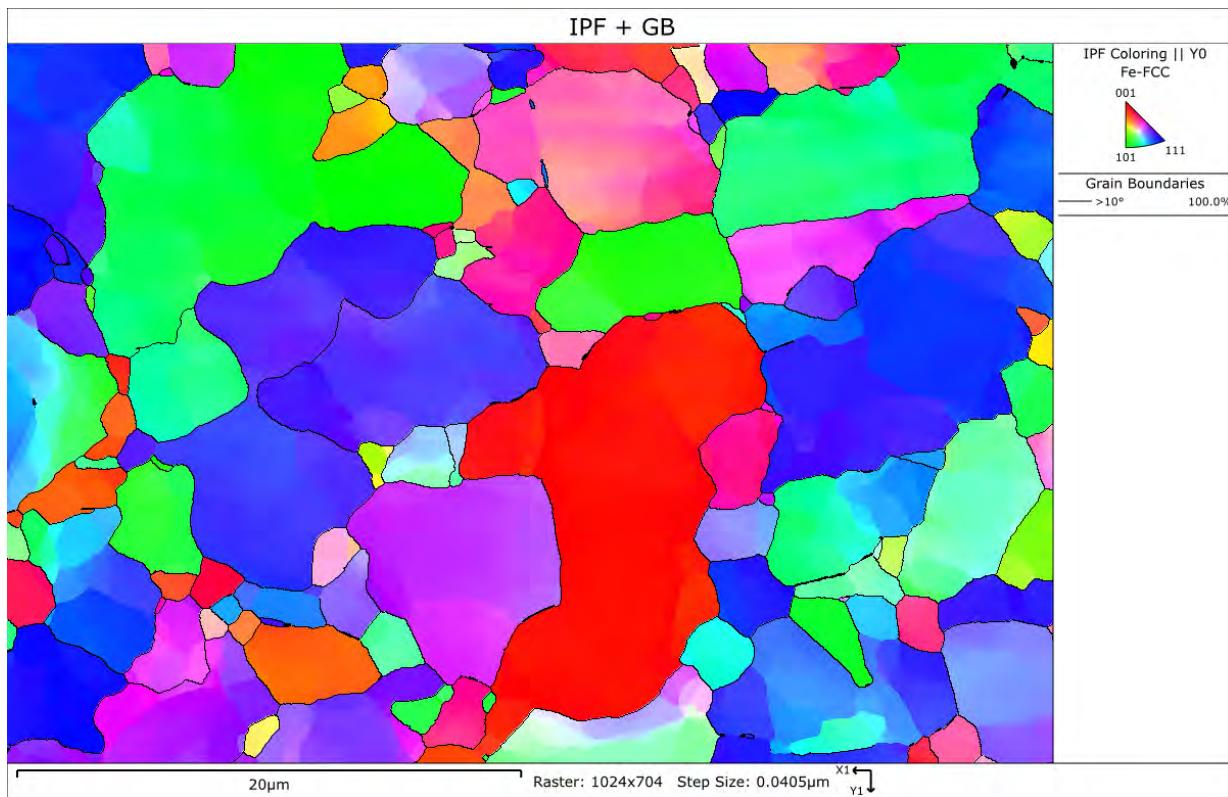


Figure 7.78. Inverse Pole Function - Y Images for L02: Condition C10, Sample SS15

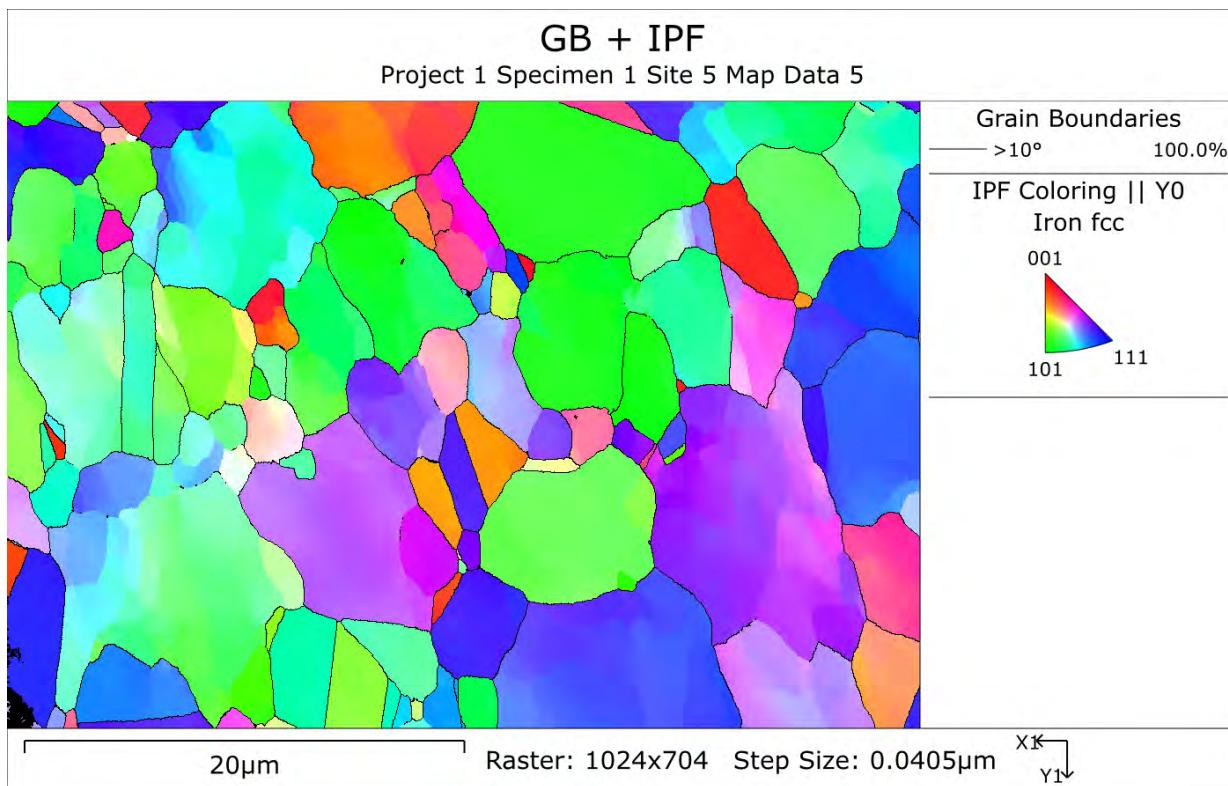


Figure 7.79. Inverse Pole Function - Y Images for L02: Condition C11, Sample SS16

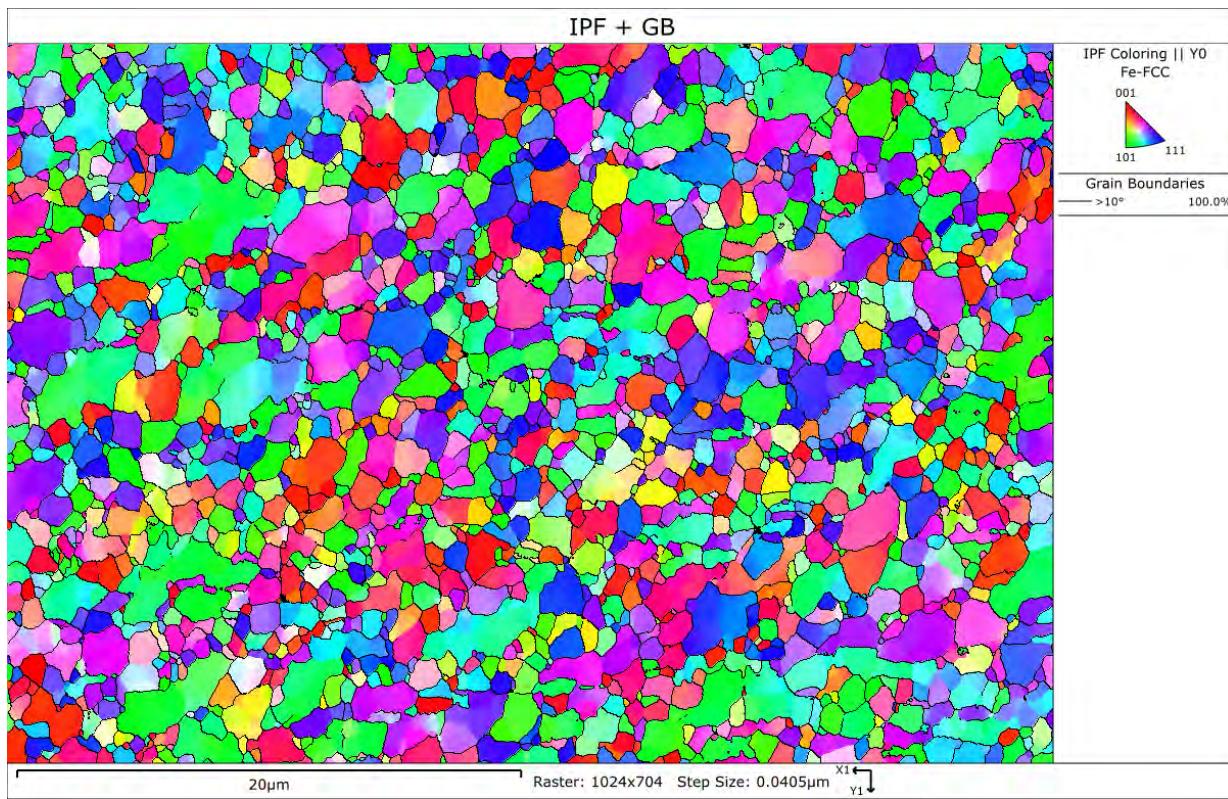


Figure 7.80. Inverse Pole Function - Y Images for L02: Condition C02, Sample SS24

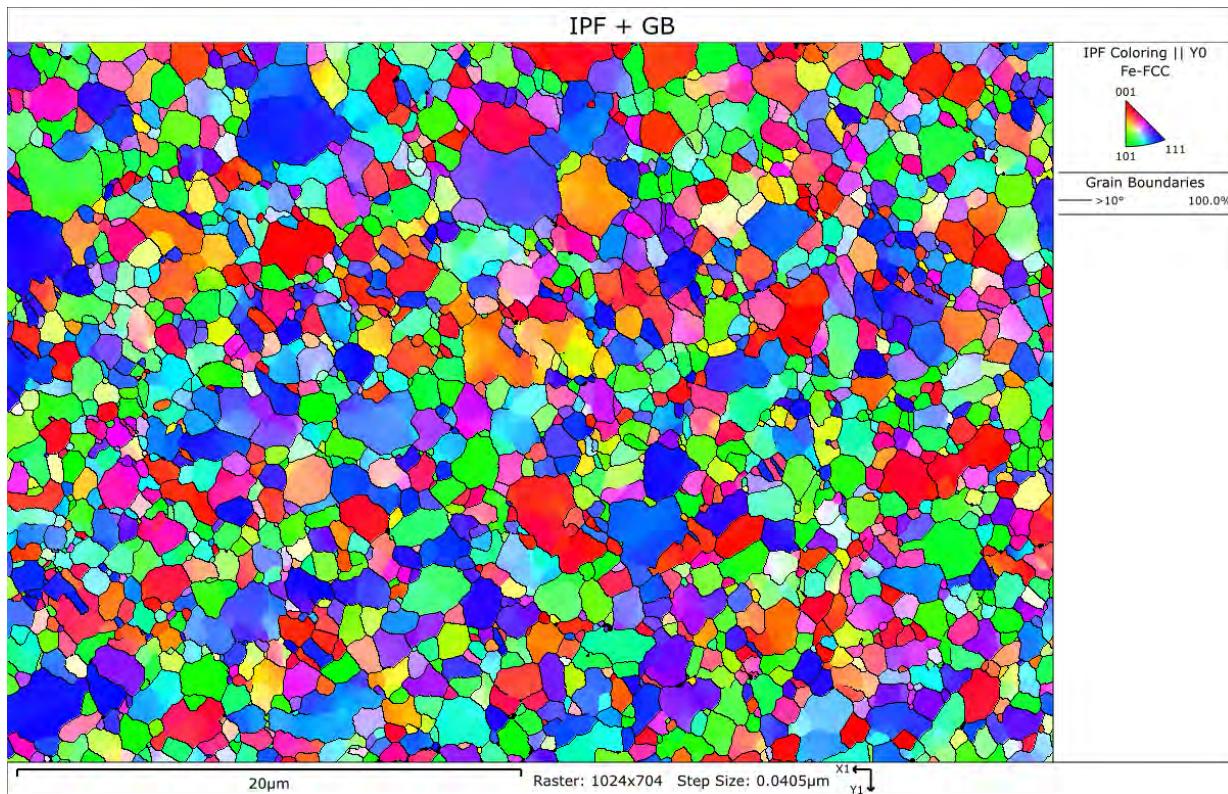


Figure 7.81. Inverse Pole Function - Y Images for L02: Condition C01, Sample SS33

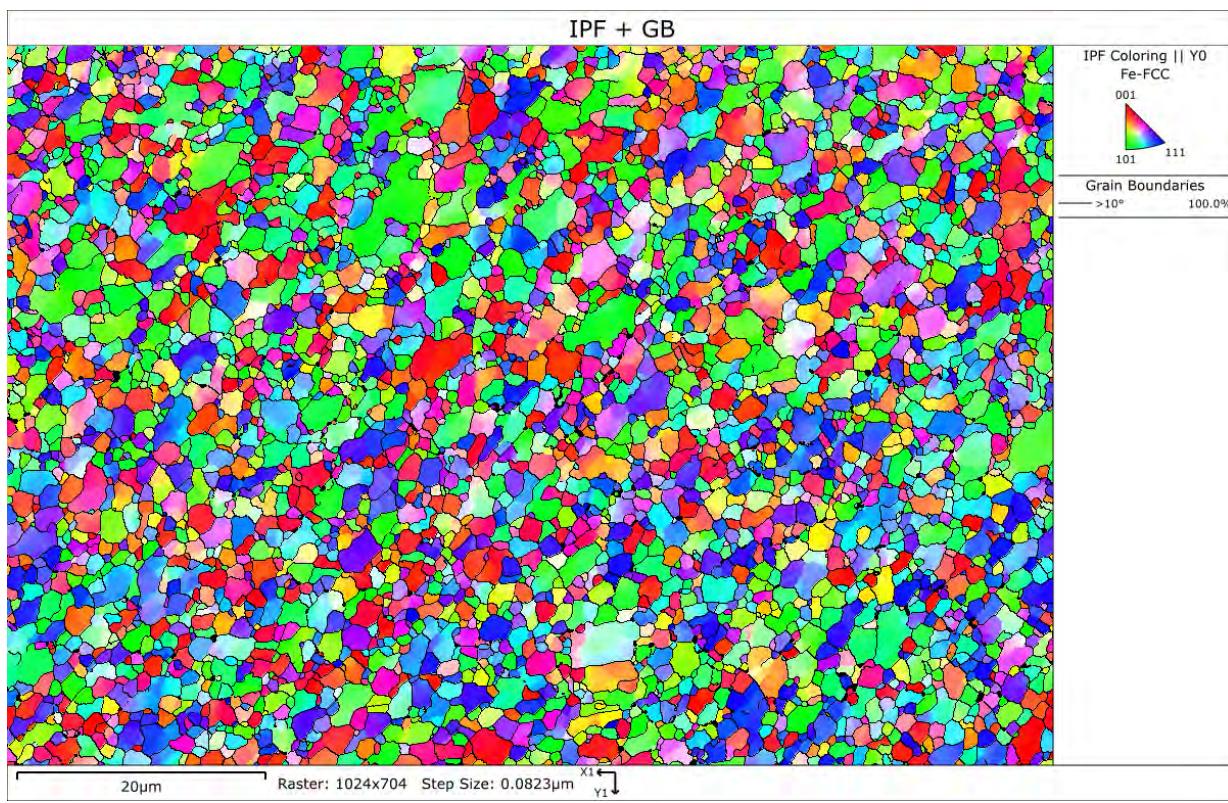


Figure 7.82. Inverse Pole Function - Y Images for L01b (2500x mag): Condition C05, Sample SS10

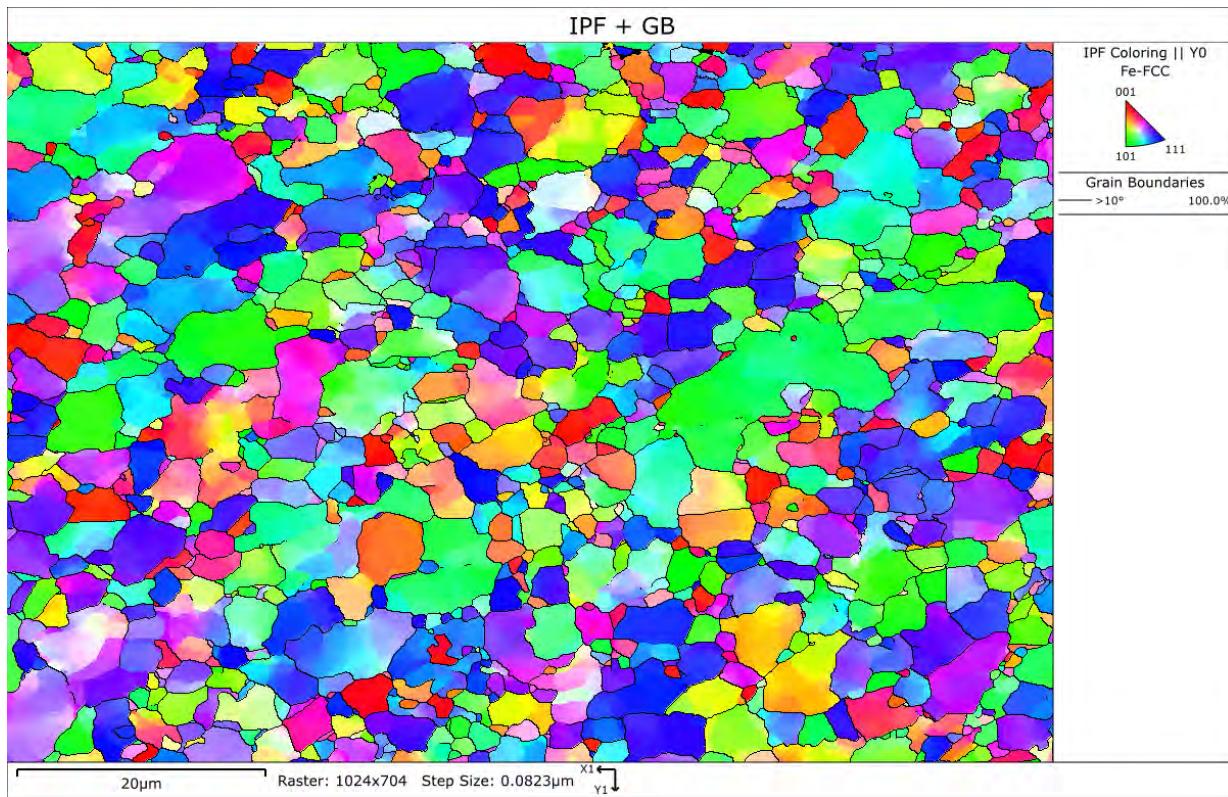


Figure 7.83. Inverse Pole Function - Y Images for L01b (2500x mag): Condition C08, Sample SS13

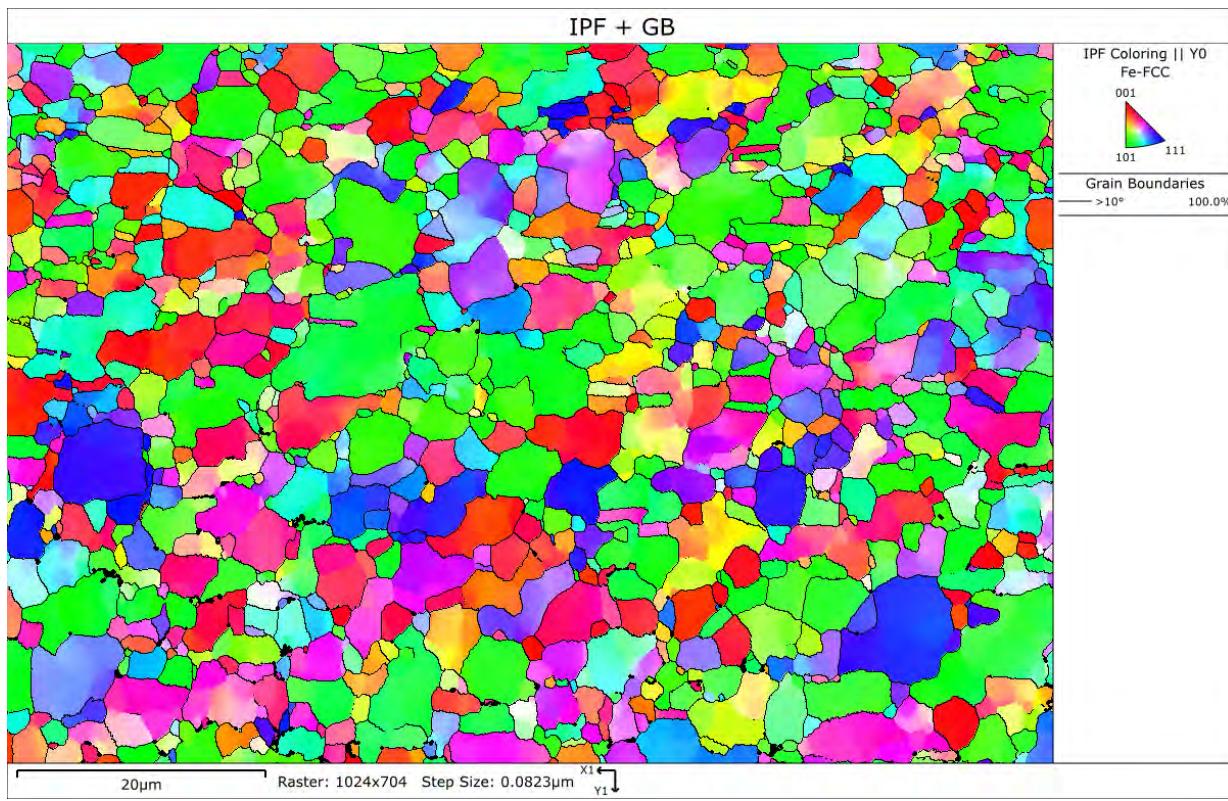


Figure 7.84. Inverse Pole Function - Y Images for L01b (2500x mag): Condition C09, Sample SS14

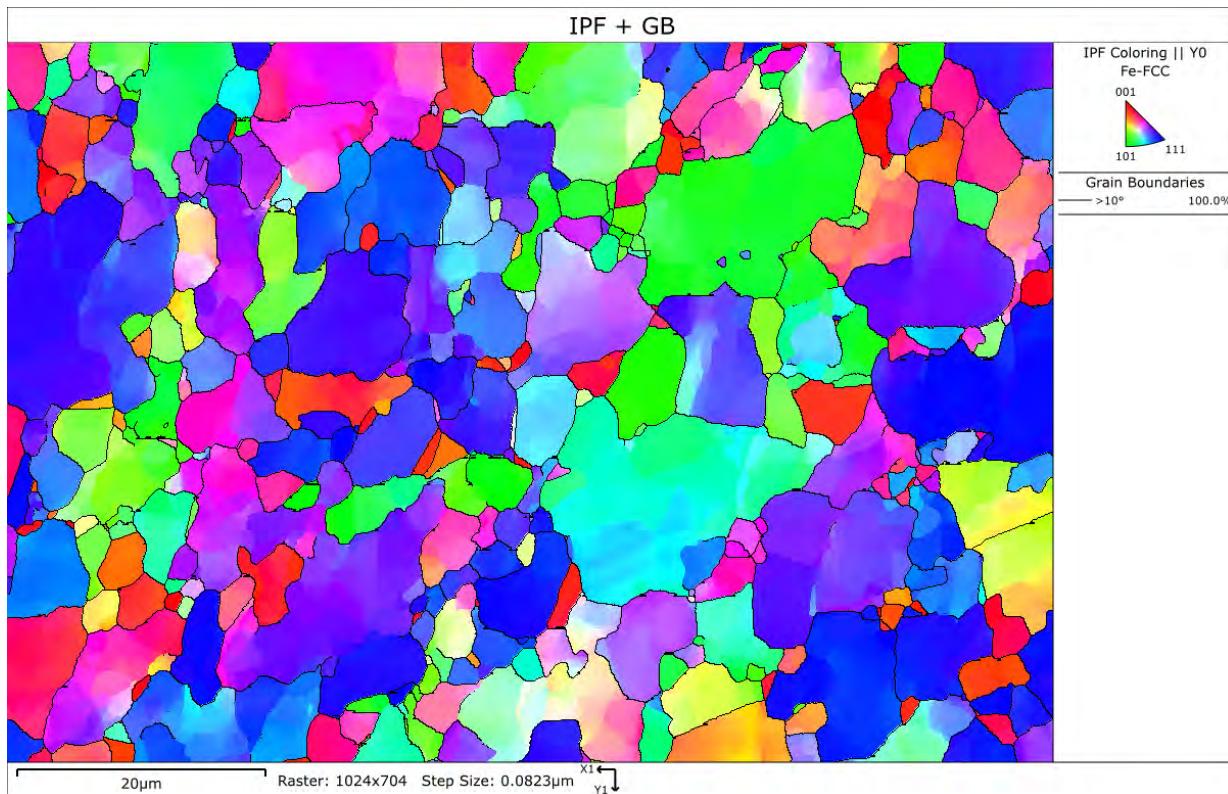


Figure 7.85. Inverse Pole Function - Y Images for L01b (2500x mag): Condition C10, Sample SS15

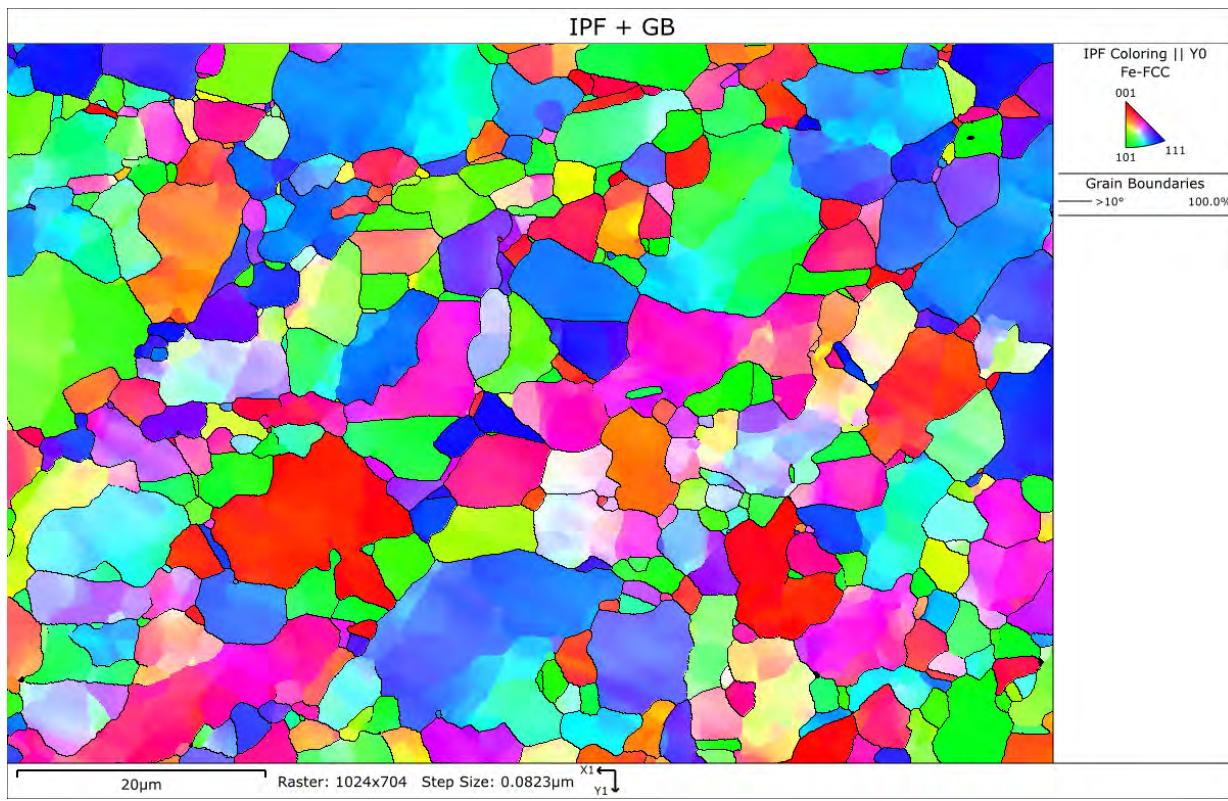


Figure 7.86. Inverse Pole Function - Y Images for L01b (2500x mag): Condition C11, Sample SS16

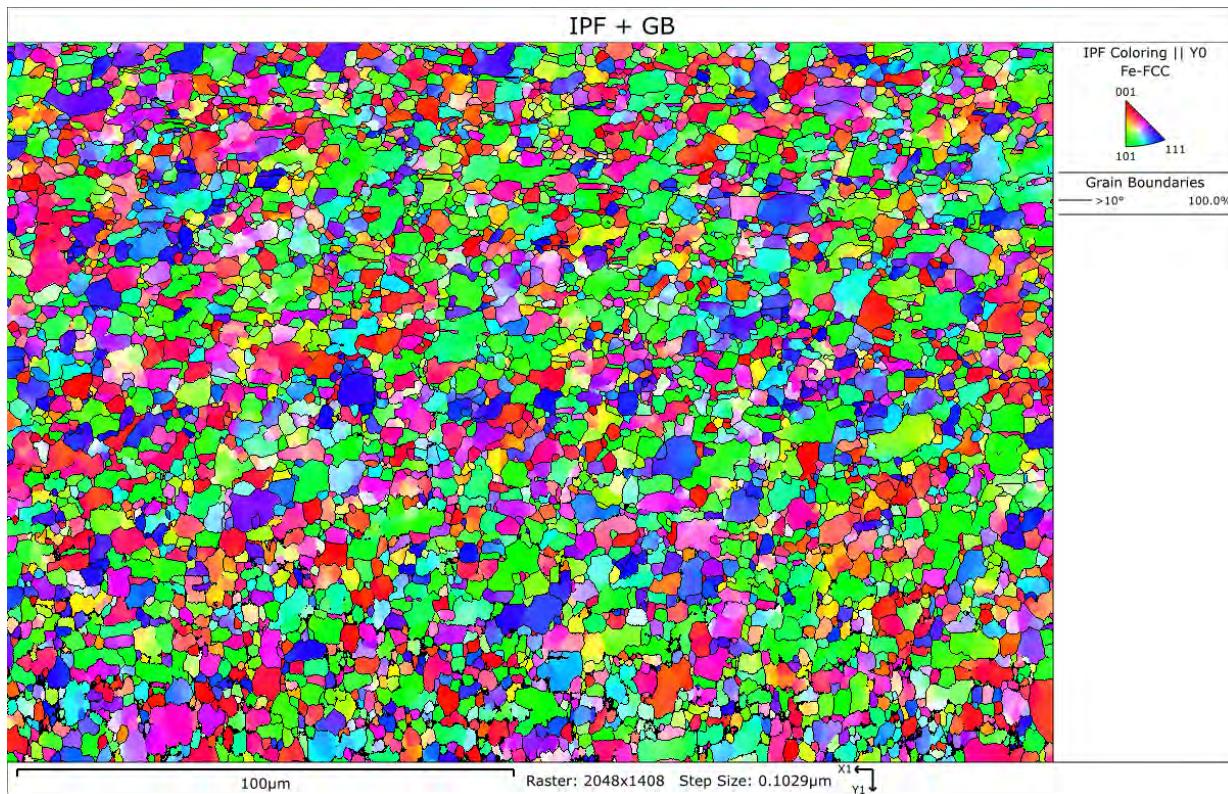


Figure 7.87. Inverse Pole Function - Y Images for L01b (1000x mag): Condition C09, Sample SS14

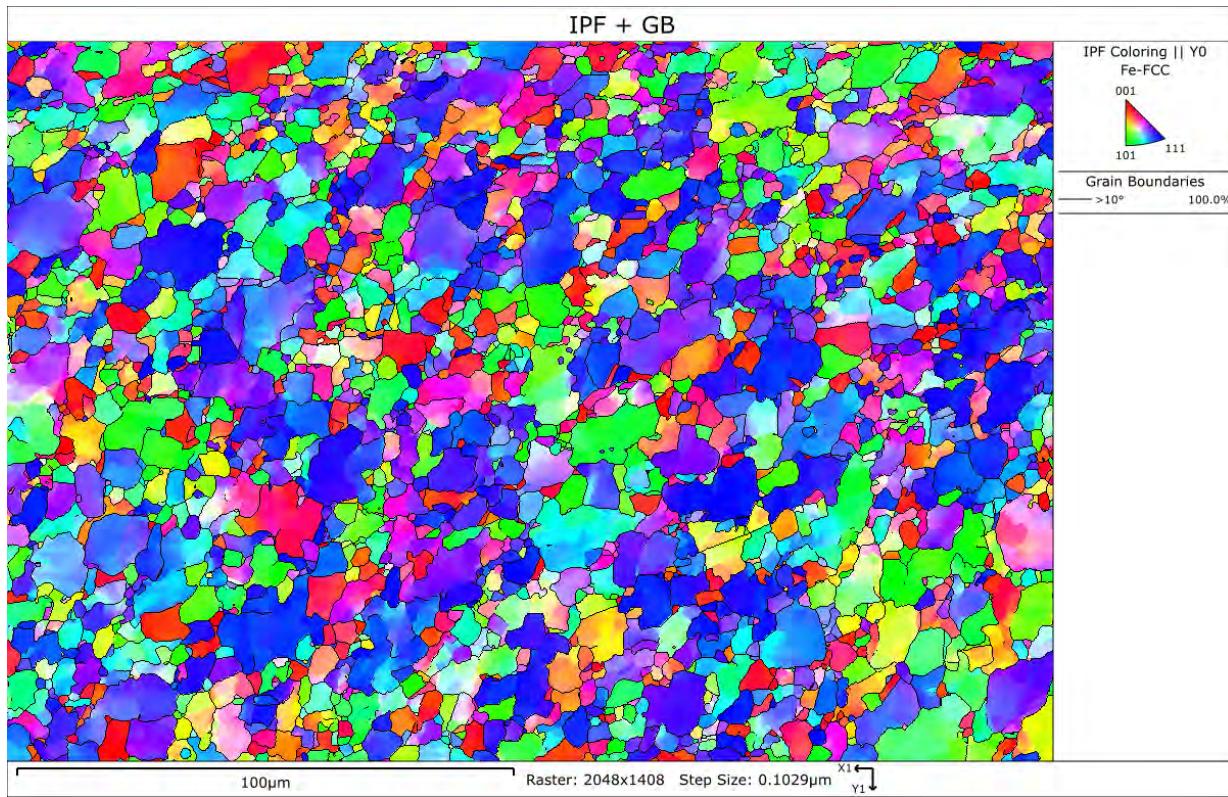


Figure 7.88. Inverse Pole Function - Y Images for L01b (1000x mag): Condition C10, Sample SS15

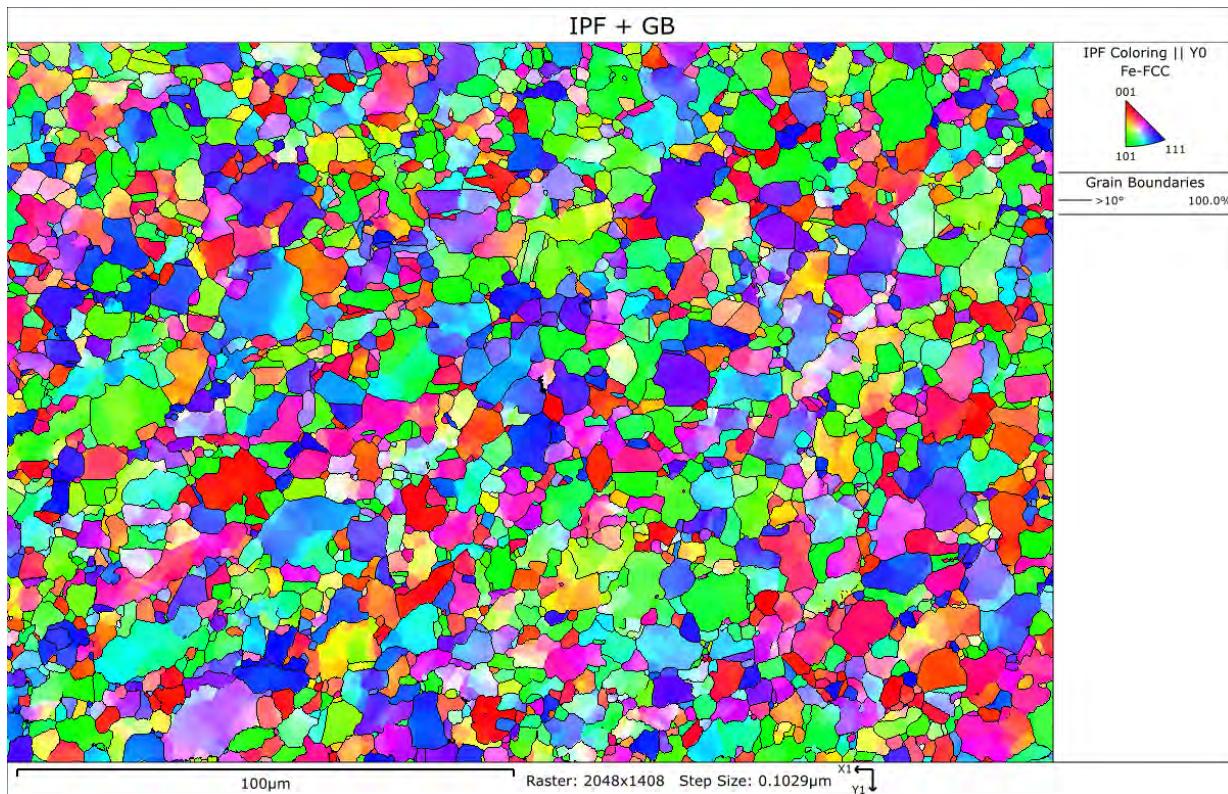


Figure 7.89. Inverse Pole Function - Y Images for L01b (1000x mag): Condition C11, Sample SS16

7.6 Inverse Pole Function - Z direction

The following figures show the IPF map in the z-direction with grain boundaries identified through segmentation.

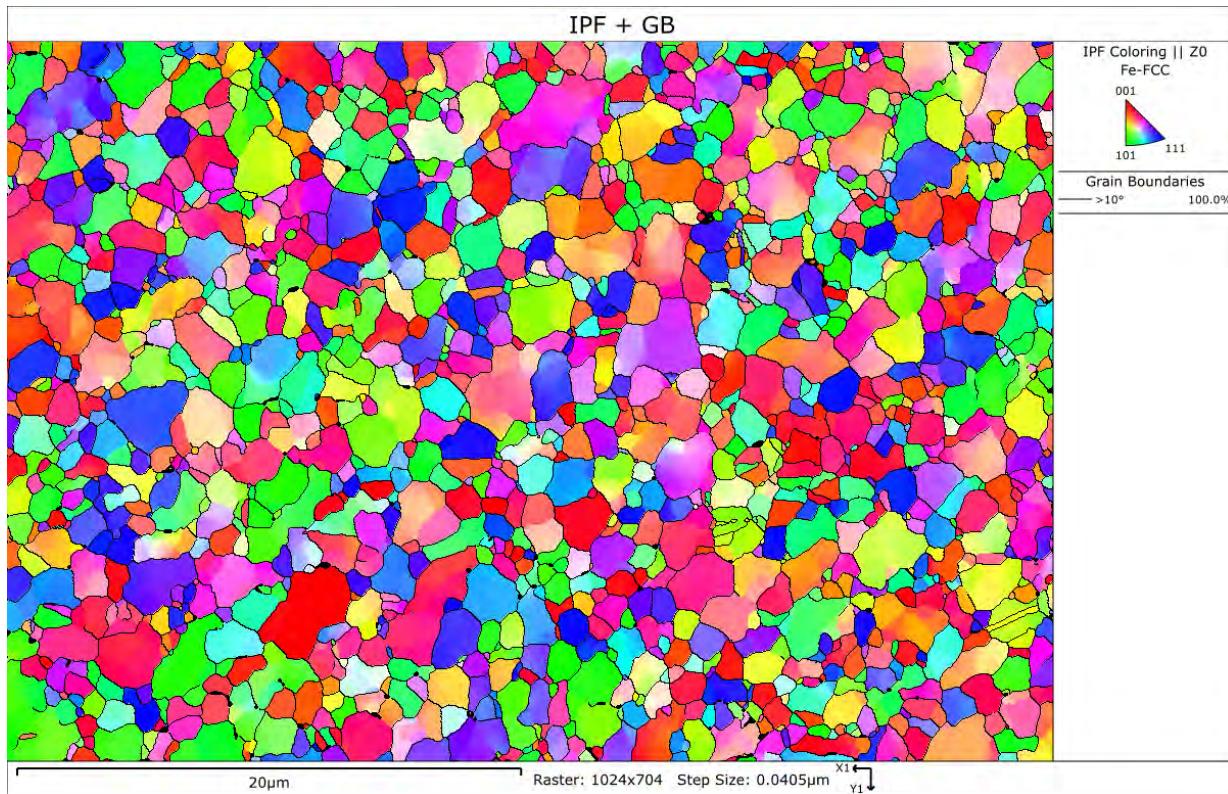


Figure 7.90. Inverse Pole Function - Z Images for L02: Condition C03, Sample SS09

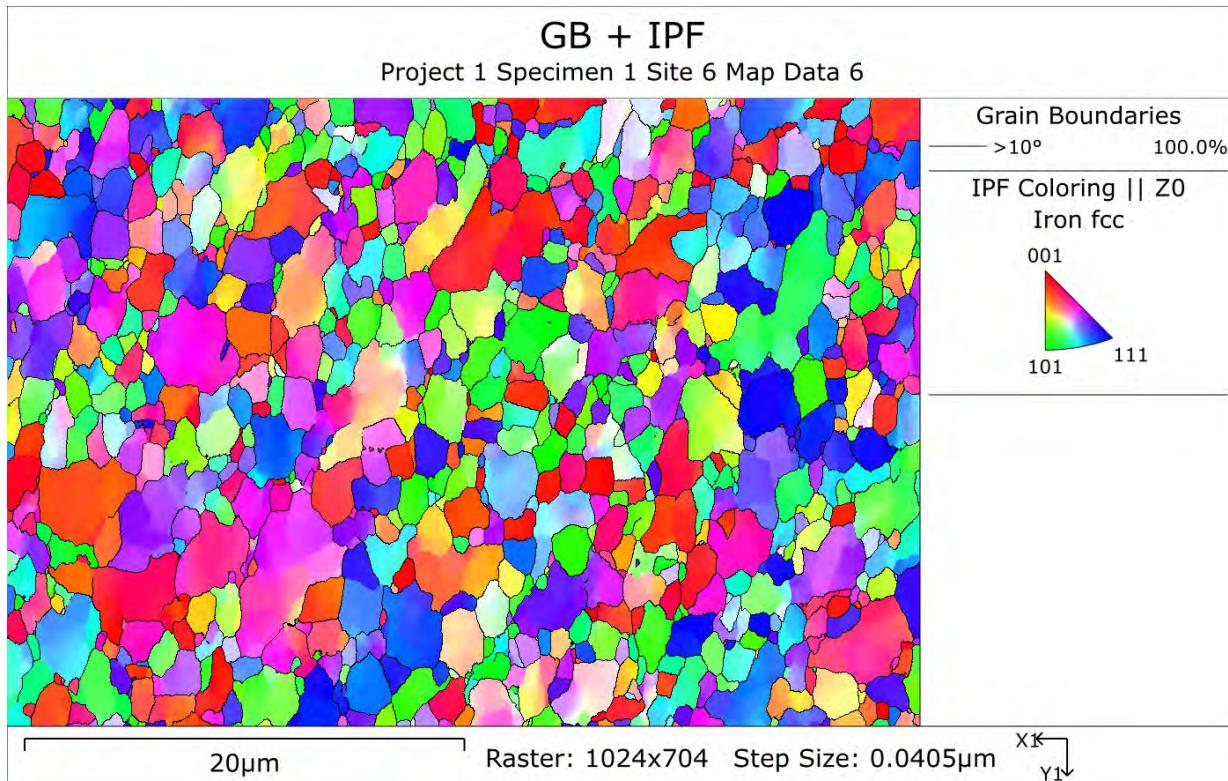


Figure 7.91. Inverse Pole Function - Z Images for L02: Condition C05, Sample SS10

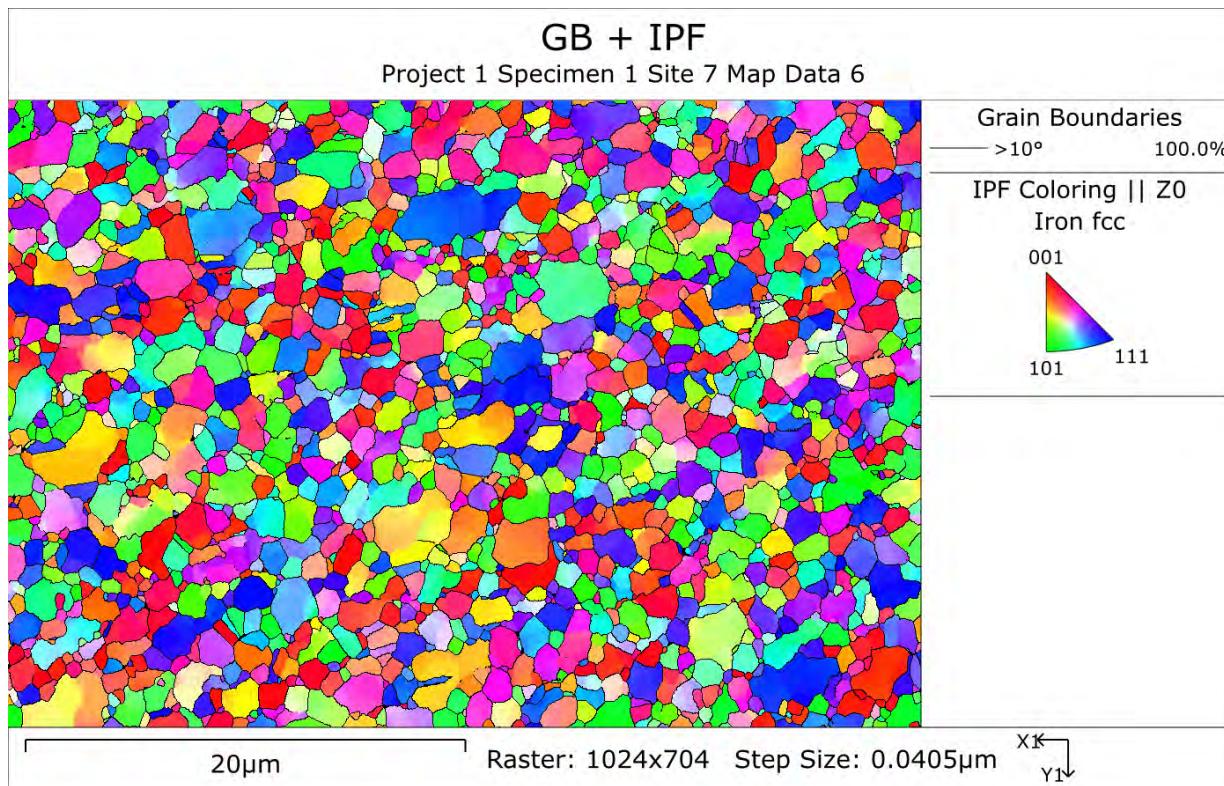


Figure 7.92. Inverse Pole Function - Z Images for L02: Condition C06, Sample SS11

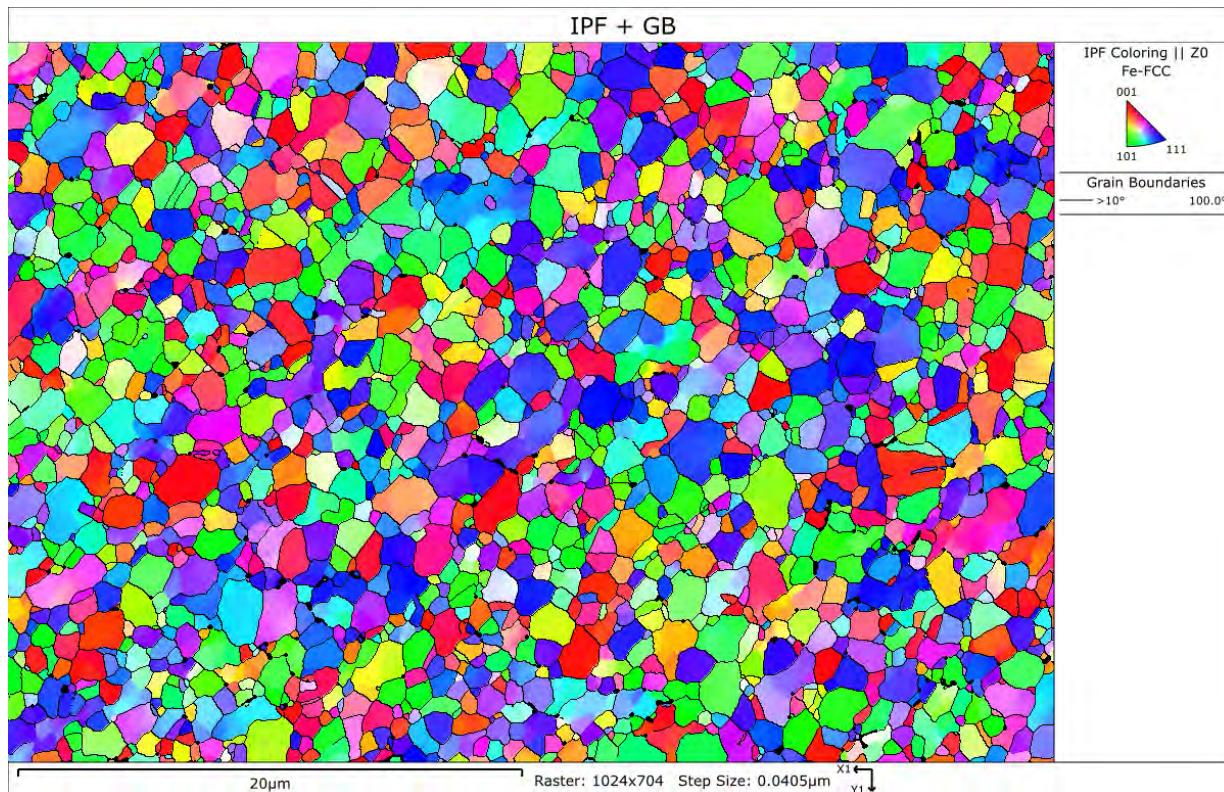


Figure 7.93. Inverse Pole Function - Z Images for L02: Condition C07, Sample SS12

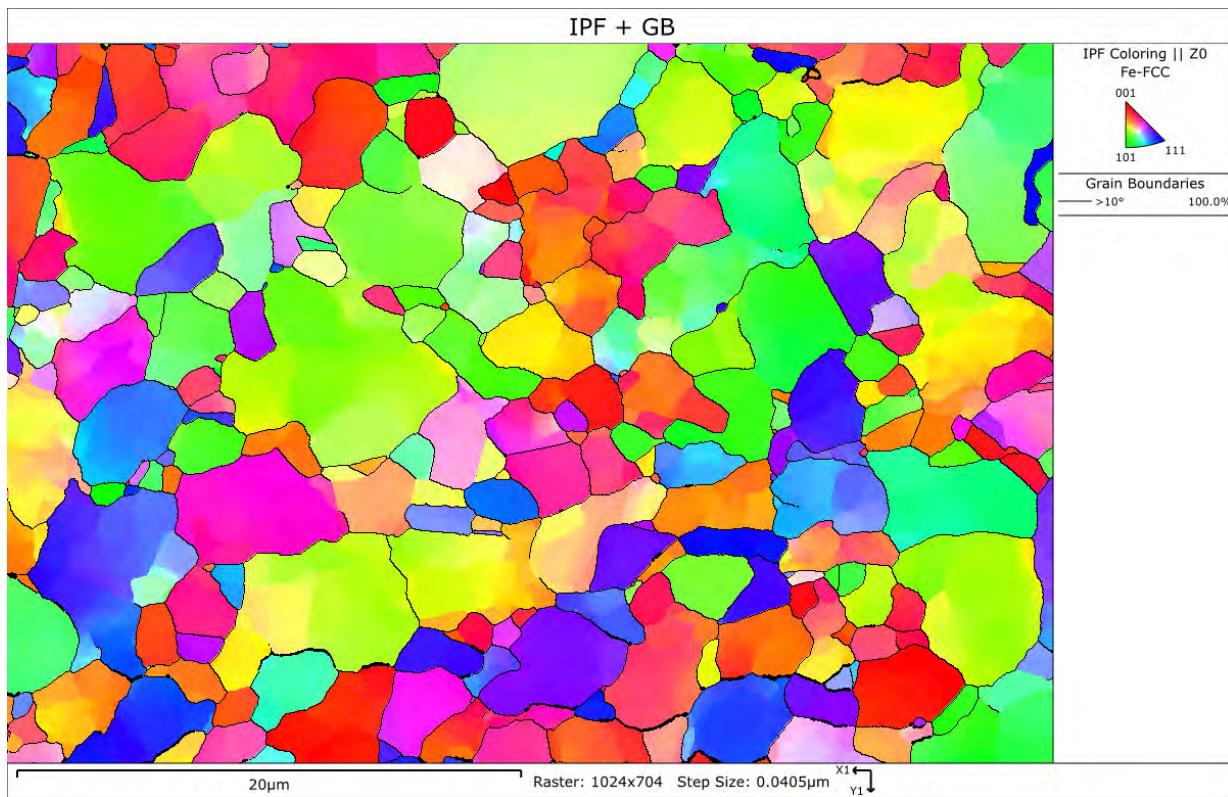


Figure 7.94. Inverse Pole Function - Z Images for L02: Condition C08, Sample SS13

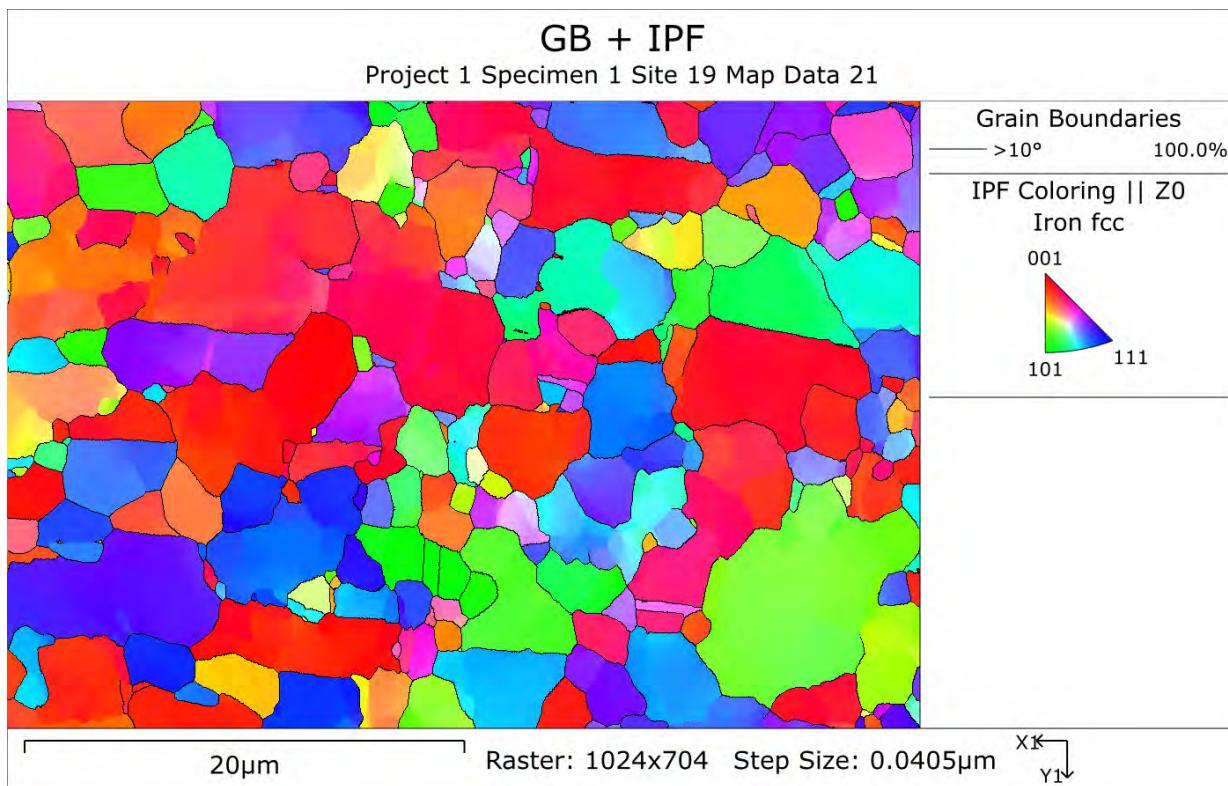


Figure 7.95. Inverse Pole Function - Z Images for L02: Condition C09, Sample SS14

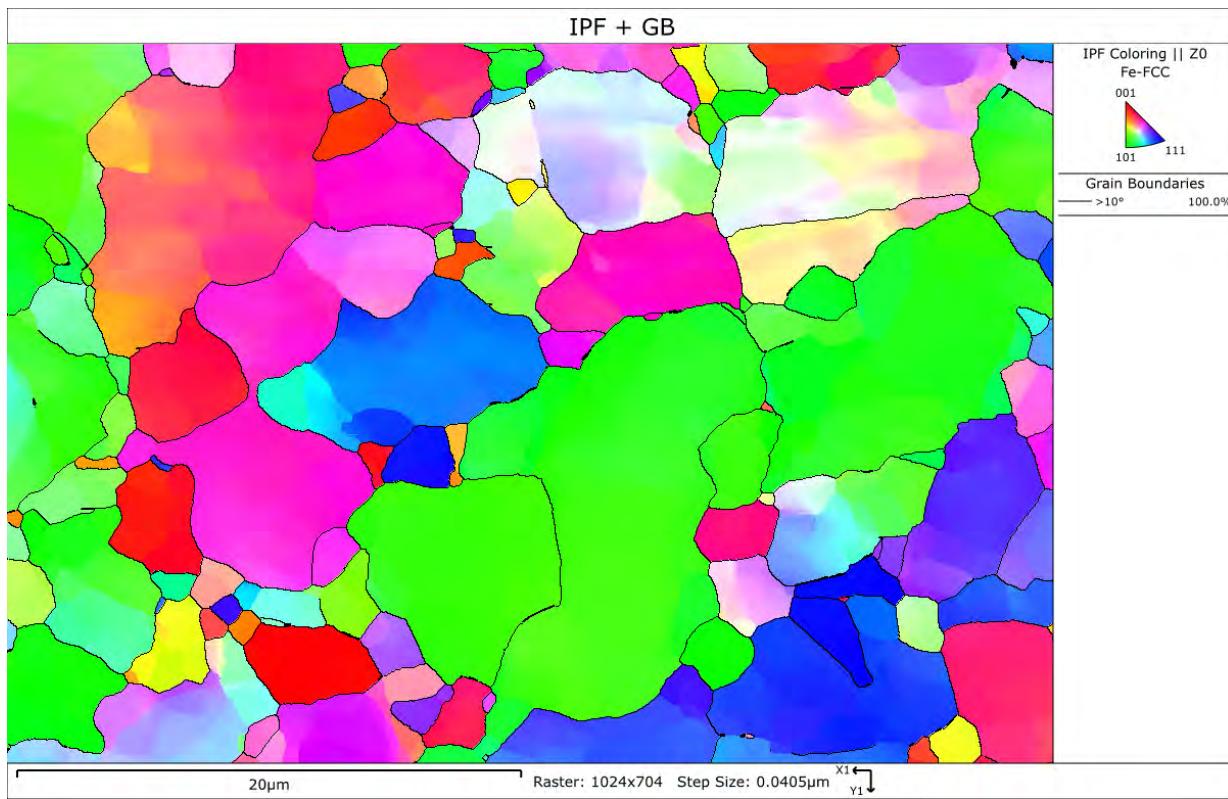


Figure 7.96. Inverse Pole Function - Z Images for L02: Condition C10, Sample SS15

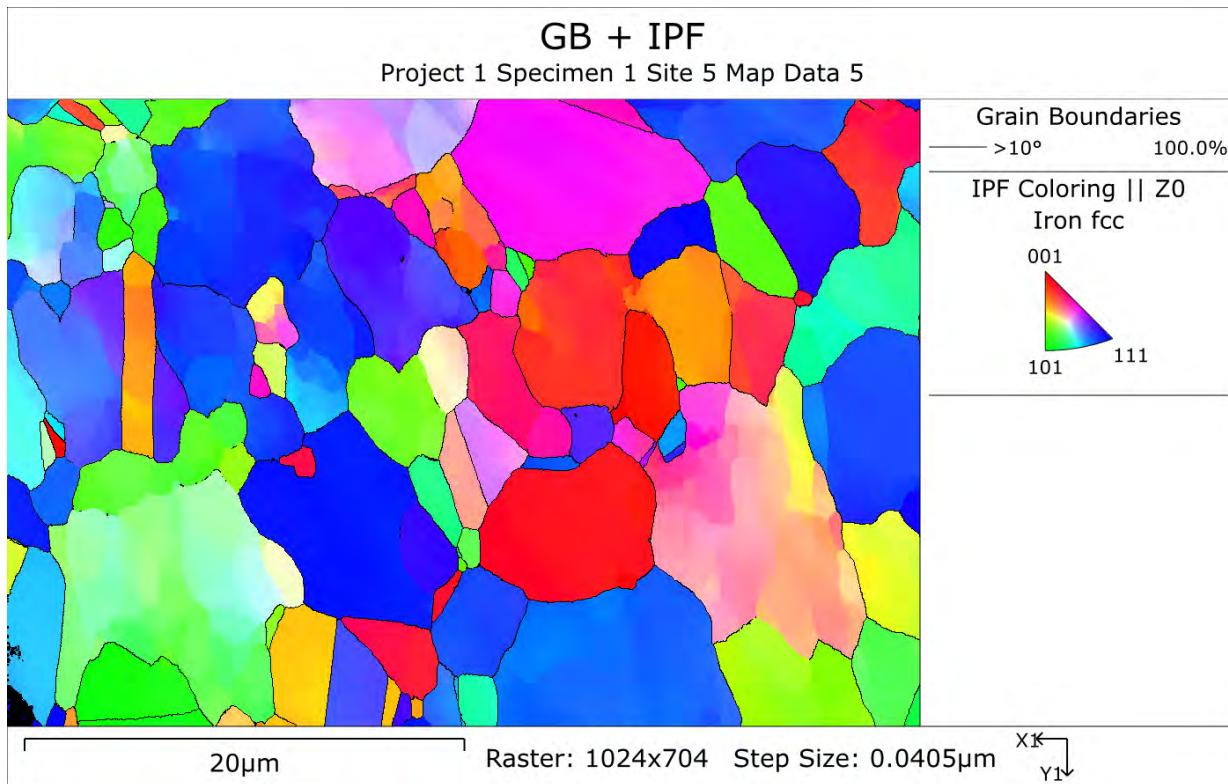


Figure 7.97. Inverse Pole Function - Z Images for L02: Condition C11, Sample SS16

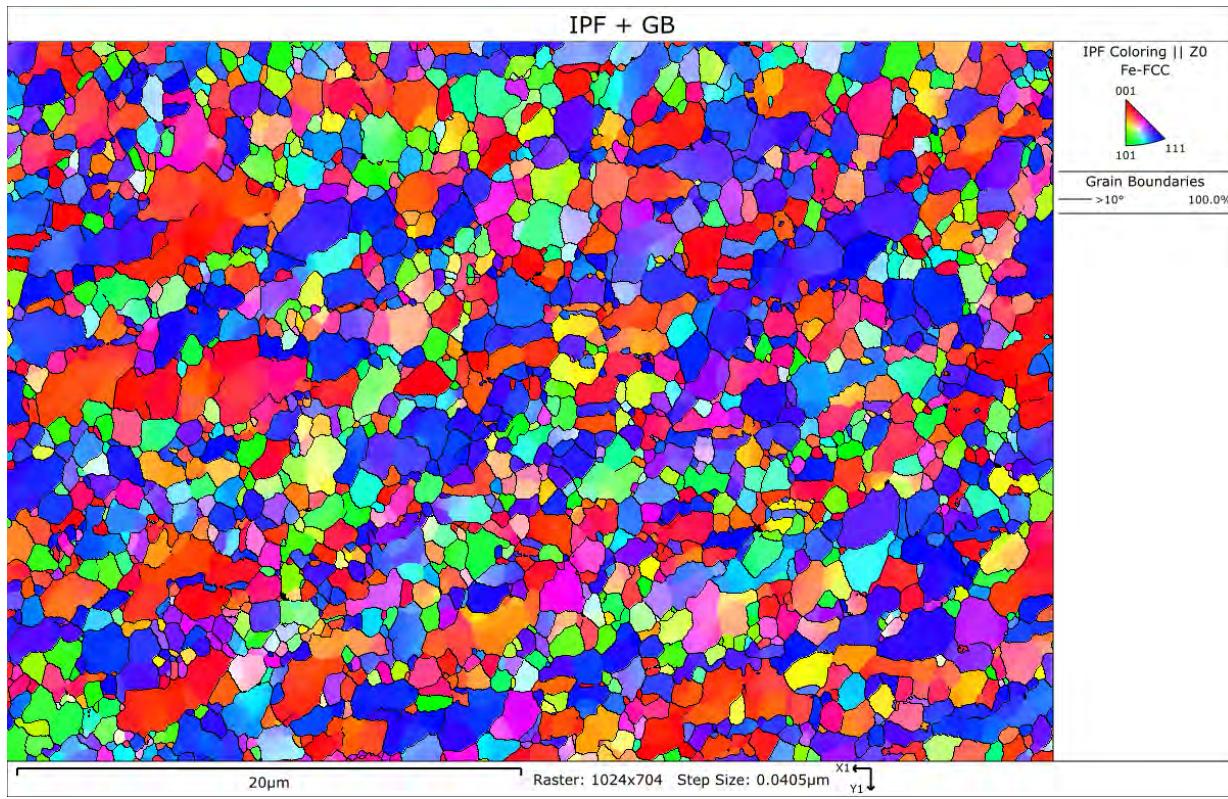


Figure 7.98. Inverse Pole Function - Z Images for L02: Condition C02, Sample SS24

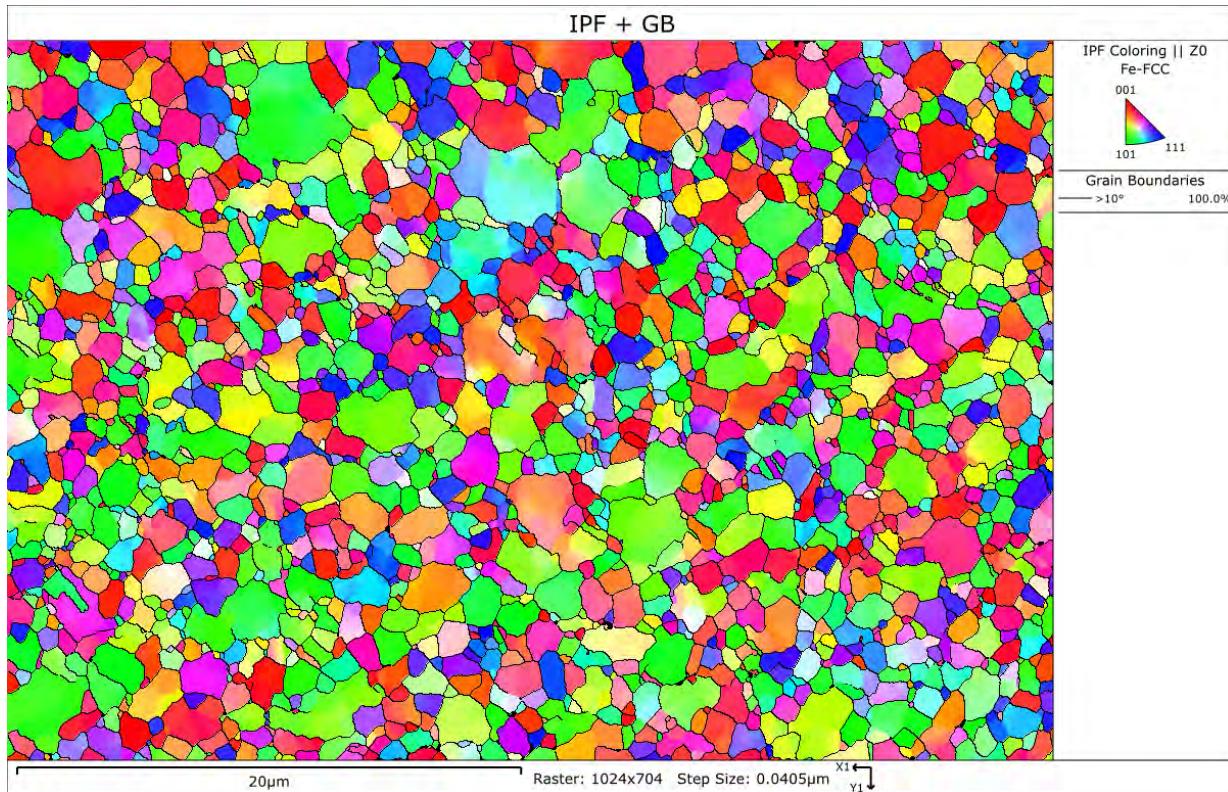


Figure 7.99. Inverse Pole Function - Z Images for L02: Condition C01, Sample SS33

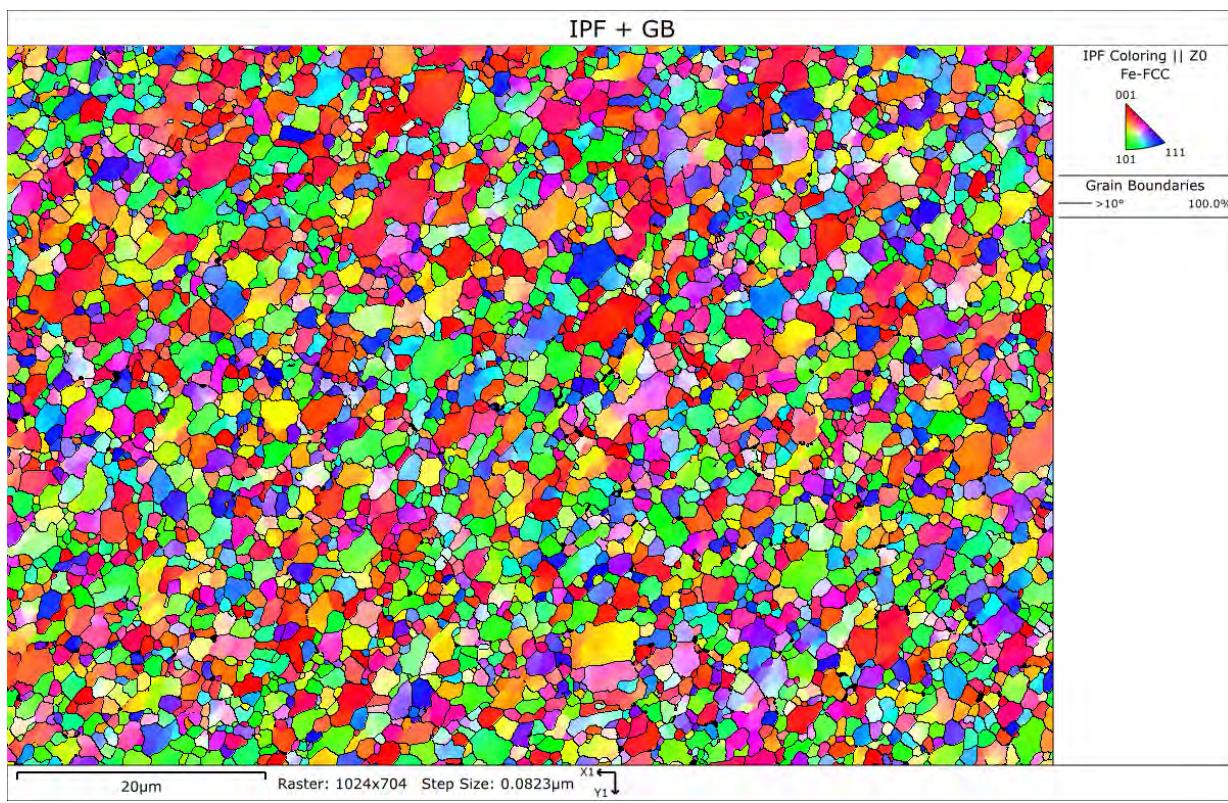


Figure 7.100. Inverse Pole Function - Z Images for L01b (2500X mag): Condition C05, Sample SS10

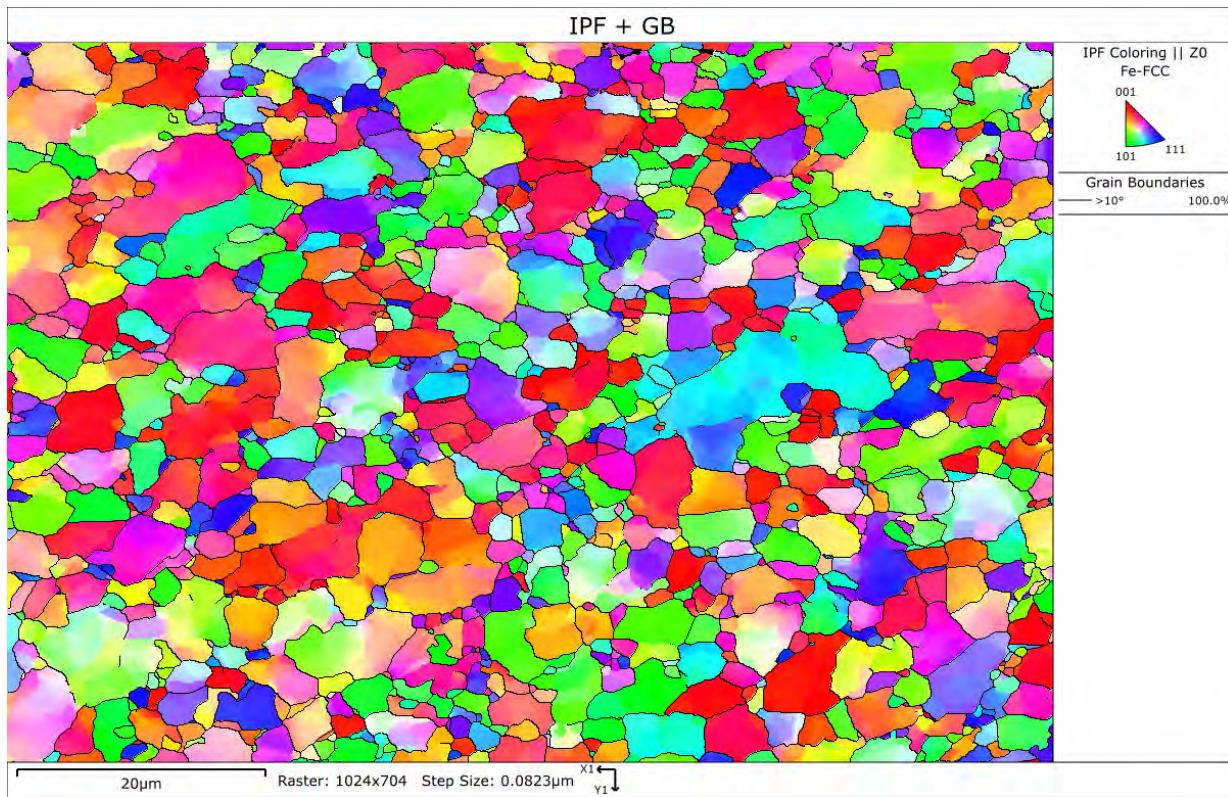


Figure 7.101. Inverse Pole Function - Z Images for L01b (2500X mag): Condition C08, Sample SS13

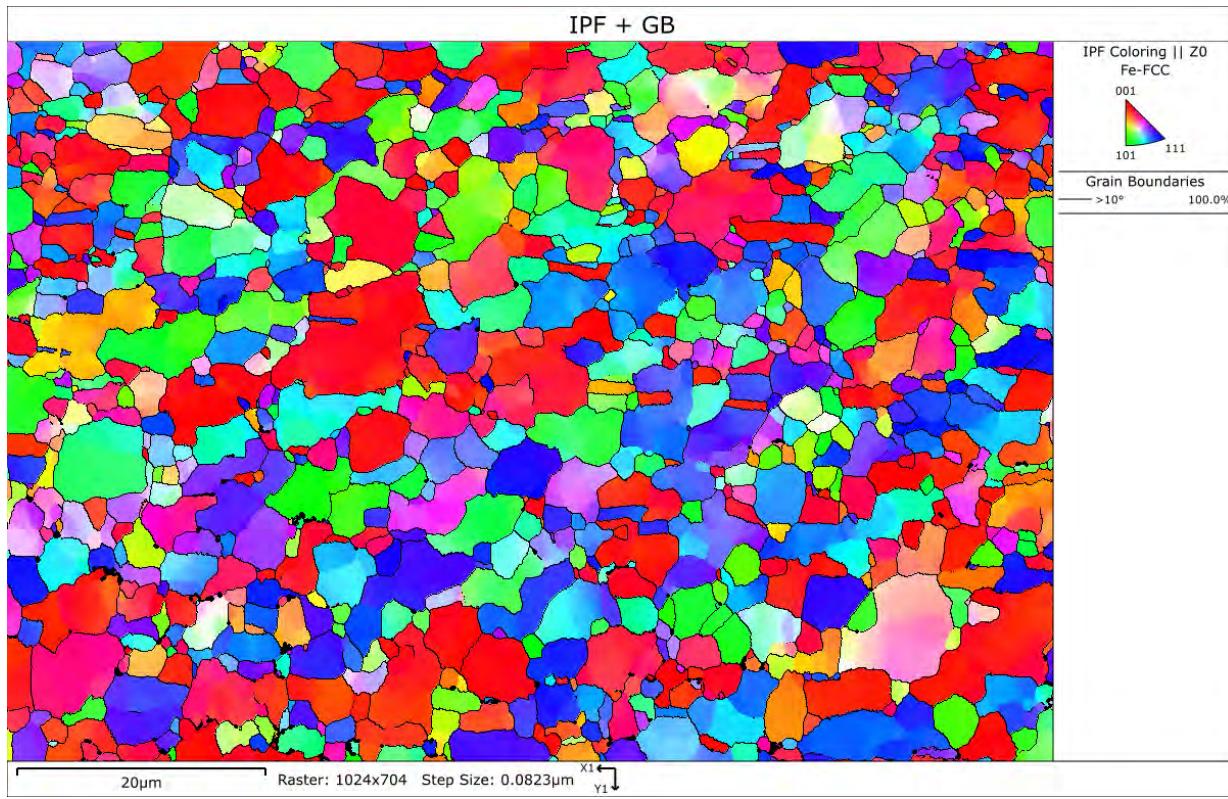


Figure 7.102. Inverse Pole Function - Z Images for L01b (2500X mag): Condition C09, Sample SS14

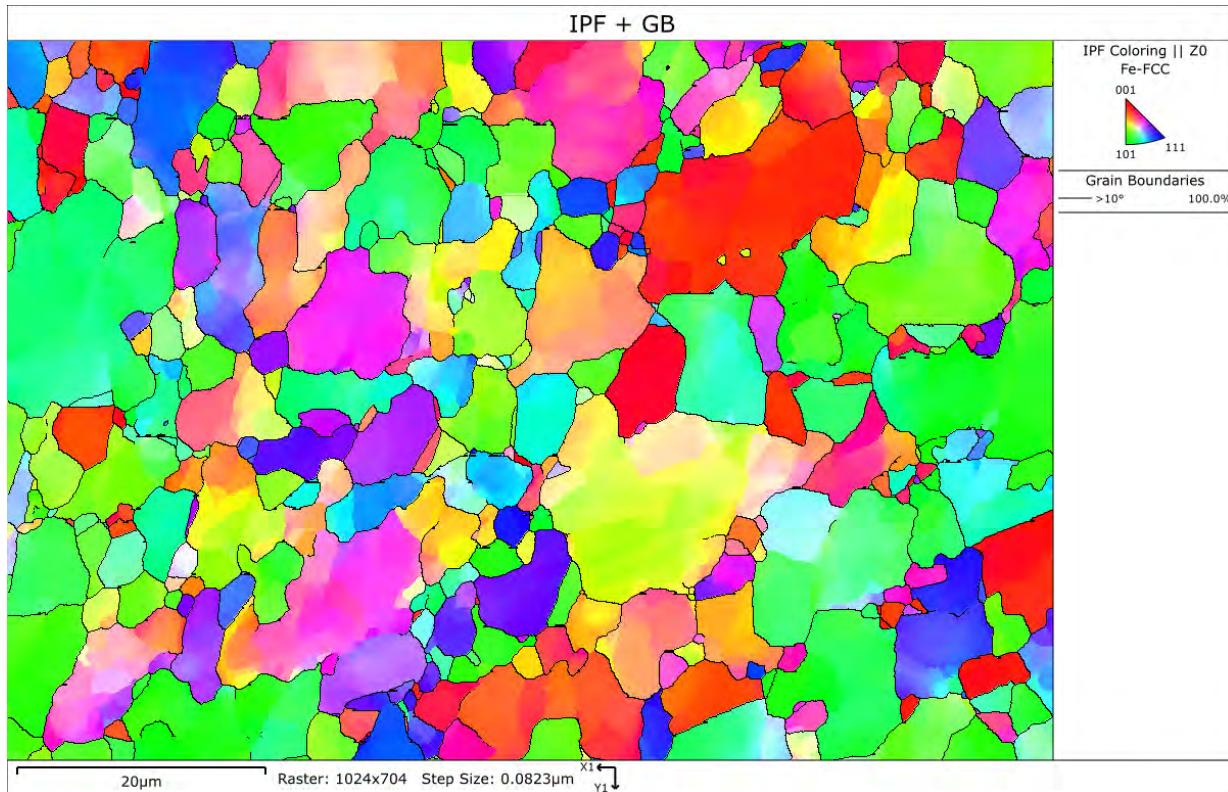


Figure 7.103. Inverse Pole Function - Z Images for L01b (2500X mag): Condition C10, Sample SS15

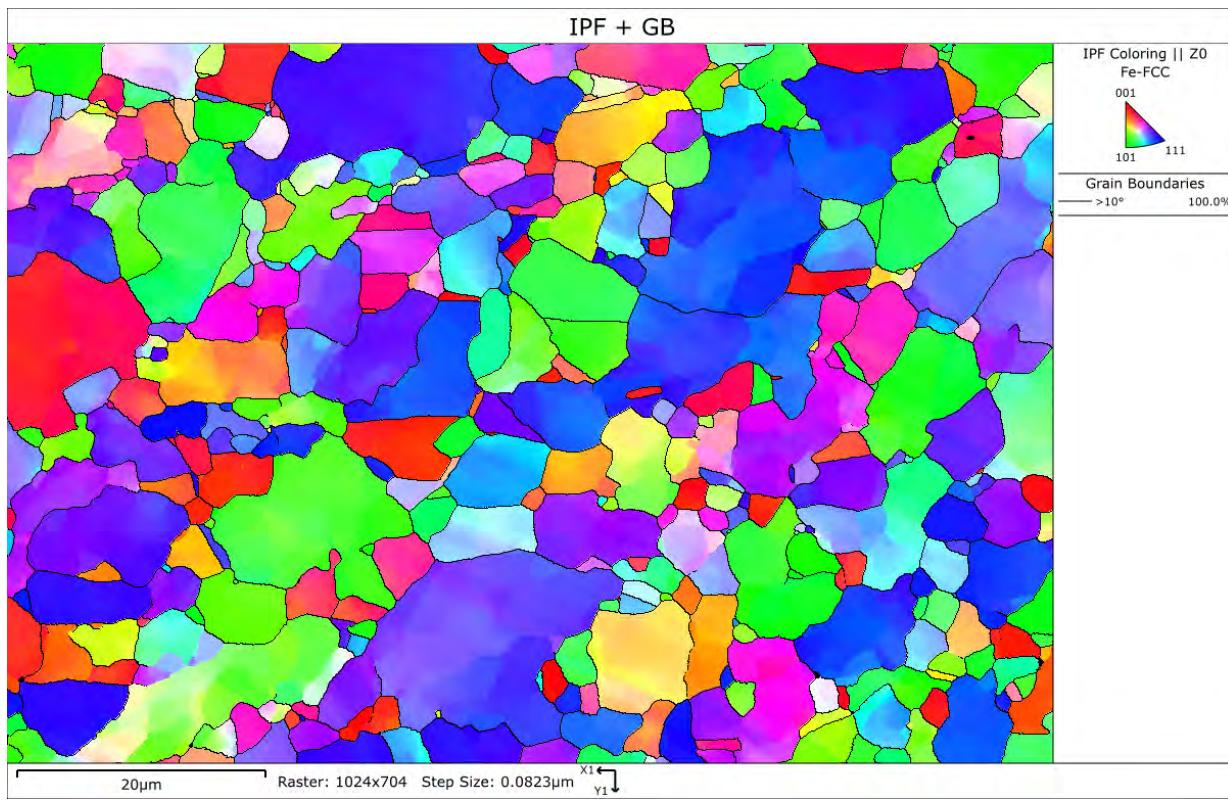


Figure 7.104. Inverse Pole Function - Z Images for L01b (2500X mag): Condition C11, Sample SS16

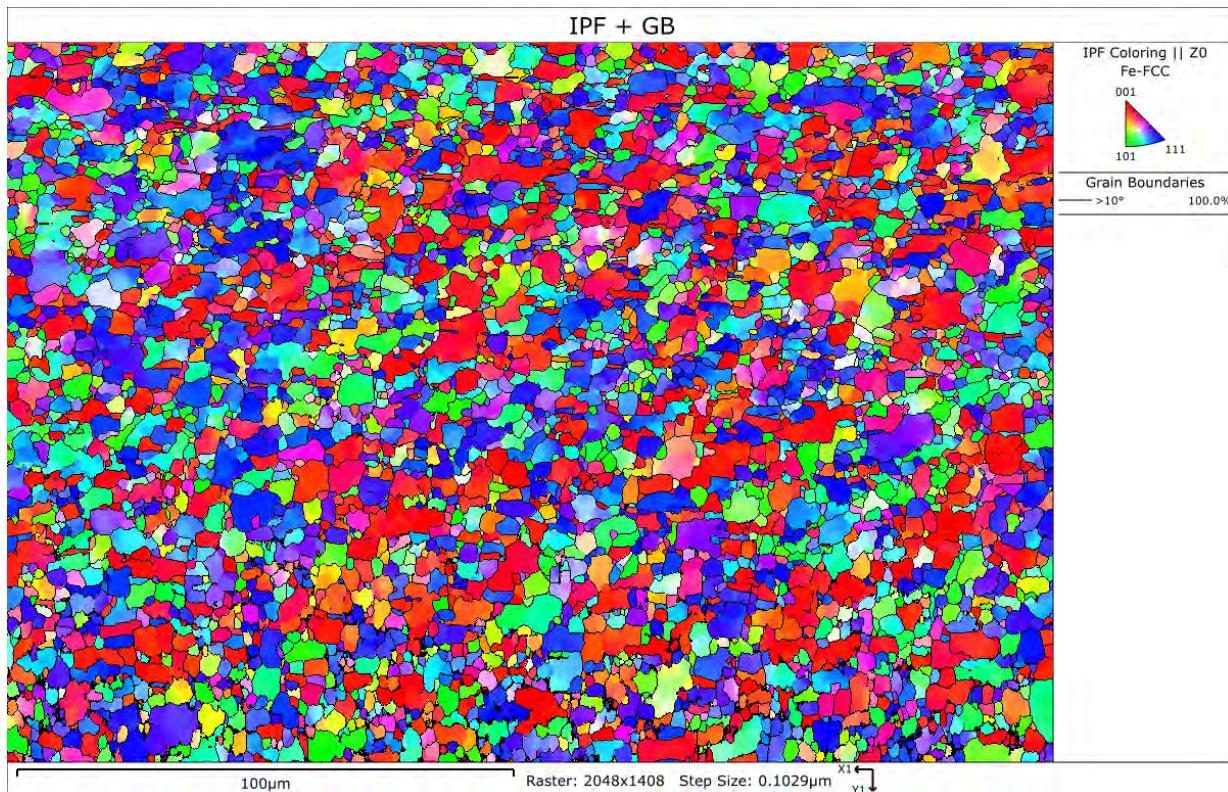


Figure 7.105. Inverse Pole Function - Z Images for L01b (1000x mag): Condition C09, Sample SS14

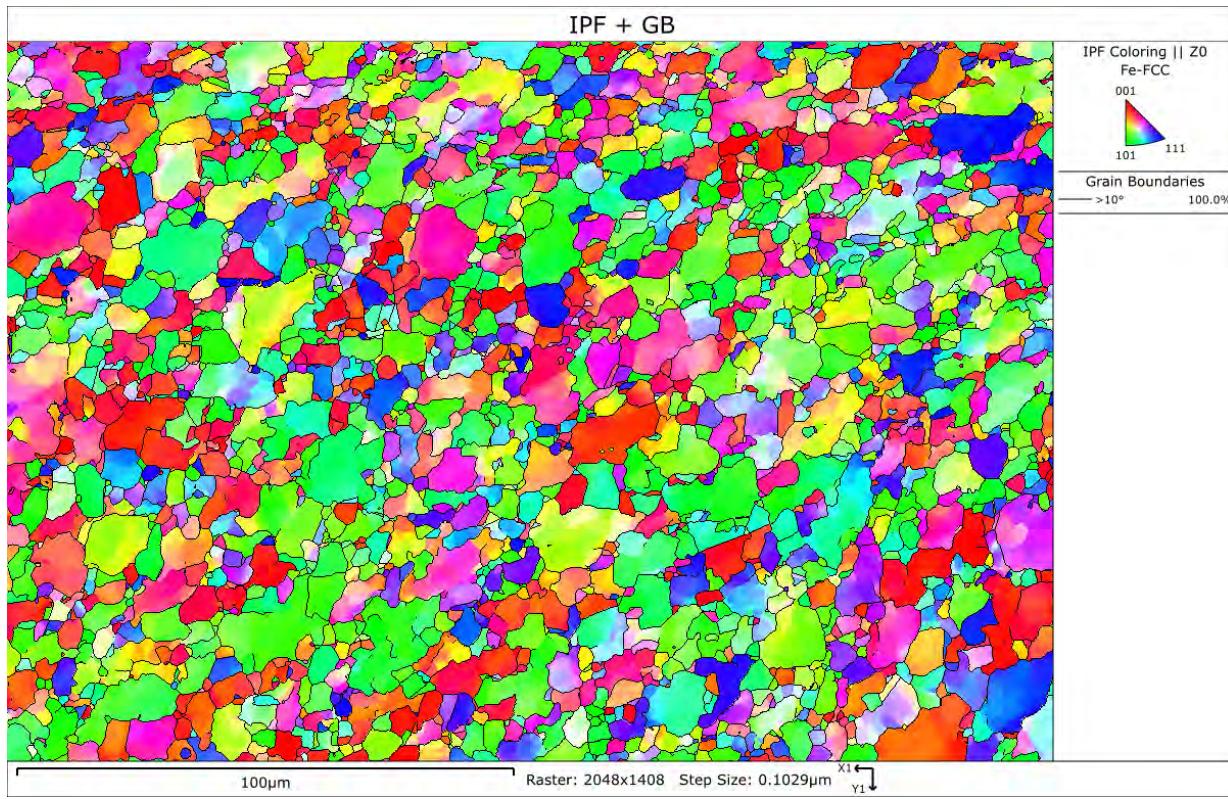


Figure 7.106. Inverse Pole Function - Z Images for L01b (1000x mag): Condition C10, Sample SS15

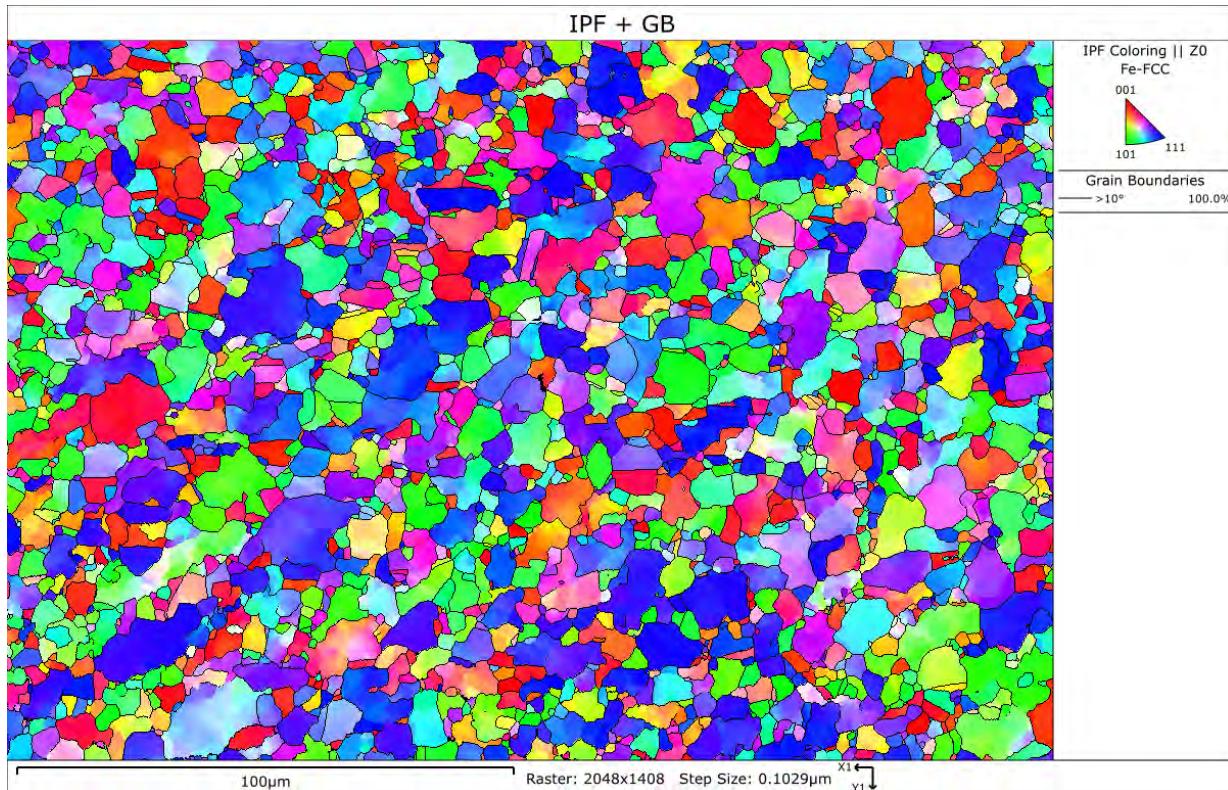


Figure 7.107. Inverse Pole Function - Z Images for L01b (1000x mag): Condition C11, Sample SS16

Attachment B: MCPC Round 2 Material Characterization Results for Modality

HARDNESS

A Ortiz A Guzman
DR Todd O Linsuain
K Nwe

Attachment B contains [20](#) pages

Acknowledgments

This research was supported by the Materials Characterization, Prediction, and Control (MCPC) investment, under the Laboratory Directed Research and Development (LDRD) Program at Pacific Northwest National Laboratory (PNNL). PNNL is a multi-program national laboratory operated for the U.S. Department of Energy (DOE) by Battelle Memorial Institute under Contract No. DE-AC05-76RL01830.

Contents

1	Introduction	5
2	Key Information and Results	6
3	Instrumentation	7
4	Results Files	8
5	Notes and Comments	9
6	Tabular Results	10
7	Graphics	11
7.1	No Interpolation, Stir Region Fit Shown	11
7.2	With Interpolation, Stir Region Fit Shown	15

Figures

7.1	Full Stir Region Region with no Interpolation: Condition C03, Sample SS09	12
7.2	Full Stir Region Region with no Interpolation: Condition C05, Sample SS10	12
7.3	Full Stir Region Region with no Interpolation: Condition C06, Sample SS11	12
7.4	Full Stir Region Region with no Interpolation: Condition C07, Sample SS12	13
7.5	Full Stir Region Region with no Interpolation: Condition C08, Sample SS13	13
7.6	Full Stir Region Region with no Interpolation: Condition C09, Sample SS14	13
7.7	Full Stir Region Region with no Interpolation: Condition C10, Sample SS15	14
7.8	Full Stir Region Region with no Interpolation: Condition C11, Sample SS16	14
7.9	Full Stir Region Region with no Interpolation: Condition C02, Sample SS24	14
7.10	Full Stir Region Region with no Interpolation: Condition C01, Sample SS33	15
7.11	Full Stir Region Region with Interpolation: Condition C03, Sample SS09	16
7.12	Full Stir Region Region with Interpolation: Condition C05, Sample SS10	16
7.13	Full Stir Region Region with Interpolation: Condition C06, Sample SS11	16
7.14	Full Stir Region Region with Interpolation: Condition C07, Sample SS12	17
7.15	Full Stir Region Region with Interpolation: Condition C08, Sample SS13	17
7.16	Full Stir Region Region with Interpolation: Condition C09, Sample SS14	17
7.17	Full Stir Region Region with Interpolation: Condition C10, Sample SS15	18
7.18	Full Stir Region Region with Interpolation: Condition C11, Sample SS16	18
7.19	Full Stir Region Region with Interpolation: Condition C02, Sample SS24	18
7.20	Full Stir Region Region with Interpolation: Condition C01, Sample SS33	19

Tables

6.1 Listing of all hardness data.	10
---	----

1.0 Introduction

In hardness testing (also called "micro" hardness testing for the dimensional-scale of the method), an indentation is made on the specimen by a diamond indenter through the application of a load. The size of the resultant indentation is measured with the help of a calibrated optical microscope, and the hardness is evaluated as the mean stress applied underneath the indenter. Hardness testing introduces local plastic stresses and corresponding strains into the material and is generally considered a destructive test. See Section 5.2 in Glass et al. (2024) for more general information about hardness testing (the reference is listed in Section 7.0 of the main report).

The "Vickers" testing method is applied here on mounted and polished specimens. Data is obtained on a square grid covering the entire stir region and the surrounding unprocessed base material. Results are provided numerically and via several visualizations for each specimen. Visualizations are graphed with a consistent scale across all specimens in this dataset to facilitate visual comparisons across the specimens.

The following sections provide a summary of results for this modality to enhance dissemination of the large volume of similar data that are made available via the PNNL DataHub (<https://data.pnnl.gov>) platform.

2.0 Key Information and Results

The main portion of this report provides a summary of key information related to the modality, including processing conditions, identification information, and the numerical results of most focus in the project. Where to find the information and results in the main report is described below (Section, Table, and Figure numbers listed below are found in the main report):

- Nominal process conditions for the FSP experiments are defined in Table 1 and Table 3 (data is in two different sorting orders).
- The Condition, Sample, and Specimen ID matrix is defined in Table 2 that is necessary to decode the nominal conditions applied to a particular specimen.
- Details about grid spacing for hardness sample collection is defined in Section 4.0.
- Tabulation of the hardness results considered most representative per Sample ID is listed in Table 3 with discussion of what the particular result means discussed earlier in the section.
- Hardness value versus nominal processing temperature listed in Table 3 and Table 4 is displayed graphically in Figure 4.
- A classical means for evaluating the structure-property relationship is to compare hardness versus the inverse square root of mean grain diameter. This is shown in Figure 6 to highlight consistency of results across a range of conditions.

3.0 Instrumentation

The following instrument was utilized in testing of specimens described in this attachment. Specifications are provided below.

Hardness Tester Model CM-700AT

- Company Name: Sun-Tec Corporation
- Clark
- MOD: CM ARS9000
- SER#: CM908123

4.0 Results Files

Section 6.0 of the main report describes the structure of data for the modality. This includes general approaches for naming files, organizing data by each unique dataset, and collecting information from across multiple datasets of a modality in the ENSEMBLE_DATA directory. Below is a summary of the files produced for each unique dataset. Items after the first entry describe derived and interpreted data files.

- {Dataset name}.csv (DATA Directory): The key "raw" text file produced by the tester for the specimen. hardness value is listed in column "HV". The (x, y) spacial location is listed in columns "X" and "Y" with the origin at (0, 0) arbitrarily chosen. Most negative X and Y values correspond to the upper left position. Missing values for "HV" generally represent locations where voids occurred.
- {Dataset name}*.jpg (VISUALIZATION Directory): The raw data is plotted in numerous different ways, including with/without interpolation between points, with/without plot scales and axes, with/without a Gaussian fitting of the stir region used to spatially registering the center of the stir region. Note that the color scales are identical across all datasets.
- {Dataset name}*_weld_data.txt (ANALYSIS Directory): The text file contains pertinent information regarding hardness value determined in the entire stir zone, hardness value closest to the stir zone center, and the average value on a small 0.5x0.5 mm region near the center. Standard deviation of average values are listed. The location of the stir zone is listed in mm relative to the coordinates of the raw data.

The most useful data across multiple datasets is captured in directory ENSEMBLE-INFO for this modality. The information is provided for convenience and is directly replicated from the related datasets. Refer to the individual datasets for details. In the case of conflicting information between items found in this directory and with individual datasets, the individual dataset information takes precedence

- HARDNESS_Values.{csv, xlsx}: Contains a summary of all hardness data from across all the datasets as a convenience. This data is assembled from the individual dataset files.

5.0 Notes and Comments

The following observations are made about data and files for this modality:

1. NONE

6.0 Tabular Results

All hardness data is listed below in Table 6.1 for the entire stir region (SR), the "window" (Wind) described earlier near the center, and the single point value closest to the center of the stir region. This data is obtained from the HARDNESS_Values.xls file described earlier and includes values for average and standard deviation.

Table 6.1. Listing of all hardness data.

Sample ID	Condition ID	SR Ave	SR Std	Wnd Avg	Wnd Std	Center Point
SS09	C03	277.63	16.34	273.51	11.91	277.93
SS10	C05	282.96	18.45	265.19	8.99	266.53
SS11	C06	287.92	14.02	276.08	8.75	279.29
SS12	C07	296.72	24.09	275.13	15.45	276.97
SS13	C08	232.25	13.06	228.28	5.75	229.86
SS14	C09	237.02	11.59	227.65	6.76	224.58
SS15	C10	221.27	10.73	215.34	5.11	217.07
SS16	C11	223.62	10.8	211.78	3.94	217.33
SS24	C02	291.2	18.24	292.48	7.29	296.57
SS33	C01	293.8	19.84	290.87	8.39	296.14

7.0 Graphics

The following sub sections display key graphics for convenience. Other graphics are available with the electronic data and the color scale used in all graphics is the same.

7.1 No Interpolation, Stir Region Fit Shown

The following figures show graphical results for all datasets collected in the round. These graphs indicate the discrete data with no interpolation between points and include a black curve showing a Gaussian shape fit to the data that is used to identify if a data point is within or outside the stir region. This fit was used to select data points to include in the "entire stir region" average and standard deviation values previously listed in Table 6.1. Versions without scale bars and axis labels are available.

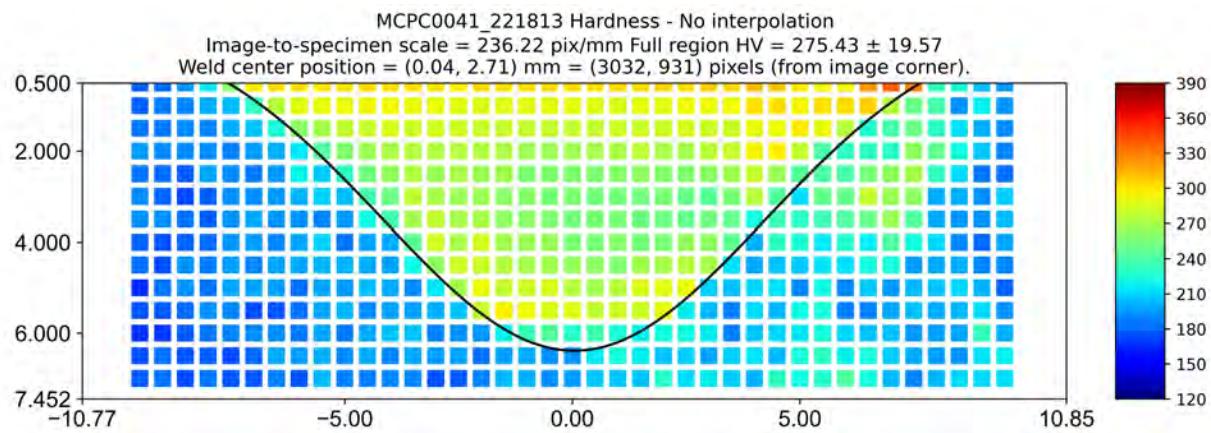


Figure 7.1. Full Stir Region Region with no Interpolation: Condition C03, Sample SS09

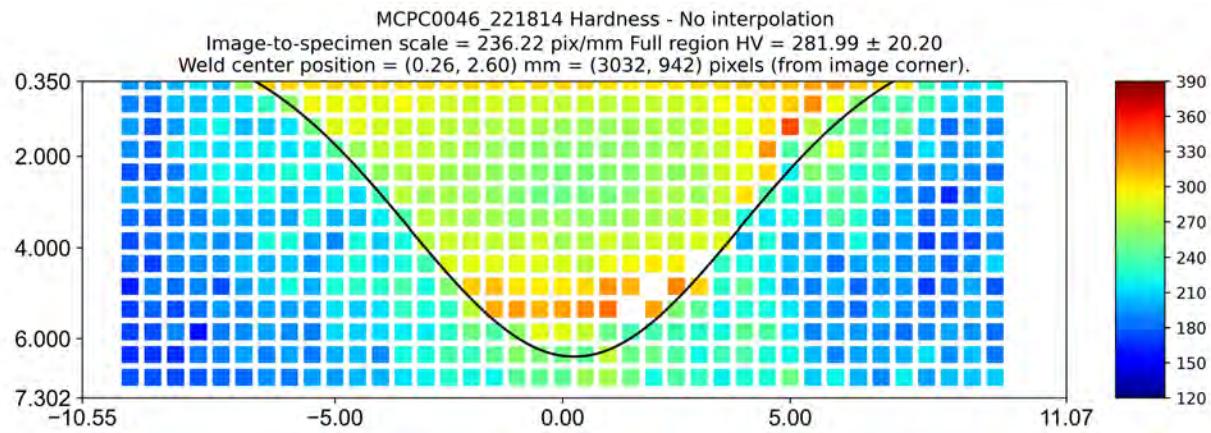


Figure 7.2. Full Stir Region Region with no Interpolation: Condition C05, Sample SS10

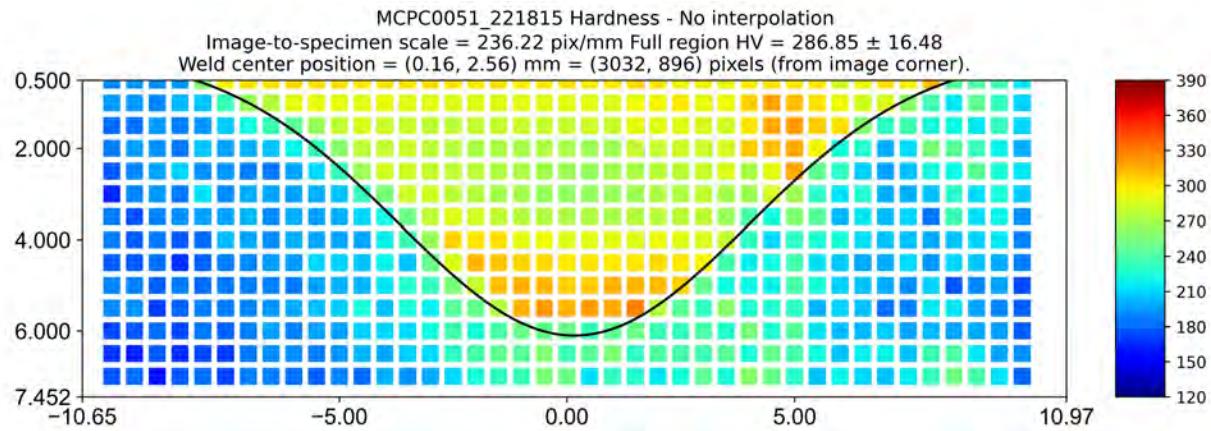


Figure 7.3. Full Stir Region Region with no Interpolation: Condition C06, Sample SS11

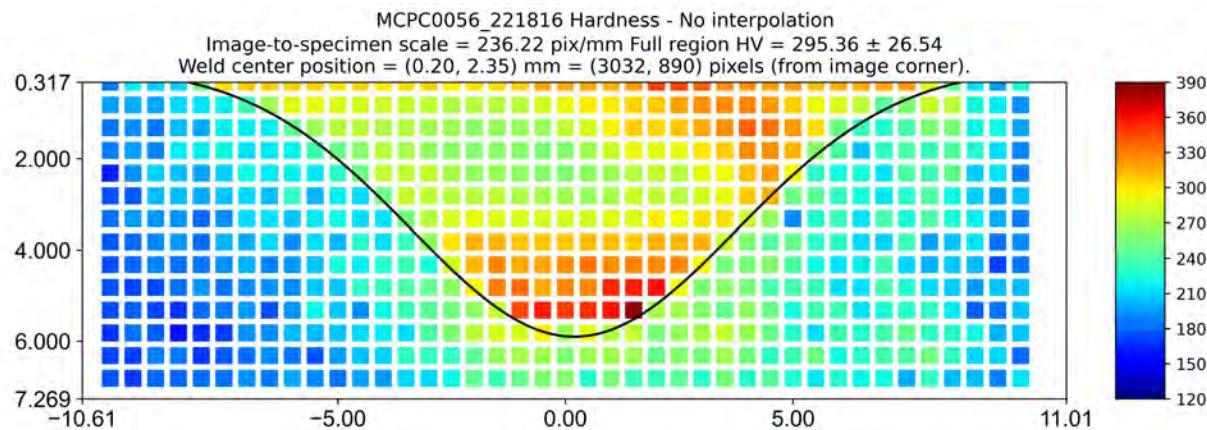


Figure 7.4. Full Stir Region Region with no Interpolation: Condition C07, Sample SS12

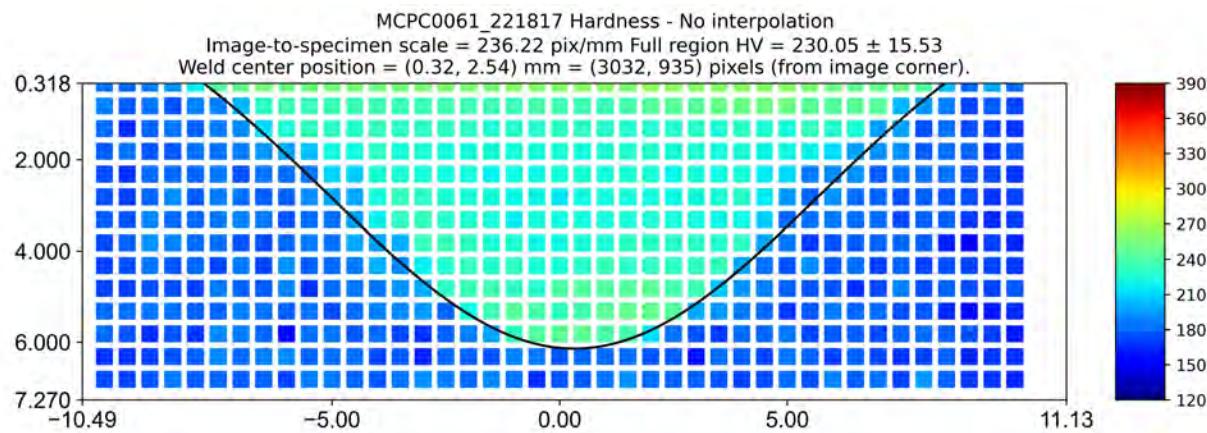


Figure 7.5. Full Stir Region Region with no Interpolation: Condition C08, Sample SS13

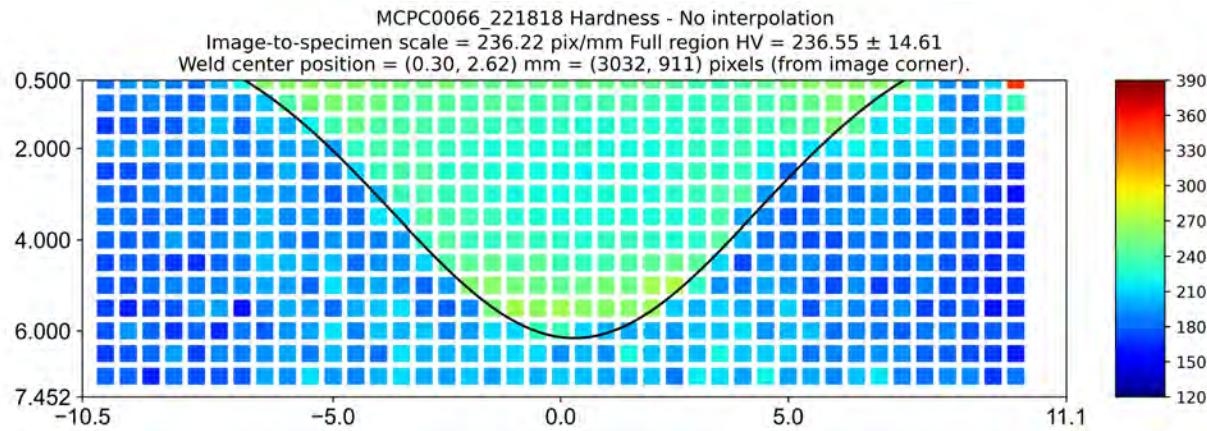


Figure 7.6. Full Stir Region Region with no Interpolation: Condition C09, Sample SS14

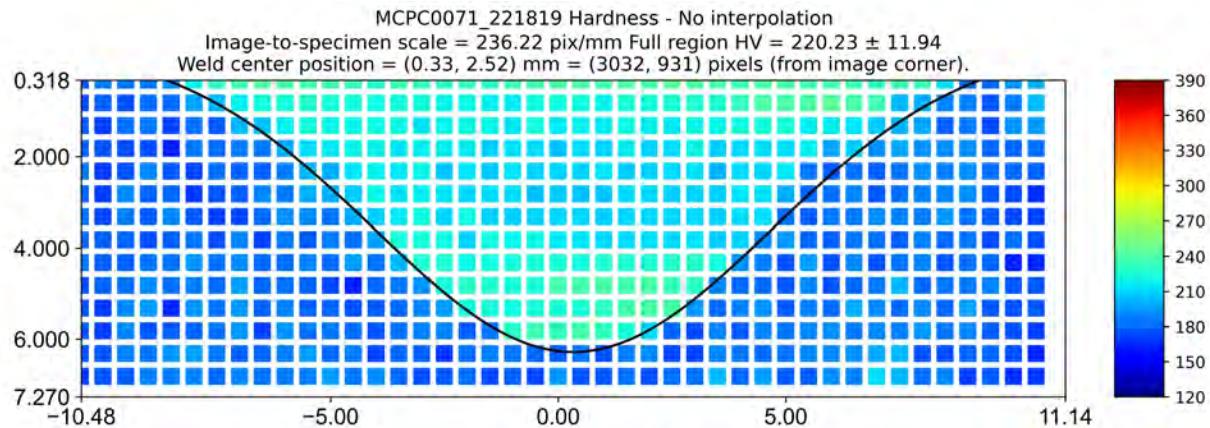


Figure 7.7. Full Stir Region Region with no Interpolation: Condition C10, Sample SS15

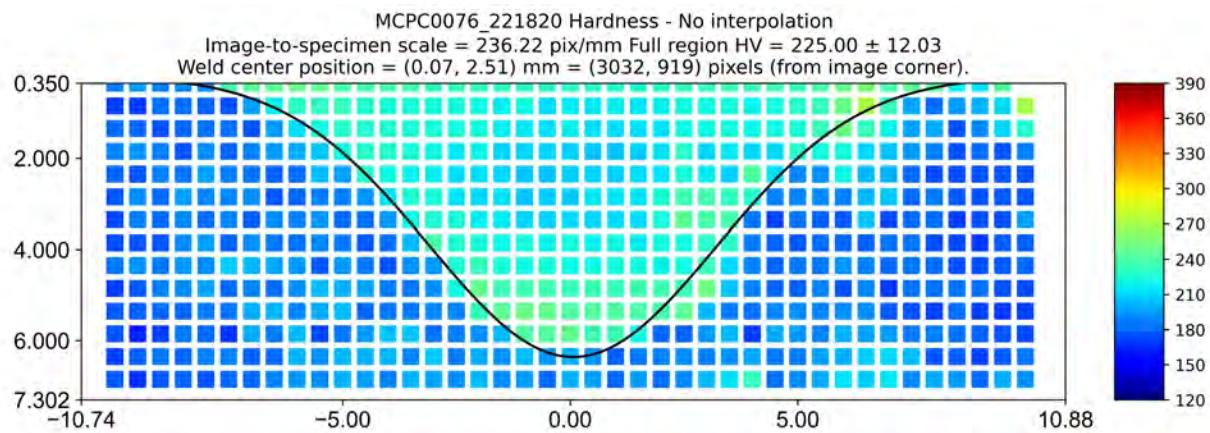


Figure 7.8. Full Stir Region Region with no Interpolation: Condition C11, Sample SS16

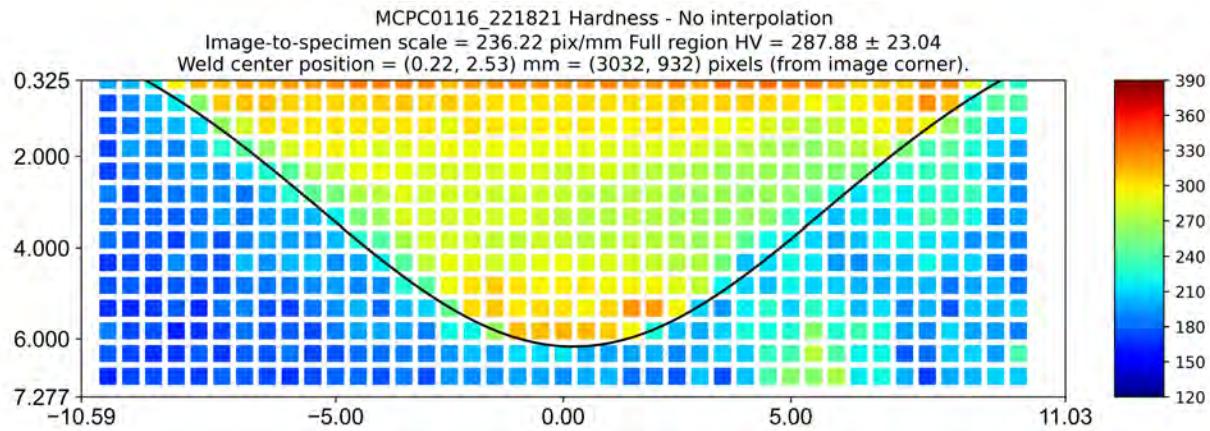


Figure 7.9. Full Stir Region Region with no Interpolation: Condition C02, Sample SS24

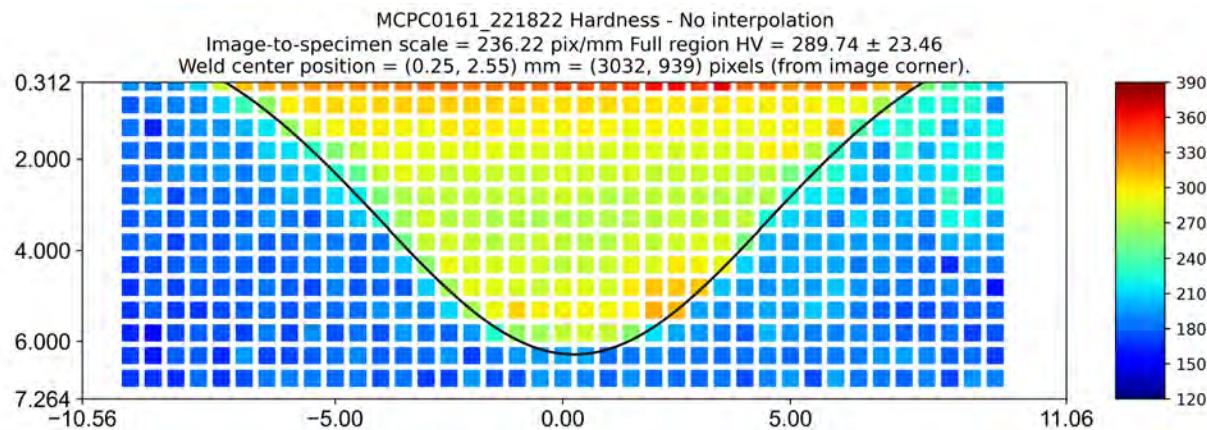


Figure 7.10. Full Stir Region Region with no Interpolation: Condition C01, Sample SS33

7.2 With Interpolation, Stir Region Fit Shown

The following figures show graphical results for all datasets in the round. These graphs are the same as the previous section, except that interpolation between points is performed.

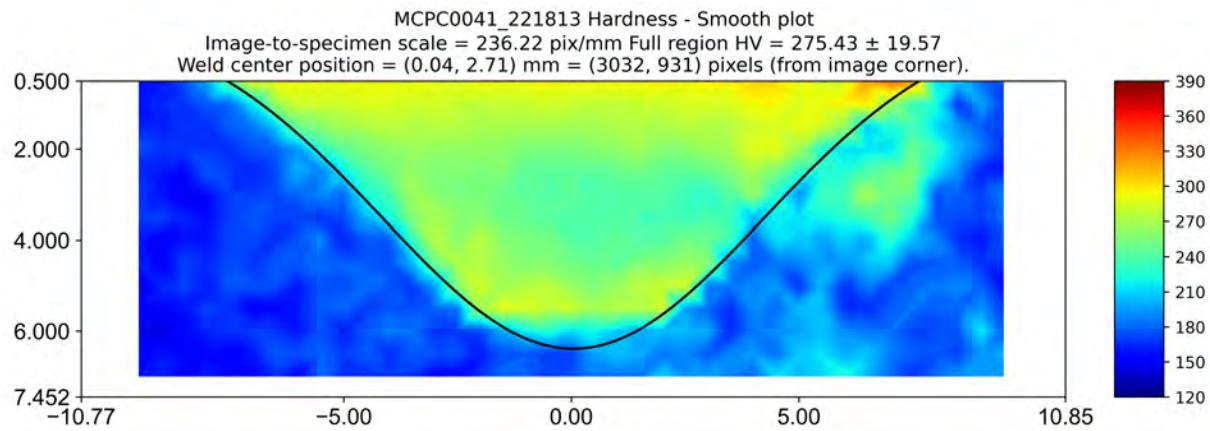


Figure 7.11. Full Stir Region Region with Interpolation: Condition C03, Sample SS09

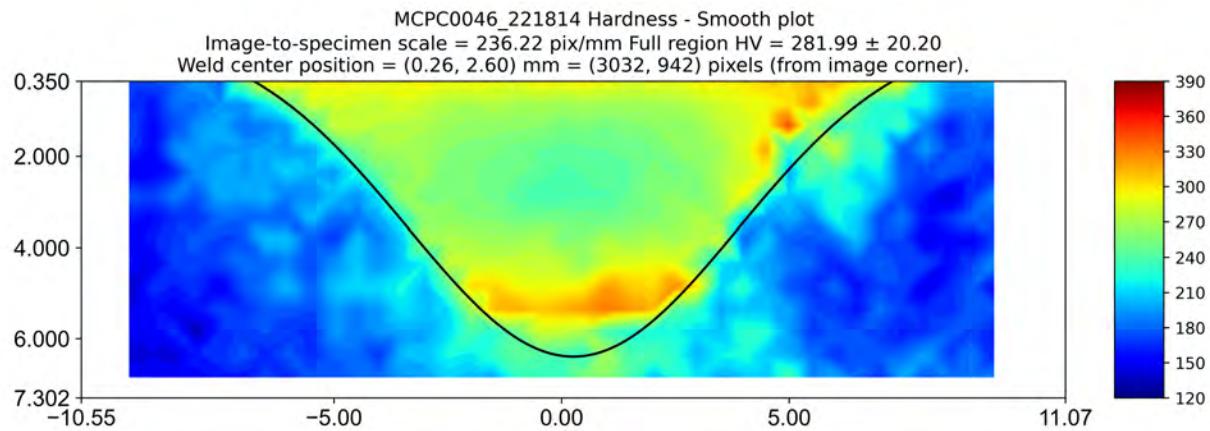


Figure 7.12. Full Stir Region Region with Interpolation: Condition C05, Sample SS10

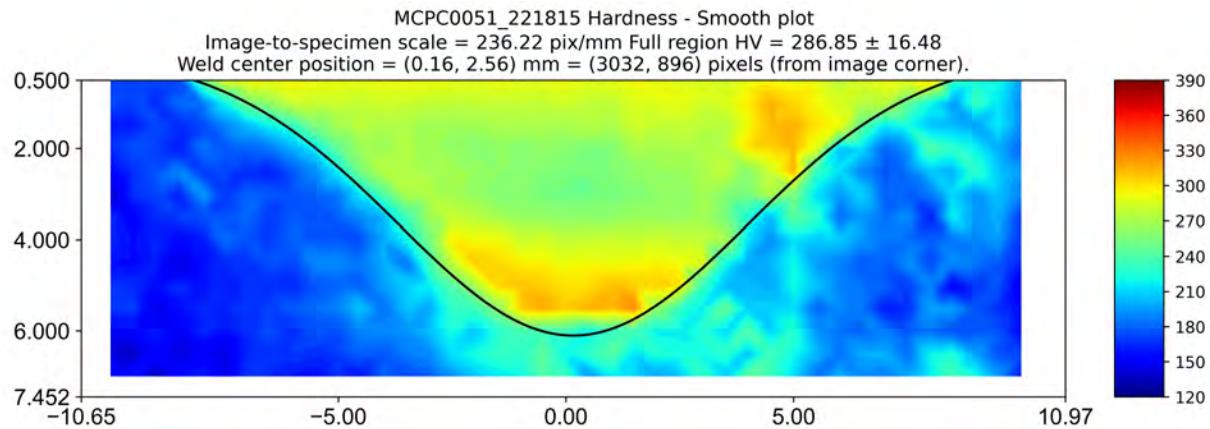


Figure 7.13. Full Stir Region Region with Interpolation: Condition C06, Sample SS11

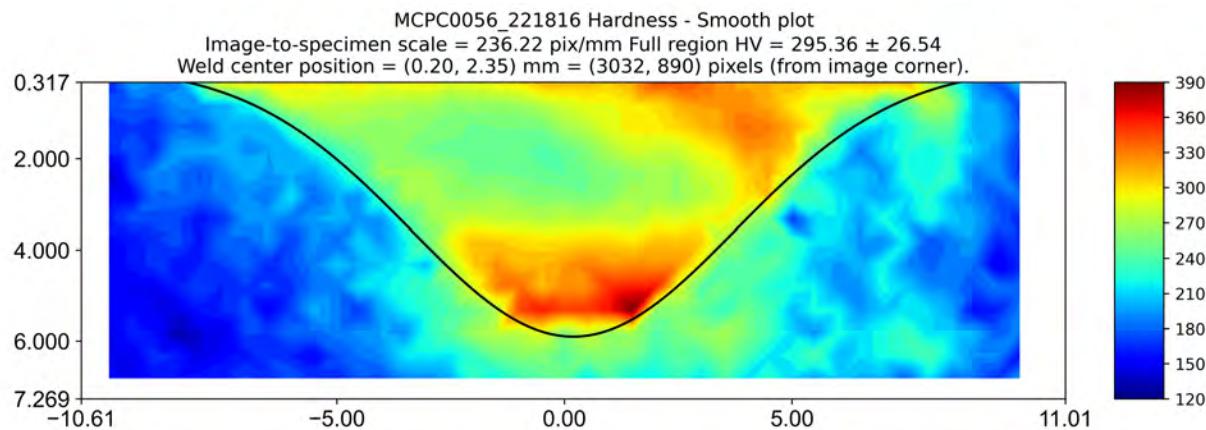


Figure 7.14. Full Stir Region Region with Interpolation: Condition C07, Sample SS12

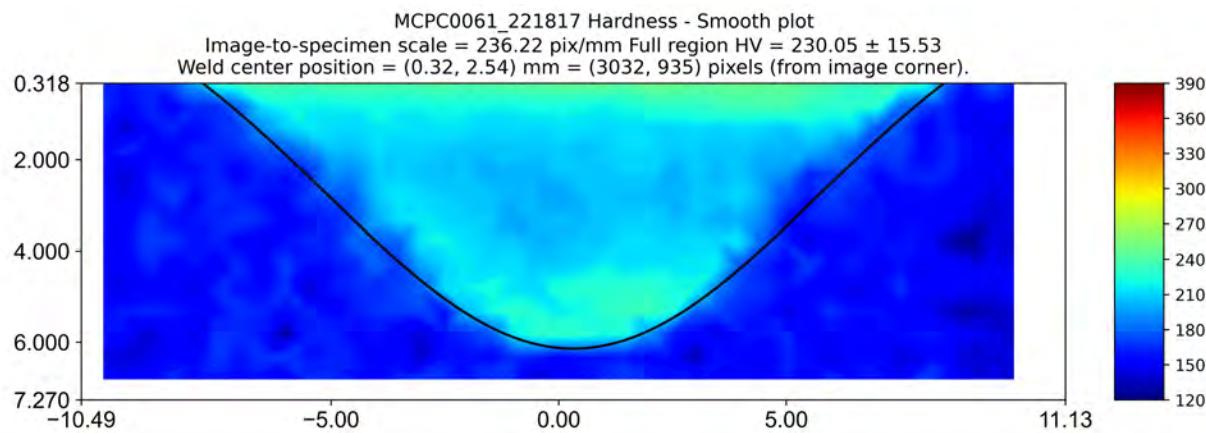


Figure 7.15. Full Stir Region Region with Interpolation: Condition C08, Sample SS13

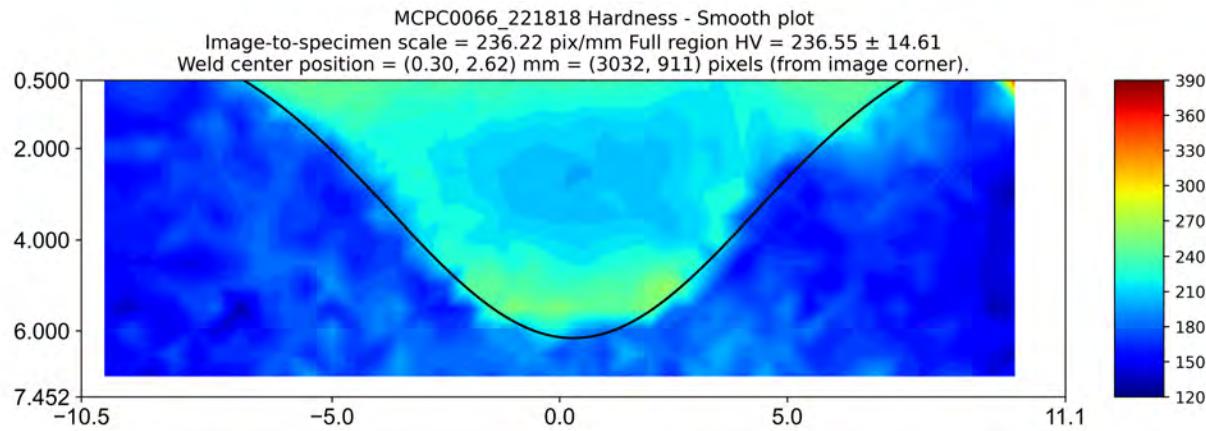


Figure 7.16. Full Stir Region Region with Interpolation: Condition C09, Sample SS14

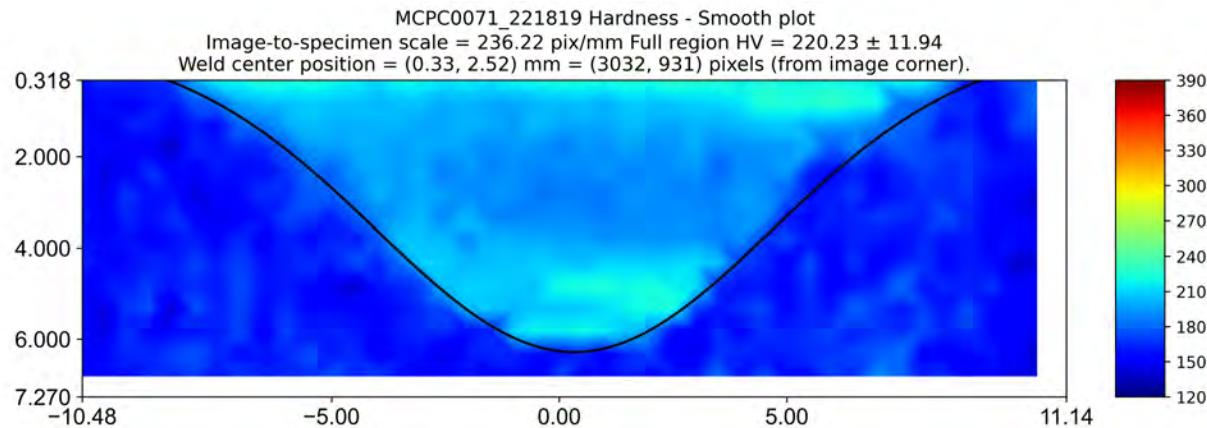


Figure 7.17. Full Stir Region Region with Interpolation: Condition C10, Sample SS15

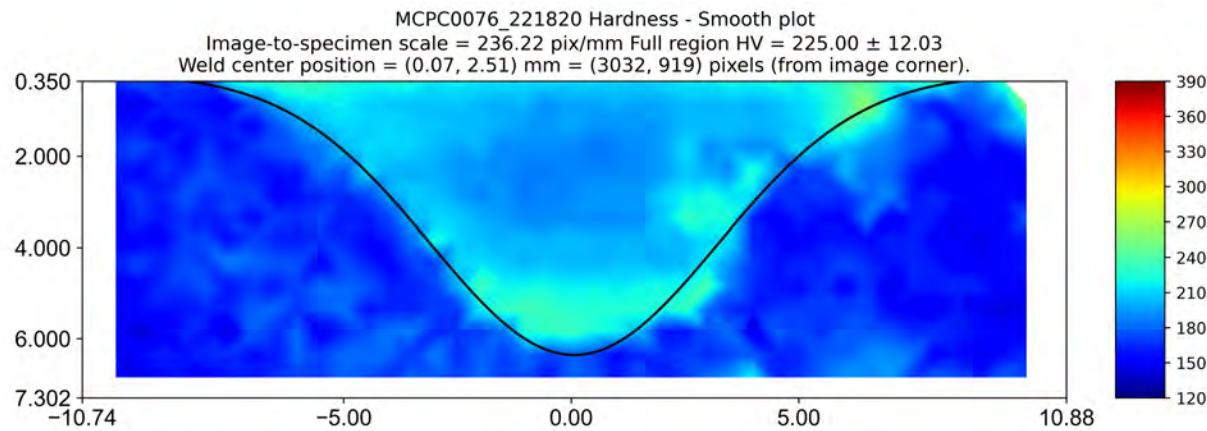


Figure 7.18. Full Stir Region Region with Interpolation: Condition C11, Sample SS16

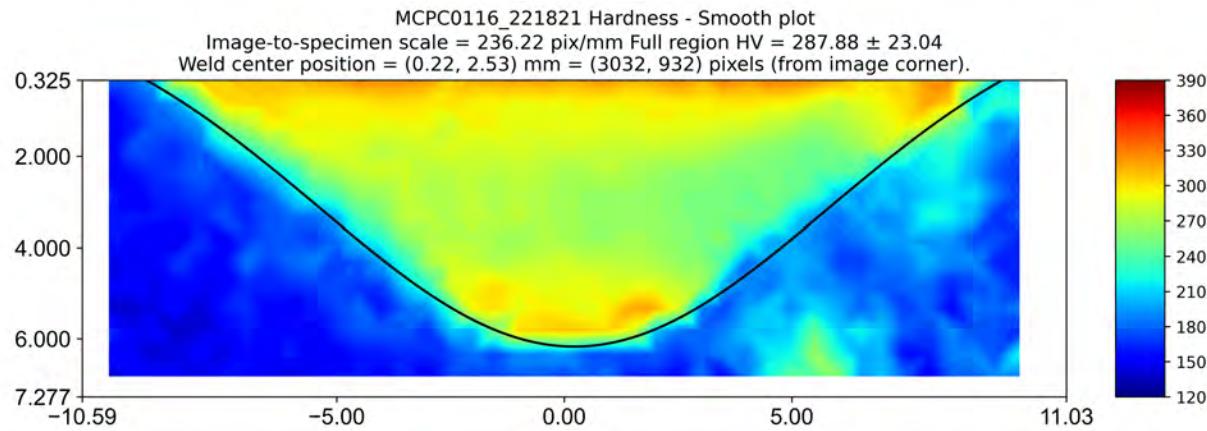


Figure 7.19. Full Stir Region Region with Interpolation: Condition C02, Sample SS24

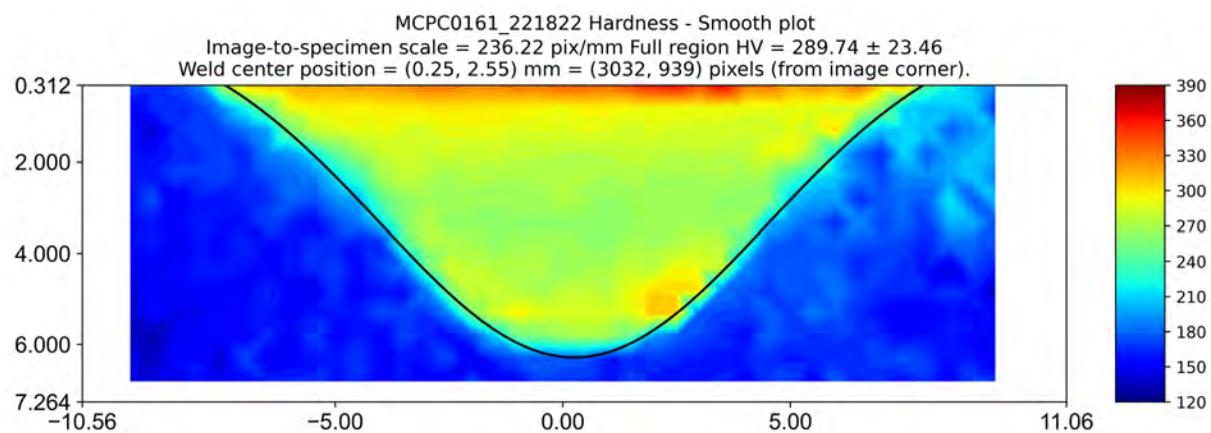


Figure 7.20. Full Stir Region Region with Interpolation: Condition C01, Sample SS33

Attachment C: MCPC Round 2 Material Characterization Results for Modality OPTICAL

A Ortiz K Nwe
DR Todd A Guzman

Attachment C contains [22](#) pages

Acknowledgments

This research was supported by the Materials Characterization, Prediction, and Control (MCPC) investment, under the Laboratory Directed Research and Development (LDRD) Program at Pacific Northwest National Laboratory (PNNL). PNNL is a multi-program national laboratory operated for the U.S. Department of Energy (DOE) by Battelle Memorial Institute under Contract No. DE-AC05-76RL01830.

Contents

1	Introduction	5
2	Key Information and Results	6
3	Instrumentation	7
4	Results Files	8
5	Notes and Comments	9
6	Tabular Results	10
7	Graphics	11
	7.1 Optical Imagery Results	11
	7.2 Results Collages, 11 mm Width	15

Figures

7.1	Optical Imagery at 100x mag: Condition C03, Sample SS09	12
7.2	Optical Imagery at 100x mag: Condition C05, Sample SS10	12
7.3	Optical Imagery at 100x mag: Condition C06, Sample SS11	12
7.4	Optical Imagery at 100x mag: Condition C07, Sample SS12	13
7.5	Optical Imagery at 100x mag: Condition C08, Sample SS13	13
7.6	Optical Imagery at 100x mag: Condition C09, Sample SS14	13
7.7	Optical Imagery at 100x mag: Condition C10, Sample SS15	14
7.8	Optical Imagery at 100x mag: Condition C11, Sample SS16	14
7.9	Optical Imagery at 100x mag: Condition C02, Sample SS24	14
7.10	Optical Imagery at 100x mag: Condition C01, Sample SS33	15
7.11	Stir Region Collage: Image number 1	16
7.12	Stir Region Collage: Image number 2	17
7.13	Stir Region Collage: Image number 3	18
7.14	Stir Region Collage: Image number 4	19
7.15	Stir Region Collage: Image number 5	20
7.16	Stir Region Collage: Image number 6	21

Tables

No Tables are associated with this Attachment

1.0 Introduction

Optical microscopy uses visible light and a system of lenses to generate magnified images of a specimen that has been mounted and polished. Contrasting agents and etchants can be used to reveal granular structures and other properties. Optical microscopy is traditional technique that is often performed early in a workflow to assist in identifying defects and areas of interest for more advanced microscopy techniques.

The following sections provide a summary of results for this modality to enhance dissemination of the large volume of similar data that are made available via the PNNL DataHub (<https://data.pnnl.gov>) platform.

2.0 Key Information and Results

The main portion of this report provides a summary of key information related to the modality, including processing conditions, identification information, and the numerical results of most focus in the project. Where to find the information and results in the main report is described below (Section, Table, and Figure numbers listed below are found in the main report). Note that application of optical microscopy did not results in quantitative data, so no tabular or quantitative results are provided in the main report or here for the modality.

- Nominal process conditions for the FSP experiments are defined in Table 1 and Table 3 (data is in two different sorting orders).
- The Condition, Sample, and Specimen ID matrix is defined in Table 2 that is necessary to decode the nominal conditions applied to a particular specimen.
- Details about the modality data collection approach is defined in Section 4.0. This includes information about magnification levels for optical microscopy.

3.0 Instrumentation

An Olympus Model DP74 was used to collect all results

4.0 Results Files

A 100x magnification image (10x ocular and 10x magnification) is available for all stir regions where the specimens were etched to reveal more contrast of the grain structure. Two versions, one without and one with a scale bar were provided. The files have the following in their names:

- 10X_Nugget-Region-Etched
- 10X_Nugget-Region-Etched_scale

5.0 Notes and Comments

The following observations are made about data and files for this modality:

1. Imagery with a scale bar was in gray scale, but saved with RGB color channels when adding the scale. This resulted in the imagery containing a scale bar being 3x larger than the original image.
2. The microscope used to collect this data automatically produces the montage image and individual tiles captured as the instrument raster scans the specimens cannot be saved by the proprietary software. When creating montages, the software applies subtle blending between tiles that is acceptable for visual evaluation. However, machine learning applications may be impacted by the blending and may need to avoid using these regions of the montage.
3. Spatial location and rotation data to align the center of the stir region is only approximate.

6.0 Tabular Results

No tabular results are available for this modality.

7.0 Graphics

The following sub sections display key graphics for convenience:

7.1 Optical Imagery Results

Optical imagery for available specimens follows. Imagery for the control is not provided. The displayed images have been slightly rotated to improve alignment and image size reduced to 2000 pixels in width for handling convenience. The raw (gigabit sized) files are provided with electronic data.

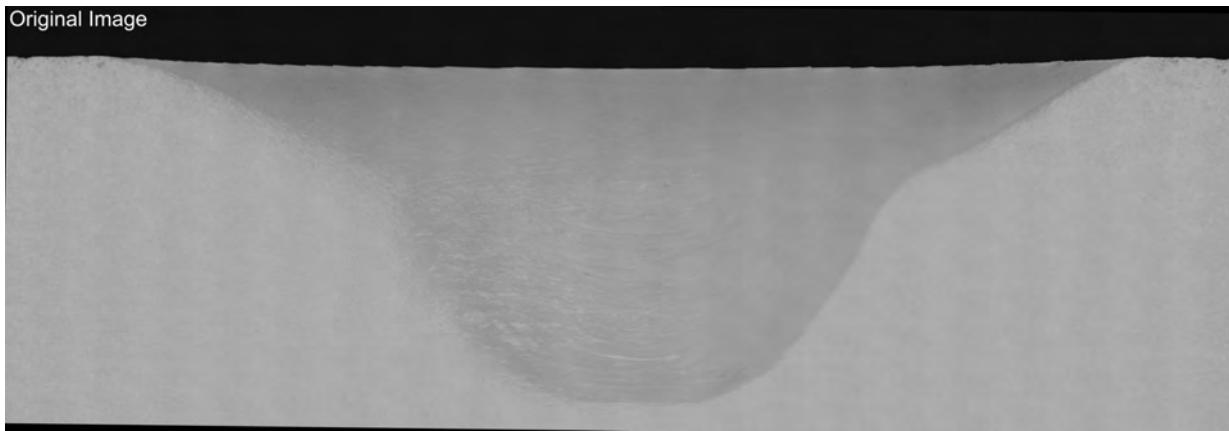


Figure 7.1. Optical Imagery at 100x mag: Condition C03, Sample SS09



Figure 7.2. Optical Imagery at 100x mag: Condition C05, Sample SS10

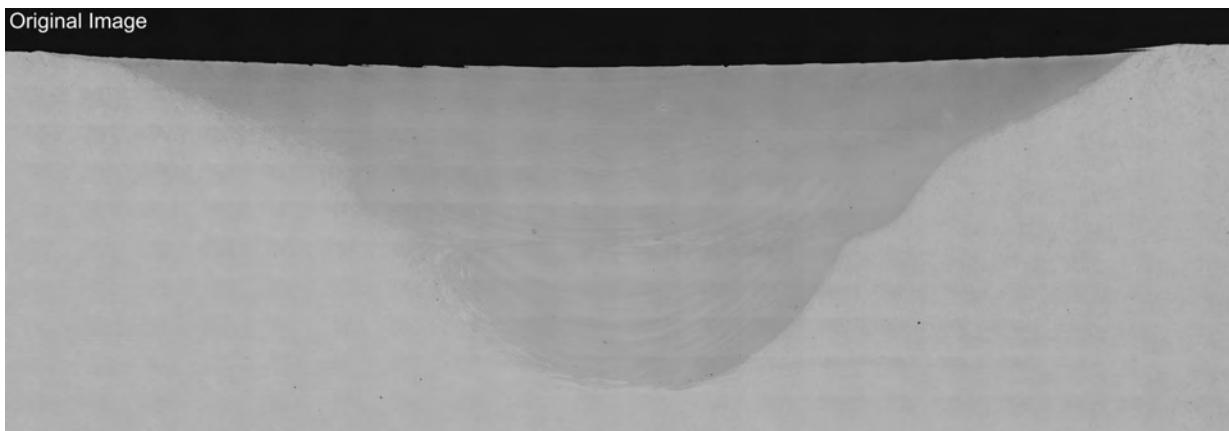


Figure 7.3. Optical Imagery at 100x mag: Condition C06, Sample SS11

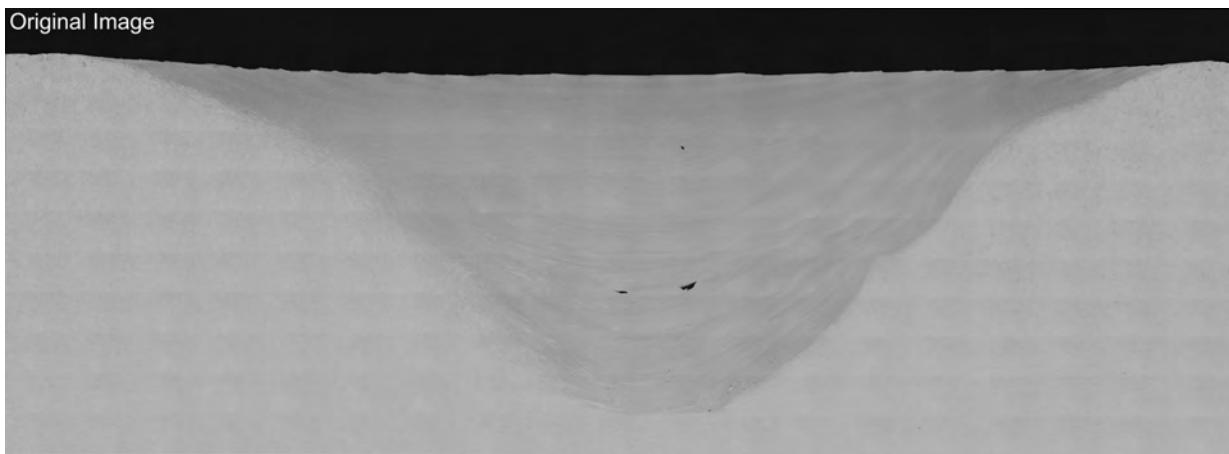


Figure 7.4. Optical Imagery at 100x mag: Condition C07, Sample SS12

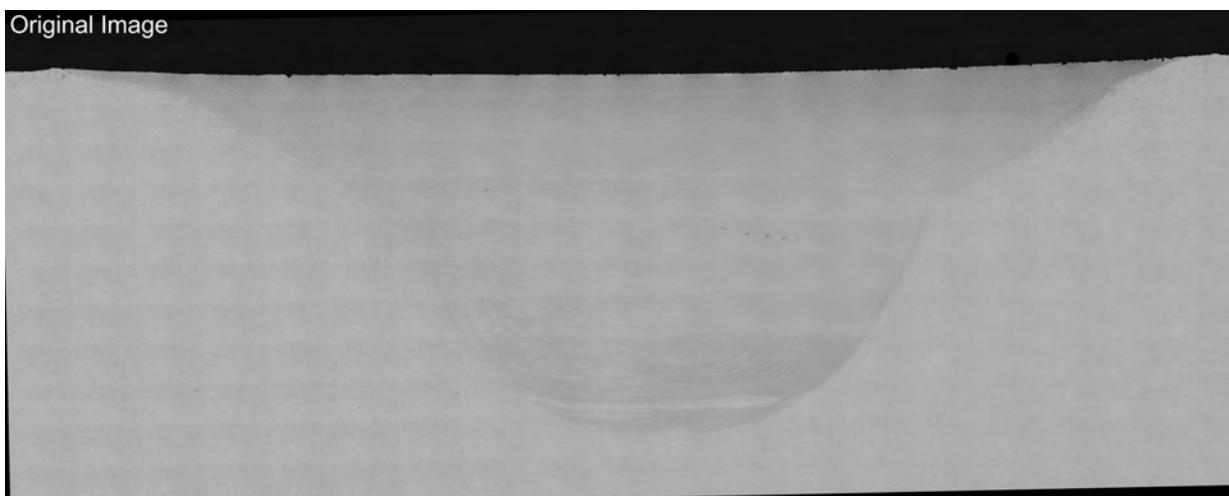


Figure 7.5. Optical Imagery at 100x mag: Condition C08, Sample SS13

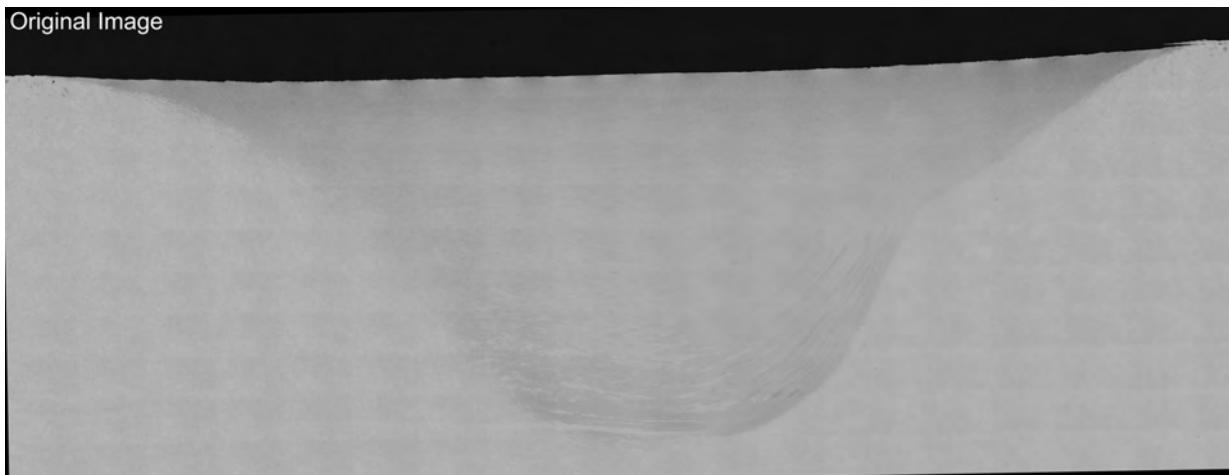


Figure 7.6. Optical Imagery at 100x mag: Condition C09, Sample SS14



Figure 7.7. Optical Imagery at 100x mag: Condition C10, Sample SS15



Figure 7.8. Optical Imagery at 100x mag: Condition C11, Sample SS16

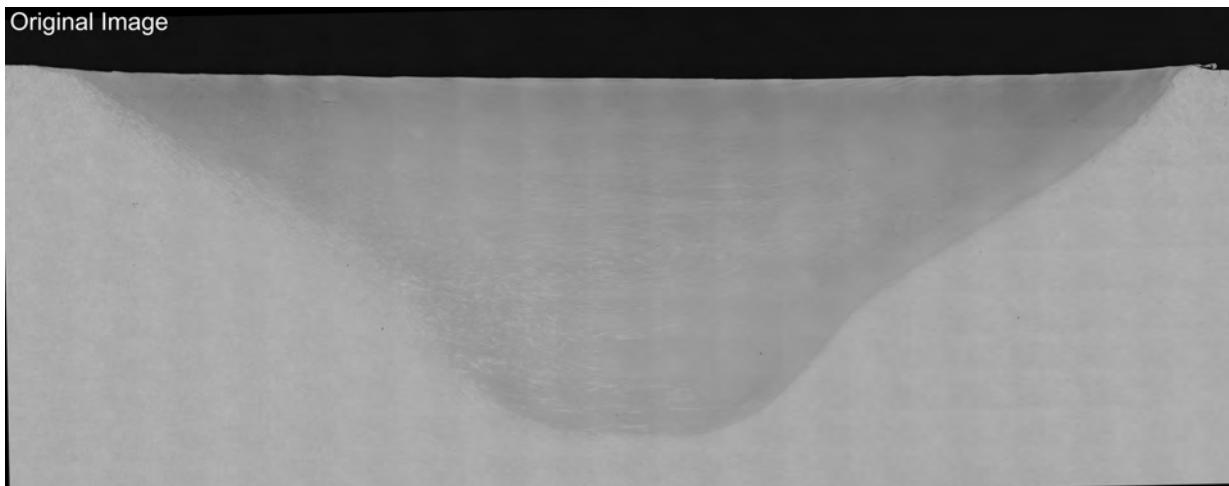


Figure 7.9. Optical Imagery at 100x mag: Condition C02, Sample SS24

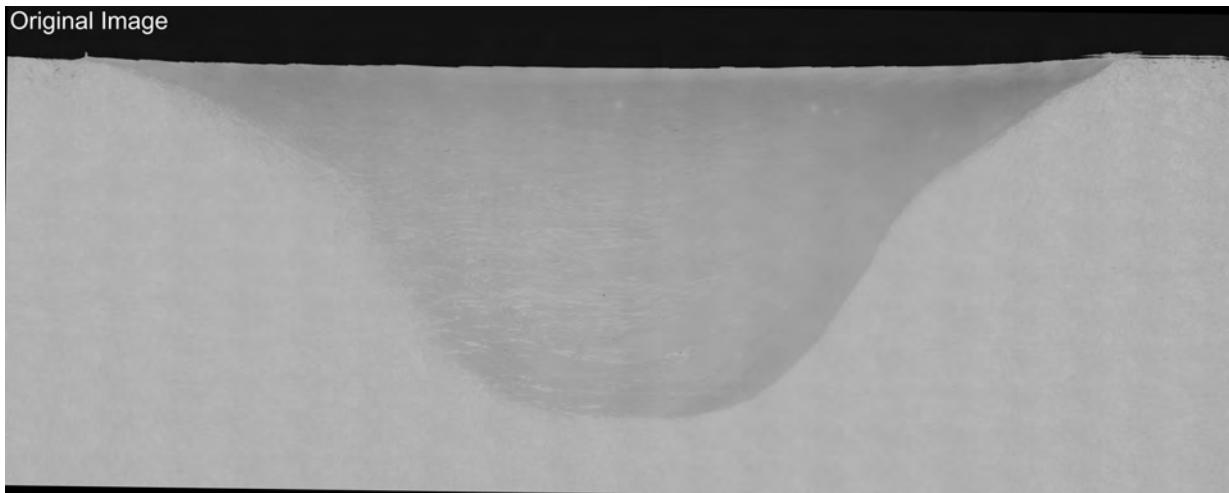


Figure 7.10. Optical Imagery at 100x mag: Condition C01, Sample SS33

7.2 Results Collages, 11 mm Width

The following figures show collages of all the results with the stir region in each specimen cropped to 11 mm in width. Note that the image for each specimen in the collage contains a label listing identification information, results for mean grain diameter and hardness, along with the nominal processing conditions. These values are the same as listed in the main report, except that the hardness values reflect stir region average value found in Attachment B, Table 6.1 (SR Ave), instead of the value for the small window near the center that is listed in Table 3 of the main report.

Three versions of each image collage are provided. One with no refinement of the gray scale pixel values (the raw image) but with some rotational adjustments, one with a global equalization of the gray scale pixel values meant to reveal larger trends in the data that can be hidden in low contrast regions, and a third in which local histogram equalization is applied to reveal very localized variations.

Other collage versions are available in electronic files with different cropping width and arrangements of the collage images.

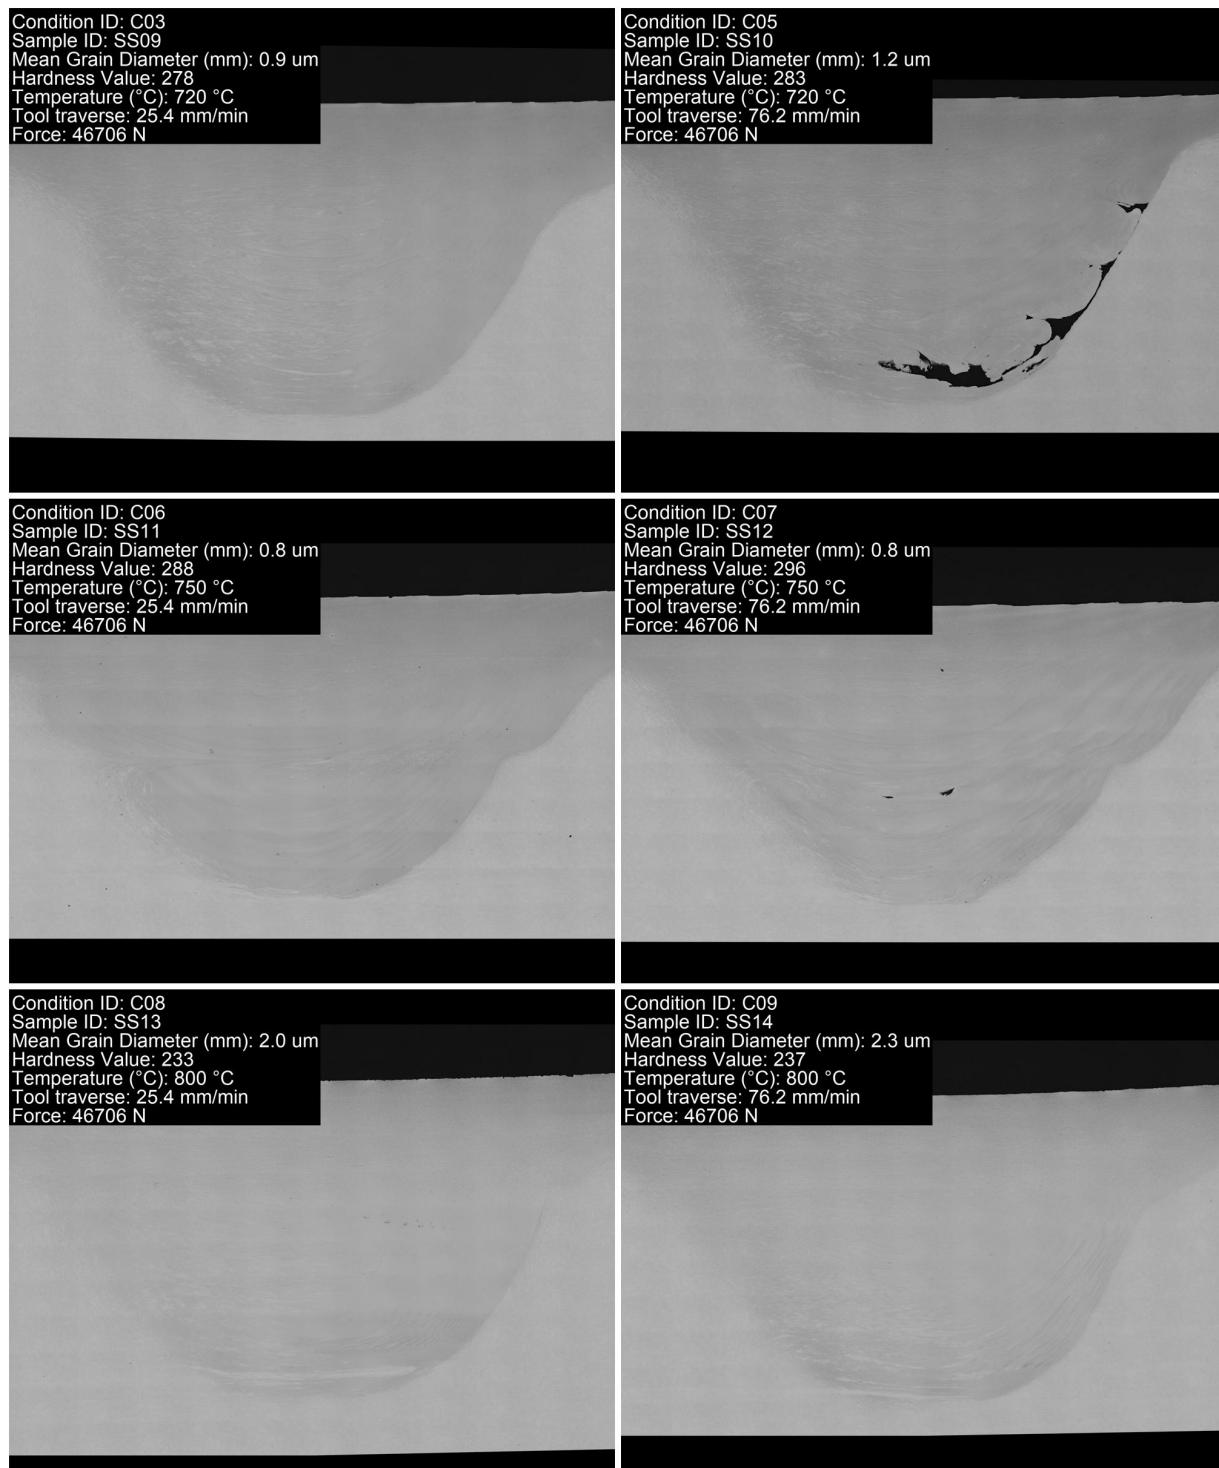


Figure 7.11. Stir Region Collage: Image number 1

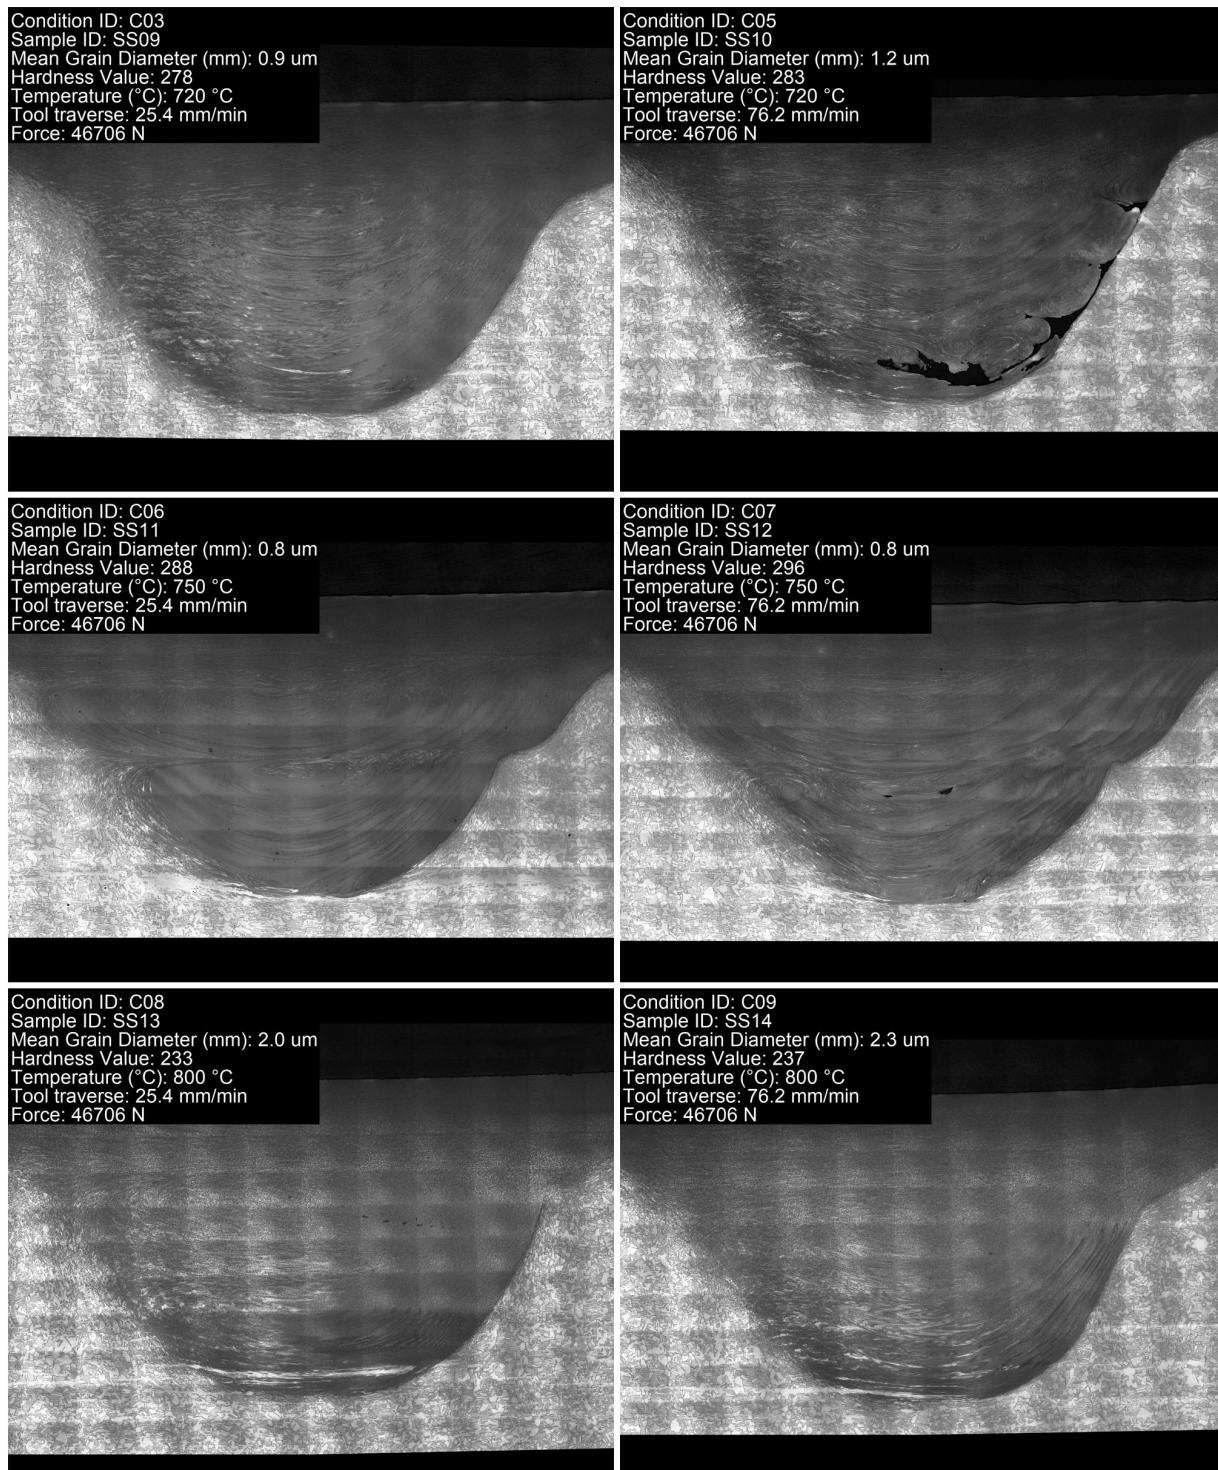


Figure 7.12. Stir Region Collage: Image number 2

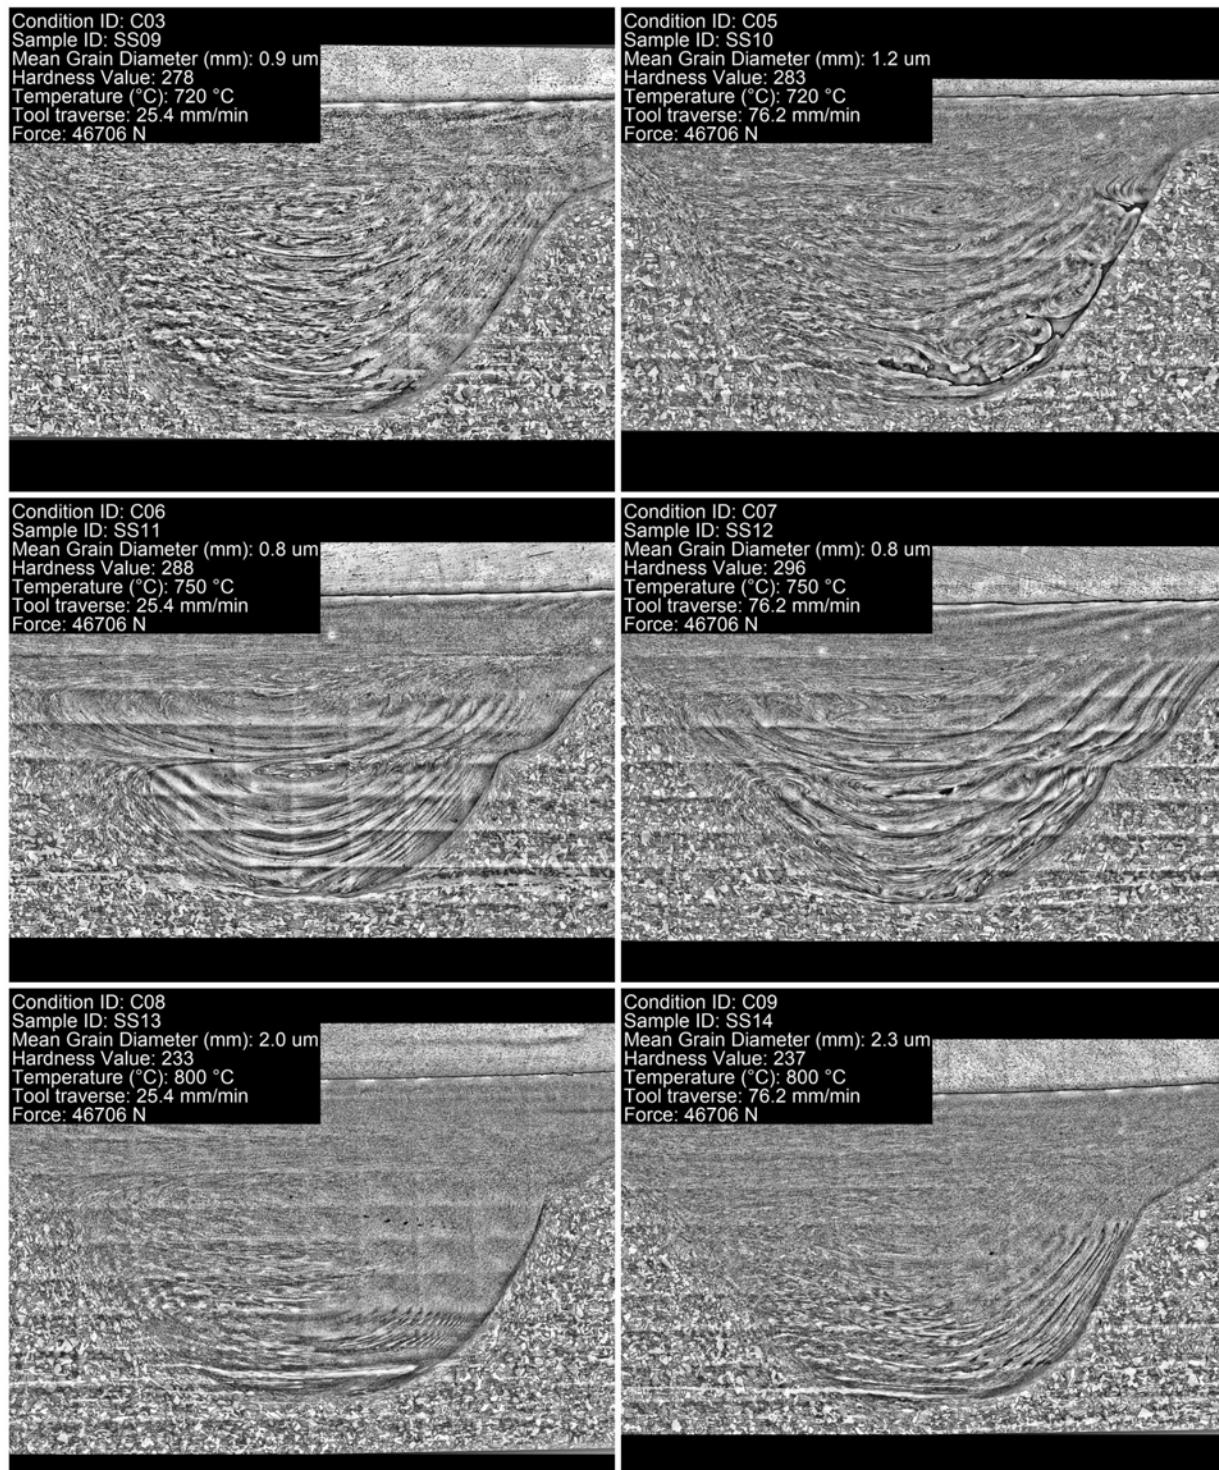


Figure 7.13. Stir Region Collage: Image number 3

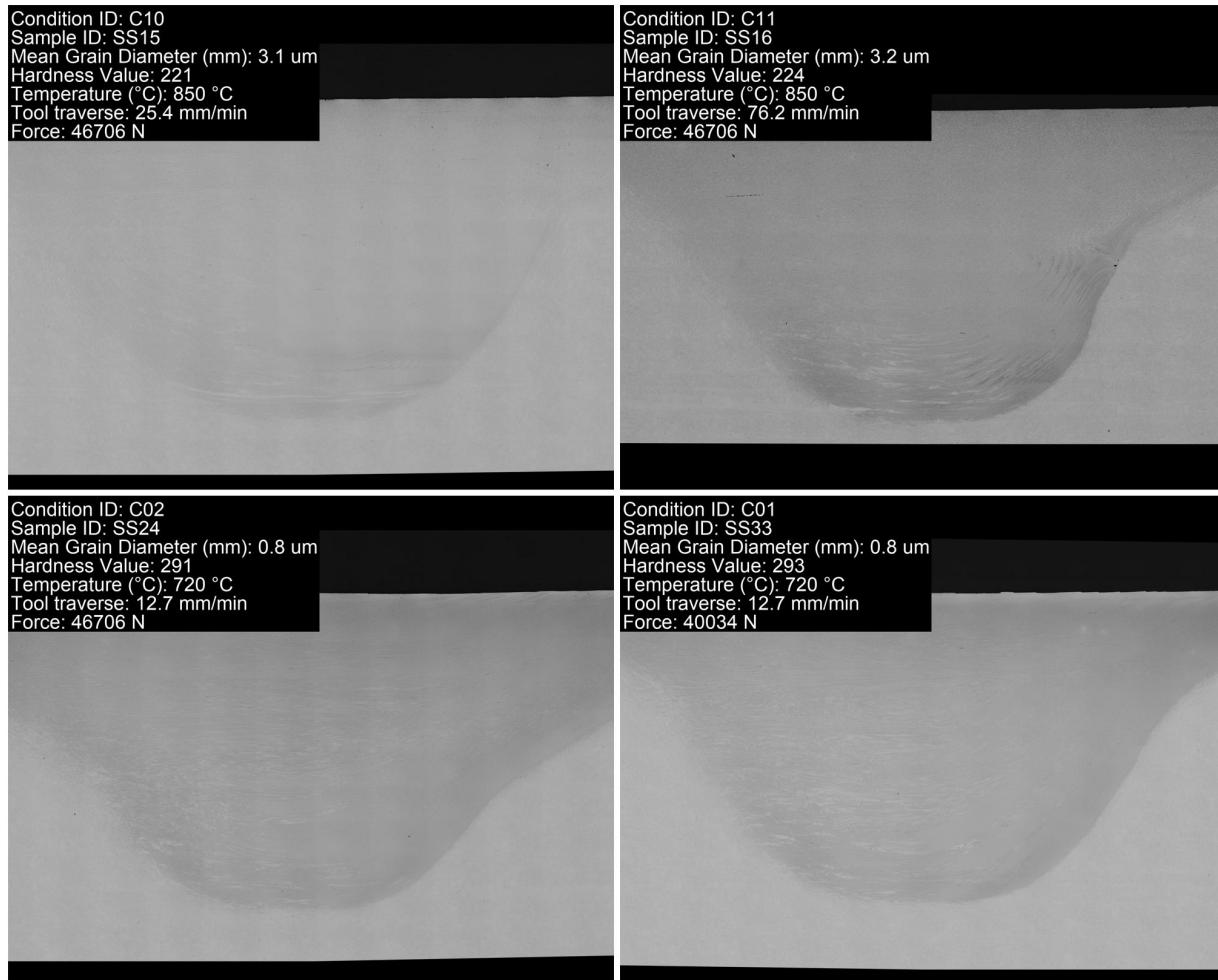


Figure 7.14. Stir Region Collage: Image number 4

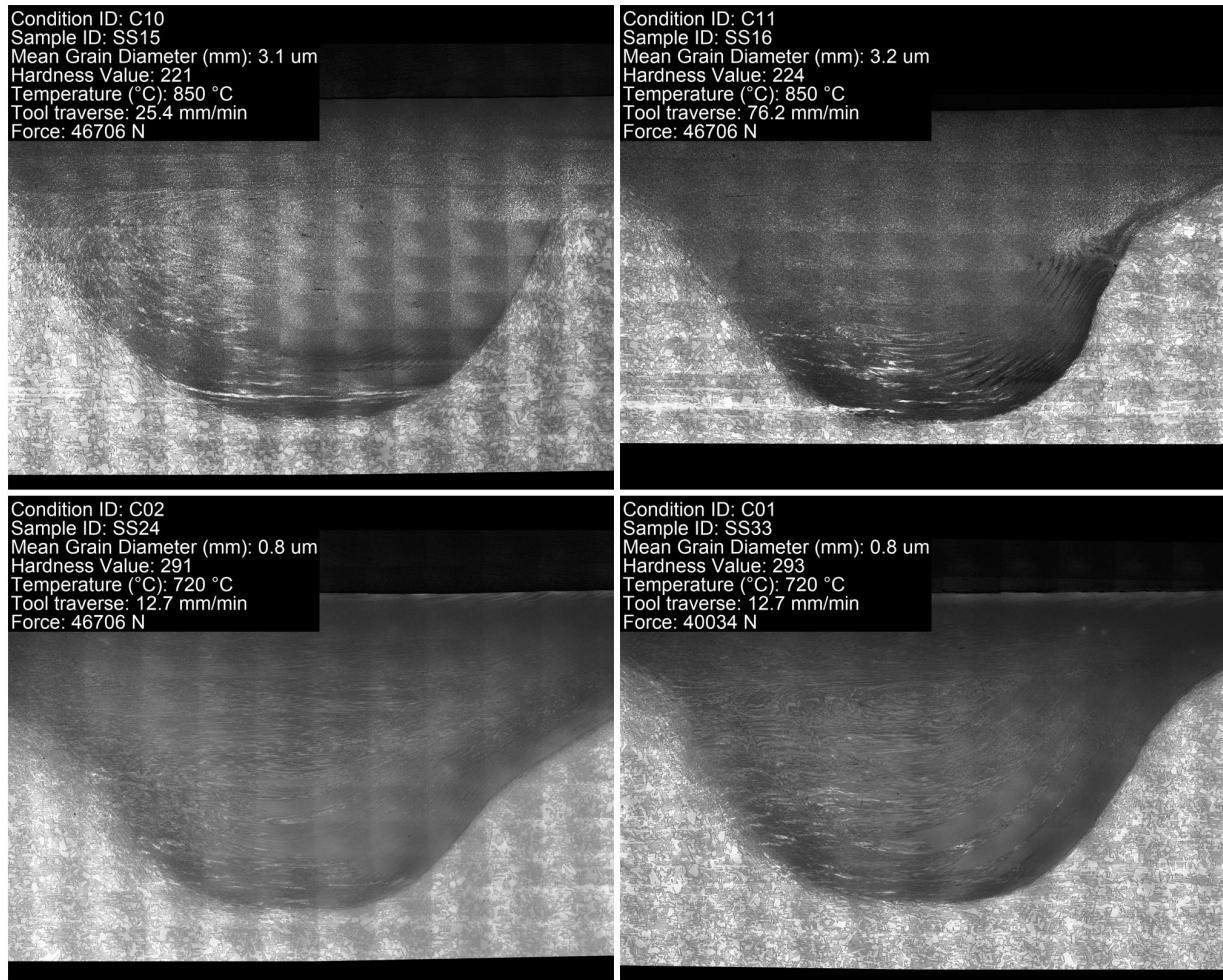


Figure 7.15. Stir Region Collage: Image number 5

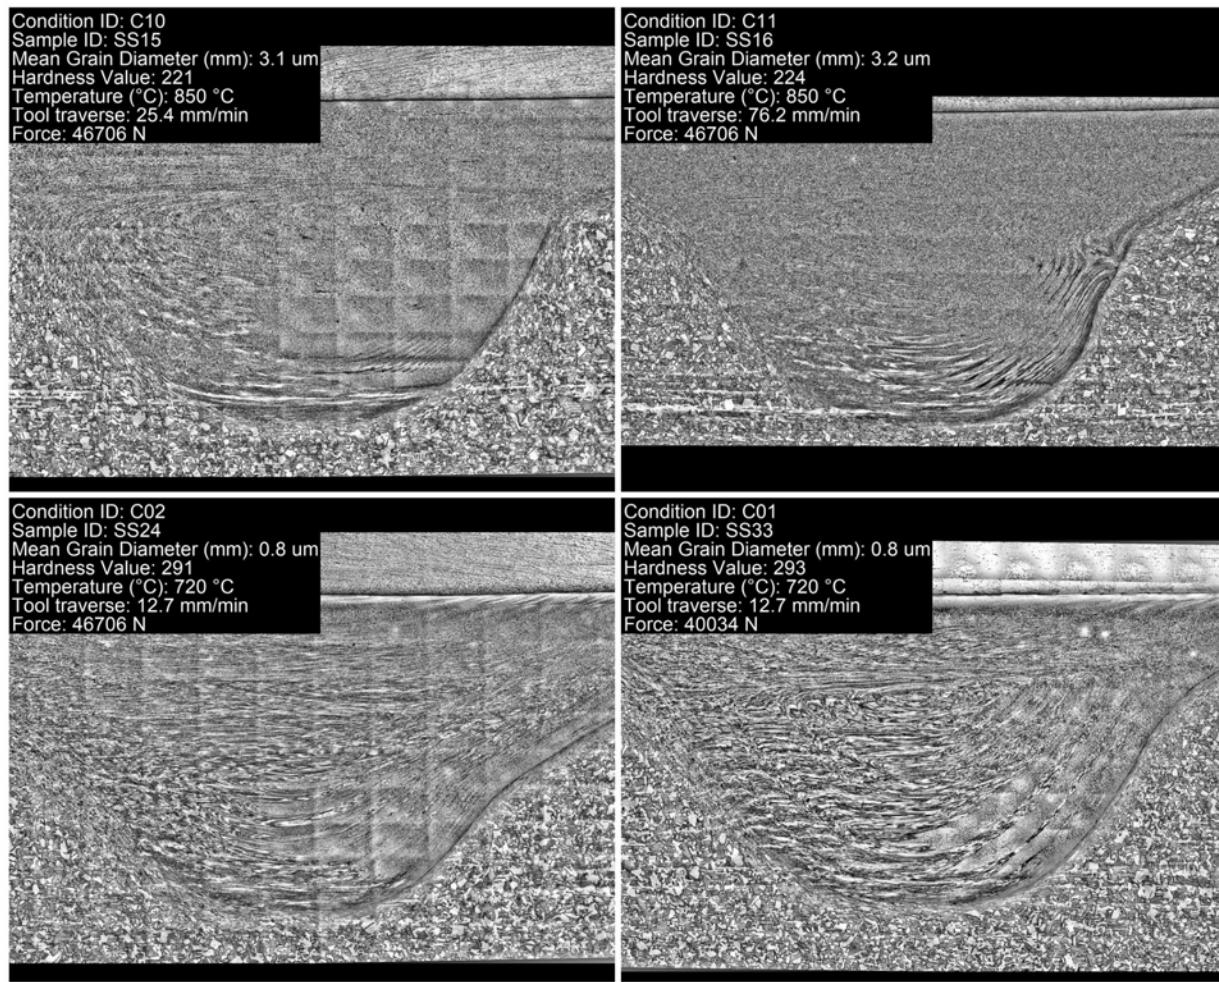


Figure 7.16. Stir Region Collage: Image number 6

Attachment D: MCPC Round 2 Material Characterization Results for Modality SEM

MJ Olszta K Nwe
DR Todd A Guzman

Attachment D contains [32](#) pages

Acknowledgments

This research was supported by the Materials Characterization, Prediction, and Control (MCPC) investment, under the Laboratory Directed Research and Development (LDRD) Program at Pacific Northwest National Laboratory (PNNL). PNNL is a multi-program national laboratory operated for the U.S. Department of Energy (DOE) by Battelle Memorial Institute under Contract No. DE-AC05-76RL01830.

Contents

1	Introduction	5
2	Key Information and Results	6
3	Instrumentation	7
4	Results Files	8
	4.1 DATA Directory Contents	8
	4.2 VISUALIZATION Directory Contents	8
5	Notes and Comments	9
6	Tabular Results	10
7	Graphics	11
	7.1 Stir Region	11
	7.2 Tile Maps	21

Figures

7.1	SEM Montage within Stir Region: Condition C03, Sample SS09	12
7.2	SEM Montage within Stir Region: Condition C05, Sample SS10	13
7.3	SEM Montage within Stir Region: Condition C06, Sample SS11	14
7.4	SEM Montage within Stir Region: Condition C07, Sample SS12	15
7.5	SEM Montage within Stir Region: Condition C08, Sample SS13	16
7.6	SEM Montage within Stir Region: Condition C09, Sample SS14	17
7.7	SEM Montage within Stir Region: Condition C10, Sample SS15	18
7.8	SEM Montage within Stir Region: Condition C11, Sample SS16	19
7.9	SEM Montage within Stir Region: Condition C02, Sample SS24	20
7.10	SEM Montage within Stir Region: Condition C01, Sample SS33	21
7.11	SEM Tile Map: Condition C03, Sample SS09	22
7.12	SEM Tile Map: Condition C05, Sample SS10	23
7.13	SEM Tile Map: Condition C06, Sample SS11	24
7.14	SEM Tile Map: Condition C07, Sample SS12	25
7.15	SEM Tile Map: Condition C08, Sample SS13	26
7.16	SEM Tile Map: Condition C09, Sample SS14	27
7.17	SEM Tile Map: Condition C10, Sample SS15	28
7.18	SEM Tile Map: Condition C11, Sample SS16	29
7.19	SEM Tile Map: Condition C02, Sample SS24	30
7.20	SEM Tile Map: Condition C01, Sample SS33	31

Tables

No Tables are associated with this Attachment

1.0 Introduction

Backscatter Scanning Electron Microscopy (SEM) is a technique that uses accelerated electrons in the primary beam of a scanning electron microscope to diffract atomic layers in crystalline materials. These diffracted electrons can be detected when they impinge on a phosphor screen and generate visible lines

The following sections provide a summary of results for this modality to enhance dissemination of the large volume of similar data that are made available via the PNNL DataHub (<https://data.pnnl.gov>) platform.

2.0 Key Information and Results

The main portion of this report provides a summary of key information related to the modality, including processing conditions, identification information, and the numerical results of most focus in the project. Where to find the information and results in the main report is described below (Section, Table, and Figure numbers listed below are found in the main report). Note that application of SEM did not results in quantitative data, so no tabular or quantitative results are provided in the main report or here for the modality.

- Nominal process conditions for the FSP experiments are defined in Table 1 and Table 3 (data is in two different sorting orders).
- The Condition, Sample, and Specimen ID matrix is defined in Table 2 that is necessary to decode the nominal conditions applied to a particular specimen.
- Details about the modality data collection approach is defined in Section 4.0. This includes information about magnification levels for SEM.

3.0 Instrumentation

The following instrument was utilized in testing of specimens:

Thermoscientific Helios Hydra UX, Plamsa Focused Ion Beam microscope

4.0 Results Files

4.1 DATA Directory Contents

Data files obtained for each dataset from the instrumentation are saved in the associated DATA directory. For SEM, the key data file is a montage image provided in TIF file format that highlights all information obtained for the dataset. Additionally, the individual tiles obtained by the instrument and used to construct the montage are provided for use in machine learning analysis.

- **(name).tif** (TIF Image type): The montage SEM image. Tiles are stitched and rotated by proprietary software to produce the montage.
- **(name)_Tile-nnnn.tif** (TIF Image type, nnnn is a unique four digit tile number): The individual tiles obtained by the instrument and used to construct the montage. These tiles are added to the montage by moving from the bottom left corner of the montage to the upper right. Enumeration of the tiles may not start at zero or one.

4.2 VISUALIZATION Directory Contents

The following visualizations are provided:

- **(name)_Tile-map.jpg** (JPG Image type): A reconstructed map of the tile locations in the montage. Tile boundaries and tile numbers are indicated to assist in finding specific SEM tiles in the DATA directory. This image is intended as an aide and not for computational analysis, so it is reduced size and in JPG format.

5.0 Notes and Comments

The following observations are made about data and files for this modality:

1. None

6.0 Tabular Results

No tabular results are available for this modality.

7.0 Graphics

The following sub sections display key graphics for convenience:

7.1 Stir Region

Measurements with SEM were performed on focused a 0.5mmx0.5mm location within the stir region to resolve individual grains within the FSP-affected region. Results are provided below in a montaged image constructed of individual image tiles.

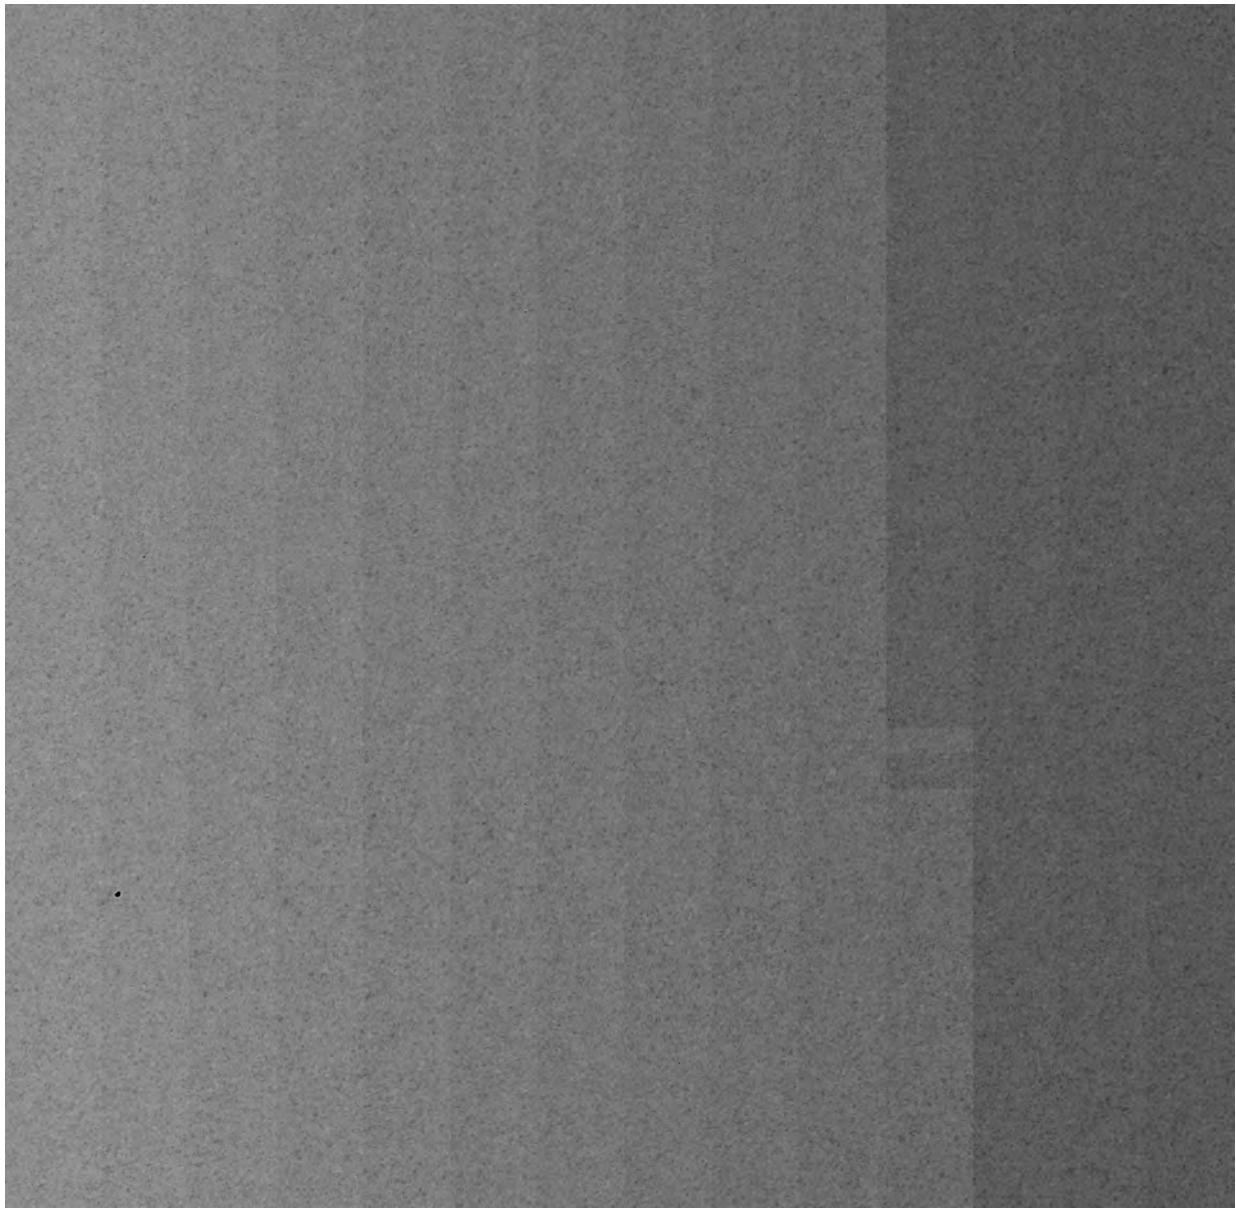


Figure 7.1. SEM Montage within Stir Region: Condition C03, Sample SS09

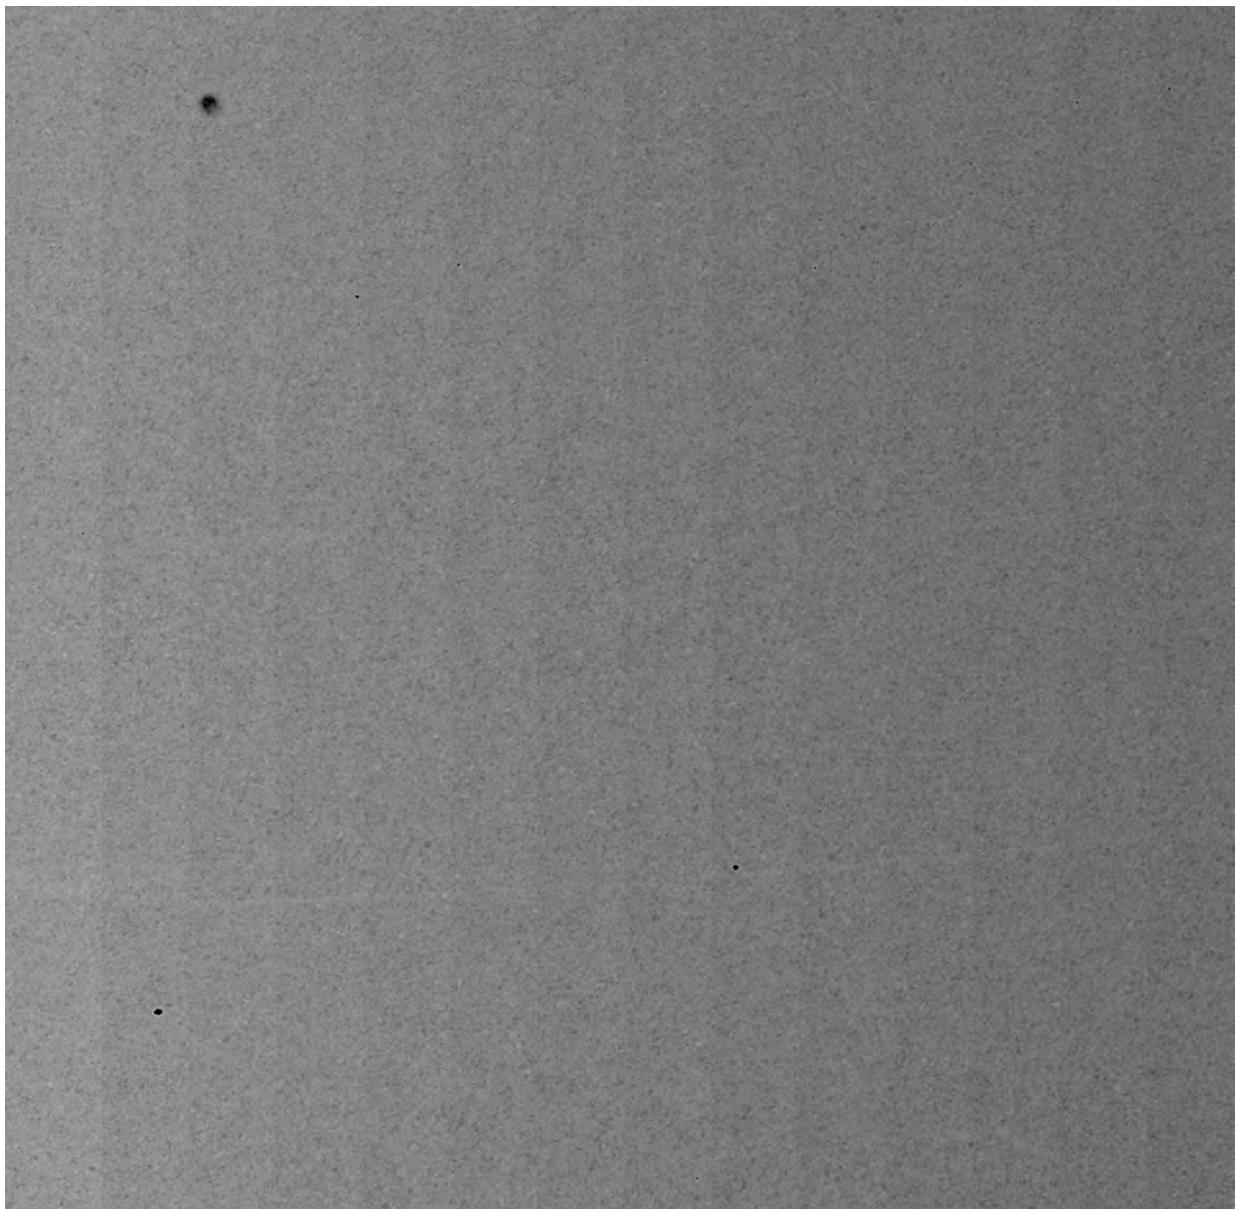


Figure 7.2. SEM Montage within Stir Region: Condition C05, Sample SS10



Figure 7.3. SEM Montage within Stir Region: Condition C06, Sample SS11

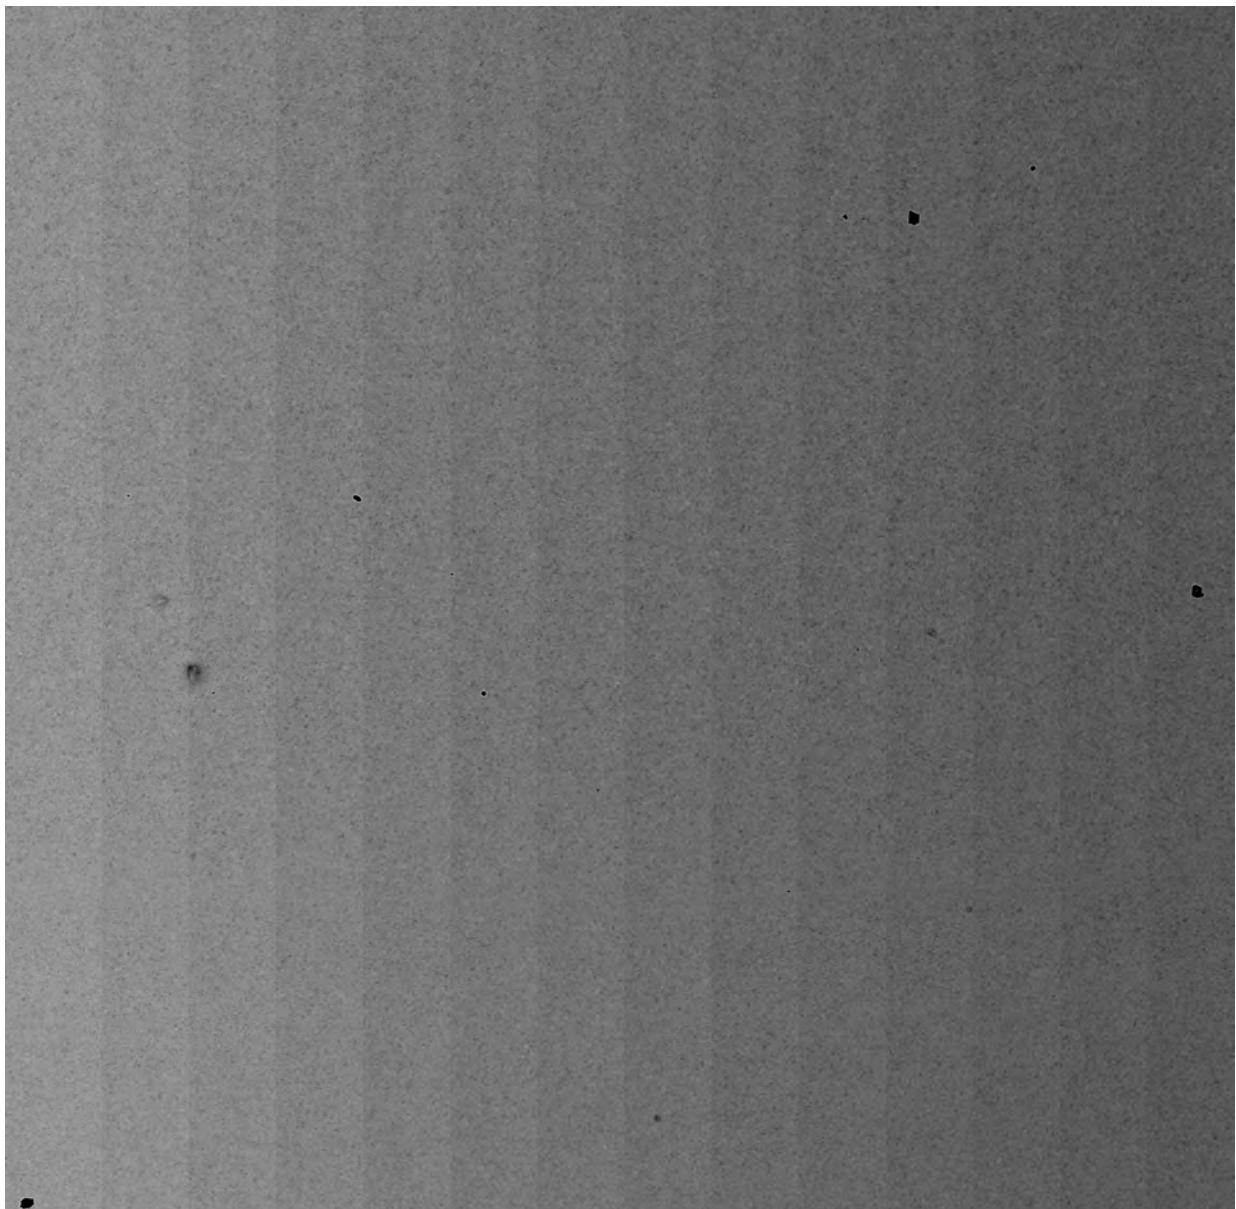


Figure 7.4. SEM Montage within Stir Region: Condition C07, Sample SS12

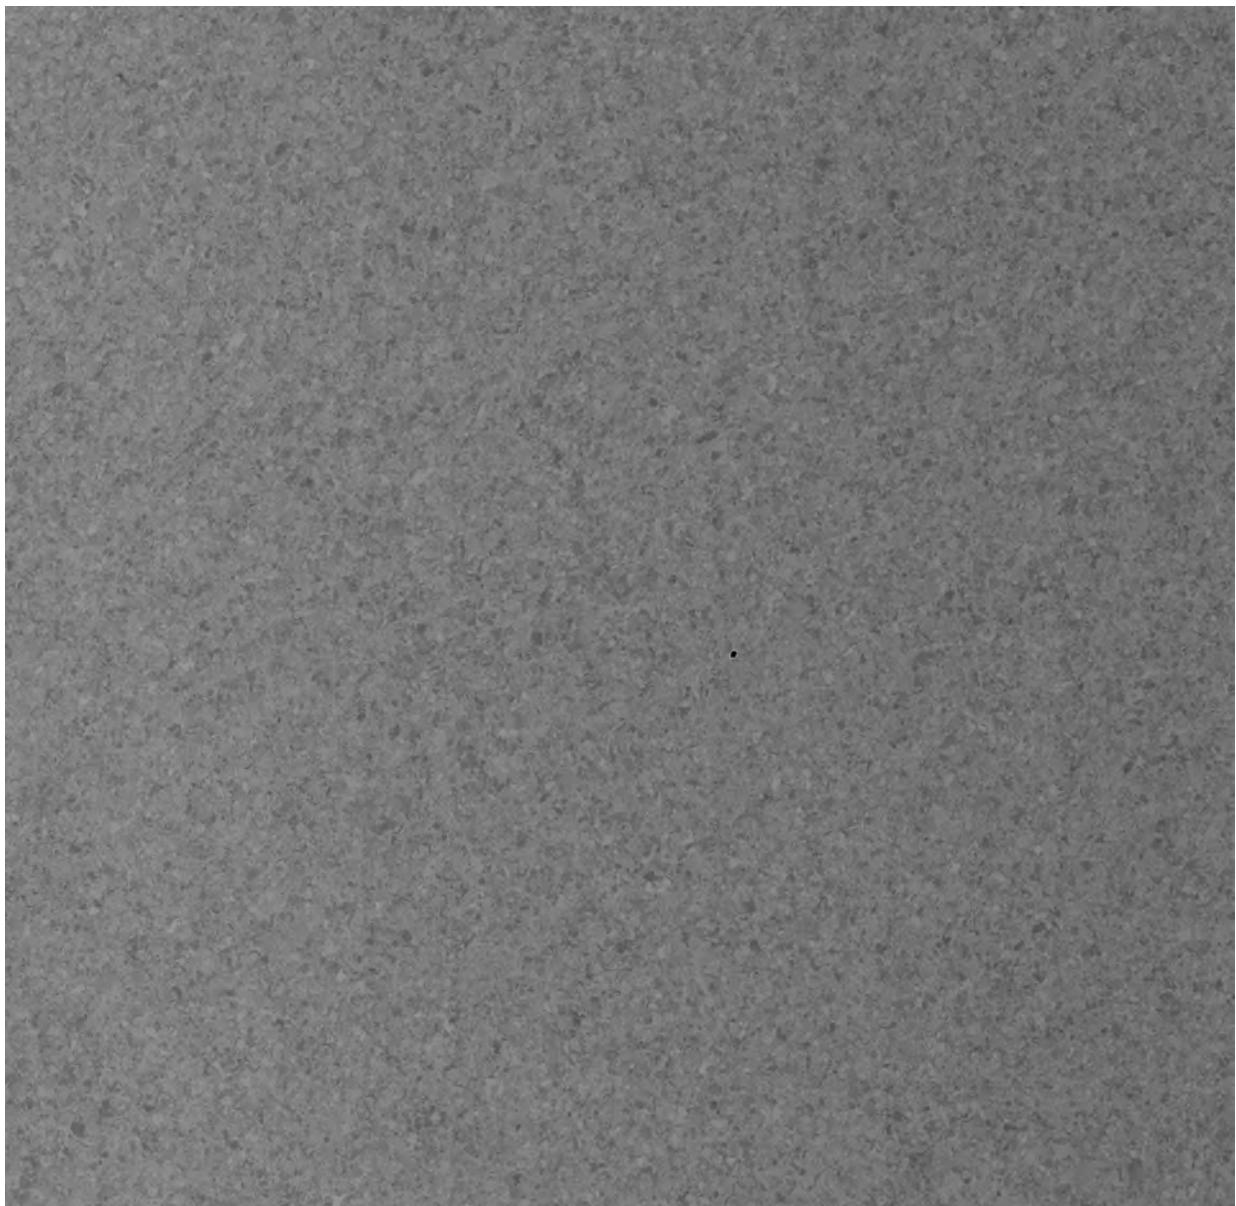


Figure 7.5. SEM Montage within Stir Region: Condition C08, Sample SS13

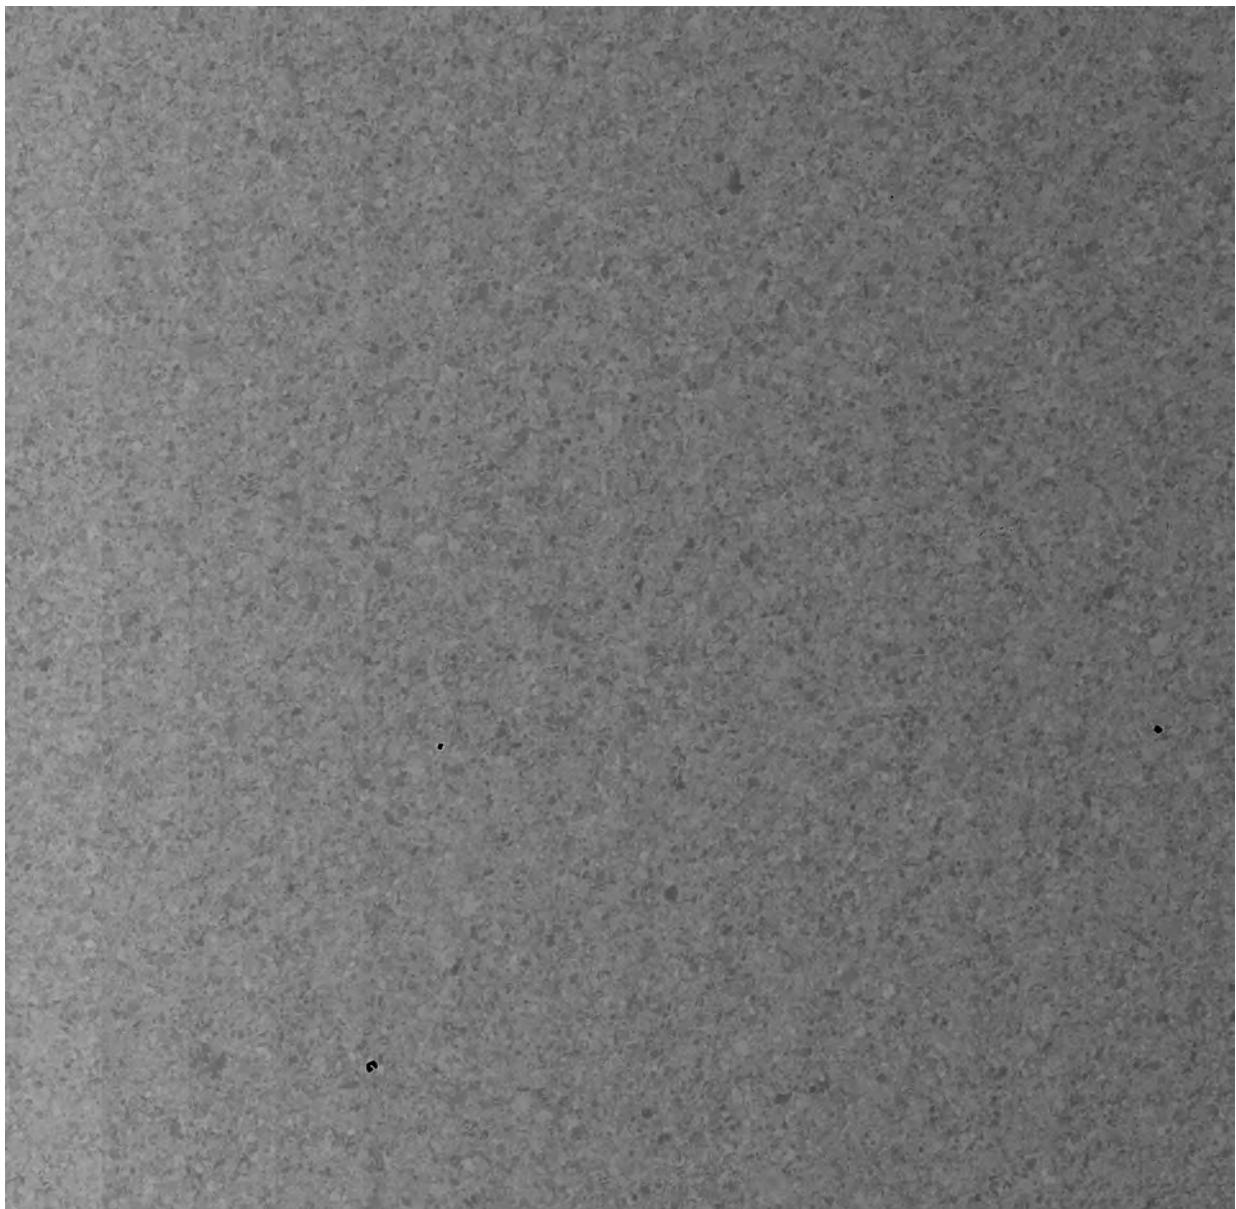


Figure 7.6. SEM Montage within Stir Region: Condition C09, Sample SS14

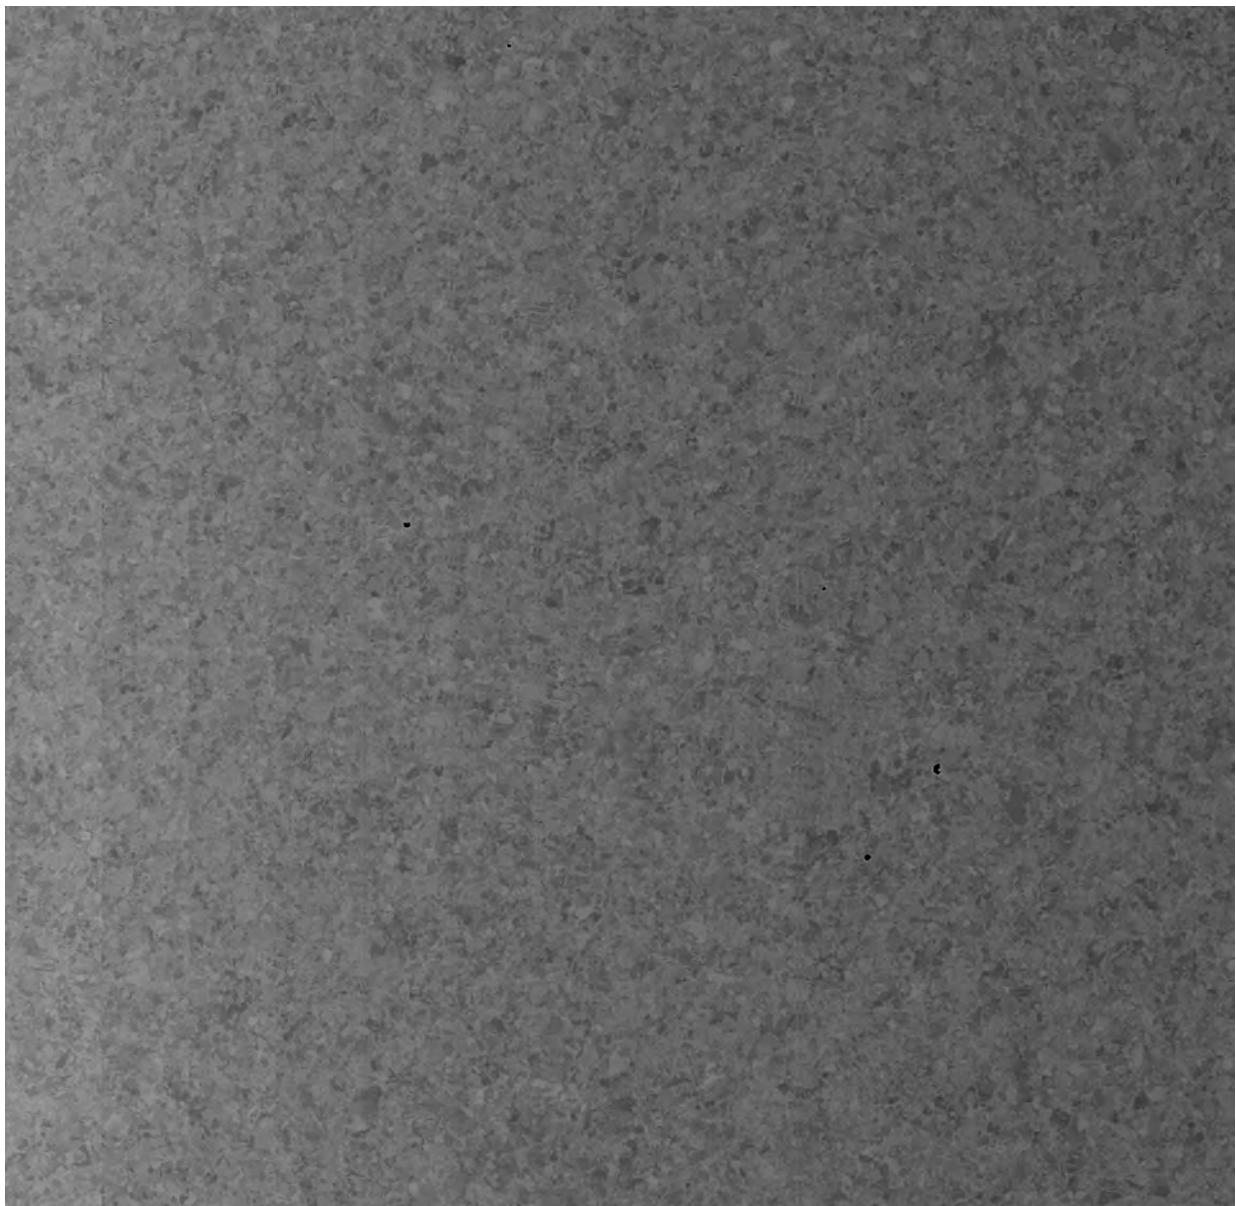


Figure 7.7. SEM Montage within Stir Region: Condition C10, Sample SS15

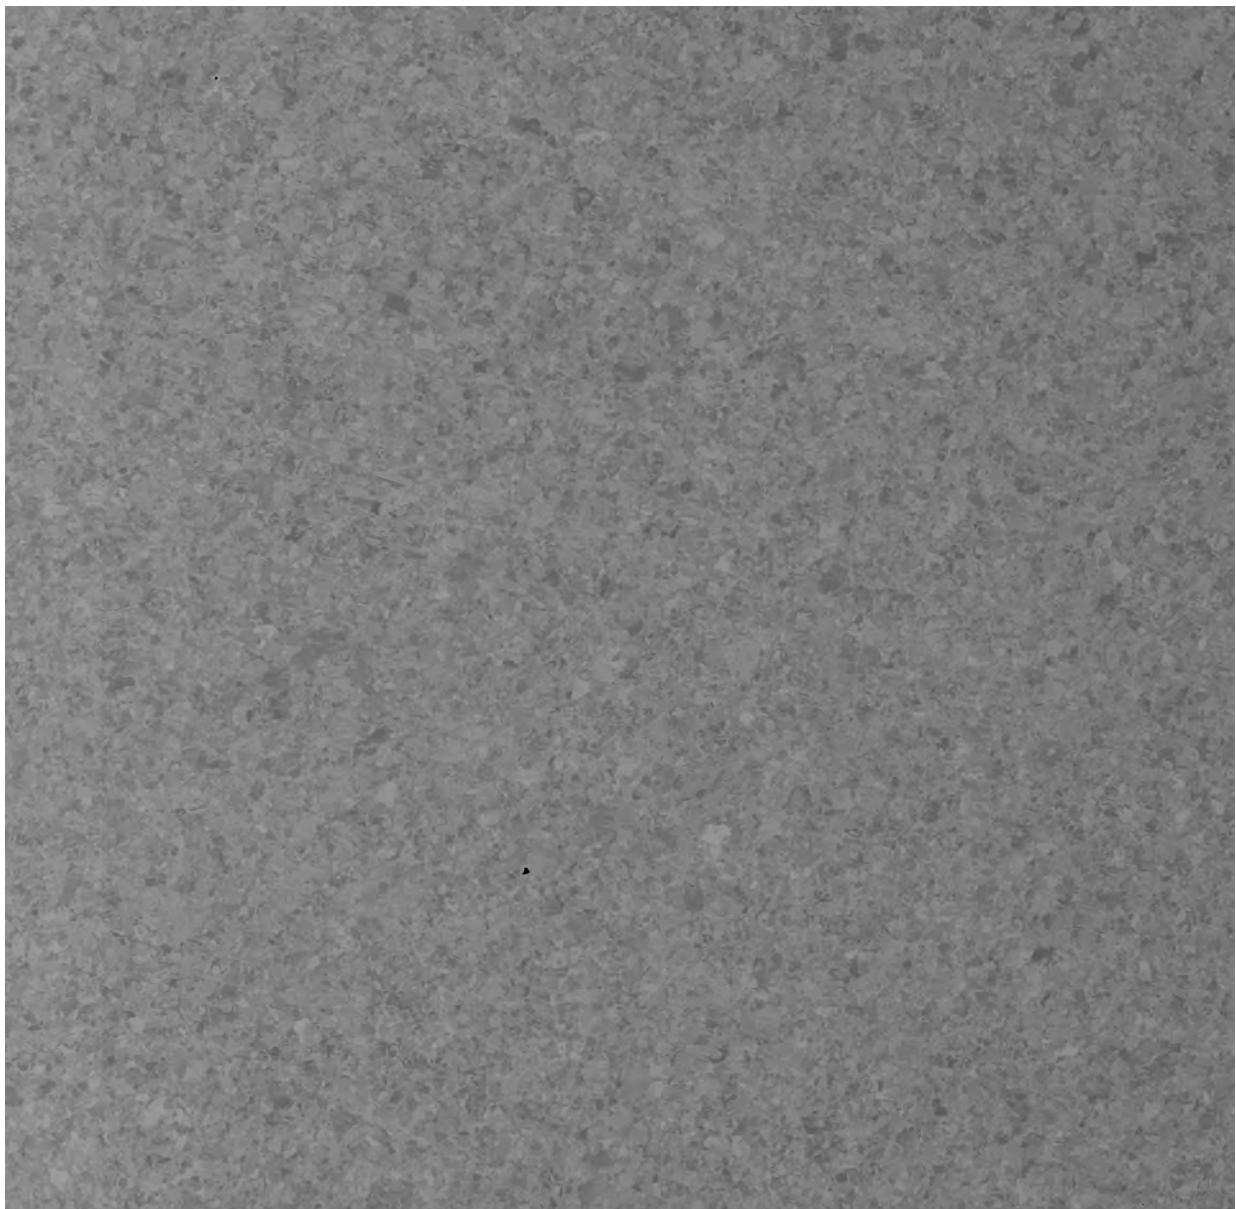


Figure 7.8. SEM Montage within Stir Region: Condition C11, Sample SS16

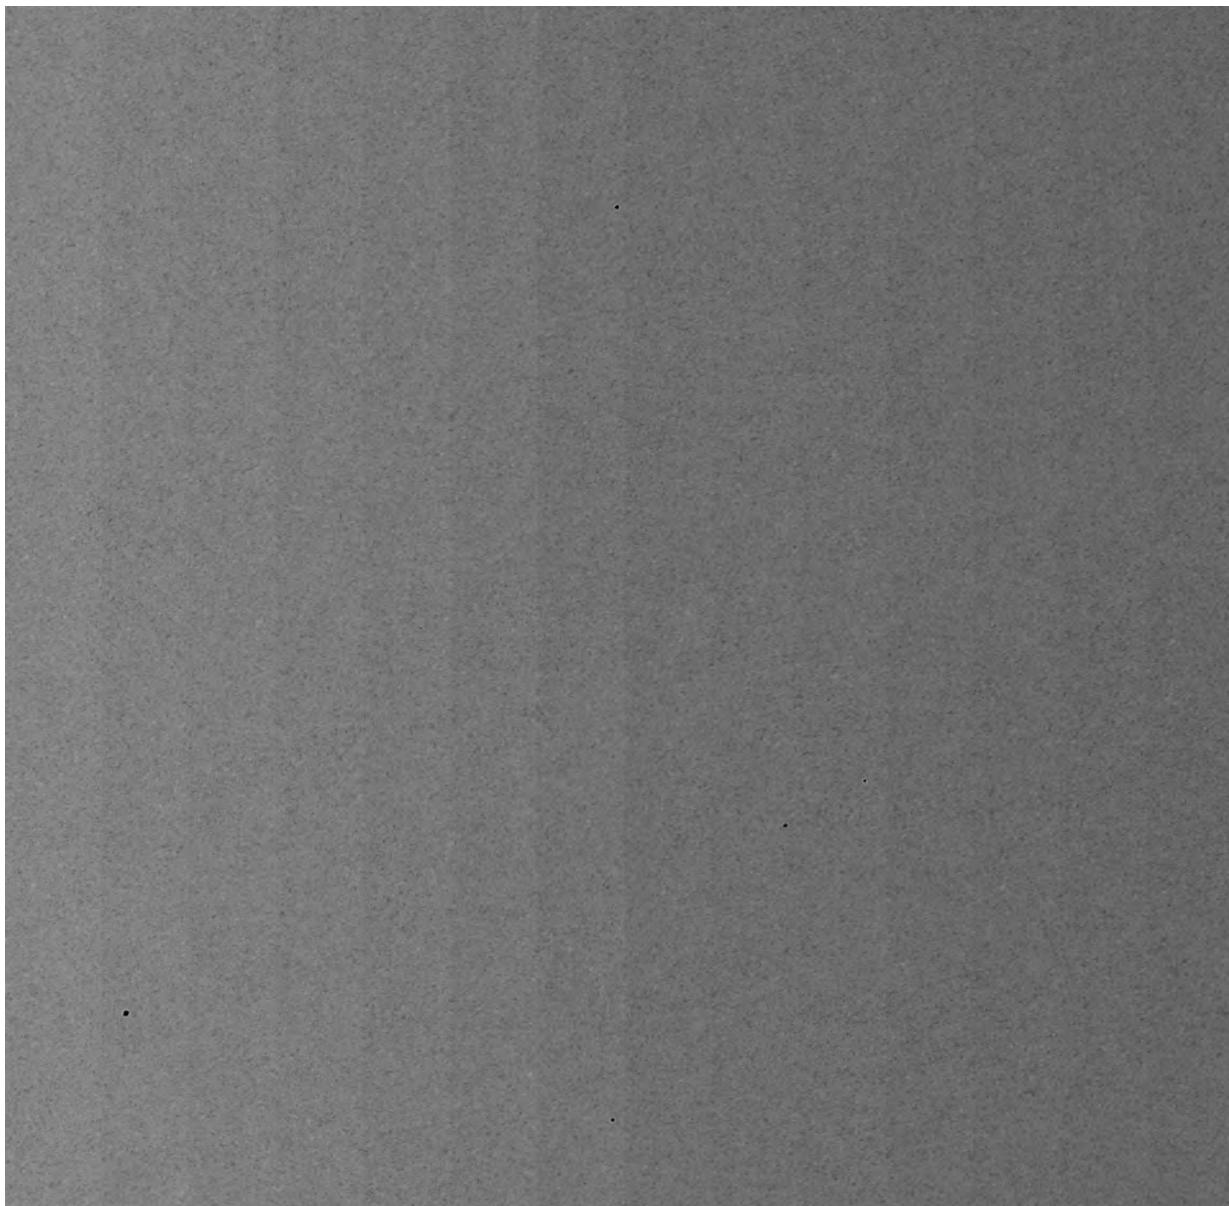


Figure 7.9. SEM Montage within Stir Region: Condition C02, Sample SS24

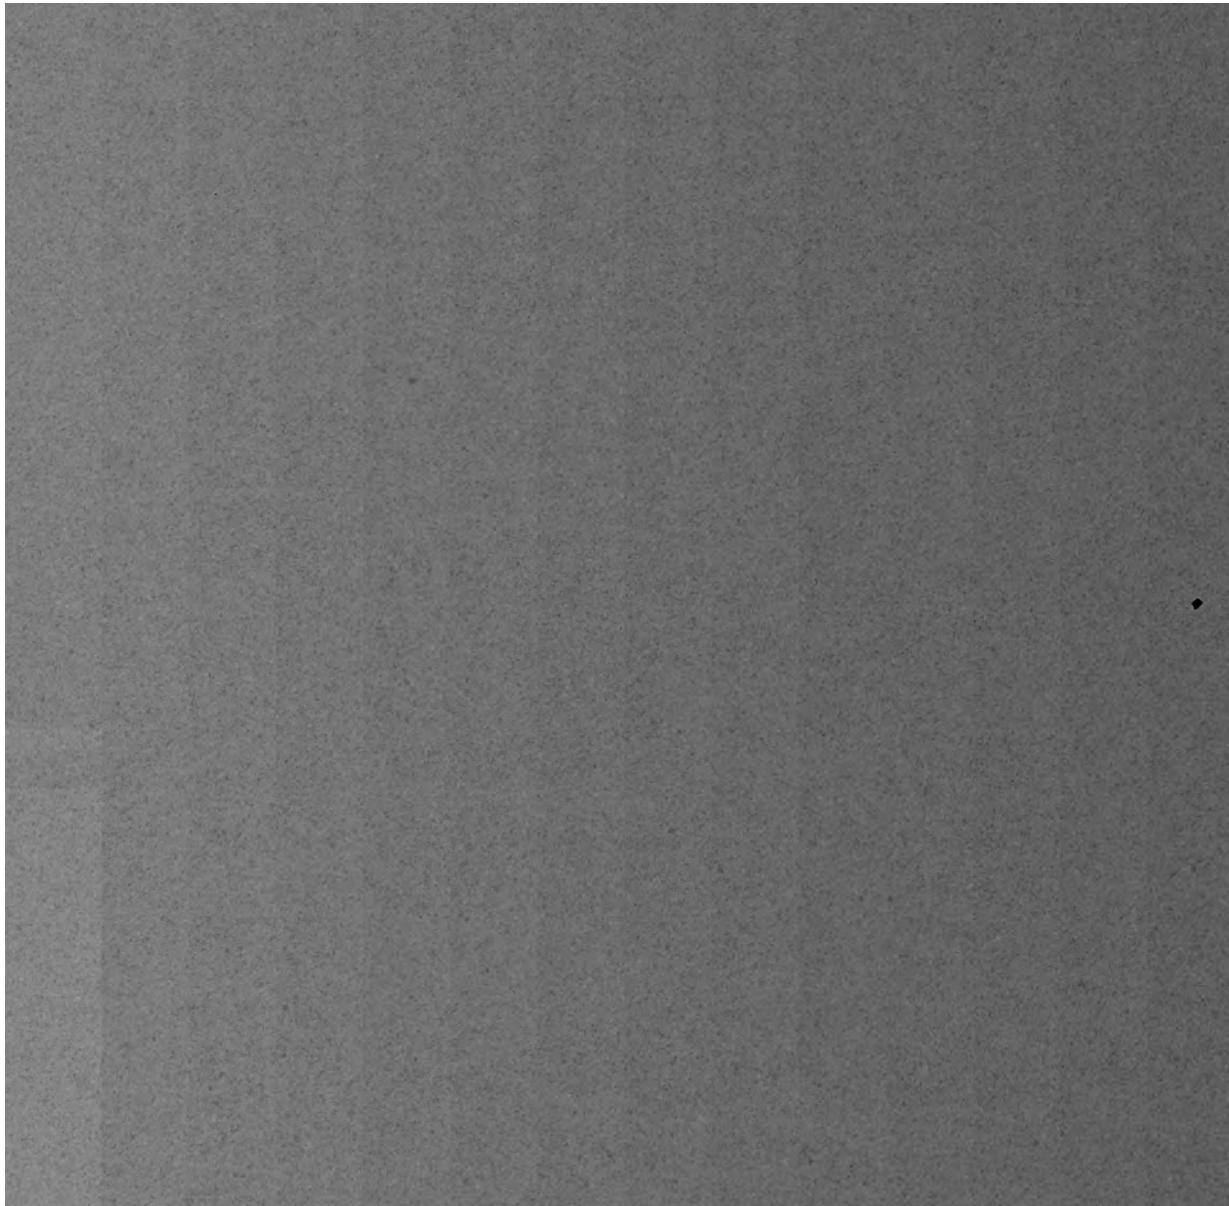


Figure 7.10. SEM Montage within Stir Region: Condition C01, Sample SS33

7.2 Tile Maps

The image montages in the last section were constructed from individual SEM collections. In general, ordering of the SEM tiles proceeded from the lower left hand corner of the montage. But not necessarily from zero or one. Results are provided below that show the reconstructed tile locations in each montage with blue numbers corresponding to the tile numbers. The numerical labels in these images are small. Either zoom in on the figure or refer to the archived numbers associated with nnnn in archived files.

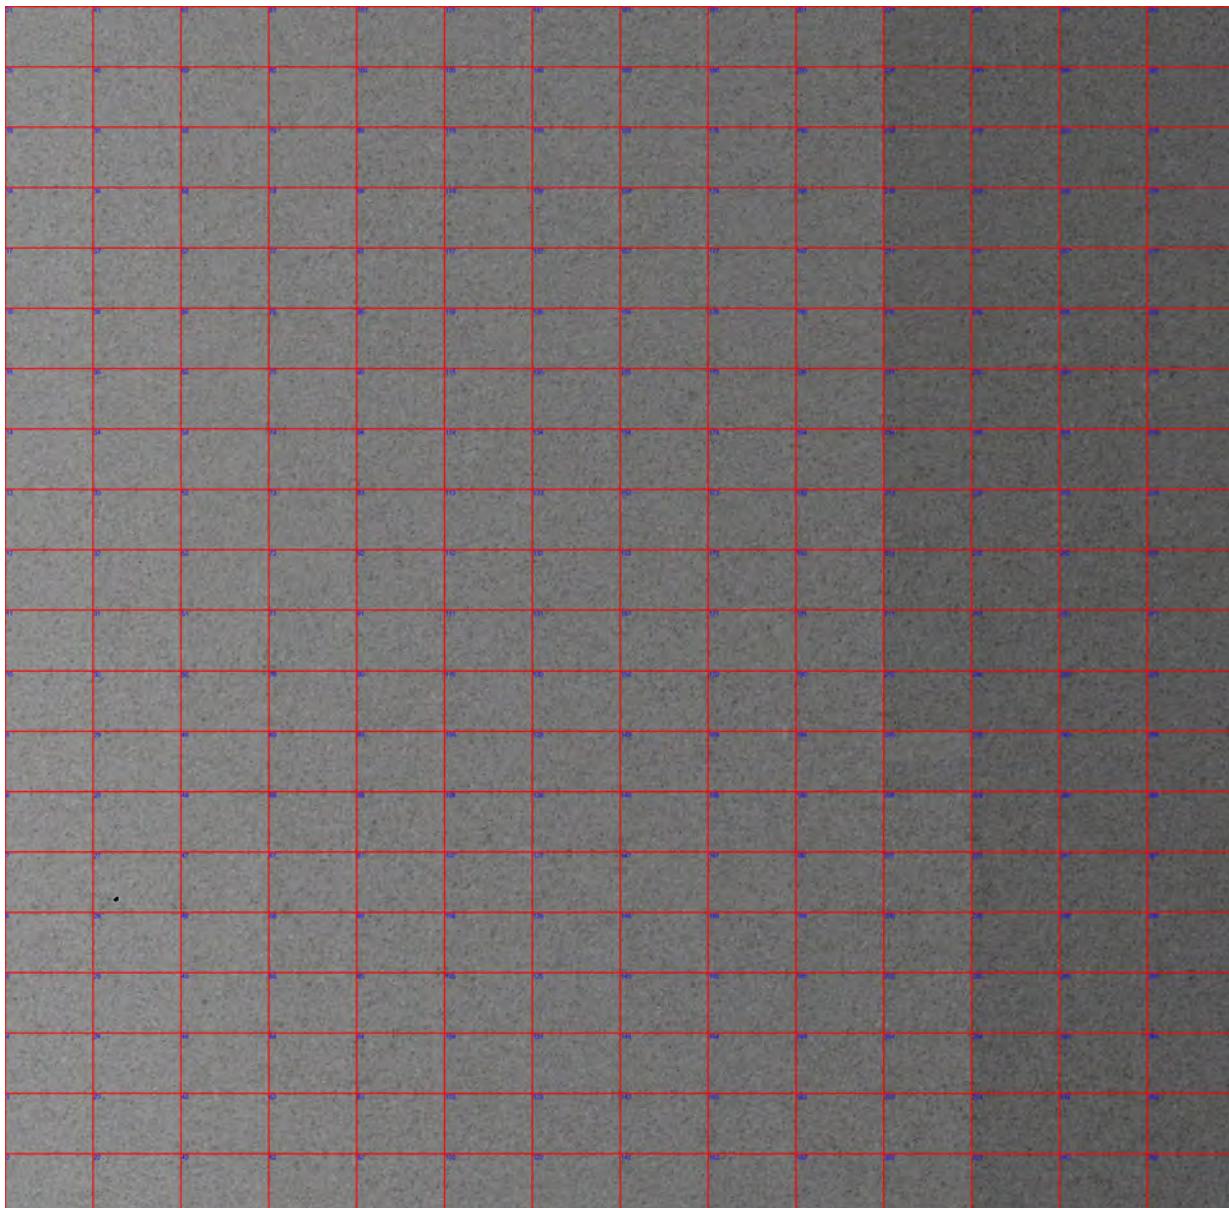


Figure 7.11. SEM Tile Map: Condition C03, Sample SS09

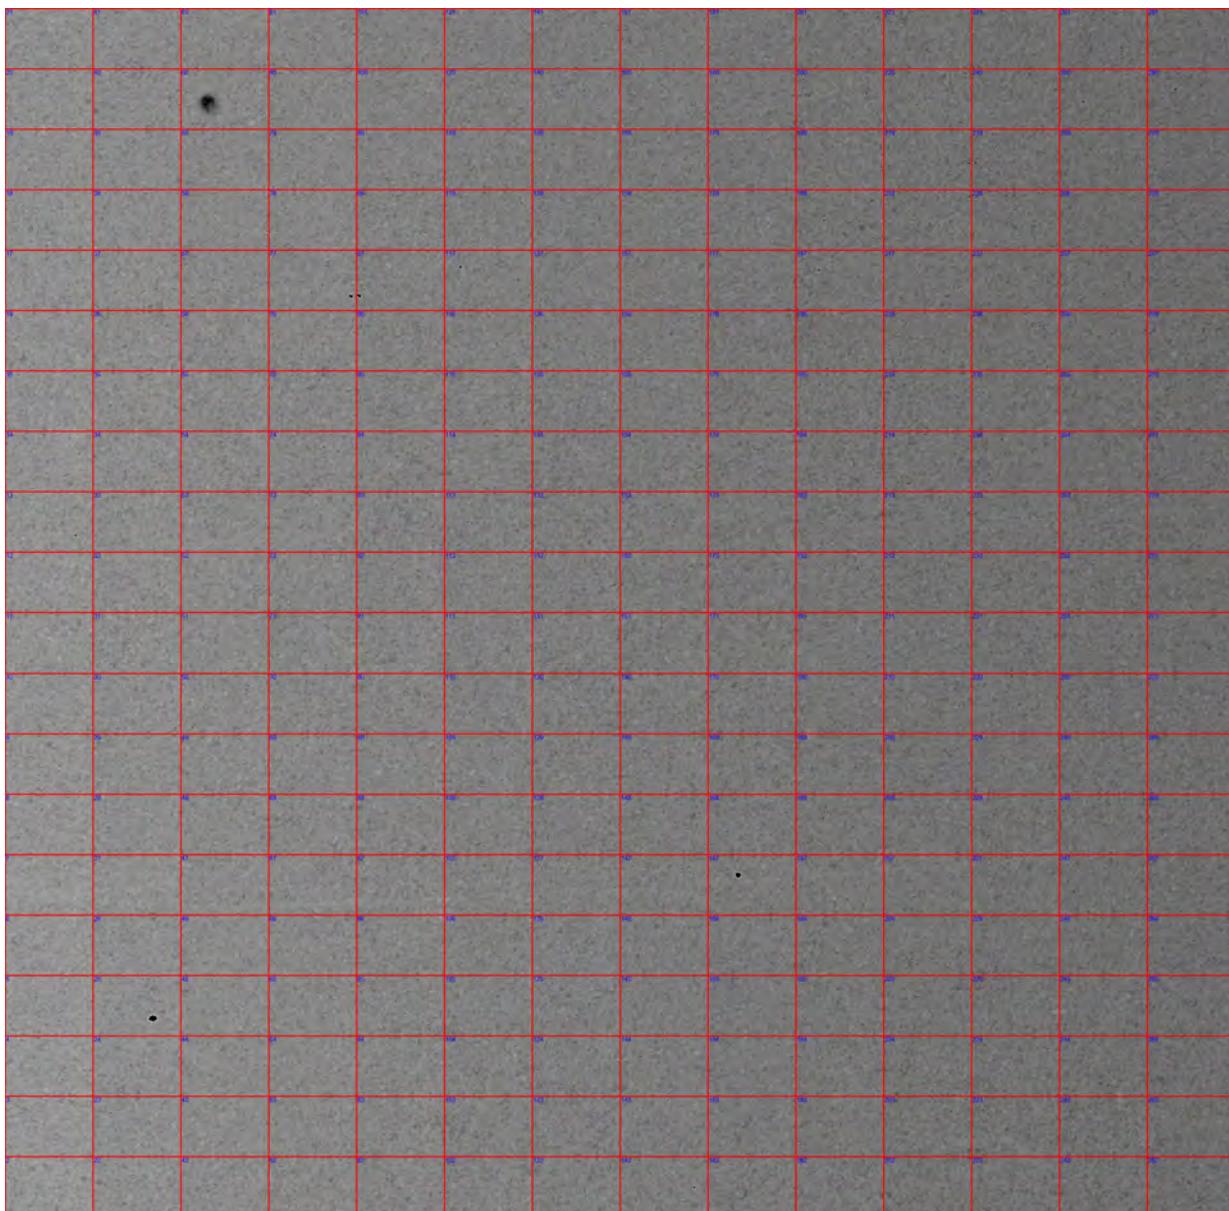


Figure 7.12. SEM Tile Map: Condition C05, Sample SS10

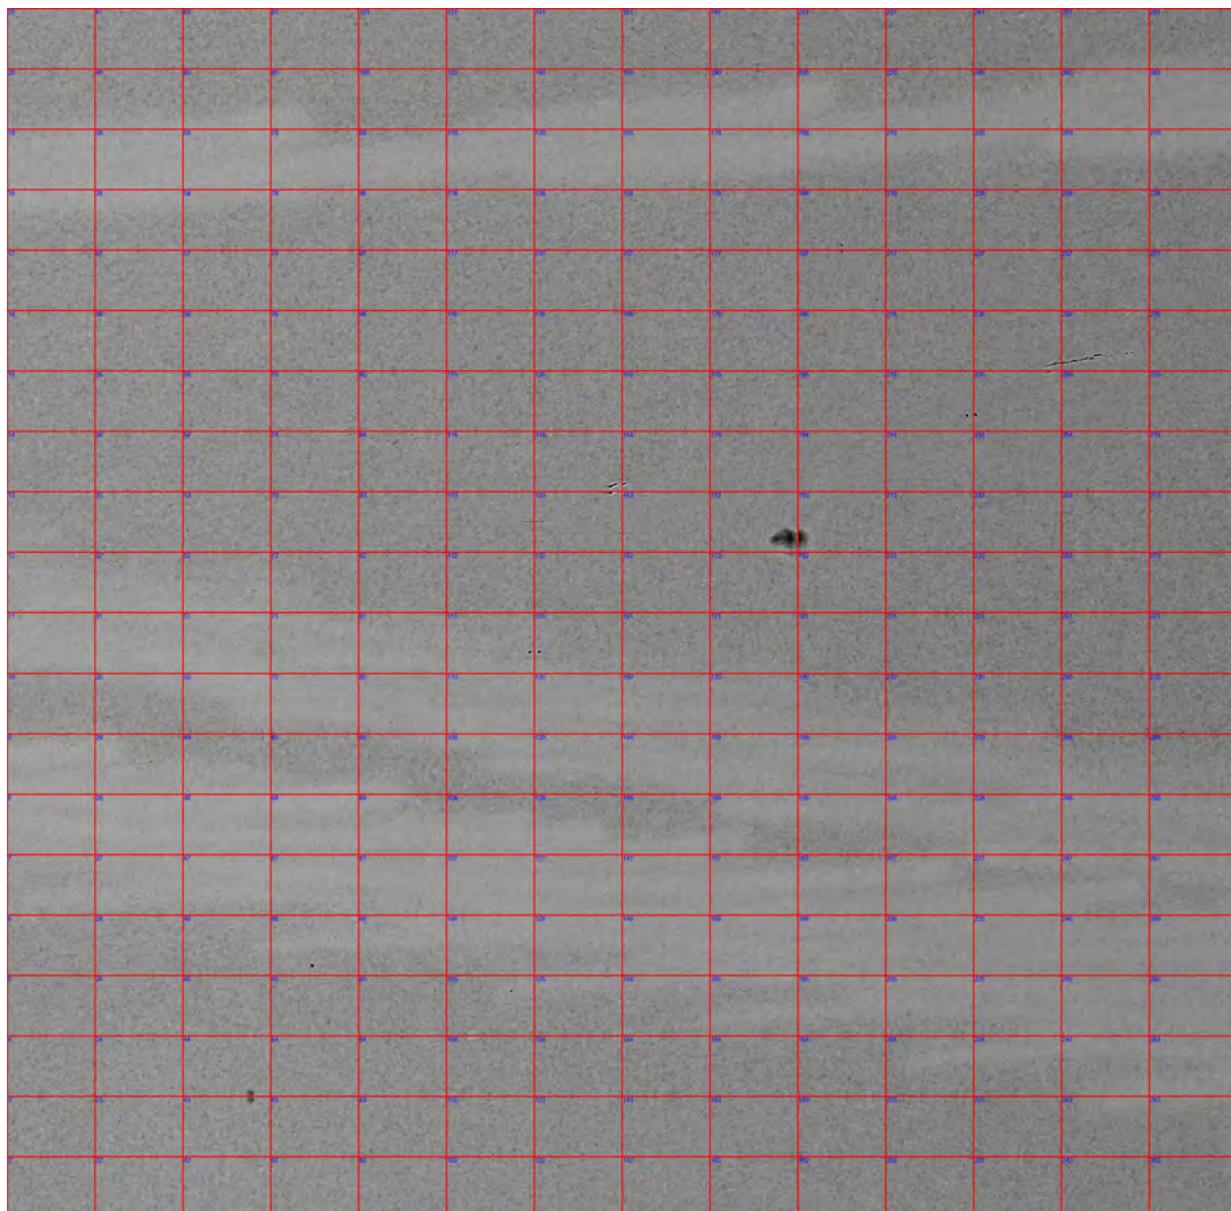


Figure 7.13. SEM Tile Map: Condition C06, Sample SS11

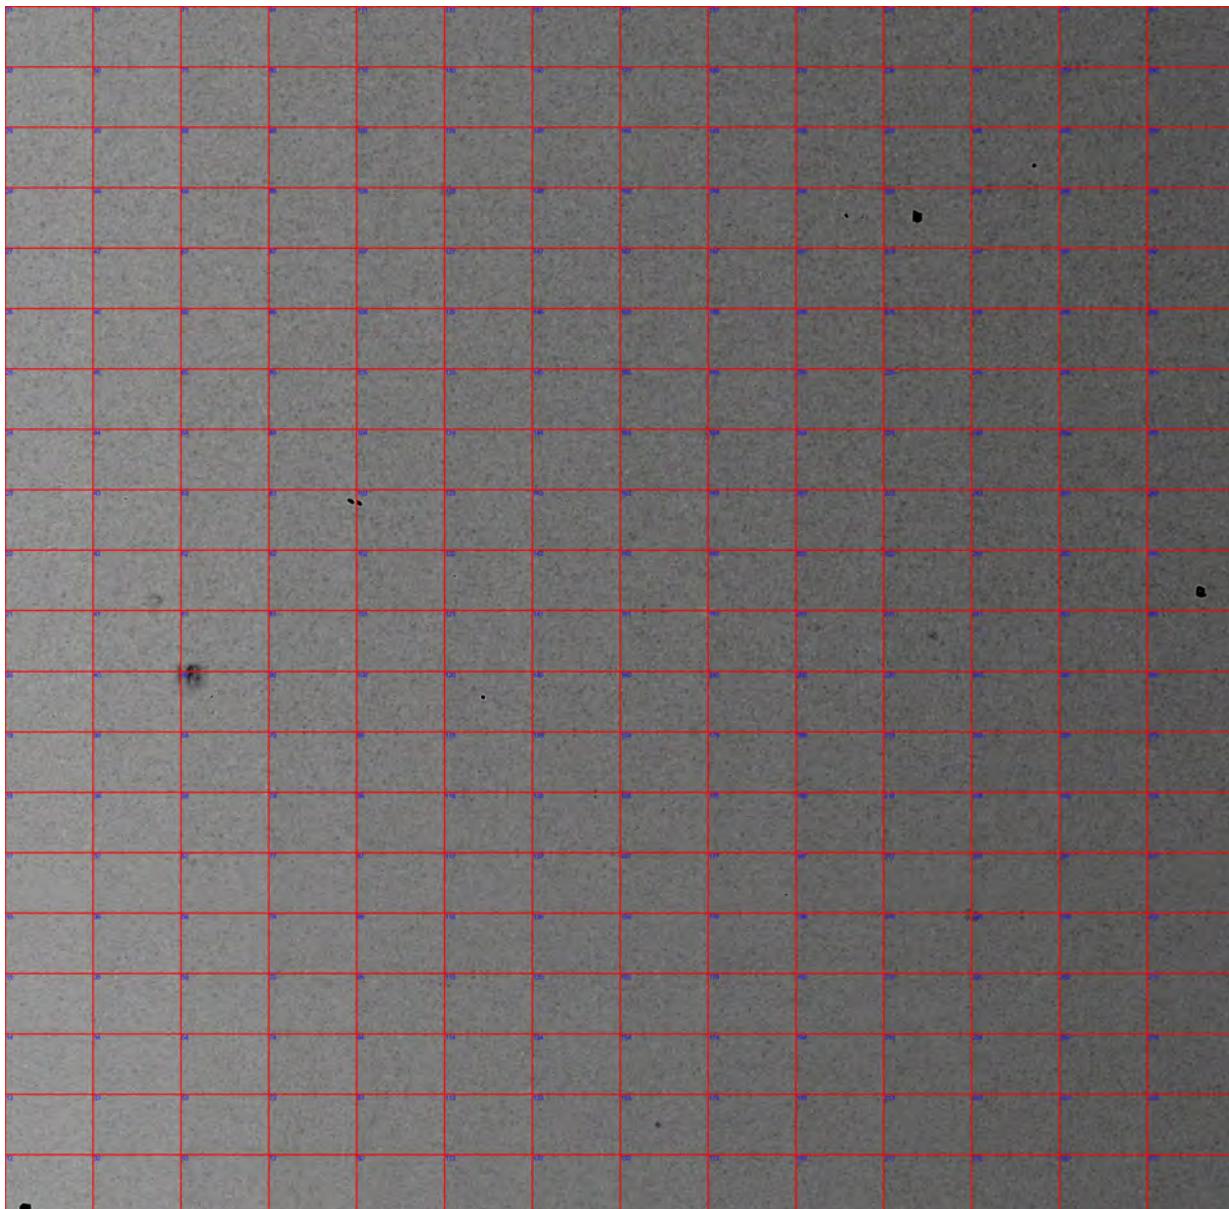


Figure 7.14. SEM Tile Map: Condition C07, Sample SS12

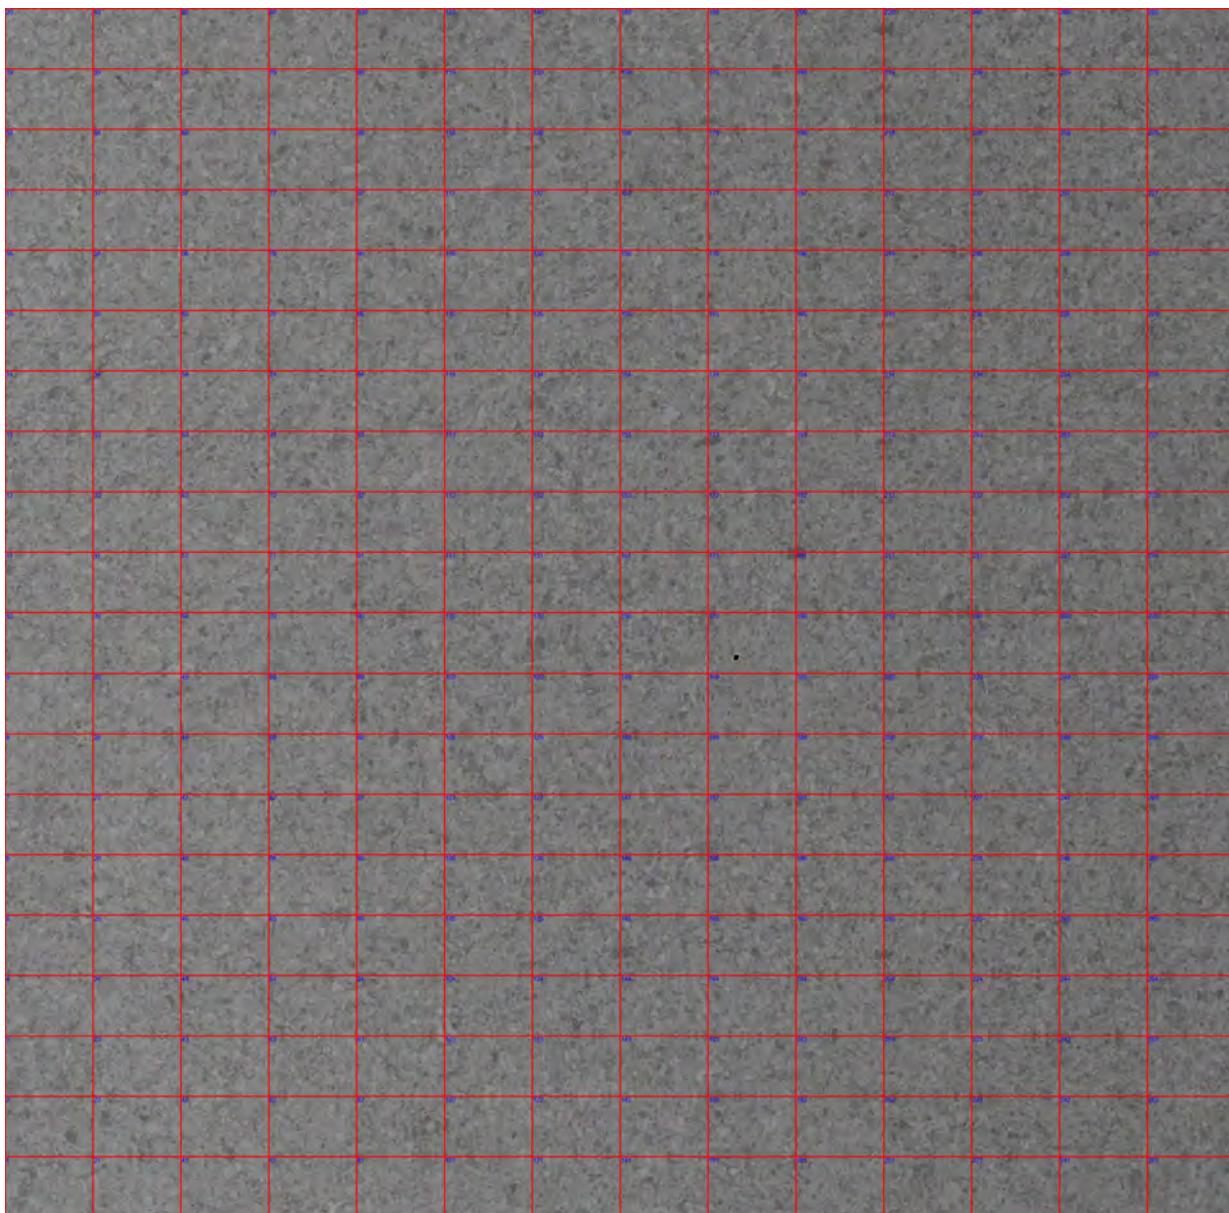


Figure 7.15. SEM Tile Map: Condition C08, Sample SS13

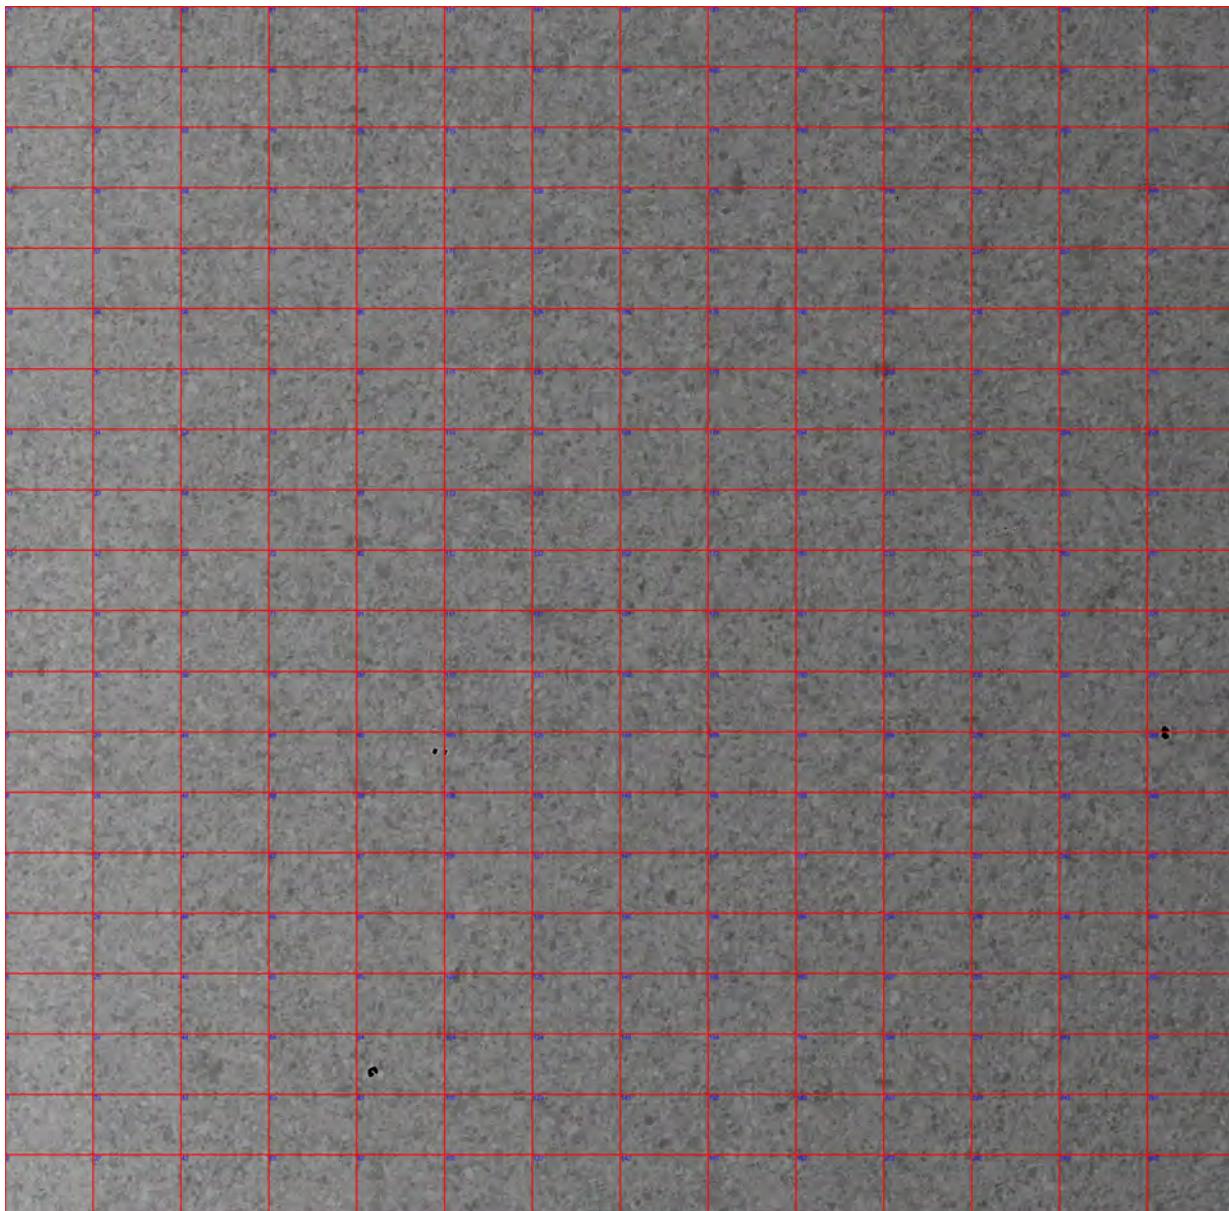


Figure 7.16. SEM Tile Map: Condition C09, Sample SS14

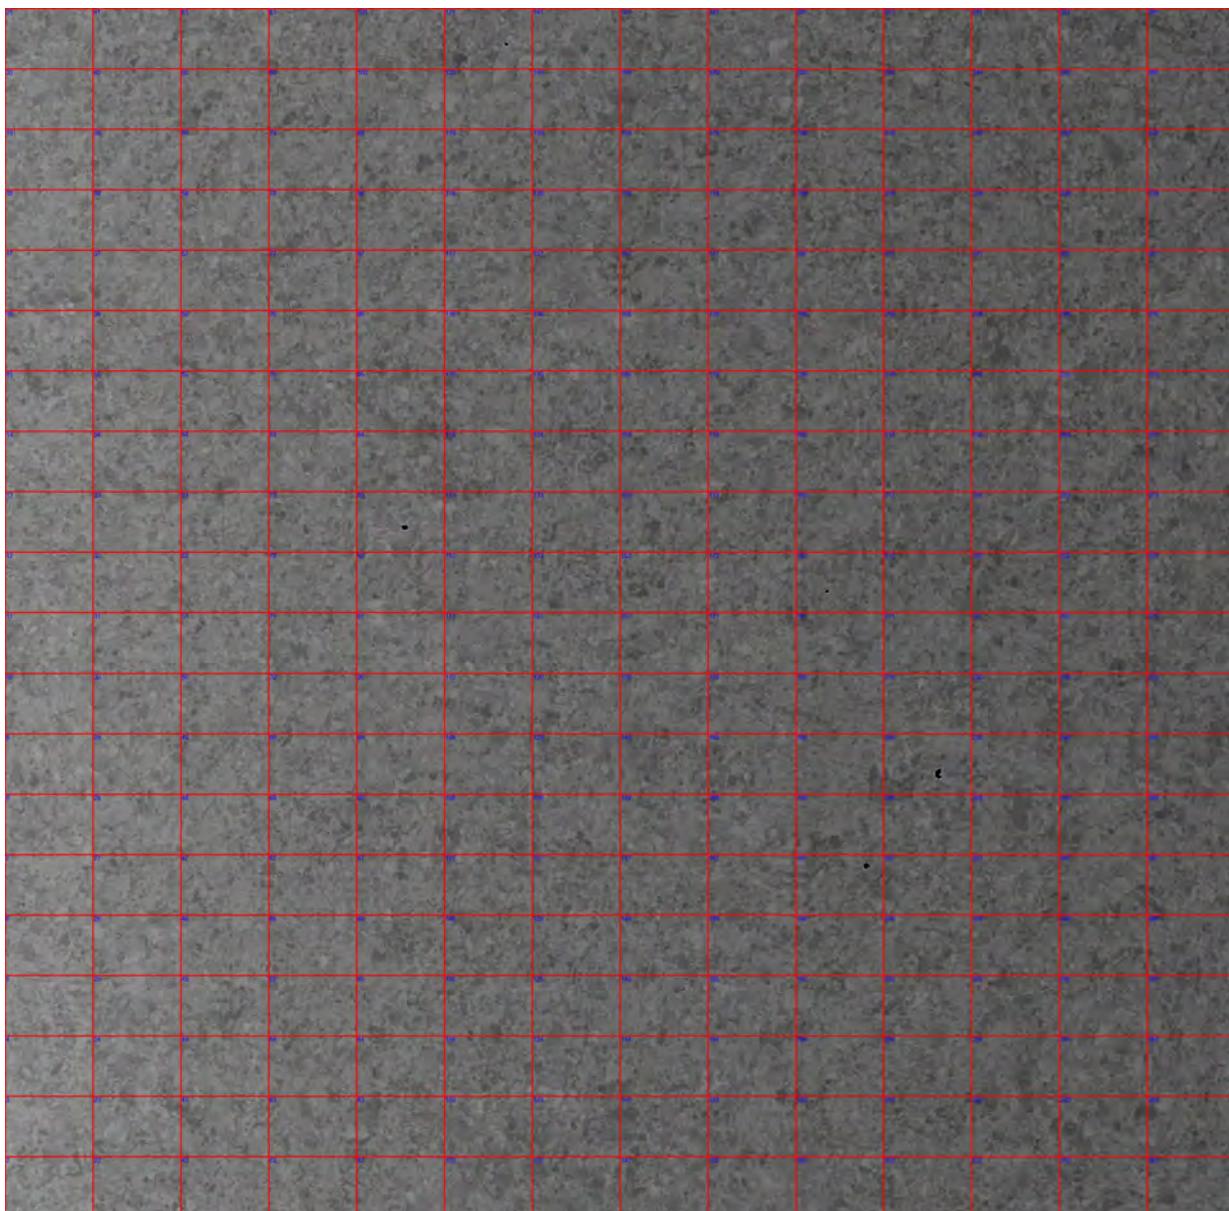


Figure 7.17. SEM Tile Map: Condition C10, Sample SS15

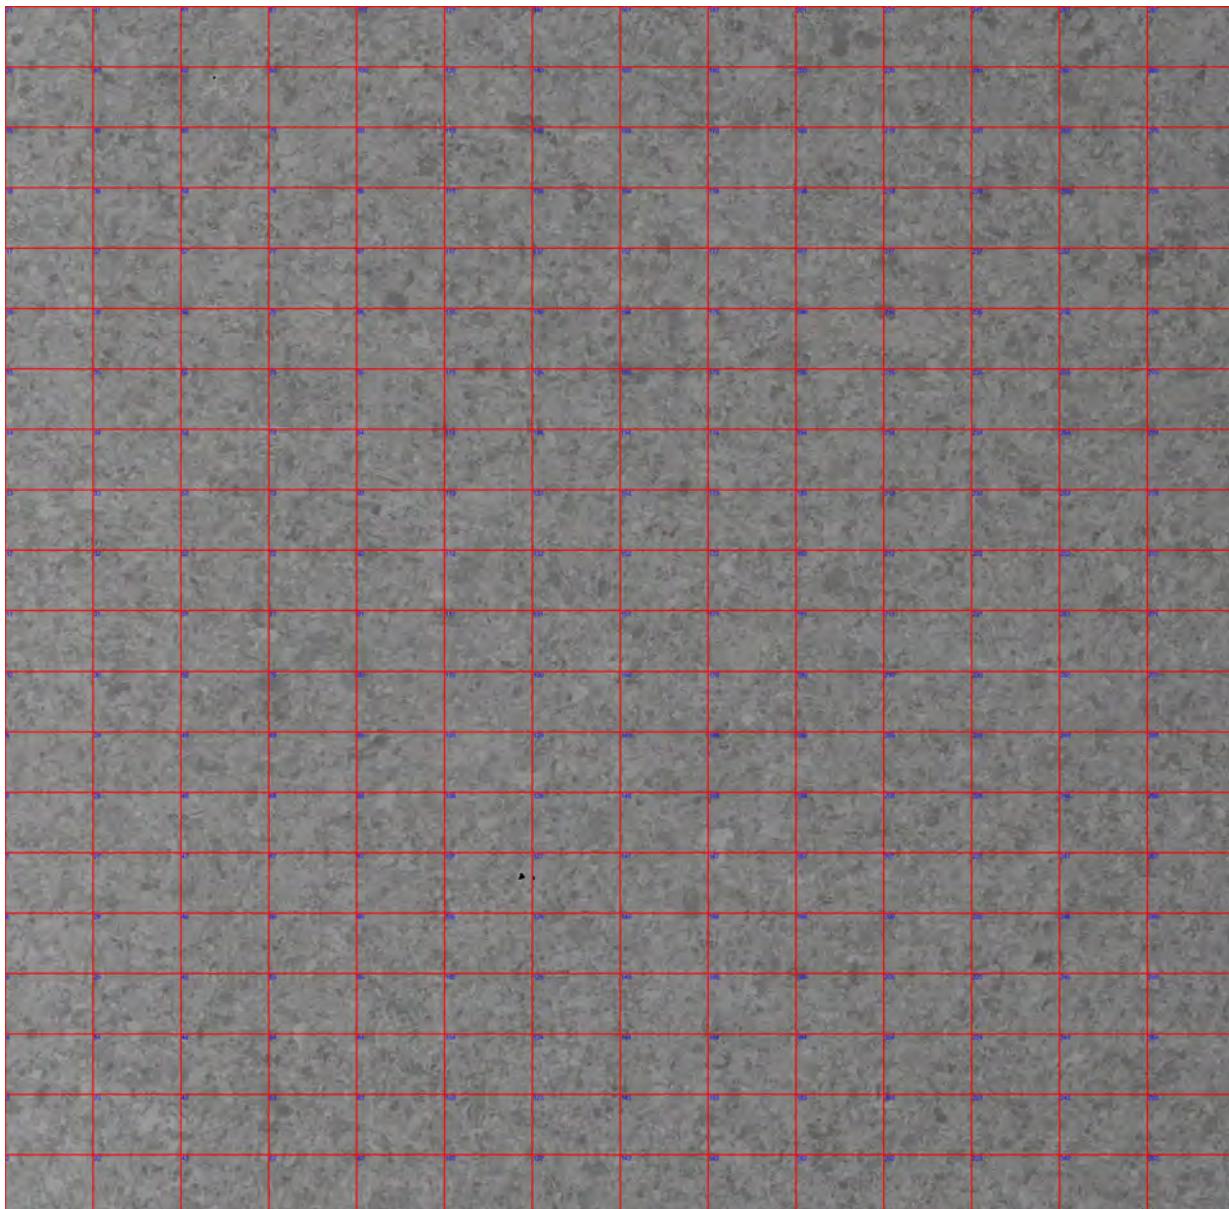


Figure 7.18. SEM Tile Map: Condition C11, Sample SS16

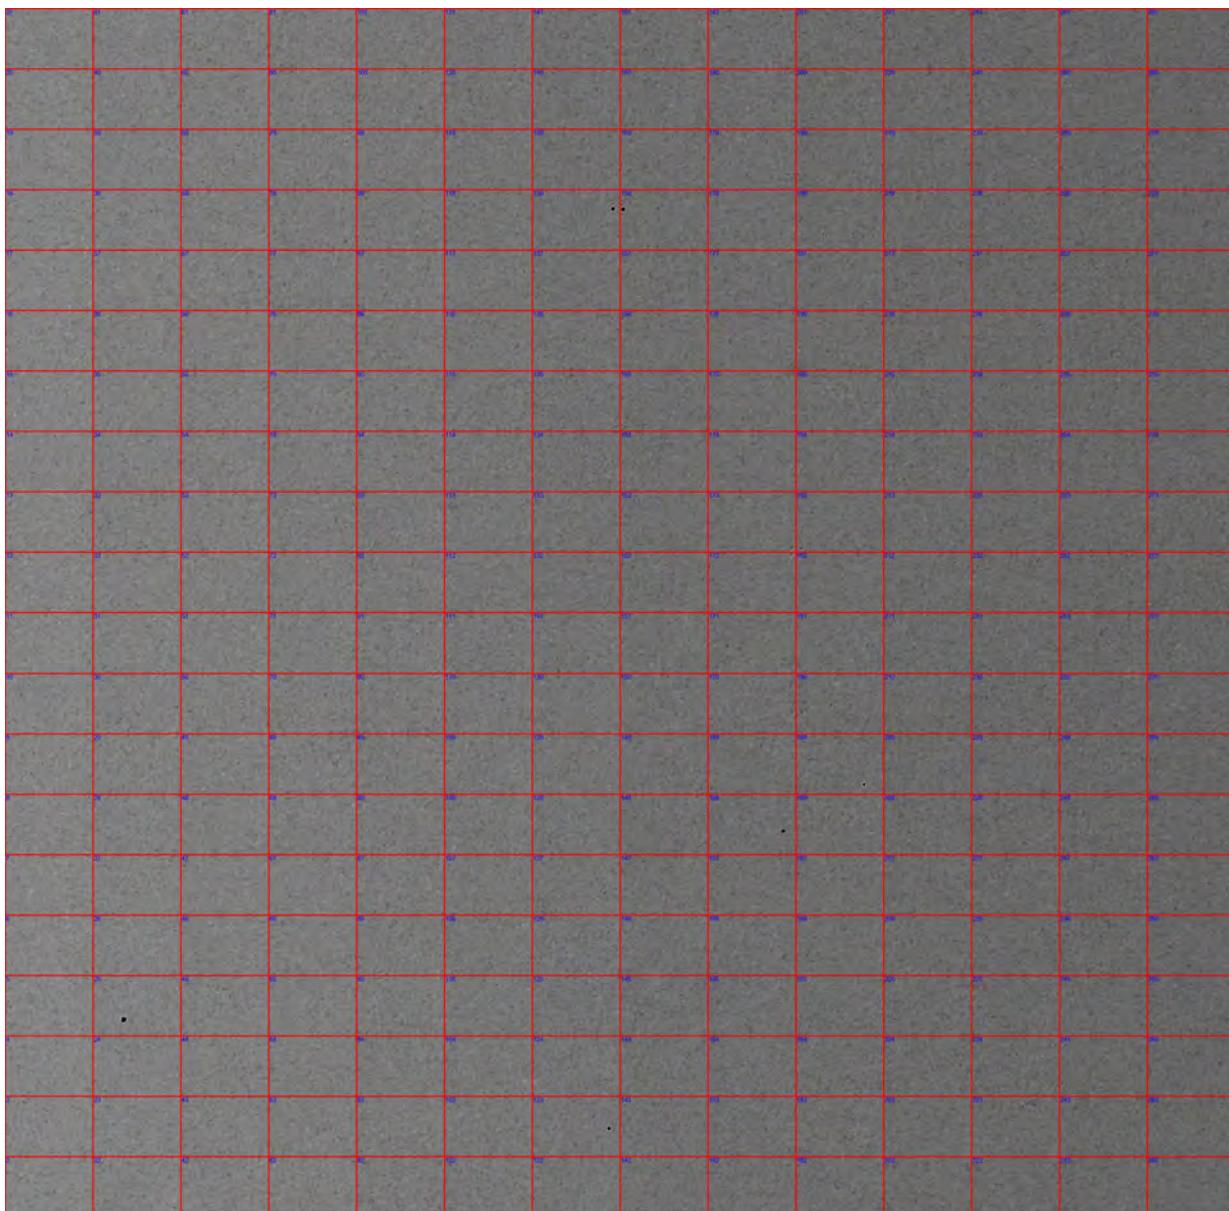


Figure 7.19. SEM Tile Map: Condition C02, Sample SS24

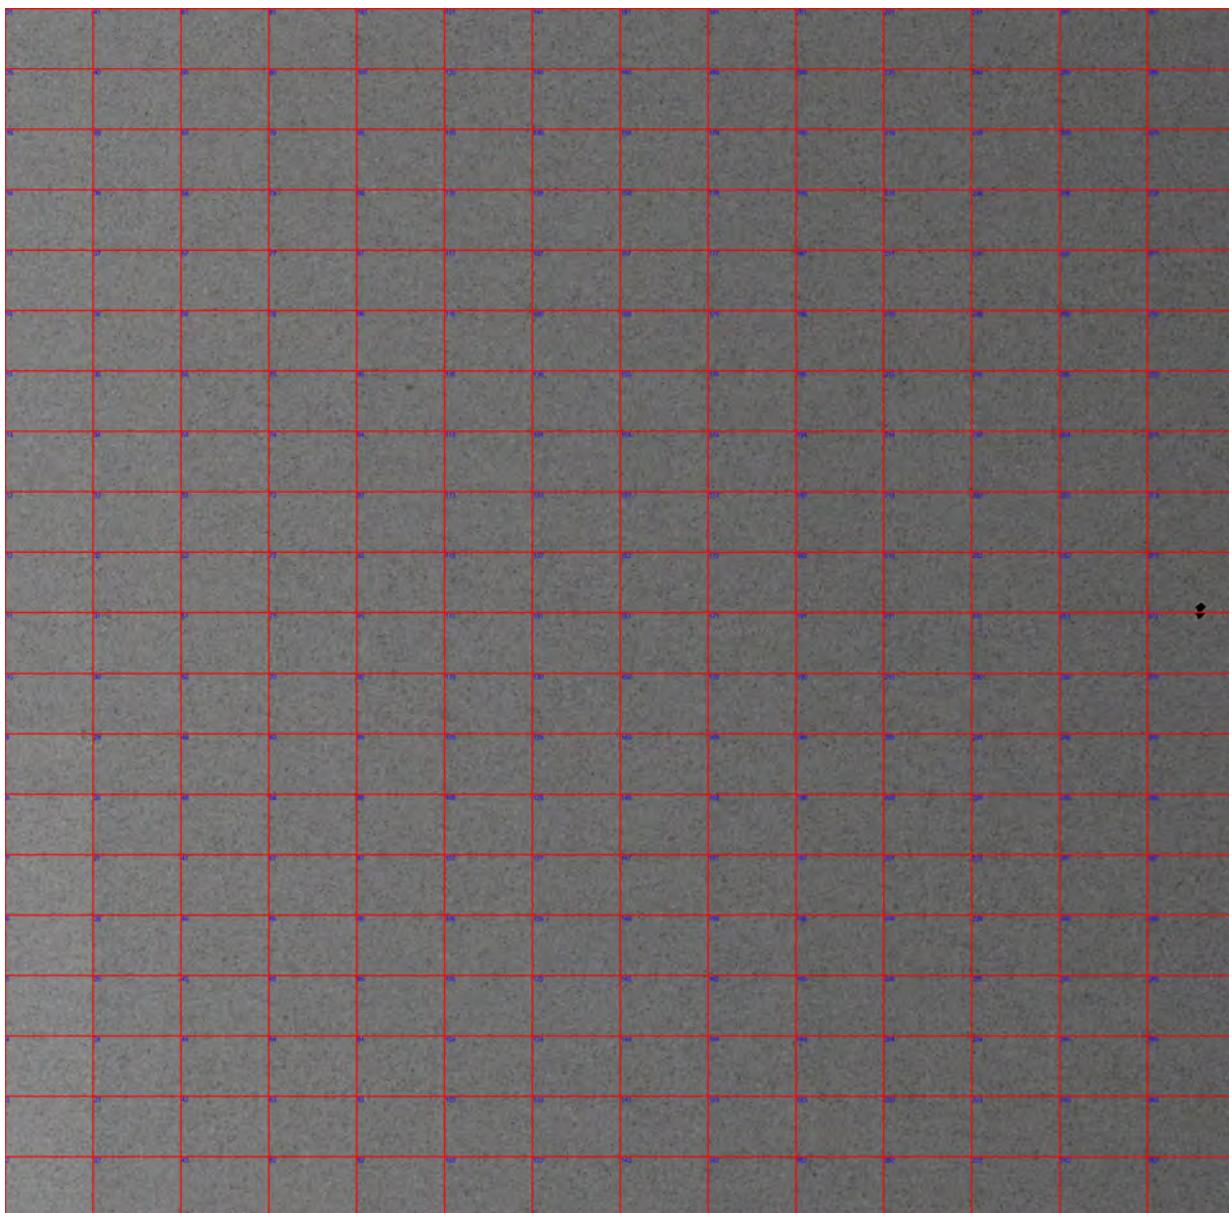


Figure 7.20. SEM Tile Map: Condition C01, Sample SS33

Attachment E: MCPC Round 2 Material Characterization Results for Modality

ULTRASONIC

Y Guo K Nwe
DR Todd N Conway

Attachment E contains [18](#) pages

Acknowledgments

This research was supported by the Materials Characterization, Prediction, and Control (MCPC) investment, under the Laboratory Directed Research and Development (LDRD) Program at Pacific Northwest National Laboratory (PNNL). PNNL is a multi-program national laboratory operated for the U.S. Department of Energy (DOE) by Battelle Memorial Institute under Contract No. DE-AC05-76RL01830.

Contents

1	Introduction	5
2	Key Information and Results	6
3	Instrumentation	7
4	Summary of Results	8
5	Results Files	9
	5.1 DATA Directory Contents	9
	5.2 VISUALIZATION Directory Contents	9
6	Notes and Comments	10
7	Tabular Results	11
8	Graphics	12
	8.1 Grain Noise at Stir Zone and Its Immediate Transition Area	12

Figures

8.1	Transverse wave grain noise (GN) configuration (mid-specimen): Condition C03, Sample SS09	13
8.2	Transverse wave grain noise (GN) configuration (mid-specimen): Condition C05, Sample SS10	13
8.3	Transverse wave grain noise (GN) configuration (mid-specimen): Condition C06, Sample SS11	14
8.4	Transverse wave grain noise (GN) configuration (mid-specimen): Condition C07, Sample SS12	14
8.5	Transverse wave grain noise (GN) configuration (mid-specimen): Condition C08, Sample SS13	15
8.6	Transverse wave grain noise (GN) configuration (mid-specimen): Condition C09, Sample SS14	15
8.7	Transverse wave grain noise (GN) configuration (mid-specimen): Condition C10, Sample SS15	16
8.8	Transverse wave grain noise (GN) configuration (mid-specimen): Condition C11, Sample SS16	16
8.9	Transverse wave grain noise (GN) configuration (mid-specimen): Condition C02, Sample SS24	17
8.10	Transverse wave grain noise (GN) configuration (mid-specimen): Condition C01, Sample SS33	17

Tables

7.1 Listing of all ultrasonic FOM data.	11
---	----

1.0 Introduction

The UT measurement technique uses ultrasonic waves to measure and analyze the properties of a medium. Ultrasonic attenuation and backscattering are used to infer material microstructure (specifically grain sizes) in the polycrystalline steel specimens through sensing changes in speed of sound of the anisotropic crystals. UT scans performed here produce two text-based file for each measurement. Data is copied manually from the instrument. The files contain ASCII text in comma separated values (CSV) format. The collected data represents time-averaged (over many pulses) amplitude versus measured time after each pulse. This collection is repeated at numerous discrete scan and index locations on the specimen. The process applied here is effectively a raster scan applied to the specimen top surface with information at each discrete location about potential defects and grain sizes collected for different depths at each discrete location. Measurements are made in two configurations.

The following sections provide a summary of results for this modality to enhance dissemination of the large volume of similar data that are made available via the PNNL DataHub (<https://data.pnnl.gov>) platform.

2.0 Key Information and Results

The main portion of this report provides a summary of key information related to the modality, including processing conditions, identification information, and the numerical results of most focus in the project. Where to find the information and results in the main report is described below (Section, Table, and Figure numbers listed below are found in the main report):

- Nominal process conditions for the FSP experiments are defined in Table 1 and Table 3 (data is in two different sorting orders).
- The Condition, Sample, and Specimen ID matrix is defined in Table 2 that is necessary to decode the nominal conditions applied to a particular specimen.
- Details about the modality data collection approach is defined in Section 4.0. This includes information about where ULTRASONIC is performed.
- Tabulation of the modality results per Sample ID is listed in Table 4 with discussion of what the particular result means discussed earlier in the section.
- UT figure of merit value versus nominal processing temperature listed in Table 3 and Table 4 is displayed graphically in Figure 5. This is shown to highlight consistency of results across a range of conditions.

3.0 Instrumentation

See Guo et al. (2024) (Reference provided in the main report) for details.

4.0 Summary of Results

Three types of data are archived; the raw ultrasonic scan data, the visualization of the raw data, and the ultrasonic figure-of-merit (FOM) results calculated from the grain noise data. Under the folder for each specimen, the raw ultrasonic scan data is in the DATA folder, the visualization is in the VISUALIZATION folder, and the FOM results are in the RESULTS folder. The DATA folder contains two CSV files for the front surface (FS) reference signal and the grain noise (GN) data, respectively. The VISUALIZATION folder contains image files visualizing the grain noise data in the form of B-Scan images. The RESULTS folder contains a CSV file that lists FOM values for a few different frequencies. See Guo, et al. (2024) for more details (the reference is provided in the main report).

5.0 Results Files

5.1 DATA Directory Contents

Data files obtained for each dataset from the instrumentation are saved in the associated DATA directory. For ultrasound, two data files are generated for each specimen: a CSV text file containing an ultrasonic waveform later used as a reference signal in data analysis, and a CSV text file containing all the ultrasonic grain noise waveforms for the raster scan later used to calculate ultrasonic FOM.

- **(name)_FS.csv** (CSV Text type): When the probe is in the normal incidence configuration (oriented directly downward at the specimen), only a single front surface (FS) echo is acquired that is a reference signal for later analysis.
- **(name)_GN.csv** (CSV Text type): When the probe is in the transverse wave grain noise (GN) configuration, a full raster scan is performed. This orientation is at roughly 22 degrees from the top surface of the specimen to produce a transverse wave.

5.2 VISUALIZATION Directory Contents

Visualizations are derived directly from data to illustrate or interpret results. Different colors, scales, magnifications, file formats (images vs animation) etc. may be present. The following visualizations are provided:

- **(name)_GN** (TIFF Image type, MP4 Movie type, Directory): A collection of imagery and animations of the grain noise data. The TIFF is a multipage object. The embedded imagery in the TIFF is also provided in the directory for easy import of a single image into reports and presentations.

The most useful data across multiple datasets is captured in directory ENSEMBLE-INFO for this modality. The information is provided for convenience and is directly replicated from the related datasets. Refer to the individual datasets for details. In the case of conflicting information between items found in this directory and with individual datasets, the individual dataset information takes precedence

- **ULTRASONIC_Values.csv**: Contains a summary of all ultrasonic data from across all the datasets as a convenience. This data is assembled from the individual dataset files.

6.0 Notes and Comments

The following observations are made about data and files for this modality:

- None.

7.0 Tabular Results

Figure of Merit (FOM) is listed Table 7.1 along with the intercept-based grain size in microns (these are the same values shown in Table 4 of the main report). This data is obtained from the (name)_FOM.csv file. The file contains additional tabular FOM values at different frequencies obtained by analyzing the grain noise data.

Table 7.1. Listing of all ultrasonic FOM data.

Sample ID	Condition ID	Mean Grain Size (um)	FOM at 20.5 MHz
SS09	C03	1.58	0.1038
SS10	C05	1.86	0.0650
SS11	C06	1.52	0.0946
SS12	C07	1.30	0.0950
SS13	C08	4.14	0.2752
SS14	C09	3.29	0.2441
SS15	C10	4.87	0.4417
SS16	C11	4.86	0.3746
SS24	C02	1.48	0.0610
SS33	C01	1.42	0.0551

8.0 Graphics

The following sub sections display key graphics for convenience:

8.1 Grain Noise at Stir Zone and Its Immediate Transition Area

A grain noise B-Scan image of the transverse cross-section at index 25, selected from the {name}_GN-Color folder, is shown below for each condition and sample as an example.

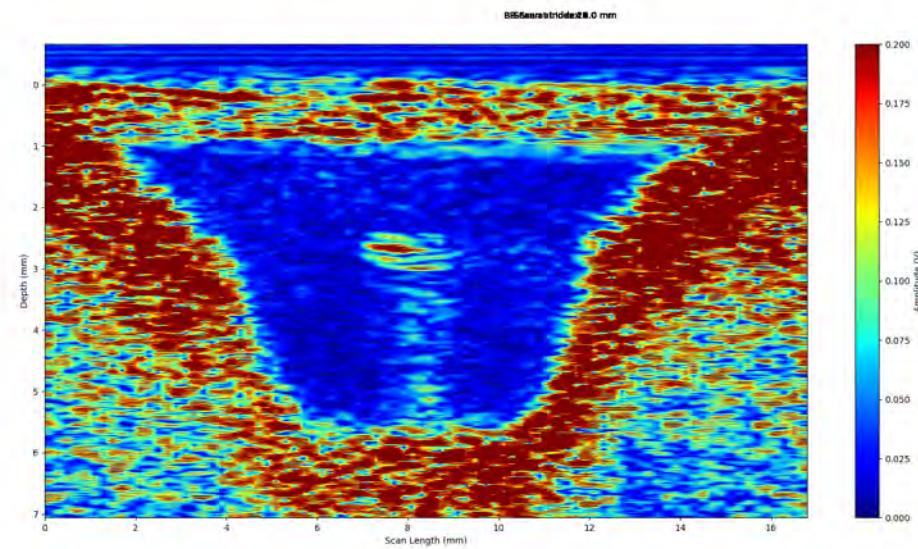


Figure 8.1. Transverse wave grain noise (GN) configuration (mid-specimen): Condition C03, Sample SS09

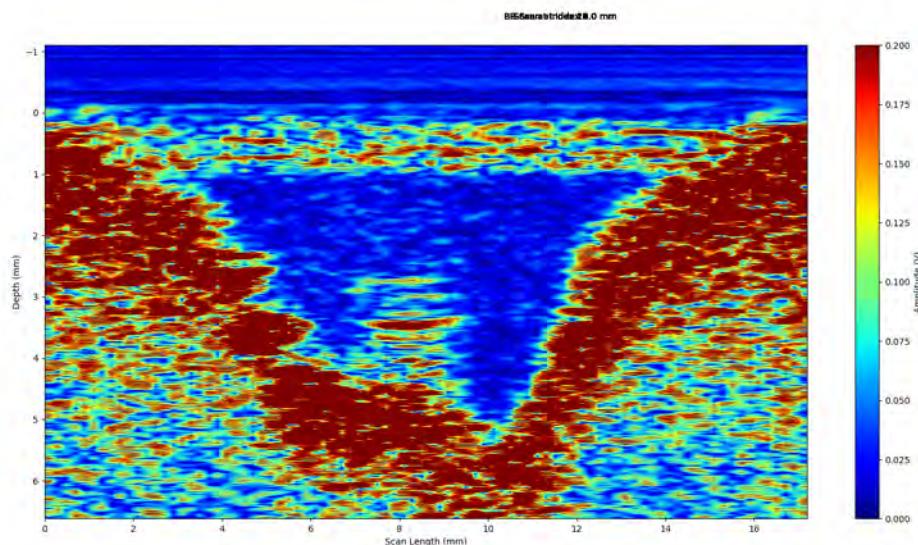


Figure 8.2. Transverse wave grain noise (GN) configuration (mid-specimen): Condition C05, Sample SS10

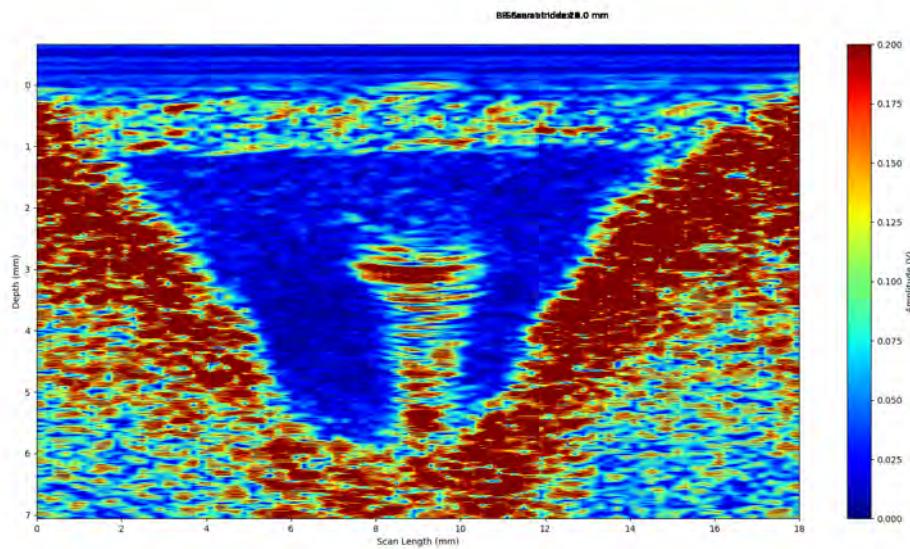


Figure 8.3. Transverse wave grain noise (GN) configuration (mid-specimen): Condition C06, Sample SS11

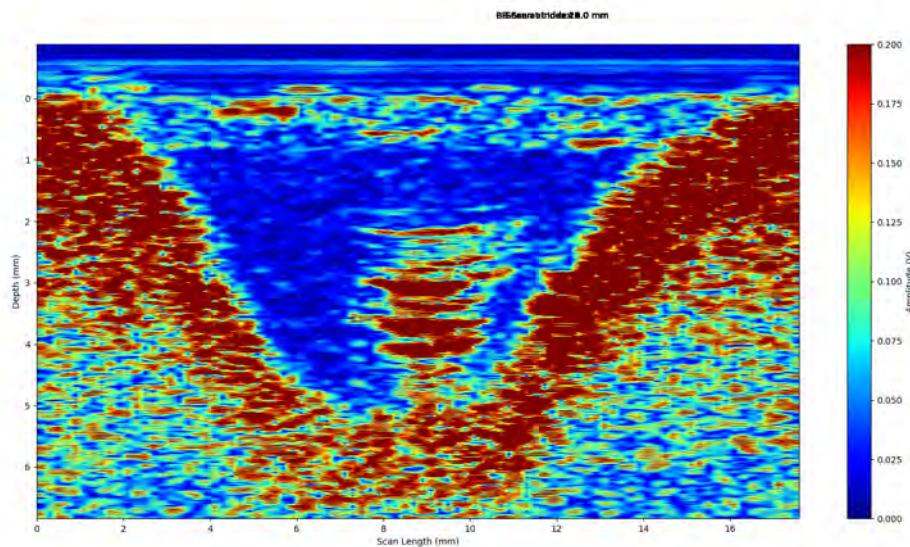


Figure 8.4. Transverse wave grain noise (GN) configuration (mid-specimen): Condition C07, Sample SS12

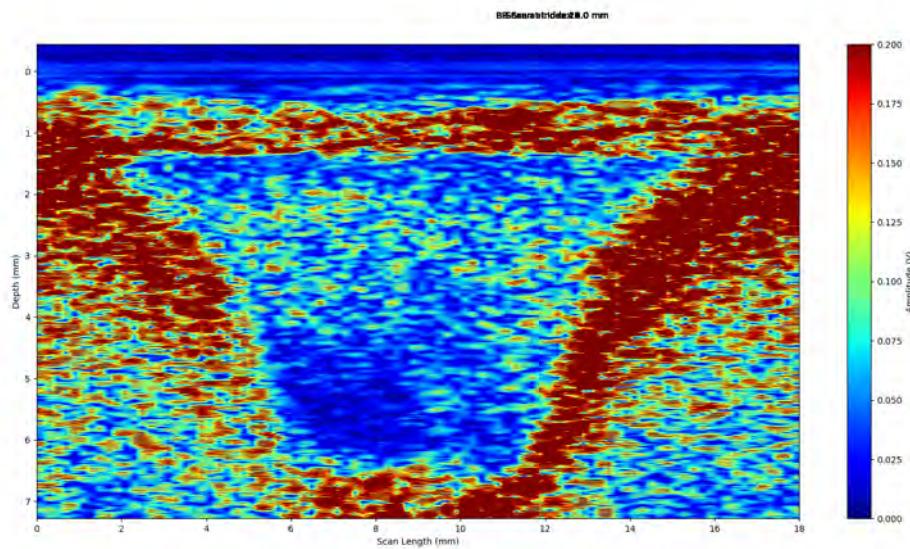


Figure 8.5. Transverse wave grain noise (GN) configuration (mid-specimen): Condition C08, Sample SS13

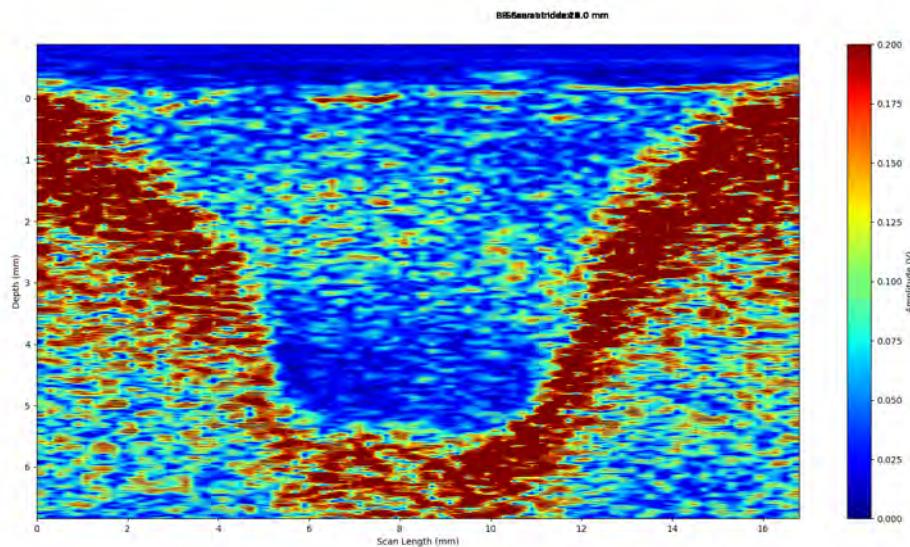


Figure 8.6. Transverse wave grain noise (GN) configuration (mid-specimen): Condition C09, Sample SS14

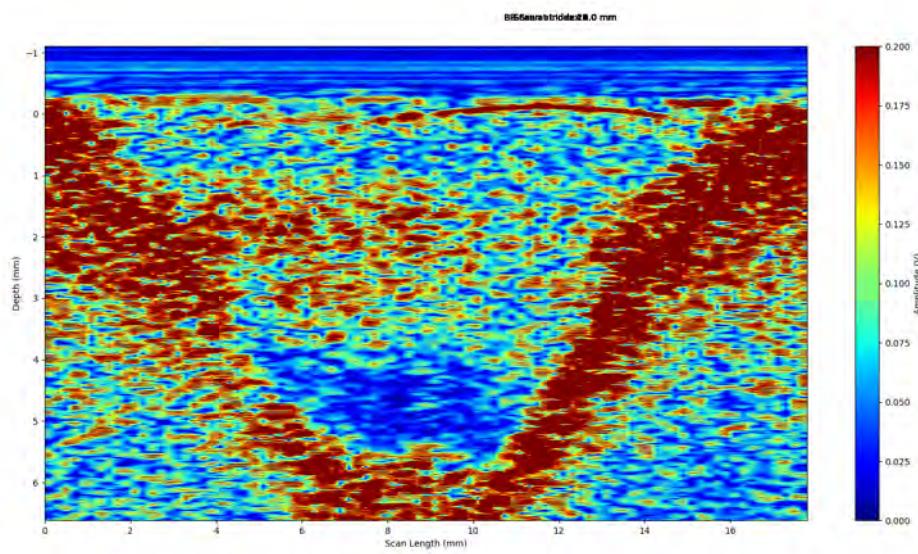


Figure 8.7. Transverse wave grain noise (GN) configuration (mid-specimen): Condition C10, Sample SS15

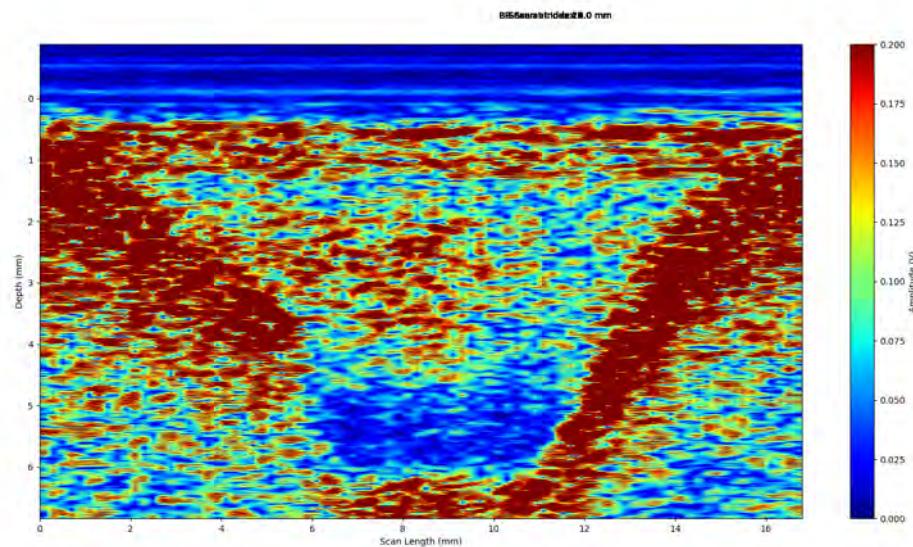


Figure 8.8. Transverse wave grain noise (GN) configuration (mid-specimen): Condition C11, Sample SS16

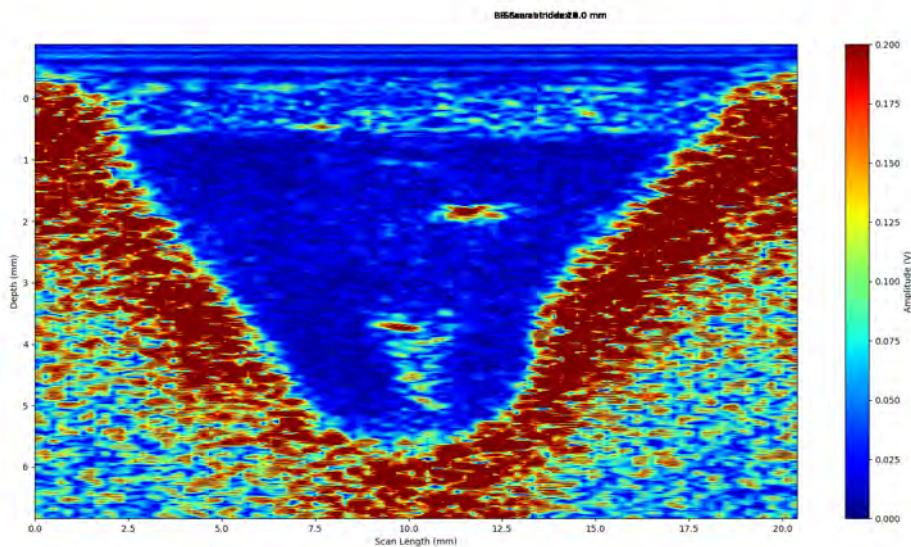


Figure 8.9. Transverse wave grain noise (GN) configuration (mid-specimen): Condition C02, Sample SS24

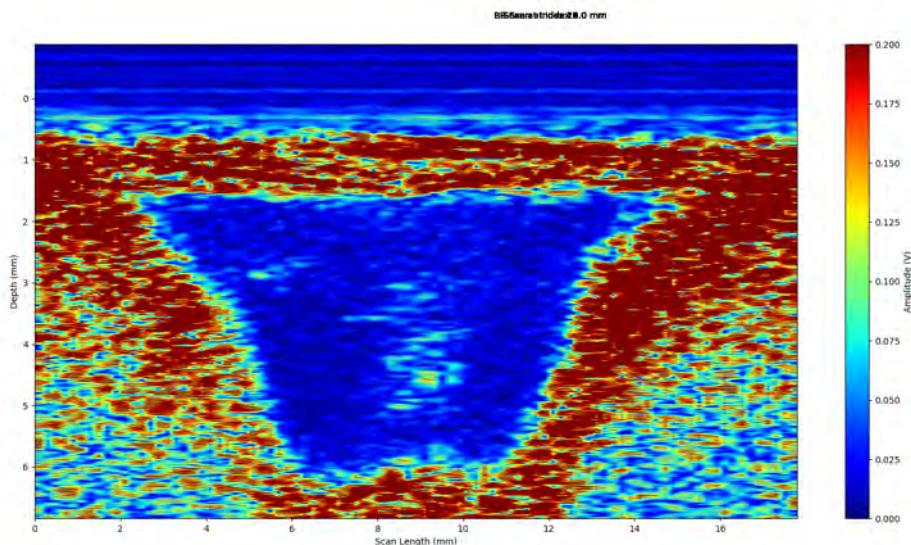


Figure 8.10. Transverse wave grain noise (GN) configuration (mid-specimen): Condition C01, Sample SS33

Pacific Northwest National Laboratory

902 Battelle Boulevard
P.O. Box 999
Richland, WA 99354

1-888-375-PNNL (7665)

www.pnnl.gov