

PNNL-18013
WTP-RPT-176, Rev. 0



Prepared for the U.S. Department of Energy
under Contract DE-AC05-76RL01830

Development and Characterization of Gibbsite Component Simulant

RL Russell
HD Smith

DE Rinehart
RA Peterson

January 2009



Pacific Northwest
NATIONAL LABORATORY

DISCLAIMER

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor Battelle Memorial Institute, nor any of their employees, makes **any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights.** Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or Battelle Memorial Institute. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

PACIFIC NORTHWEST NATIONAL LABORATORY
operated by BATTELLE
for the UNITED STATES DEPARTMENT OF ENERGY
under Contract DE-AC05-76RL01830.

Printed in the United States of America

Available to DOE and DOE contractors from the
Office of Scientific and Technical Information,
P.O. Box 62, Oak Ridge, TN 37831-0062;
ph: (865) 576-8401
fax: (865) 576 5728
email: reports@adonis.osti.gov

Available to the public from the National Technical Information Service,
U.S. Department of Commerce, 5285 Port Royal Rd., Springfield, VA 22161
ph: (800) 553-6847
fax: (703) 605-6900
email: orders@nits.fedworld.gov
online ordering: <http://www.ntis.gov/ordering.htm>

Development and Characterization of Gibbsite Component Simulant

RL Russell
HD Smith

DE Rinehart
RA Peterson

January 2009

Test specification: 24590-PTF-TSP-RT-06-006, Rev 0

Test plan: TP-RPP-WTP-469, Rev 0

Test exceptions: None

R&T focus area: Pretreatment


Test Scoping Statement: None

Pacific Northwest National Laboratory
Richland, Washington 99352


Completeness of Testing

This report describes the results of work and testing specified by Test Specification, 24590-PTF-TSP-RT-06-006, Rev 0 and Test Plan TP-RPP-WTP-469, Rev 0. The work followed the quality assurance requirements outlined in the Test Specification and Test Plan. The descriptions provided in this report are an accurate account of both the conduct of the work and the data collected. Test plan results are reported. Also reported are any unusual or anomalous occurrences that are different from expected results. The test results and this report has been reviewed and verified.

Approved:

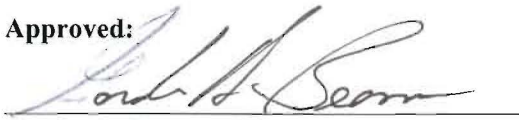

Gordon H. Beeman, Manager
WTP R&T Support Project



Date

Contents

Abbreviations and Acronyms	vii
Testing Summary	ix
1.0 Introduction.....	1.1
2.0 Gibbsite Source Characterization	2.1
2.1 X-ray Diffraction (XRD).....	2.1
2.2 Particle-Size Distribution.....	2.4
2.3 Scanning Electron Microscope (SEM)	2.6
2.4 Surface Area	2.9
2.5 Screening Leach Test.....	2.10
3.0 Determination of the Appropriate Gibbsite Simulant	3.1
4.0 Gibbsite Simulant Dissolution Test Matrix Results.....	4.1
5.0 Gibbsite Simulant Blend Testing	5.1
6.0 Nitrate Effect on Gibbsite Dissolution.....	6.1
7.0 Anion Effect on Gibbsite Dissolution.....	7.1
8.0 Gibbsite Simulant Evaluation Against Actual Waste Results	8.1
9.0 Conclusions and Recommendations	9.1
10.0 References.....	10.1
11.0 Further Reading	11.1
Appendix A: Actual Analytical Data	A.1
Appendix B: Testing Conditions.....	B.1
Appendix C: Gibbsite Product Specifications	C.1

Figures

2.1. XRD Pattern of Gibbsite Sample G1 (BASF CP-5).....	2.2
2.2. XRD Pattern of Gibbsite Sample G2 (Almatis C31C).....	2.2
2.3. XRD Pattern of Gibbsite Sample G3 (Almatis H710).....	2.3
2.4. XRD Pattern of Gibbsite Sample G4 (Almatis C333).....	2.3
2.5. XRD Pattern of Gibbsite Sample G5 (Almatis C33).....	2.4
2.6. Volume Distribution of Particle Size Plot of Gibbsite Sources.....	2.5
2.7. Number Distribution Particle Size Plot of the Gibbsite Sources.....	2.6
2.8. SEM Picture of “Gibbsite Sample G1” at 500×, 1000×, 5000×, and 10,000×.....	2.7
2.9. SEM Picture of Gibbsite Sample G2 at 1000×, 5000×, 10,000×, and 25,000×.....	2.7
2.10. SEM Picture of Gibbsite Sample G3 at 1000×, 5000×, 10,000×, and 25,000×.....	2.8
2.11. SEM Picture of Gibbsite Sample G4 at 1000×, 5000×, 10,000×, and 25,000×.....	2.8
2.12. SEM Picture of Gibbsite Sample G5 at 500×, 1000×, 5000×, and 10,000×.....	2.9
2.13. Schematic Drawing of the Caustic Leaching Test Setup.....	2.10
2.14. Percent Al Dissolved in the Screening Gibbsite Leaching Test Results.....	2.11
3.1. Gibbsite Simulant Crystals Compared to Actual Tank Waste Crystals at 1000×.....	3.2
3.2. XRD Pattern for Sample G1.....	3.3
3.3. XRD Pattern for Sample G4.....	3.3
4.1. Effect of Hydroxide Concentration on Gibbsite Dissolution.....	4.3
4.2. Effect of Temperature on Gibbsite Dissolution.....	4.4
4.3. Mixing Effect on Gibbsite Dissolution in 1 M (MTG-7 and MTG-8) and 5 M NaOH (MTG-5 and MTG-6) at 40°C.....	4.5
5.1. Gibbsite Dissolution in the Blended Simulant (BSM-3 and BSM-4).....	5.3
6.1. Gibbsite Dissolution in 3 M NaOH and Nitrate Solutions.....	6.2
6.2. Gibbsite Precipitation in 3-M NaOH and Nitrate Solutions.....	6.2
6.3. Gibbsite Supersaturation in 3-M NaOH and Nitrate Solutions.....	6.3
7.1. Gibbsite Dissolution Results with Aluminate and Anions.....	7.2
8.1. Gibbsite Dissolution in 1 M NaOH.....	8.2
8.2. Gibbsite Dissolution in 3 M NaOH.....	8.2
8.3. Gibbsite Dissolution in 5 M NaOH.....	8.3

Tables

S.1. Test Objectives	ix
S.2. Results and Performance against Success Criteria	x
S.3. R&T Test Conditions.....	xi
2.1. Gibbsite Sources Characterized and Tested	2.1
2.2. Volume Distribution of Gibbsite Particle-Size Results.....	2.5
2.3. Number Distribution of Gibbsite Particle-Size Results.....	2.6
2.4. BET Surface Area of Gibbsite Samples	2.10
2.5. Screening Gibbsite Leaching Test Results	2.11
4.1. Gibbsite Testing Matrix	4.2
5.1. Supernate Composition at 3.2 M Na	5.1
5.2. Blended Component Test Matrix	5.2
6.1. Densities of Leach Solutions.....	6.1
7.1. Molar Concentration of Sodium Salts	7.1
8.1. Gibbsite Revision Test Matrix	8.1

Abbreviations and Acronyms

BET	Brunauer, Emmet, and Teller surface area measurement method
BNI	Bechtel National, Incorporated
CUF	cell unit filter, bench-scale crossflow filtration system
DIW	de-ionized water
DOE	U.S. Department of Energy
DST	double-shell tank
EFRT	External Flowsheet Review Team
FIZ	Fachinformationszentrum
HLW	high-level waste
IC	ion chromatography
ICDD	International Centre for Diffraction Data
ICP-AES	inductively coupled plasma- atomic emission spectroscopy
ICSD	Inorganic Crystal Structure Database
LANL	Los Alamos National Laboratory
LAW	low-activity waste
ORNL	Oak Ridge National Laboratory
PEP	Pretreatment Engineering Platform
PNNL	Pacific Northwest National Laboratory
PSD	particle-size distribution
PTF	Pretreatment Facility
QAM	Quality Assurance Manual
QAP	quality assurance program
QARD	Quality Assurance Requirements and Descriptions (document)
RPM	revolutions per minute

RPP	River Protection Project
R&T	research and technology
SARM	Standard Analytical Reference Material
SEM	scanning electron microscopy
SST	single-shell tank
SWRI	Southwest Research Institute
TRU	transuranic elements
WTP	Hanford Tank Waste Treatment and Immobilization Plant
XRD	X-ray diffraction

Testing Summary

According to Bechtel National, Inc.’s (BNI’s) Test Specification 24590-PTF-TSP-RT-06-006, Rev 0, “Simulant Development to Support the Development and Demonstration of Leaching and Ultrafiltration Pretreatment Processes,” simulants for boehmite, gibbsite, and filtration are to be developed so they can be used in subsequent bench and integrated testing of the leaching/filtration processes for the River Protection Project-Waste Treatment and Immobilization Plant (RPP-WTP). These simulants will then be used to demonstrate the leaching process and to help refine processing conditions that may impact safety basis considerations (Smith 2006). This report documents PNNL’s results of the gibbsite simulant development.

Objective

The test objectives for the work addressed in this report are summarized in Table S.1 along with a discussion of how the objectives were met. The overall objective of this work was to develop a gibbsite (monoclinic $\text{Al}(\text{OH})_3$) simulant that appropriately mimics the performance of the actual waste gibbsite for use in subsequent testing and to provide a technical performance basis for the use of this simulant. The specific objective of this work was to develop and characterize a gibbsite component simulant for testing of aluminum leaching and provide a basis for the selected simulant. Once the gibbsite simulant was chosen, it was fully tested and characterized.

Table S.1. Test Objectives

Test Objective	Objective Met? (Y/N)	Discussion
1) Develop and characterize a gibbsite component simulant for testing aluminum leaching and provide a basis for the selected simulant.	Y	A gibbsite was chosen (Almatis Hydrated Alumina Ath C333) that was similar to the actual waste based primarily on the crystal size and shape of the simulant in comparison to the actual waste gibbsite particles.
2) The gibbsite simulant will be fully tested and characterized.	Y	The gibbsite simulant was leached under several different conditions and with the entire simulant as well as filtered to determine the effect of these variables on its leaching behavior. It was then compared to the actual gibbsite waste leaching results.

Success Criteria

This work meets the second of the Success Criteria described in Section 4 of BNI’s Test Specification 24590-PTF-TSP-RT-06-006, Rev 0:

Development of a gibbsite simulant that has physical properties—in particular crystal size and habit—similar to that observed in prior actual waste samples and the development of a correlation that predicts gibbsite simulant dissolution rate as a function of gibbsite properties such as crystal size and crystal habit, as well as other physical properties.

How this success criterion was met is listed in Table S.2.

Table S.2. Results and Performance against Success Criteria

List Success Criteria	Explain How the Tests Did or Did Not Meet the Success Criteria
Develop (including a detailed preparation procedure) a gibbsite simulant that has physical properties—in particular crystal size and habit—similar to that observed in prior actual waste samples and develop a correlation that predicts gibbsite simulant dissolution rate as a function of gibbsite properties, such as crystal size and crystal habit.	Several gibbsite sources were characterized at PNNL by particle size distribution, X-ray diffraction (XRD), scanning electron microscopy (SEM), surface-area analysis, and caustic leaching. These results were then compared against available data (Lumetta 1996) for actual gibbsite waste, which consisted primarily of crystal size and shape, using XRD and SEM. When more actual waste data from Groups 3 and 4 were available, these results were compared based on caustic leaching, and it was found that the gibbsite source that had been picked matched closely. More details of this are given in Sections 3.0 and 8.0.

Test Exceptions

None.

Quality Requirements

Pacific Northwest National Laboratory (PNNL) is operated for the U.S. Department of Energy (DOE) by Battelle under Contract DE-AC05-76RL01830. PNNL implements a Quality Assurance Program that is based upon the requirements as defined in DOE Order 414.1C, “Quality Assurance,” and 10 CFR 830, “Energy/Nuclear Safety Management,” Subpart A—“Quality Assurance Requirements.” PNNL has chosen to implement the requirements of DOE Order 414.1C and 10 CFR 830, Subpart A by integrating them into the laboratory’s management systems and daily operating processes. The procedures necessary to implement the requirements are documented through the laboratory’s Standards-Based Management System (SBMS).

PNNL implemented the RPP-WTP quality requirements by performing work in accordance with the River Protection Project – Waste Treatment Plant Support Program (RPP-WTP) Quality Assurance Plan (RPP-WTP-QA-001, QAP). Work was performed to the quality requirements of NQA-1-1989 Part I, *Basic and Supplementary Requirements*, NQA-2a-1990, Part 2.7, and DOE/RW-0333P, Rev 13, *Quality Assurance Requirements and Descriptions (QARD)*. These quality requirements were implemented through the River Protection Project – Waste Treatment Plant Support Program (RPP-WTP) Quality Assurance Manual (RPP-WTP-QA-003, QAM). The analytical requirements are implemented through RPP-WTP’s Statement of Work (WTPSP-SOW-005 and RPP-WTP-QA-005, respectively) with Southwest Research Institute (SWRI). The requirements of DOE/RW-0333P, Rev 13, *Quality Assurance Requirements and Descriptions (QARD)* were not required for this work.

A matrix that cross-references the NQA-1 and NQA-2a requirements with RPP-WTP’s procedures for this work is given in TP-RPP-WTP-469. It includes justification for those requirements not implemented.

Experiments that were not method-specific were performed in accordance with RPP-WTP’s procedures QA-RPP-WTP-1101 “Scientific Investigations” and QA-RPP-WTP-1201 “Calibration and Control of Measuring and Testing Equipment” so that sufficient data were taken with properly calibrated measuring and test equipment (M&TE) to obtain quality results.

RPP-WTP addressed internal verification and validation activities by conducting an Independent Technical Review (ITR) of the final data report in accordance with PNNL’s procedure QA-RPP-WTP-604. This review verifies that the reported results were traceable, inferences and conclusions were soundly based, and the reported work satisfied the Test Plan objectives. This review procedure is part of PNNL’s RPP-WTP QAM.

R&T Test Conditions

The research and technology (R&T) test conditions, as defined in BNI’s Test Specification,^(a) are summarized in Table S.3.

Table S.3. R&T Test Conditions

List R&T Test Conditions	Were Test Conditions Followed?
1) Review the available literature and actual waste testing and characterization data. Based on this review, target parameters for the proposed simulant that will be developed. Note that the development of these criteria must also consider the requirements for scaled testing. It will likely be necessary to develop simulants with a range of parameters that can be adjusted to provide a scaled simulant for use in the integrated test platform.	Gibbsite sources were researched, and different gibbsites were studied to see which matched the particle sizes that PNNL was trying to match the best. Based on this, it was determined which vendors to approach and from which sources to obtain samples for testing.
2) Search available vendors and preparation methods to identify available sources of gibbsite materials. This review will include identifying available characterization data associated with each source material and will recommend which gibbsite source materials should be obtained and tested. This recommendation should consider the diversity of both particle size and morphology in identifying candidate samples for additional testing.	Five samples of gibbsite were obtained from two sources, BASF and Almatris. The d_{50} particle sizes varied from 60 μm to 1.4 μm . XRD ranged from amorphous to very strong, crystalline gibbsite peaks.
3) Prepare and test the identified gibbsite source materials. It is anticipated that testing will involve multiple samples over a range of material properties, including particle size and morphology. At a minimum, the following properties will be measured for each gibbsite source material: <ul style="list-style-type: none"> Particle size Surface area Crystal pattern by XRD 	Each gibbsite source obtained was fully characterized by XRD, particle-size distribution (PSD), the Brunauer, Emmet, and Teller surface area measurement method (BET), SEM, and caustic dissolution before testing, as shown and discussed in Section 2.0 of this report.

(a) GL Smith. Nov. 2006. *Simulant Development to Support the Development and Demonstration of Leaching and Ultrafiltration Pretreatment Processes*. 24590-PTF-TSP-RT-06-006, Rev. 0.

List R&T Test Conditions	Were Test Conditions Followed?
<p>Dissolution rate under a variety of fixed testing conditions measured under multiple conditions. Note that sufficient data must be obtained for selected samples to provide an adequate description of the reaction-rate equation. Further note that the temperature range should be sufficient to provide a range of behaviors. In addition, sufficient information, including density and water content, should be obtained to provide meaningful correlation to actual waste samples. Equilibrium solubility under various test conditions.</p>	
<p>4) A correlation will be developed to predict dissolution rate as a function of other physical characteristics. In addition, a gibbsite source—or blend of gibbsite sources—will be selected to best meet the criteria defined in 1). These results will be compared against the simulant basis criteria, and an appropriate method to correlate simulant performance to actual waste performance will be documented.</p>	<p>A correlation was developed to predict the dissolution rate as a function of other physical characteristics, as discussed in Sections 2.5 and 4.0 of this report. A gibbsite source was selected (Almatis Hydrated Alumina Ath C333) for further testing and discussed in Section 3.0 of this report.</p>

Simulant Use

Use of actual waste in PNNL’s Pretreatment Engineering Platform (PEP) is not possible due to safety, cost, and volume. Therefore, a simulant needed to be developed for use in the PEP testing. One of the objectives of the work described in this report was to develop a simulant to determine the dissolution of gibbsite and its effect on the dissolution of boehmite in the WTP to be used in the PEP. The reasoning behind the simulant selection, a comparison of it to the actual tank waste, and a description of it are described in this report.

Discrepancies and Follow-on Tests

None.

1.0 Introduction

At the River Protection Project-Waste Treatment and Immobilization Plant (RPP-WTP), the high level waste (HLW) is separated from the low-activity waste (LAW) liquid stream by ultrafiltration in the Pretreatment Facility (PTF), the concentrated HLW will undergo caustic and oxidative leaching processes to dissolve and wash out materials (aluminum, chromium, phosphates, and sulfates) that would otherwise limit HLW loading in the immobilized waste glass. The current BNI design indicates that the leaching processes may be carried out in the ultrafiltration feed vessels (UFP-2a and UFP-2b). The concentrated HLW solids are sequentially caustic leached, washed, and oxidatively leached and washed once more during pretreatment. While the caustic leaching dissolves the aluminum in the HLW solids, the oxidative leaching is carried out to oxidize the chromium using a sodium permanganate (NaMnO_4) solution and dissolve it in a mild caustic solution. The HLW solids are concentrated after each leach and wash operation using the cell unit filter (CUF) system.

Caustic-leaching experiments were first performed by PNNL on actual Hanford tank sludge samples in FY 1993. The original caustic-leaching experiments were performed by PNNL as a prelude to acid dissolution of the sludge solids, with the intent that the acid-dissolved fraction would be processed through solvent extraction to separate the very small mass fraction of the radioactive elements (the transuranics [TRUs], ^{90}Sr , and ^{137}Cs) from the bulk mass of non-radioactive components (Lumetta et al. 1996). In this respect, caustic leaching was meant to remove the large amount of aluminum from the waste, thus reducing the nitric acid demand and simplifying the solvent extraction feed. However, subsequently, caustic leaching was chosen as the baseline method for Hanford tank sludge pretreatment; this process was sometimes referred to as “Enhanced Sludge Washing” (Lumetta et al. 1998). Following this decision, caustic-leaching tests were performed under a standard set of conditions at Pacific Northwest National Laboratory (PNNL) and Los Alamos National Laboratory (LANL); these tests were conducted from FY 1995 through FY 1997. In subsequent years, a limited number of parametric caustic-leaching experiments were performed at PNNL and also at Oak Ridge National Laboratory (ORNL). After the Hanford Waste Treatment and Immobilization Plant (WTP) project was established, a limited number of laboratory-scale caustic-leaching experiments were performed using a standard testing protocol, but these were generally focused on processing double-shell tank (DST) wastes rather than the single-shell tanks (SST) where the bulk of the sludge is stored.

Caustic-leaching data are needed on the various types of wastes to be processed through the RPP-WTP to support the plant design. The data needed include 1) information regarding the removal of key HLW sludge components (e.g., Al, Cr, P, and S) as a function of caustic concentration, temperature, and time, 2) a description of the behavior of radionuclides during the leaching process, 3) particle-size distribution (PSD) data, and 4) identification of the chemical and mineral forms of important sludge components (e.g., Al, Cr, and P) in the sludge solids. These new data will support the development of various waste simulants for scaled process demonstrations.

Most of the aluminum in the wastes is believed to be present in the two most common mineralogical phases: gibbsite (monoclinic $\text{Al}(\text{OH})_3$) and boehmite (orthorhombic AlOOH). Other phases present include bayorite, dawsonite, alumina silicates, and amorphous aluminum hydroxide. The dissolution rates of the two primary mineralogical phases are considerably different. Therefore, the leaching kinetics will depend on the relative amounts of these phases in the waste as well as particle size, crystal habit (i.e.,

particle size and shape), operating temperature, hydroxide activity, aluminum solubility limits, particle Reynolds number associated with the mixing system, etc. While there may be other phases of aluminum compounds in the waste solids, they are present in relatively smaller amounts and therefore are considered less significant to the caustic leaching for the removal of aluminum from the HLW.

The simulant development strategy is based on a two-phased approach. The first phase includes simulant development and the validation of initial single-component chemical and physical simulants for boehmite, gibbsite, chromium, and filtration. The data obtained from the actual waste testing (Sundar 2006) are to serve as benchmarks for defining the simulant characteristics and behaviors to develop chemical, rheological, and physical simulants to more closely simulate actual waste and as a basis for revising the parameters used in evaluating WTP process performance using the appropriate process models.

The second phase of the simulant development work involves refinement of the first four component simulants based on additional tank waste characterization data. In addition, the other component simulants (such as phosphate) will be developed during this stage. This report only addresses the first phase of the simulant development work relating to the gibbsite simulant development.

For the gibbsite simulant developed as part of this report, this process involved two steps. In the first step, since no historical dissolution rate data was available for gibbsite phases in actual waste, the gibbsite was chosen solely based on physical characteristics and primarily based upon appearance in SEM micrographs. In the second step, once dissolution rate data was available for gibbsite in actual waste, this dissolution rate data was used to assess the choice of gibbsite material used.

2.0 Gibbsite Source Characterization

Five samples of gibbsite were obtained from two sources, BASF and Almatris, as shown in Table 2.1. The characterization and testing of these five gibbsite samples are described in this section.

Table 2.1. Gibbsite Sources Characterized and Tested

Sample ID	Gibbsite Sources
G1	BASF CP-5
G2	Almatris Hydrated Alumina Ath C31C
G3	Almatris Hydrated Alumina Ath H710
G4	Almatris Hydrated Alumina Ath C333
G5	Almatris Hydrated Alumina Ath C33

2.1 X-ray Diffraction (XRD)

The XRD instrument used for this analysis was a Scintag PAD V X-ray Diffractometer. Data were taken from 5 to 65 degrees 2-theta with a step size of 0.02 degrees 2-theta and a counting time between 2 and 19 seconds per step. Copper K α X-rays were used. Tube conditions were 45 kV and 40 mA.

Phases were identified with the JADE search match routines (Version 8.0, Materials Data Inc.) with comparison to the International Centre for Diffraction Data (ICDD) database PDF-2 release 2006, Version 2.0602, which includes the Inorganic Crystal Structure Database (ICSD) maintained by Fachinformationszentrum (FIZ), Karlsruhe, Germany. The first identification pass was done with no chemistry restrictions and usually identified TiO₂, the internal standard. The next pass was done with the identified chemistry restrictions of Al, O, H with probable phases boehmite, gibbsite, and “pseudoboehmite” required. This resulted in identifying the aluminum-containing phases.

Crystalline phases in sample G1 (BASF CP-5) were essentially unidentifiable due to very high background and very low peak intensity, indicating that it was at least partially amorphous. Samples G2 through G5 were identified as gibbsite. The XRD patterns for these gibbsite samples are shown in Figure 2.1 through Figure 2.5.

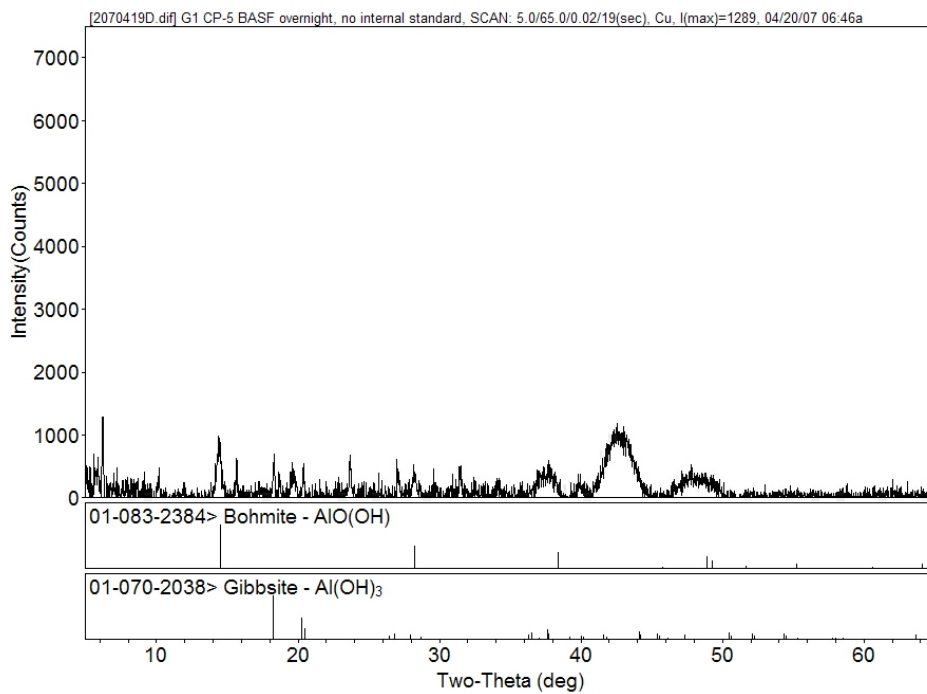


Figure 2.1. XRD Pattern of Gibbsite Sample G1 (BASF CP-5)

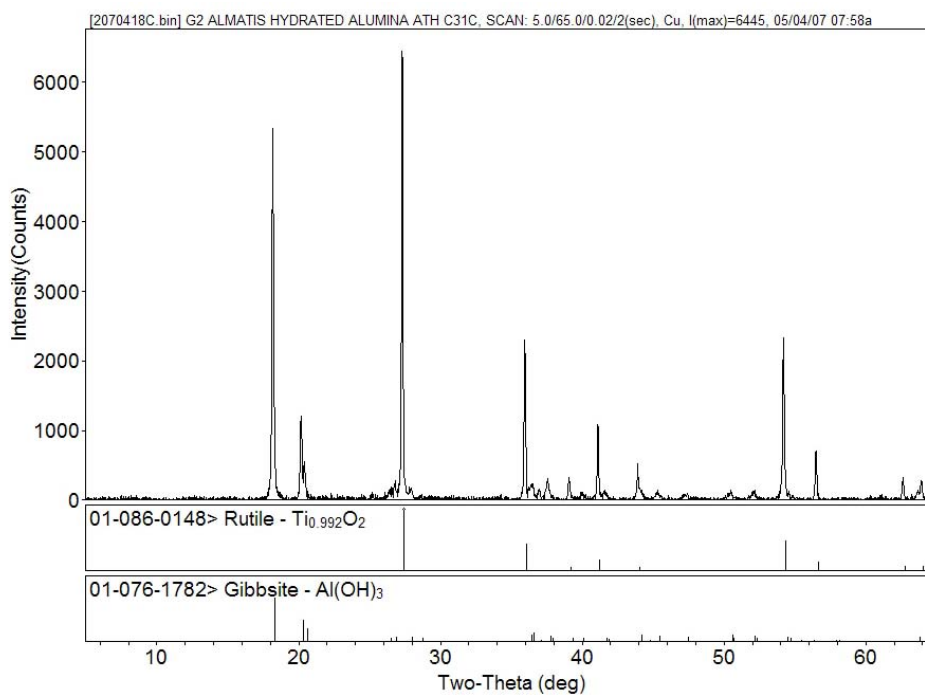


Figure 2.2. XRD Pattern of Gibbsite Sample G2 (Almatis C31C)

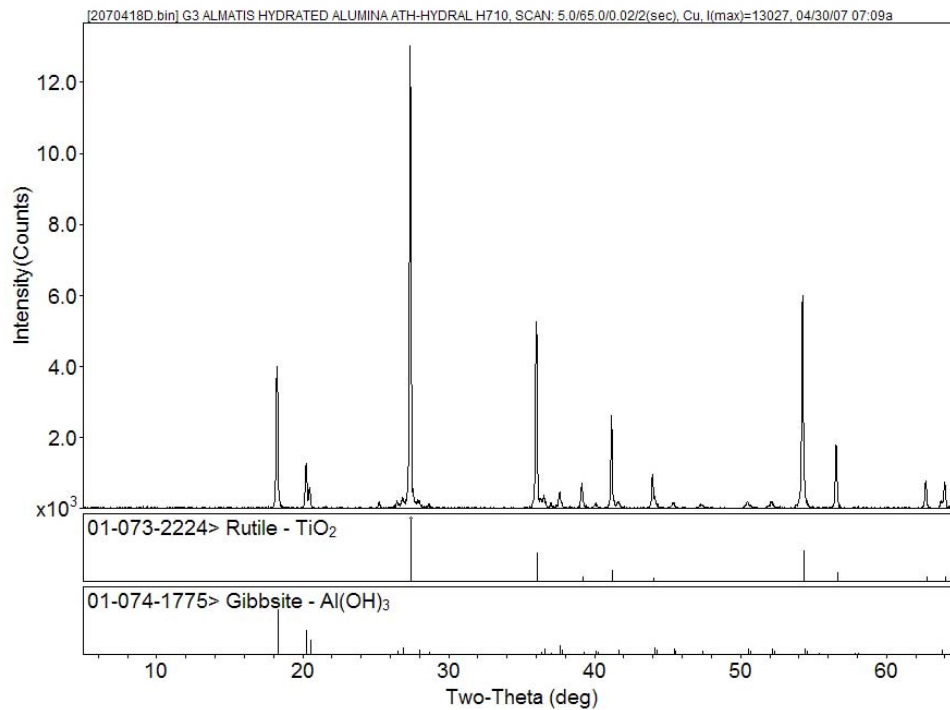


Figure 2.3. XRD Pattern of Gibbsite Sample G3 (Almatis H710)

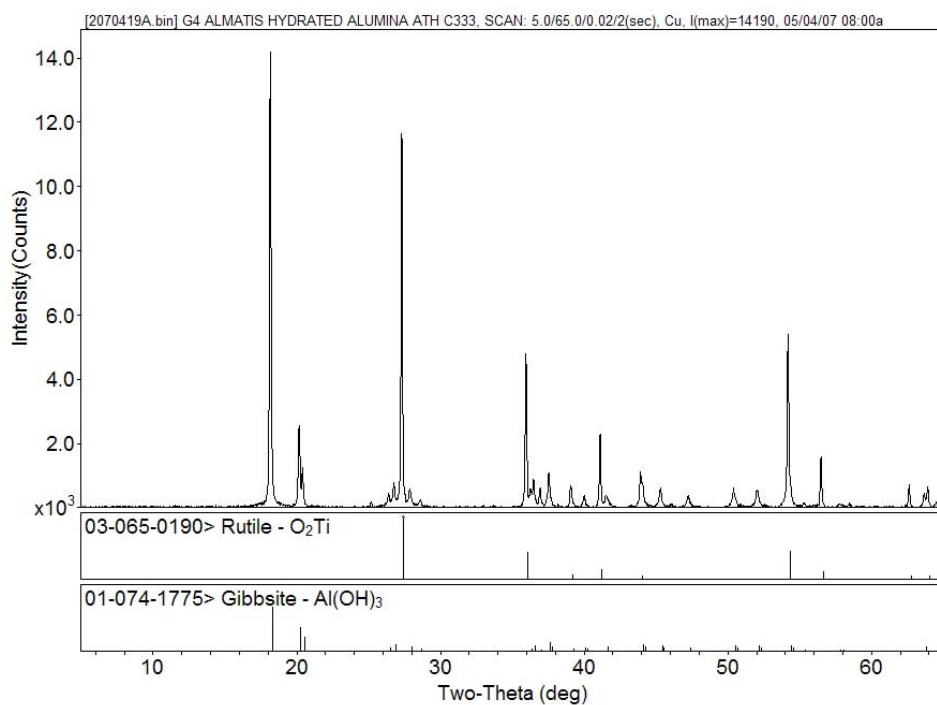


Figure 2.4. XRD Pattern of Gibbsite Sample G4 (Almatis C333)

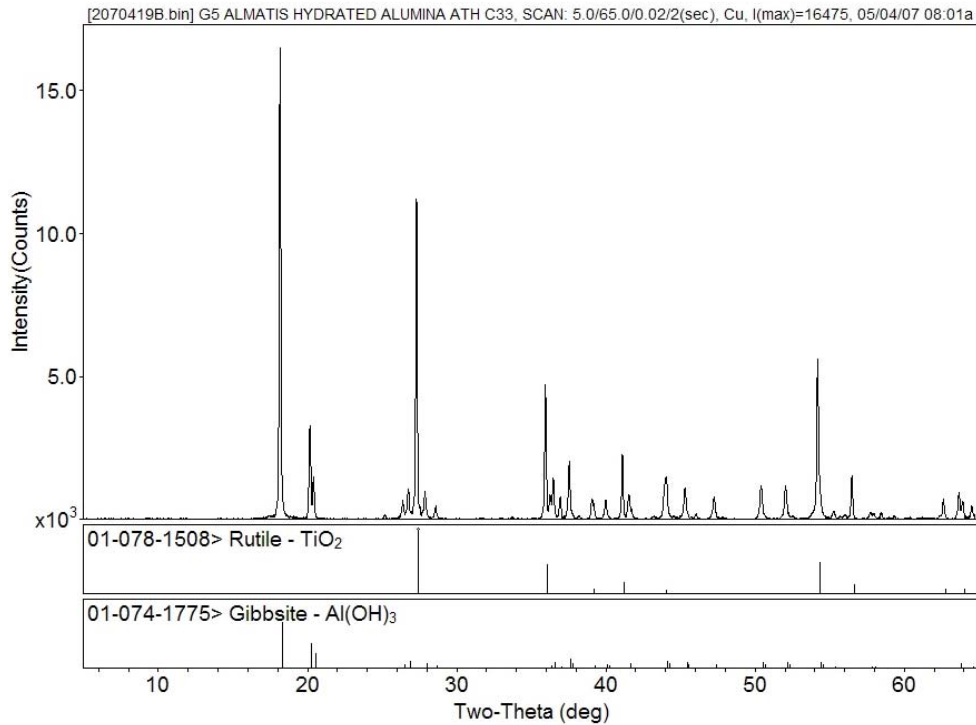


Figure 2.5. XRD Pattern of Gibbsite Sample G5 (Almatis C33)

2.2 Particle-Size Distribution

The gibbsite samples were analyzed with a S3000 Microtrac Analyzer according to procedure TPR-RPP-WTP-222, Rev. 3 to obtain the particle size distribution (PSD). Nominally 0.2 grams of each sample (run in duplicate) was placed into approximately 10 grams of de-ionized water (DIW), and 2 to 3 drops of Darvan[®] 821A Dispersing Agent were added. The resultant slurry was de-agglomerated using an ultrasonic horn (MICROGON Ultrasonic Cell Disrupter) intermittently for 15 to 20 seconds. A transfer pipette was used to mix the slurry and transfer the required amount to the analyzer. The amount of the slurried sample aliquot required for analysis varied with the actual mass of the sample and the actual volume of DIW in the sonicated sample. Neither the amount of sample nor the amount of water was critical to the analytical process since the internal system software visually indicated to the analyst the amount needed for analysis. Summary results are shown in Table 2.2 and Table 2.3, and the complete data sets are plotted in Figure 2.6 and Figure 2.7.

Table 2.2. Volume Distribution of Gibbsite Particle-Size Results

Percentile	G1 (μm)	G2 (μm)	G3 (μm)	G4 (μm)	G5 (μm)
5	1.08	0.61	0.60	0.72	27.23
20	2.64	0.92	0.89	1.72	45.26
30	3.85	1.12	1.05	2.75	50.74
40	5.37	1.31	1.21	4.12	55.58
50	7.21	1.50	1.36	5.88	60.44
60	9.16	1.72	1.52	8.04	65.87
70	11.19	1.97	1.71	10.89	72.53
80	13.53	2.29	1.96	15.01	82.14
90	16.98	2.83	2.39	22.05	100.6
95	20.27	3.40	2.84	29.33	123.3

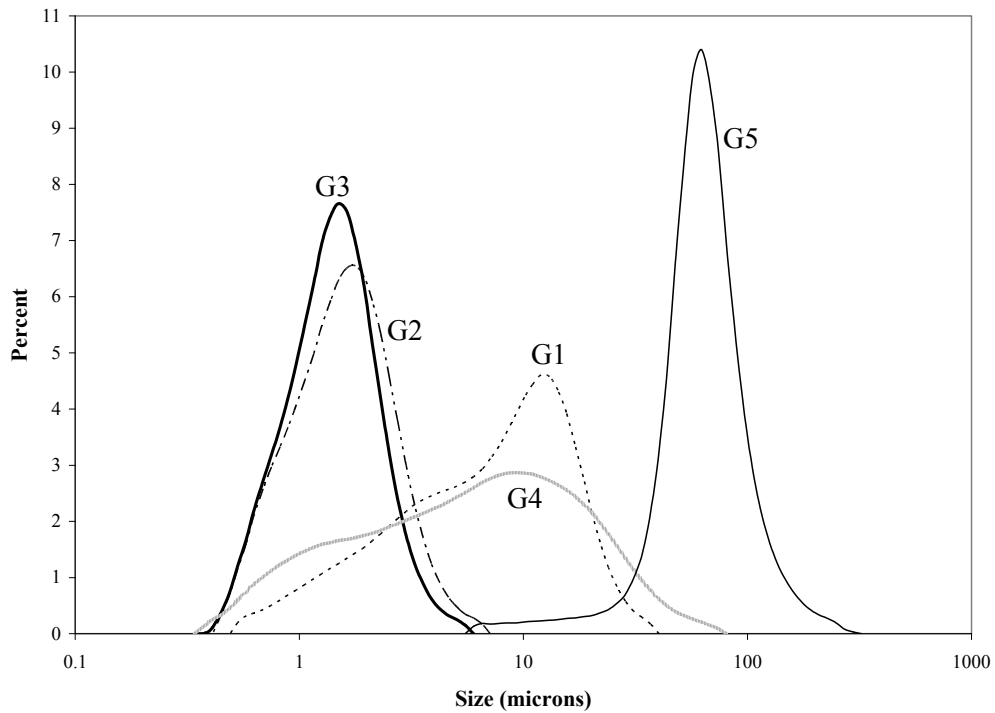


Figure 2.6. Volume Distribution of Particle Size Plot of Gibbsite Sources

Table 2.3. Number Distribution of Gibbsite Particle-Size Results

Percentile	G1 (μm)	G2 (μm)	G3 (μm)	G4 (μm)	G5 (μm)
5	0.51	0.45	0.43	0.37	5.72
20	0.57	0.52	0.52	0.43	6.21
30	0.62	0.57	0.57	0.47	6.54
40	0.68	0.62	0.62	0.52	7.05
50	0.76	0.68	0.69	0.57	7.77
60	0.85	0.76	0.77	0.63	8.82
70	0.98	0.86	0.88	0.71	10.54
80	1.19	1.02	1.03	0.84	14.60
90	1.61	1.30	1.28	1.09	36.01
95	2.17	1.58	1.52	1.41	49.95

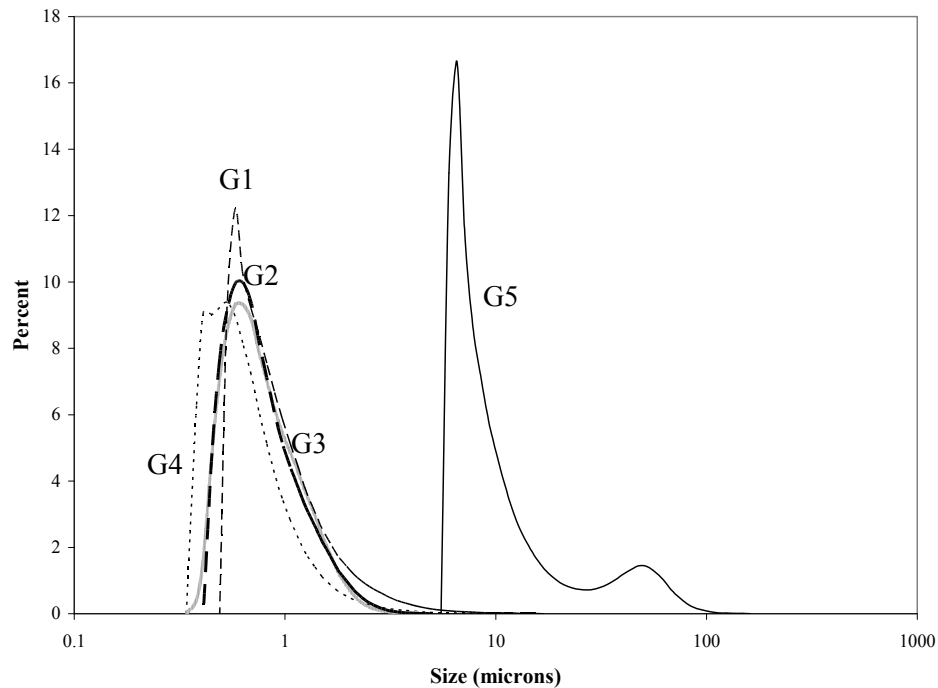


Figure 2.7. Number Distribution Particle Size Plot of the Gibbsite Sources

2.3 Scanning Electron Microscope (SEM)

The SEM images were obtained with a Jeol JSM-5900 SEM with the sample on a glass slide and coated with carbon. The micrographs are secondary electron images. They all showed similar crystal structure with a range in sizes as shown in Figure 2.8 through Figure 2.12. The crystals from samples G2 and G3

were very small. Sample G5 crystals appeared to be highly agglomerated. Samples G1 and G4 had similar crystal sizes that were between the sizes of the others.

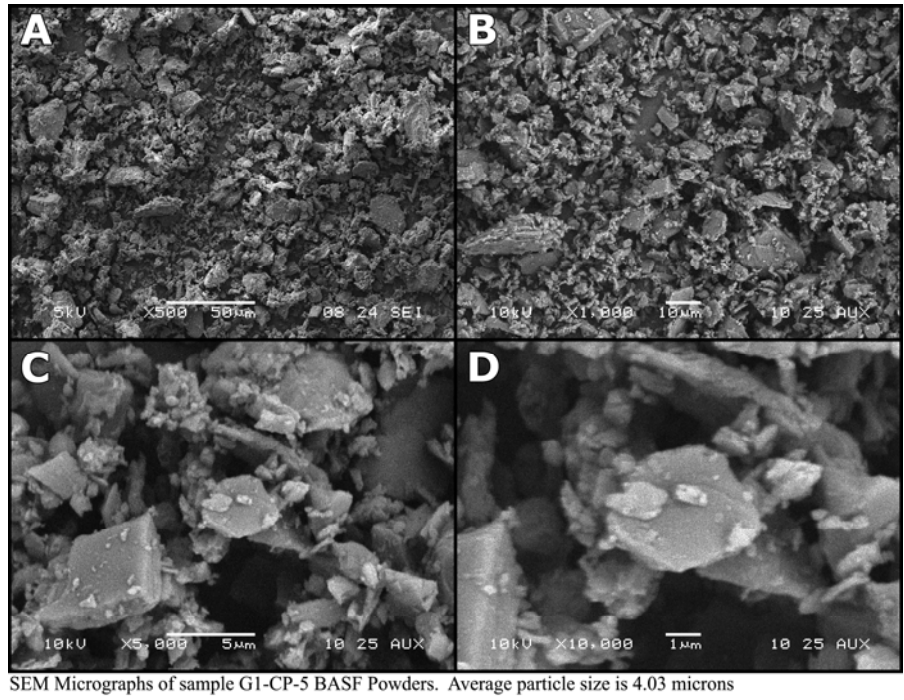


Figure 2.8. SEM Picture of “Gibbsite Sample G1” at 500×, 1000×, 5000×, and 10,000× (note that this sample was later determined to not contain gibbsite)



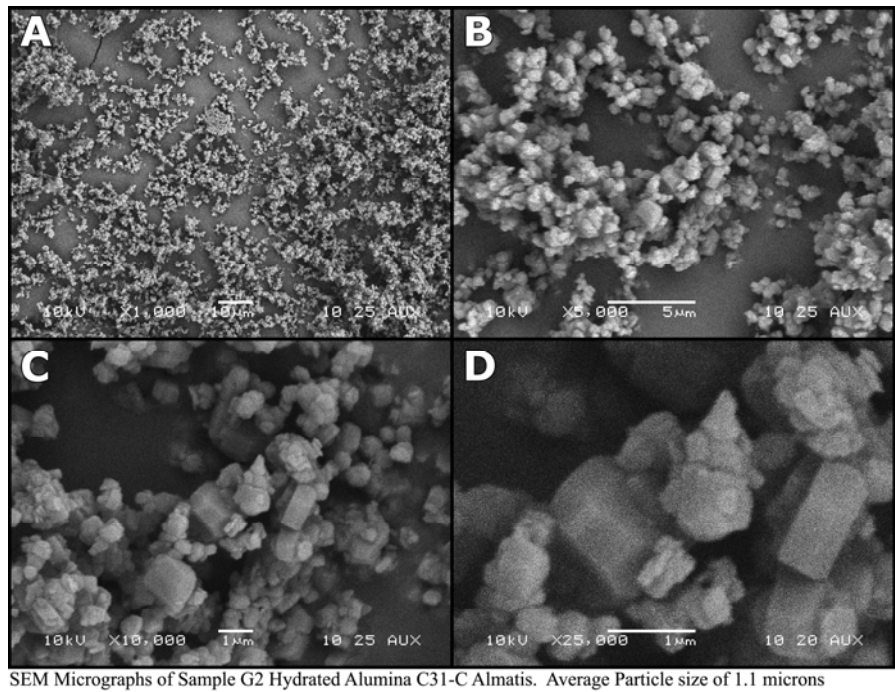


Figure 2.9. SEM Picture of Gibbsite Sample G2 at 1000×, 5000×, 10,000×, and 25,000×

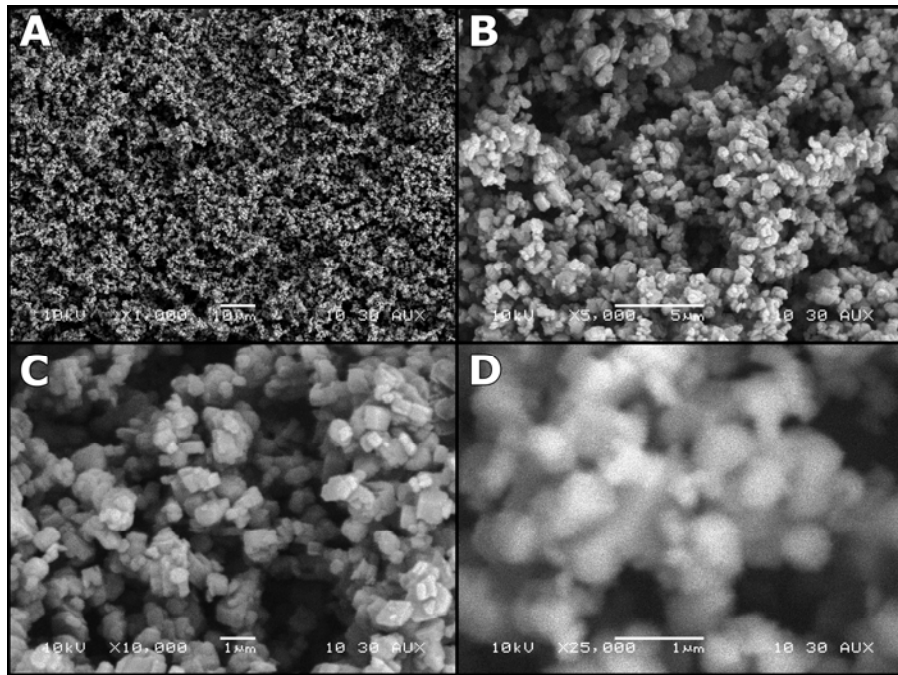

SEM micrographs of G3 Hydrated Alumina ATH Hydral H710 Almatiss. Average Particle Size of 0.86 microns.

Figure 2.10. SEM Picture of Gibbsite Sample G3 at 1000×, 5000×, 10,000×, and 25,000×

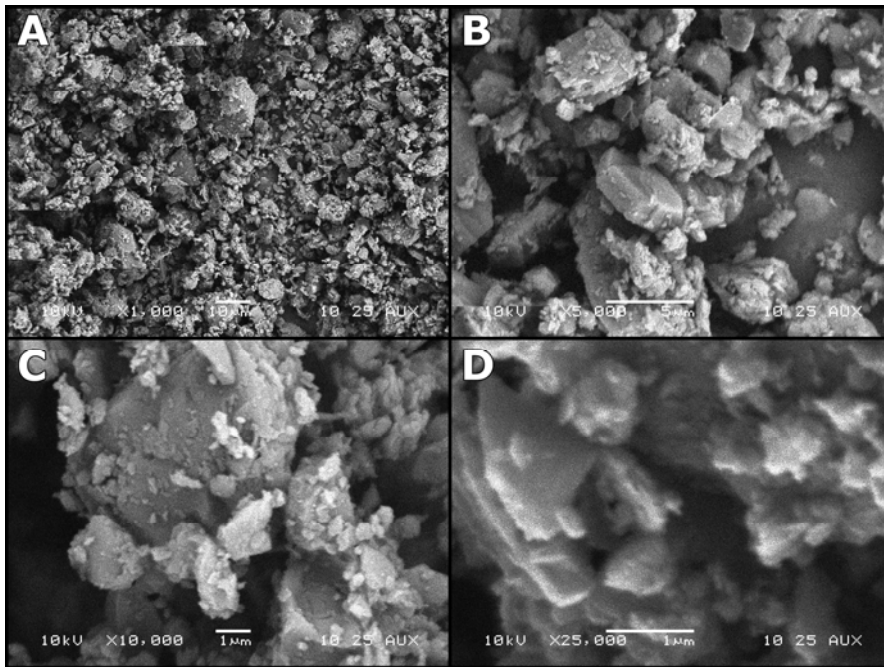

SEM micrographs of Sample G4 Hydrated Alumina ATH C333 Almatiss. Average Particle Size of 4.05 microns.

Figure 2.11. SEM Picture of Gibbsite Sample G4 at 1000×, 5000×, 10,000×, and 25,000×

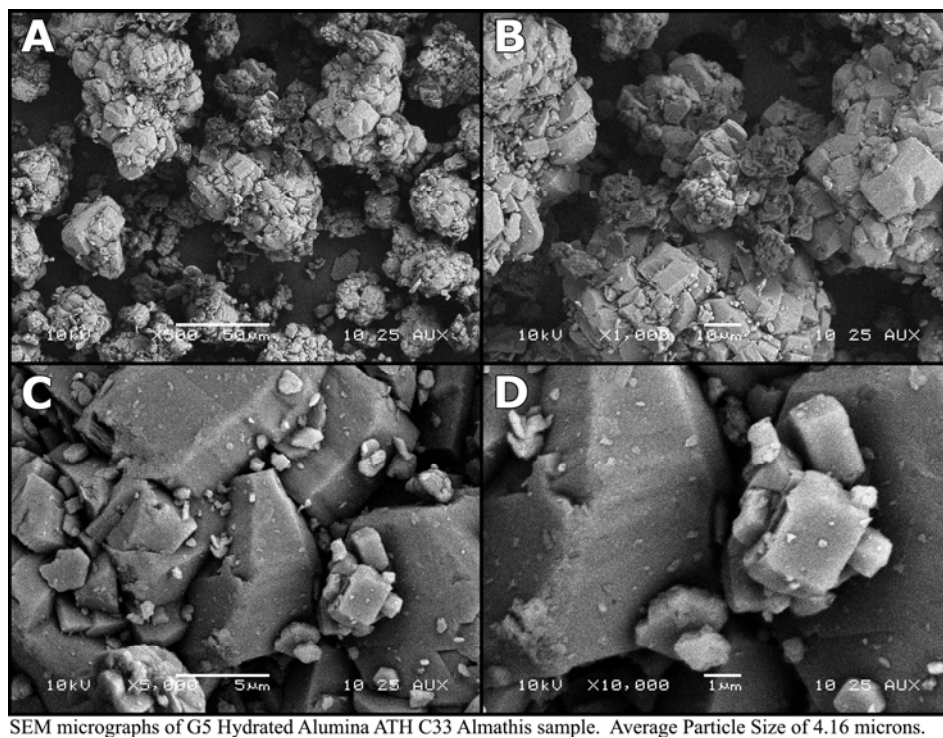


Figure 2.12. SEM Picture of Gibbsite Sample G5 at 500×, 1000×, 5000×, and 10,000×

2.4 Surface Area

The surface areas were measured with a Quantachrome Instruments Monosorb Surface Area Analyzer. The Monosorb is a direct-reading, dynamic-flow, surface-area analyzer that uses a modified Brunauer, Emmett, and Teller (BET) equation for single-point determinations of surface area. Measurements were taken in accordance with PNL-RW-05-BET and OCRWM-BET-01.

Standard surface-area reference material (SARM) was used to calibrate the instrument over the anticipated range of interest. Each sample was weighed and dried for no less than 30 minutes before analysis. The Monosorb measures the quantity of a gas adsorbed on a solid surface by sensing the change in thermal conductivity of a flowing mixture of an adsorbate and an inert carrier gas, nitrogen and helium, respectively. The specific surface area is calculated by dividing the average of the surface area measurements obtained by the BET method by the weight of the sample. Based on the small sample used for G3 and the fact that the data is not consistent with the PSD and the leaching results, this data may not be accurate and should be used as information only. These results are shown in Table 2.4.

Table 2.4. BET Surface Area of Gibbsite Samples

Sample ID	Mass (g)	Surface Area (m ²)	Specific Surface Area (m ² /g)	Std Dev
G1	0.0359	0.2902	8.084	0.017
G2	0.2903	1.376	4.739	0.018
G3	0.0043	0.046	10.775	2.032
G4	0.2722	1.315	4.832	0.221
G5	0.455	0.252	0.545	0.097

2.5 Screening Leach Test

A screening test approach to provide dissolution rate data for these gibbsite samples was used that could be compared to the data for actual waste gibbsite dissolution rates.

These caustic leaching tests were set up as shown in Figure 2.13 using 1-wt% gibbsite solids in 800 grams of 3M NaOH solution that was heated to a temperature of 60°C while stirring in a 1-liter reaction vessel. The temperature was measured with a calibrated thermocouple and controlled using a calibrated temperature controller. Gibbsite was added as a powder to the reaction vessel through the sample port while stirring after the NaOH solution had reached temperature, which then started the clock for the test. The test solution was sampled at 1, 2, 4, 8, and 24 hours. Each sample consisted of 5-mL supernatant, which was filtered through a 0.45- μ m filter after being drawn from the reaction vessel and then analyzed for aluminum and sodium by inductively coupled plasma-atomic emission spectrometry (ICP-AES) with the results shown in Table A.1.

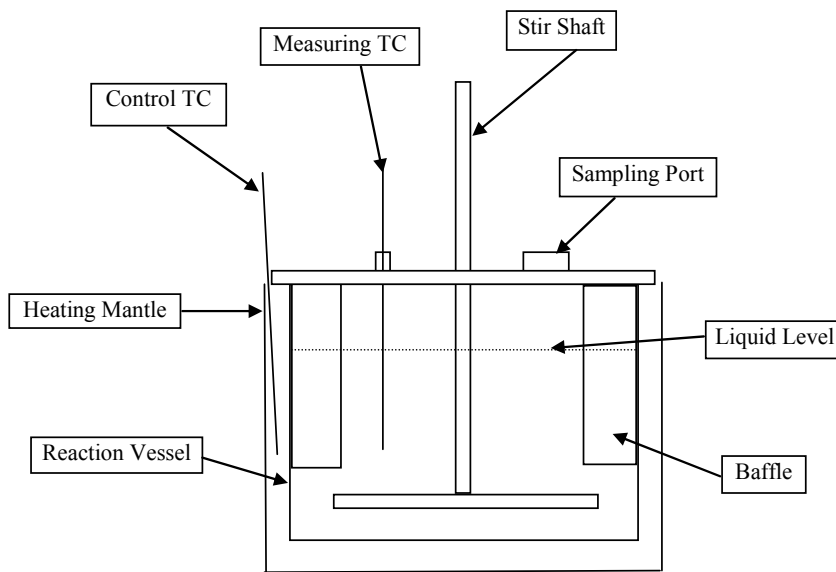


Figure 2.13. Schematic Drawing of the Caustic Leaching Test Setup

The percent gibbsite dissolved results from the gibbsite leaching tests are given in Table 2.5 and shown in Figure 2.14. The actual amounts of aluminum and sodium in solution are given in Appendix A. Based on the characterization and leaching results, it was determined that G1 (BASF CP-5) was not gibbsite but appeared to be amorphous alumina. Therefore, this sample was immediately eliminated from consideration for further testing. Samples G2 and G3 behaved similarly with 100% dissolving by the end of the test. Sample G4 dissolved a little slower than G2 and G3. Sample G5 dissolved very slowly and had not completely dissolved by the end of the leaching test. This is most likely due to the large particle size and low surface area of this gibbsite.

Table 2.5. Screening Gibbsite Leaching Test Results

Percent of Gibbsite Dissolved						
Time - h	G1 (as gibbsite)	G1 (as alumina)	G2	G3	G4	G5
0	0	0	0	0	0	0
1	87.5	57.2	90.5	101.2	56.6	23.7
2	99.5	65.1	98.9	100.1	67.3	38.5
4	119	77.7	101.7	98.3	80.8	54.5
8	130	85.0	103.5	101.8	91.5	72.8
24	132	86.2	100.5	102.6	100.6	91.2

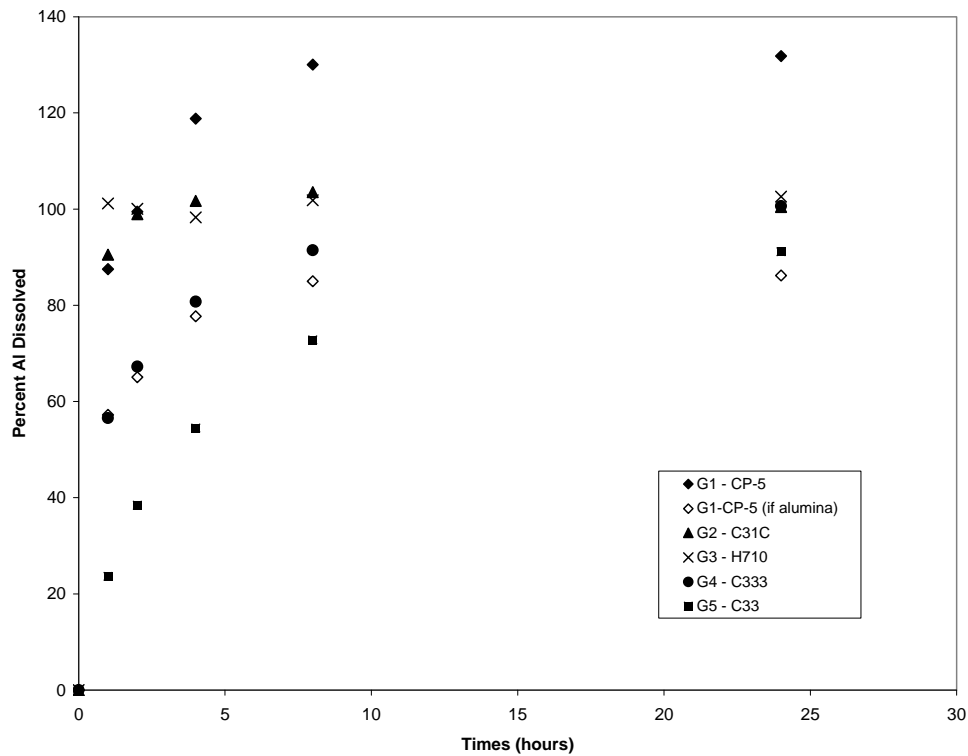


Figure 2.14. Percent Al Dissolved in the Screening Gibbsite Leaching Test Results

3.0 Determination of the Appropriate Gibbsite Simulant

The gibbsite simulant to use for further testing was based primarily on the crystal size and shape of the simulant in comparison to the actual waste gibbsite particles. Figure 3.1 shows the images of actual waste gibbsite crystals along with images of the five gibbsite simulants at 1000X. The crystals from samples G2 and G3 are clearly too small. Sample G5 appears to have an appropriate crystal size, but the crystals appear to be highly agglomerated, eliminating it from consideration.

A preliminary inspection of particle size suggests that either Sample G1 or Sample G4 would be most appropriate for carrying forward in future testing. However, XRD analysis of these two samples (shown in Figure 3.2 and Figure 3.3) along with caustic leaching results indicate that sample G1 does not contain gibbsite, but rather an amorphous alumina material, while sample G4 does contain gibbsite (note that the XRD pattern for sample G4 also shows a rutile internal standard added to validate the performance of the instrumentation).

Based on these results, PNNL proceeded with parametric testing using sample G4 (Almatis C333). The product specifications are shown in Appendix C.

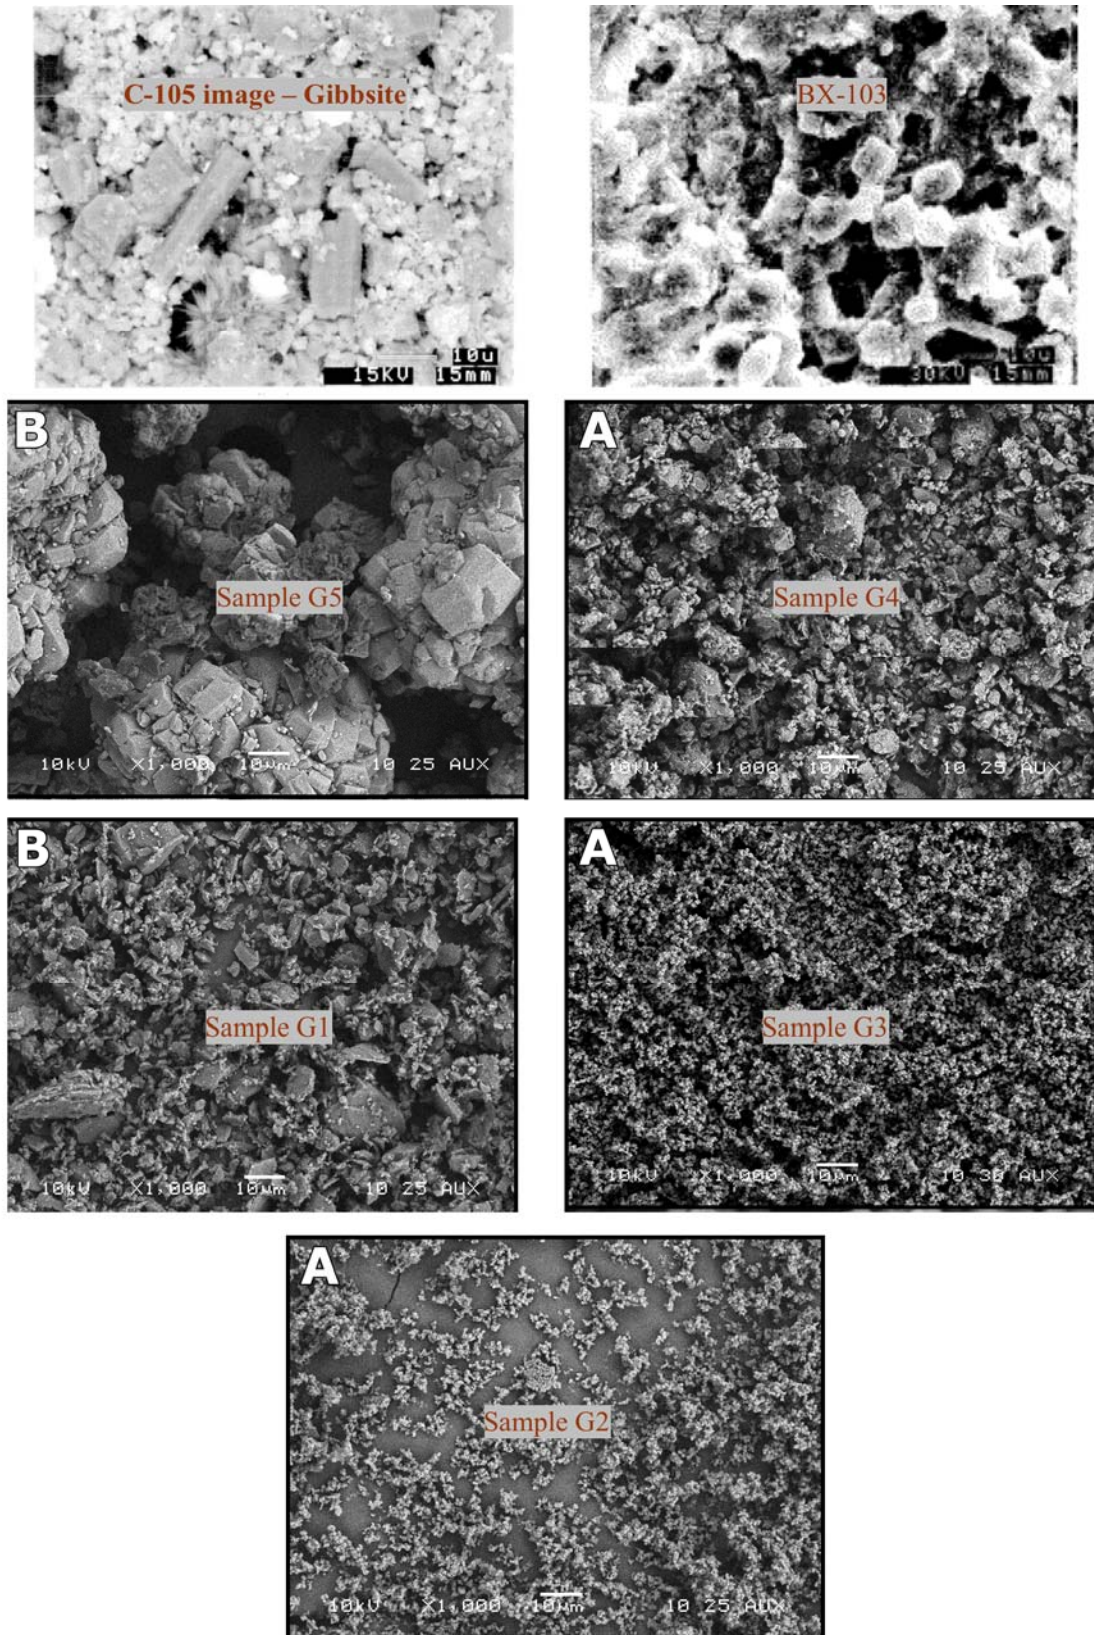


Figure 3.1. Gibbsite Simulant Crystals Compared to Actual Tank Waste Crystals at 1000×

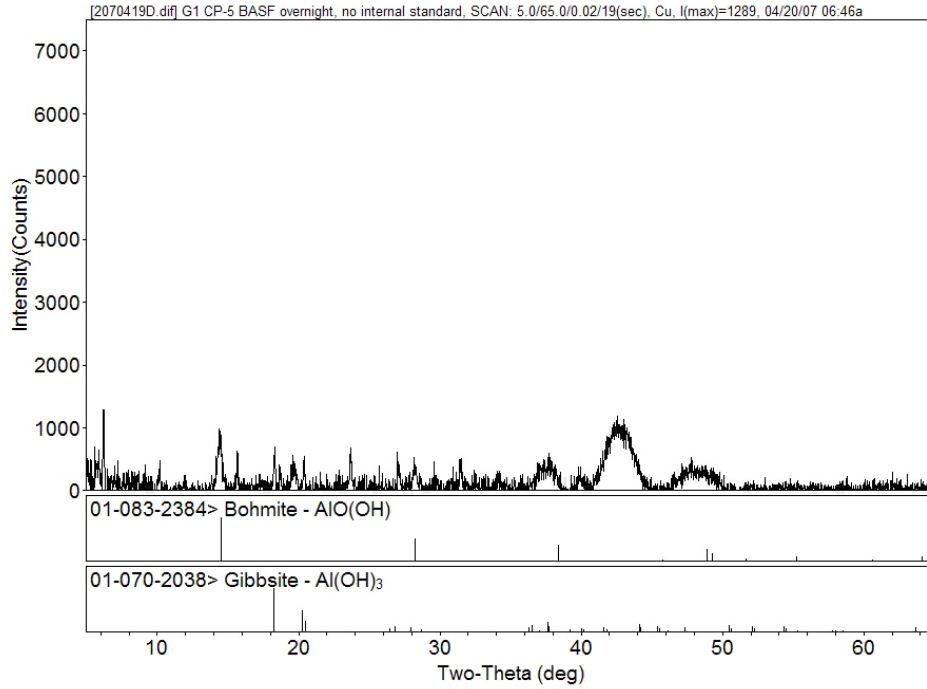


Figure 3.2. XRD Pattern for Sample G1

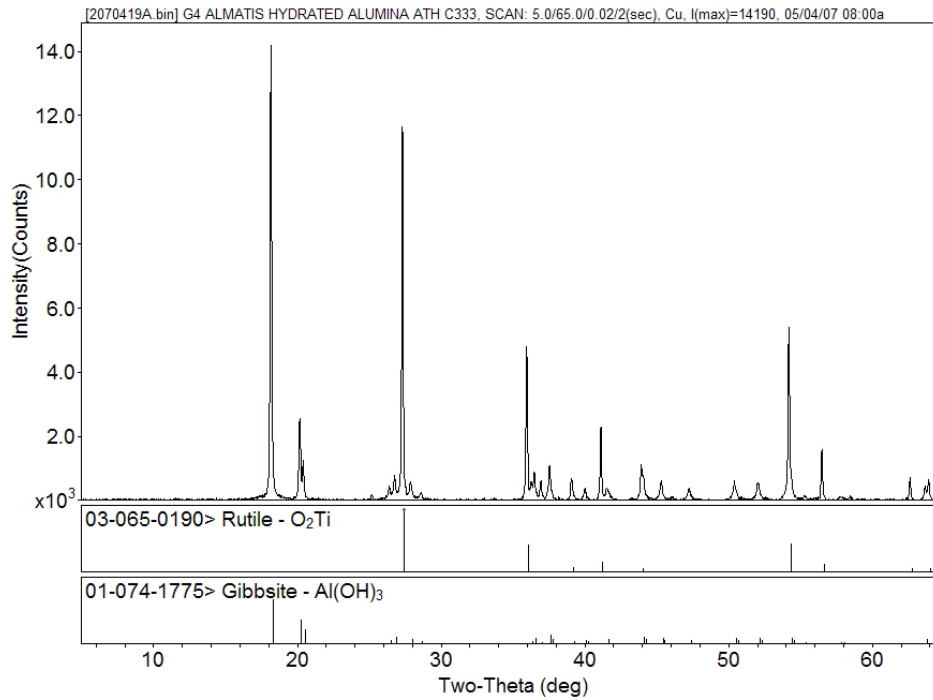


Figure 3.3. XRD Pattern for Sample G4

4.0 Gibbsite Simulant Dissolution Test Matrix Results

The dissolution rate for gibbsite is expected to be a function of temperature, solution chemistry, surface-to-volume ratio, and stirring rate. These variables were tested to determine the effect of each on the dissolution rate of the G4 (Almatis C333) gibbsite, as shown in Table 4.1. This test matrix is based on a statistical design with the temperature, leach solution concentration, and the expected percent solubility of the sample being the primary variables and the degree of mixing being a secondary variable. The time to achieve a specific dissolution percentage is the dependent variable and the temperature, stirring rate, and hydroxide concentration are the independent variables in this experimental design.

Known quantities of gibbsite were exposed with stirring to a given volume of caustic leach solution under the conditions listed in Table 4.1 in a reaction vessel. Note that tests 1 and 9 are duplicates, and tests 8 and 10 are duplicates. In addition, tests 11 through 13 are triplicate experiments. These replicates were performed to provide an understanding of the reproducibility of the tests. Also, these tests were performed as a statistical design to allow testing to obtain the maximum amount of information in a limited data set. These tests are a fractional factorial statistical design and as such do not cover all the conditions within the range tested.

The airtight reaction vessel was equipped with a mechanical stirrer, a thermocouple, and a port for sampling as shown in Figure 2.13. Samples of supernatant were taken at 1, 2, 4, 8, and 24 hours and analyzed to determine how much gibbsite had dissolved by measuring aluminum and sodium concentration using ICP-AES with the results shown in Tables A.2 and A.3.

The temperature range for the test matrix was chosen to provide an upper and lower bound on the expected plant operating condition for gibbsite leaching. A heating jacket around the vessel maintained the test mixture at a constant temperature throughout the test.

The percent solubility primary variable is an indicator of the gibbsite sample size relative to the leach solution for each test condition. It is defined as the aluminum concentration assuming 100% dissolution divided by the solubility limit. Thus, when the target value is 50%, then the test contains sufficient gibbsite to reach 50% of the solubility limit. The gibbsite solubility was calculated using the equation of Li et al. (2005), which is an empirical model based on historical solubility data and is shown below.

$$\ln(C) = 5.71 - \frac{2486.70}{T} + \frac{33.71[NaOH]}{T} + \ln[NaOH]$$

The percent solubility range was chosen to provide insight into the impact of the approach to solubility on the dissolution rate.

The leach-solution hydroxide concentration was defined as the concentration before the start of testing, and the concentrations tested were chosen to bound the expected range of conditions in the WTP.

The stirring (mixing) rates were chosen to provide different levels of solids suspension in the supernatant, based on degree of agitation of the surface of a water sample in the test vessel. The minimal speed was just slow enough to leave the water surface undisturbed when viewed with reflected light. The full

mixing resulted in a well-agitated surface, and the intermediate mixing rate resulted in minor agitation of the surface. The minimal mixing rate (40 rpm) was intended to be just sufficient to keep the solids from completely settling on the bottom of the container in order to maintain contact with the bulk liquid. The full speed rate was intended to give a completely homogeneous suspension of the solids, and the ½ speed rate was intended to result in an intermediate solids suspension. The digital rate controllers for the stirring motors were set to specific revolutions per minute (rpm), and the rates at different settings verified by direct observation and manual timing. The variation in the stirring rates is expected to be less than 1%.

Table 4.1. Gibbsite Testing Matrix

Test ID	% Solubility	Temperature (°C)	Mixing (rpm)	Leach Soln Conc.
MTG-1	100	80	Full (120)	5 M NaOH
MTG-2	50	80	Minimal (40)	5 M NaOH
MTG-3	100	80	Minimal (40)	1 M NaOH
MTG-4	50	80	Full (120)	1 M NaOH
MTG-5	100	40	Minimal (40)	5 M NaOH
MTG-6	50	40	Full (120)	5 M NaOH
MTG-7	100	40	Full (120)	1 M NaOH
MTG-8	50	40	Minimal (40)	1 M NaOH
MTG-9	100	80	Full (120)	5 M NaOH
MTG-10	50	40	Minimal (40)	1 M NaOH
MTG-11	75	60	½ Speed (60)	3 M NaOH
MTG-12	75	60	½ Speed (60)	3 M NaOH
MTG-13	75	60	½ Speed (60)	3 M NaOH

Figure 4.1 shows the effect of hydroxide concentration on gibbsite dissolution with the 5-M NaOH solution dissolving more than the 1-M NaOH solution (MTG-6 and MTG-7). This indicates that hydroxide concentration has a significant effect on the gibbsite dissolution. Complete results of these tests are shown in Appendix A.

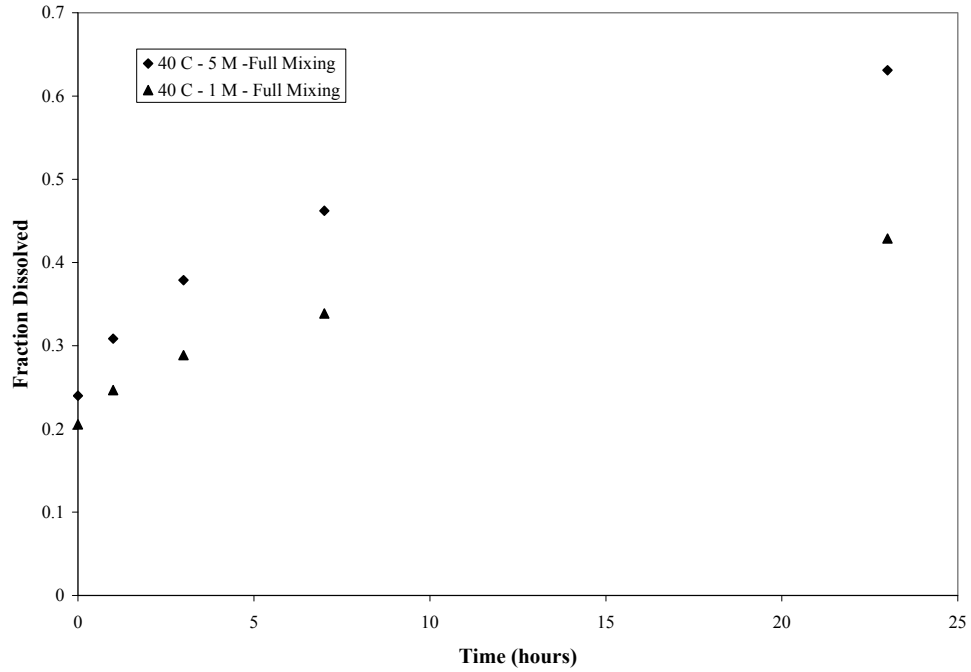


Figure 4.1. Effect of Hydroxide Concentration on Gibbsite Dissolution.
Results of Tests MTG-6 and MTG-7

Figure 4.2 compares dissolution data for gibbsite leached at 40°C and 80°C in 5 M NaOH at full mixing (120 rpm) (MTG-1 and MTG-6). Mixing over the range tested has a significant effect in the dissolution rate for the gibbsite tested (G4).

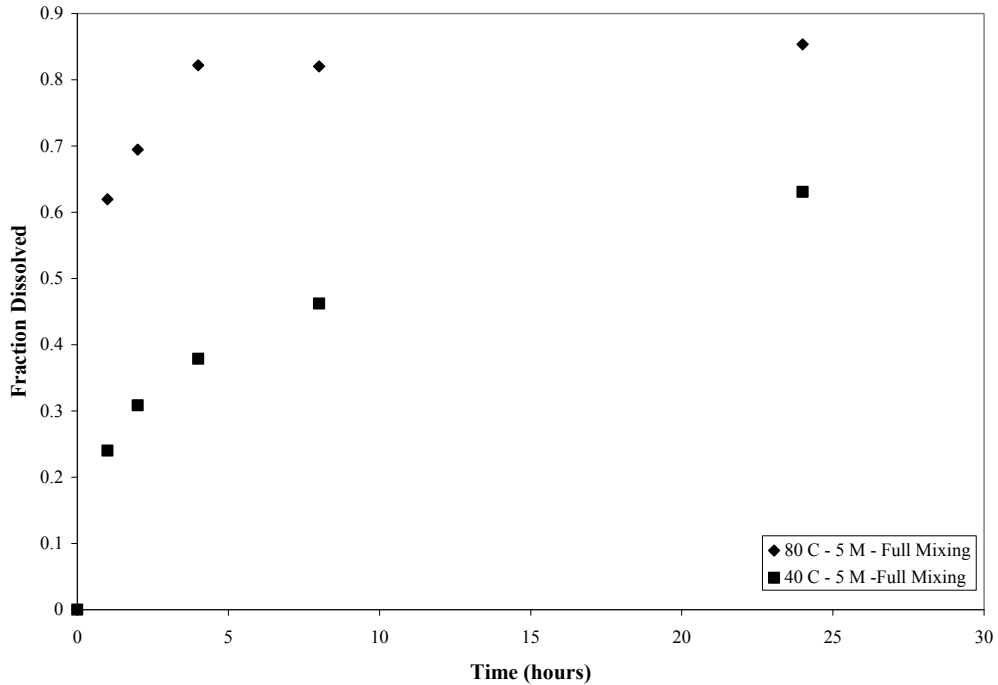


Figure 4.2. Effect of Temperature on Gibbsite Dissolution.
Results of Tests MTG-1 and MTG-6

Mixing rates of 40, 60, and 120 rpm were employed for these tests. In general, it was observed that at 40 rpm, most of the gibbsite settled to the bottom of the reaction vessel, and the supernatant remained visibly clear. At 60 rpm, the settled layer was thinner, and some material appeared to be suspended in the supernatant. At 120 rpm, there was no settled layer, and the mixture appeared to be a uniform milky white. It can be surmised that the access of the hydroxide solution to the aluminum phase was much better at the highest rate of stirring used than at the lowest.

Figure 4.3 shows that mixing at 40°C for both 1 M and 5 M NaOH had a significant effect on the gibbsite dissolution (MTG-5 through MTG-8). The effect was greater; however, in the 5-M NaOH solution indicating that hydroxide concentration has a greater effect than the mixing rate. In all cases, an increased stirring (mixing) rate was observed to increase the dissolution rate.

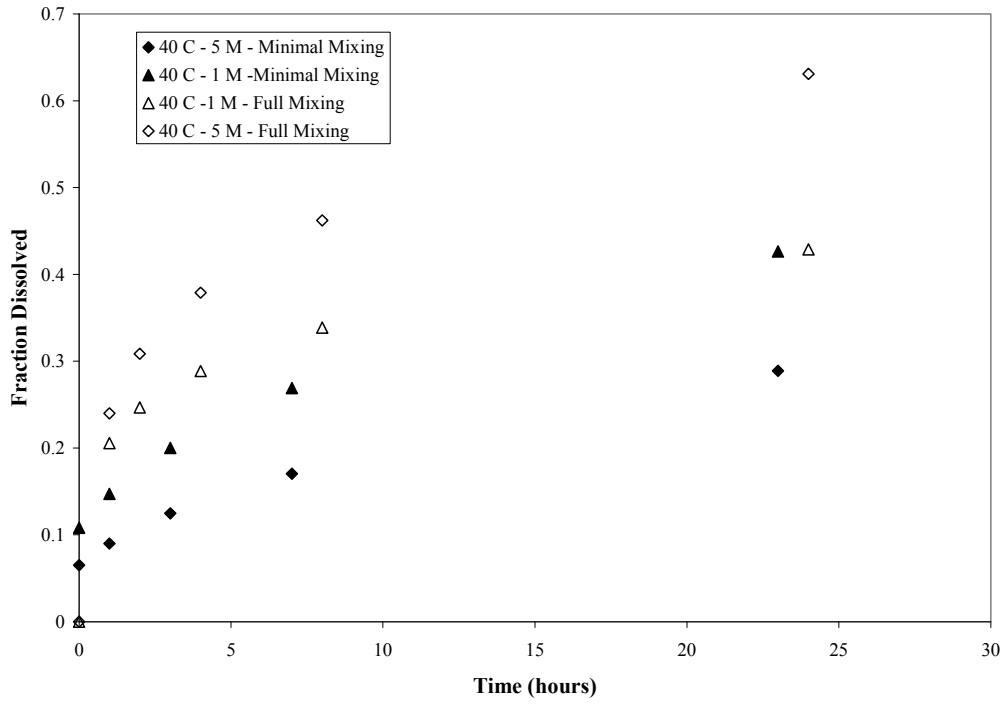


Figure 4.3. Mixing Effect on Gibbsite Dissolution in 1 M (MTG-7 and MTG-8) and 5 M NaOH (MTG-5 and MTG-6) at 40°C

5.0 Gibbsite Simulant Blend Testing

The G4 gibbsite simulant that was chosen to be the “component” simulant was blended in a specified ratio with the other chosen “component” simulants for boehmite and ultrafiltration. This blended simulant was then tested over a subset of the matrix conditions in which the component simulants had been tested previously. These results show how the other components interact with the gibbsite and whether they hinder, help, or have no effect on its dissolution. The ratios of component materials used in these tests were obtained from the response to the External Flowsheet Review Team (EFRT) Issue M4.

Table 5. provides the sequence of tests performed as part of this test matrix. Tests 1 through 6 provide a statistical design to evaluate the effect of gibbsite and filtration components on the dissolution of boehmite and the effect of filtration components on gibbsite dissolution. Only the tests examining gibbsite dissolution (BSM-3 and BSM-4) are discussed in this report with the analytical results shown in Table A.4.

Table 5. provides the composition of the supernate that was used in these tests. This supernate composition was chosen to provide continuity in boehmite leaching experiments. It is based on a 3.2-M Na concentration, which resembles a particular actual waste supernate (Fiskum 2008)—however, the choice of supernates was not significant relative to the behavior of the gibbsite simulant.

Table 5.2. Supernate Composition at 3.2 M Na

Component	Chemical Formula	Concentration (M)
Sodium phosphate	$\text{Na}_3\text{PO}_4 \cdot 12\text{H}_2\text{O}$	0.013
Sodium sulfate	Na_2SO_4	0.008
Sodium carbonate	Na_2CO_3	0.576
Sodium oxalate	$\text{Na}_2\text{C}_2\text{O}_4$	0.016
Sodium nitrite	NaNO_2	0.528
Sodium nitrate	NaNO_3	1.44

Table 5.1. Blended Component Test Matrix

Test	Sludge Simulant (g)	Boehmite (g)	Oxalate (g)	Gibbsite (g)	19 M NaOH (g)	Condensate (DI water) (g)	Supernate (g)	Mixing Speed (rpm)	[OH] Molarity	Na Molarity	Notes
BSM-3	12.99	0.00	0.00	22.73	200.27	274.96	259.82	140	5.8	7.1	Full factorial for Gibbsite/Boehmite/Sludge Solids—oxalate as secondary variable
BSM-4	0.00	0.00	6.50	22.73	200.27	274.96	259.82	140	5.8	7.1	Full factorial for Gibbsite/Boehmite/Sludge Solids—oxalate as secondary variable

The results of BSM-3 and BSM-4 showed that gibbsite dissolution is fast under the test conditions (100°C, 5.8 M OH, and 120 rpm mixing), being essentially fully dissolved within 1 hour at 100°C as shown in Figure 5.1. It appears that the oxalate tends to hold up 10% of the Al from solution over the first eight hours of leaching. However, at the end of 24 hours, both tests had 100% dissolution with data points on top of each other. Therefore, it appears that the sludge and oxalate have no significant effect on the gibbsite dissolution. It was concluded then from these results that blending the gibbsite simulant component with sludge and oxalate simulant components does not affect its dissolution from the simulant.

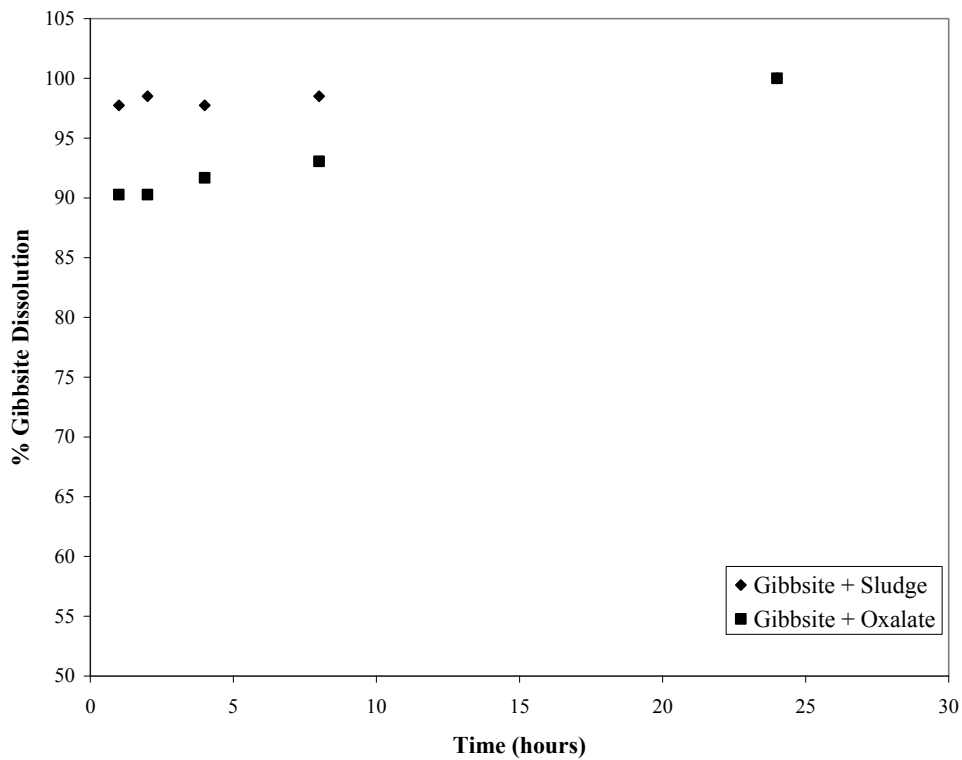


Figure 5.1. Gibbsite Dissolution in the Blended Simulant (BSM-3 and BSM-4)

6.0 Nitrate Effect on Gibbsite Dissolution

A series of tests were performed using the G4 gibbsite (Almatis C333) with varying amounts of nitrate present in the caustic leach solution to determine what effect, if any, nitrate has on the dissolution and precipitation of gibbsite in caustic solution. These tests were run in duplicate using a 3-M NaOH solution and 0-, 1-, 2-, and 3-mol sodium nitrate /kg caustic solution. Note that this was 3 mol/kg of solution and not solvent. The densities of these solutions are shown in Table 6.1. The tests were placed on a shaker table at room temperature ($\sim 20^{\circ}\text{C}$) for 30 days and allowed to approach equilibrium. The first four tests measured dissolution rates, with the dry gibbsite added to the caustic solutions at the test (room) temperature. The second four tests measured precipitation rates. In this case supersaturated solutions were created by dissolving gibbsite in solution at 100°C for 8 hours, then more gibbsite was added to the solution and the solution was cooled to the test (room) temperature. Samples were taken initially, and then after 1, 3, 5, 7, 14, 21, and 30 days. The samples were analyzed for Al and Na by ICP-AES, and the results are shown in Table A.5.

As the nitrate concentration increases, the solubility of the gibbsite in 3-M caustic solution for both dissolution and precipitation increases also as shown in Figure 6.1 and Figure 6.2. The kinetics of gibbsite dissolution does not appear to be affected by the presence of nitrate. However, the kinetics of the precipitation was slower with nitrate present. Nitrate ions can assist gibbsite dissolution, but they hinder gibbsite crystallization because they must be excluded from the forming gibbsite crystals.

The precipitation was not complete after the 30 days as the amount of aluminum in solution was still decreasing. But the amount in solution was asymptotically approaching a number greater than 1, as shown in Figure 6.3, which indicates that the aluminum in solution may be capable of remaining supersaturated which was defined based on the tests of gibbsite dissolution shown in Figure 6.1.

Table 6.1. Densities of Leach Solutions

Solution	Density (g/mL)
0 moles NO_3 /kg solution	1.12
1 moles NO_3 /kg solution	1.18
2 moles NO_3 /kg solution	1.24
3 moles NO_3 /kg solution	1.32

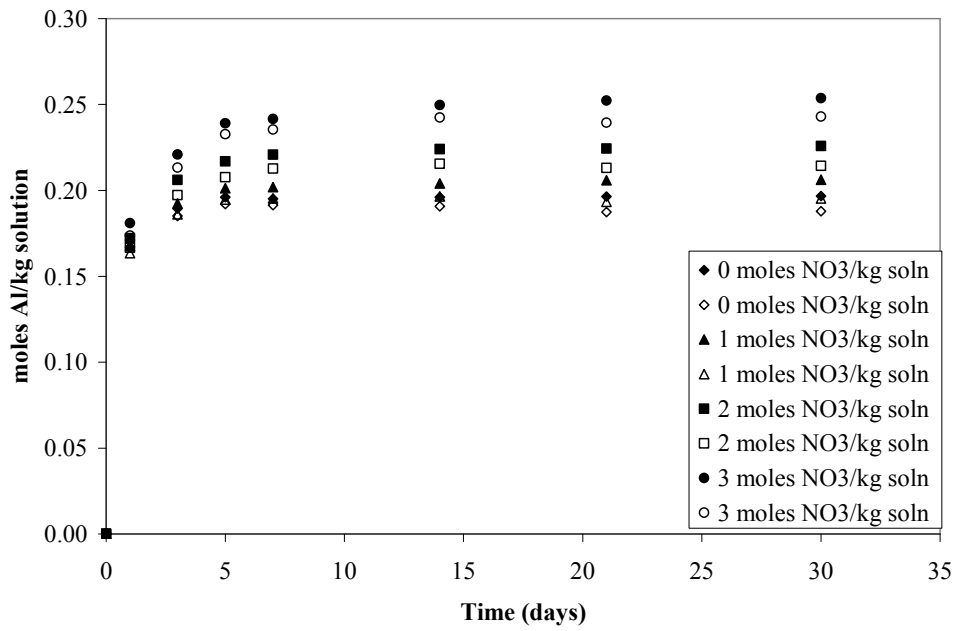


Figure 6.1. Gibbsite Dissolution in 3 M NaOH and Nitrate Solutions

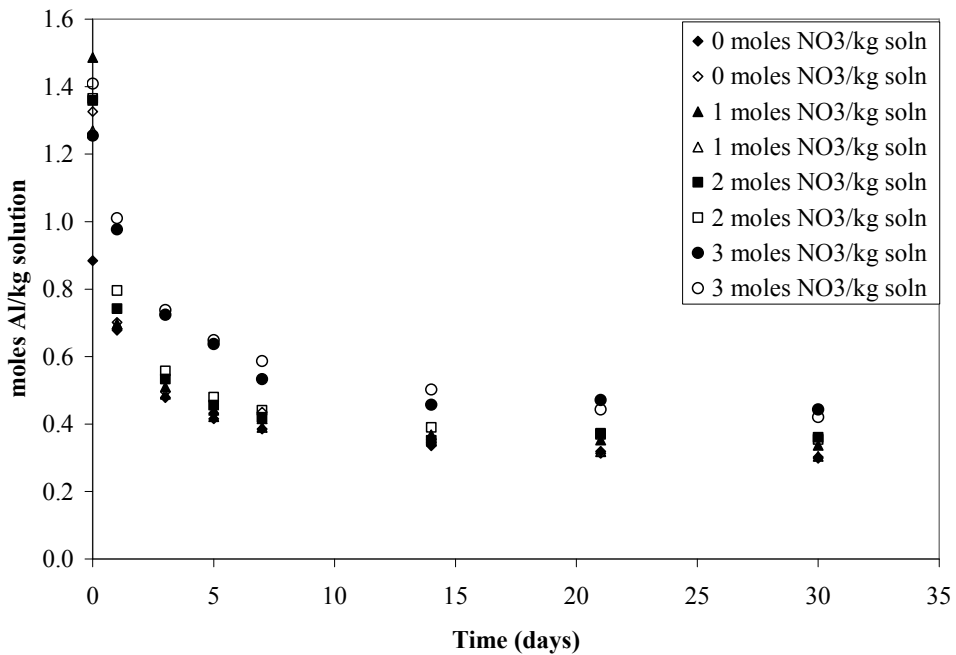


Figure 6.2. Gibbsite Precipitation in 3-M NaOH and Nitrate Solutions

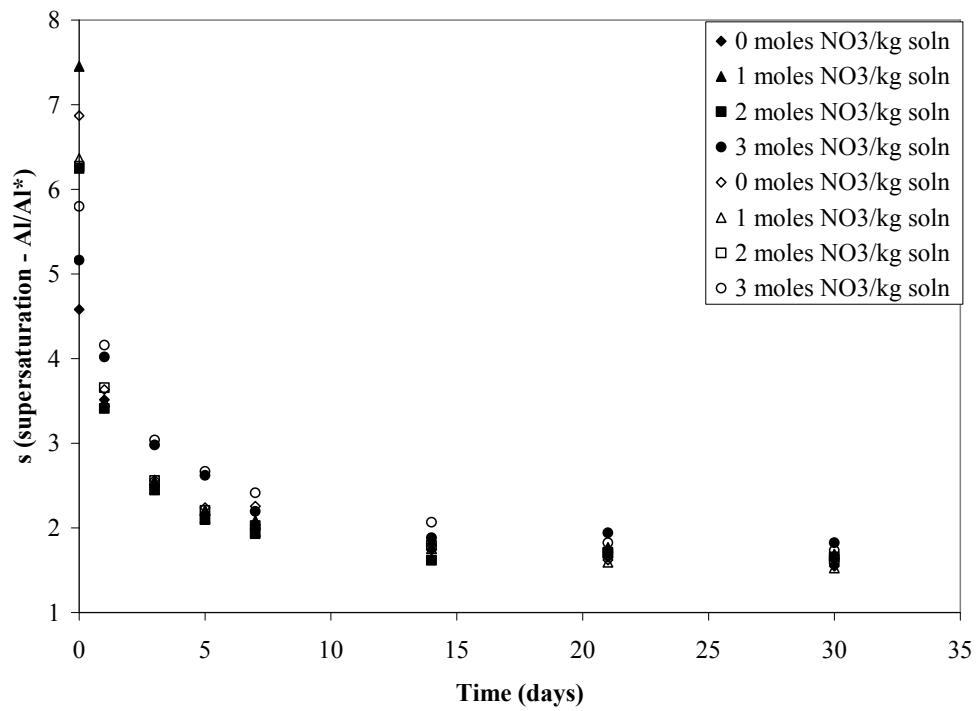


Figure 6.3. Gibbsite Supersaturation in 3-M NaOH and Nitrate Solutions

7.0 Anion Effect on Gibbsite Dissolution

With regard to gibbsite dissolution behavior, the effect of anions on the kinetics of gibbsite dissolution was examined. Two tests were completed: 1) one that examined the effect of the aluminate anion on the rate of gibbsite dissolution and 2) another that determined if the presence of secondary anions typical of Hanford tank wastes (carbonate, free-hydroxide, nitrate, nitrite, oxalate, phosphate, and sulfate) affect gibbsite dissolution. Both sets of experiments provided insight into how composition variations in the suspending phase impact the effectiveness of dissolution processes.

Two gibbsite dissolution tests were performed at 60°C and 3 M NaOH (note that these conditions were selected to provide correlation to prior test work) with 1-wt% gibbsite solids. For the first test, the initial aluminate concentration was equal to 50% of the gibbsite solubility at 60°C. No other anions were present. The second test was identical to the first, with the exception that the other ions listed in Table 7.1 were added. It was fully mixed, and samples were taken at 1, 2, 4, 8, and 24 hours. Initial and final supernate samples were submitted for ion chromatography (IC) analysis to determine anion concentrations. The intermediate samples were submitted for inductively coupled plasma-atomic emission spectroscopy (ICP-AES) analysis to determine the Na and Al concentration and potentiometric titration to determine the hydroxide concentration. The analytical results for these tests are shown in Table A.6.

Table 7.1. Molar Concentration of Sodium Salts

Component	Chemical Formula	Concentration (M)
Sodium phosphate	$\text{Na}_3\text{PO}_4 \cdot 12\text{H}_2\text{O}$	0.008
Sodium sulfate	Na_2SO_4	0.005
Sodium carbonate	Na_2CO_3	0.36
Sodium oxalate	$\text{Na}_2\text{C}_2\text{O}_4$	0.01
Sodium nitrite	NaNO_2	0.33
Sodium nitrate	NaNO_3	0.90

It was determined that adding anions and/or aluminate up to 50% of gibbsite solubility had limited if any effect on the dissolution rate of gibbsite as shown in Figure 7.1.

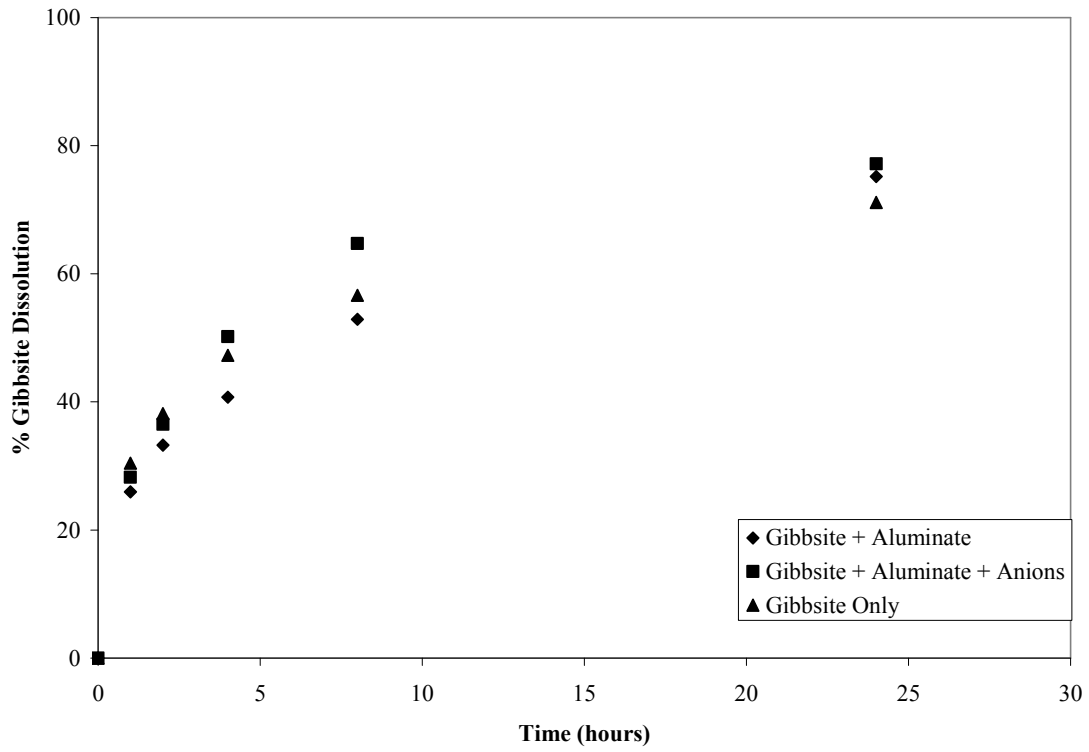


Figure 7.1. Gibbsite Dissolution Results with Aluminate and Anions

8.0 Gibbsite Simulant Evaluation Against Actual Waste Results

The objective of these tests was to determine the effect of hydroxide concentration on the dissolution kinetics of different gibbsites and compare these results to the actual waste testing to verify that the gibbsite chosen matched the behavior of the actual waste as close as possible under different leaching conditions.

The G4, G2, and G3 gibbsite sources were used in this testing. Table 8.1 shows the test matrix that was performed using 1-wt% gibbsite solids. They were fully mixed, and samples were taken at 1, 2, 4, 8, and 24 hours and analyzed for Al and Na with ICP-AES with the results shown in Tables A.7 and A.8.

Table 8.1. Gibbsite Revision Test Matrix

Test ID	Gibbsite Source	Temperature (°C)	Leach Soln. Conc.
GRT-1	G2	60	5 M NaOH
GRT-2	G2	60	3 M NaOH
GRT-3	G2	60	1 M NaOH
GRT-4	G3	60	5 M NaOH
GRT-5	G3	60	3 M NaOH
GRT-6	G3	60	1 M NaOH
GRT-7	G4	60	5 M NaOH
GRT-8	G4	60	3 M NaOH
GRT-9	G4	60	1 M NaOH

Figure 8.1 through Figure 8.3 compare the three gibbsites tested (G2, G3, and G4—which is the current baseline) in various NaOH concentrations along with the two actual waste samples from Group 3 (PUREX Cladding Waste Sludge) and Group 4 (REDOX Cladding Waste Sludge), respectively.^(a) Group 3 and Group 4 were leached with the same concentration of NaOH and the same temperature as the three gibbsite simulants.

It appears that G4 is the best fit with the actual waste samples, which were nearly pure gibbsite (~90 wt%). This is consistent with the morphology assessment on which G4 was chosen originally.

(a) LA Snow et al. Nov. 2008. *Characterization and Leach Testing for PUREX Cladding Sludge (Group 3) and REDOX Cladding Sludge (Group 4) Actual Waste Sample Composites*. WTP-RPT-167, Rev. A.

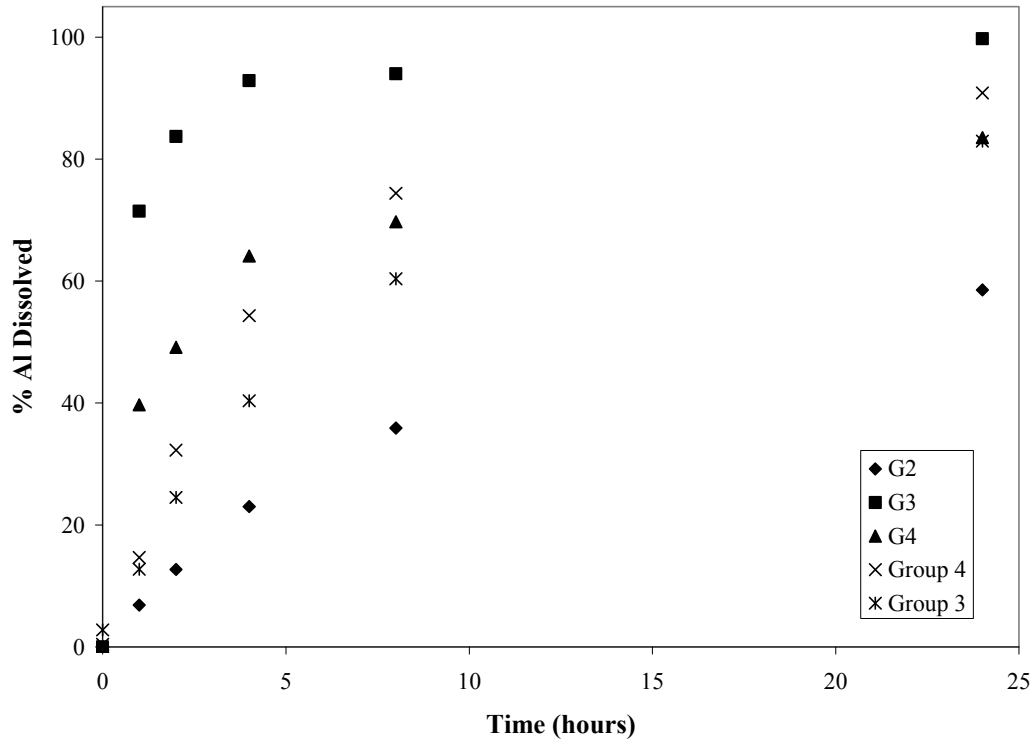


Figure 8.1. Gibbsite Dissolution in 1 M NaOH

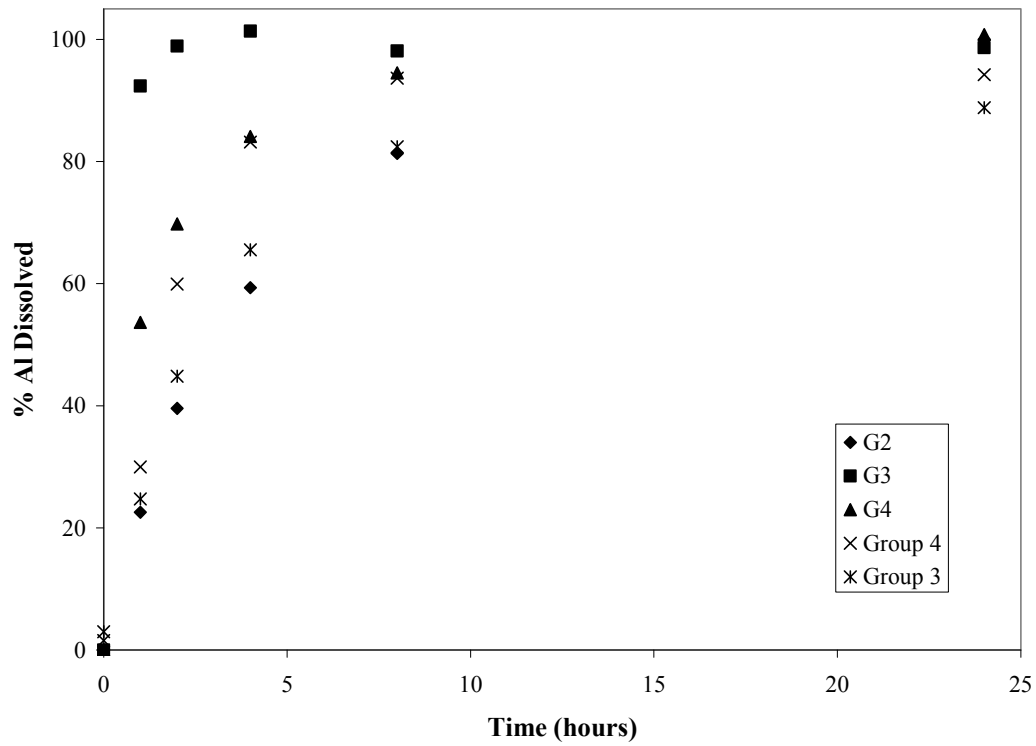


Figure 8.2. Gibbsite Dissolution in 3 M NaOH

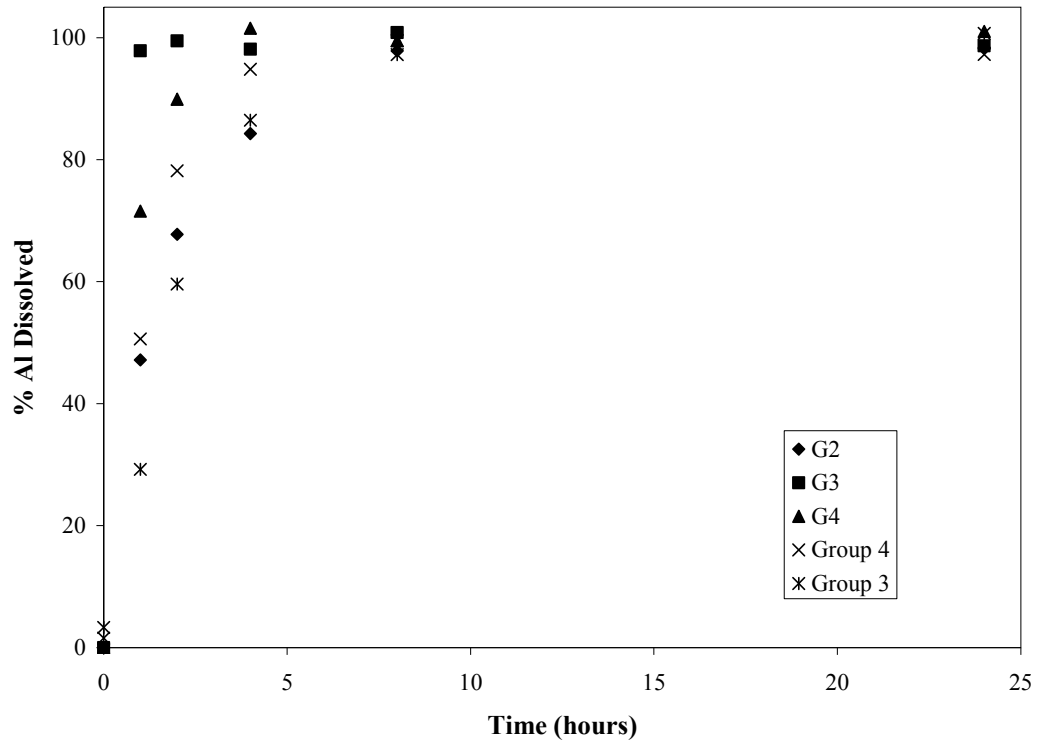


Figure 8.3. Gibbsite Dissolution in 5 M NaOH

9.0 Conclusions and Recommendations

Five samples of gibbsite were obtained from two sources, BASF and Almatris. They were physically characterized, and then a screening leach test was performed to provide dissolution rate data for these gibbsite samples that could be compared to the data for actual waste gibbsite dissolution rates.

The gibbsite simulant selection for further testing was based primarily on the crystal size and shape of the simulant particles in comparison to the actual waste gibbsite particles, due to lack of actual waste-dissolution data available at that time.

Based on the characterization and leaching results, it was determined that G1 (BASF CP-5) was not gibbsite but appeared to be amorphous alumina. Therefore, this sample was immediately eliminated from consideration for further testing. Samples G2 and G3 behaved similarly in the screening leach test, with 100% dissolving by the end of the test. Sample G4 dissolved a little slower than G2 and G3. Sample G5 dissolved very slowly and had not completely dissolved by the end of the leaching test. This is most likely because of the large particle size of this gibbsite. Therefore, it was decided to proceed with further testing using G4 (Almatris Hydrated Alumina Ath C333).

The effect of temperature, mixing speed and $[\text{OH}^-]$ on the G4 gibbsite dissolution was tested. It was found that hydroxide concentration, leaching temperature, and mixing rate all have significant effects on the gibbsite dissolution.

The G4 gibbsite simulant that was chosen to be the “component” simulant was blended in a specified ratio with the other chosen “component” simulants for boehmite and ultrafiltration. This blended simulant was then retested over a subset of the matrix conditions in which the component simulants had been tested previously. These results show how the other components interact with the gibbsite and whether they hinder, help, or have no effect on its dissolution. These results showed that gibbsite dissolution is fast under these conditions (5.8 M NaOH at 100°C) with it being essentially fully dissolved within 1 hour. It also appeared that the sludge and oxalate had no significant effect on the gibbsite dissolution. Therefore, it is concluded that blending the gibbsite simulant component with sludge and oxalate simulant components does not affect its dissolution from the simulant.

A series of tests were performed using the G4 gibbsite (Almatris C333) with varying amounts of nitrate present in the caustic leach solution to determine what effect, if any, nitrate has on the dissolution and precipitation of gibbsite in caustic solution. It was observed in the effect of nitrate on gibbsite dissolution that as the nitrate concentration increases, the solubility of the gibbsite in 3-M caustic solution for both dissolution and precipitation increases also. The kinetics of gibbsite dissolution does not appear to be affected by the presence of nitrate. However, the kinetics of the precipitation was slower with nitrate present. The precipitation was not complete after the 30 days as the amount of aluminum in solution was still decreasing, but the saturation of aluminum in solution was asymptotically approaching a number greater than 1, which indicates that the aluminum in solution may be capable of remaining supersaturated.

It was also determined that adding anions and/or aluminate had no significant effect on the dissolution rate of gibbsite.

It appears that gibbsite G4 (Almatis Hydrated Alumina Ath C333) is the best fit with the actual waste samples, which is consistent with the morphology assessment on which it was chosen and therefore is an appropriate simulant.

It is therefore recommended that Almatis Hydrated Alumina Ath C333 be used as the gibbsite simulant in the performance evaluation program testing activities at the PEP.

10.0 References

Fiskum SK, Buck, EC, Daniel, RC, Draper, K, Edwards, MK, Hubler, TL, Jagoda, LK, Jensen, ED, Lumetta, GJ, McNamara, BK, Peterson, RA, Sinkov, SI, and Snow, LA. 2008. *Characterization and Leach Testing for REDOX Sludge and S-Saltcake Actual Waste Sample Composites*. WTP-RPT-157, Rev. 0, Pacific Northwest National Laboratory, Richland, Washington.

Li H, J Addai-Mensah, J Thomas, and A Gerson. 2005. "The influence of Al (III) supersaturation NaOH concentration on the rate of crystallization of Al(OH)₃ precursor particles from sodium aluminate solutions." *Journal of Colloid and Interface Science* 286:511-519.

Lumetta GJ, BM Rapko, MJ Wagner, J Liu, and YL Chen 1996. *Washing and Caustic Leaching of Hanford Tank Sludges: Results of FY 1996 Studies*. PNNL-11278, Pacific Northwest National Laboratory, Richland, Washington.

Lumetta G. BM Rapko, J Liu, and DJ Temer. 1998. "Enhanced Sludge Washing for Pretreating Hanford Tank Sludges." *Science and Technology for Disposal of Radioactive Tank Wastes*, WW Schulz and NJ Lombardo, eds., Plenum Press, New York, pp. 203-218.

Packter A, and HS Dhillon. 1974. "Studies on recrystallised aluminum hydroxide precipitates. Kinetics and mechanism of dissolution by sodium hydroxide solutions." *Colloid and Polymer Science* 252:249-256.

Smith GL. 2006. *Characterization and Small Scale Testing of Hanford Wastes to Support the Development and Demonstration of Leaching and Ultrafiltration Pretreatment Processes*. WTP Project Doc. No. 24590-PTF-TSP-RT-06-006, Rev. 0.

Sundar PS. 2006. *Characterization and Small Scale Testing of Hanford Wastes to Support the Development and Demonstration of Leaching and Ultrafiltration Pretreatment Processes*. WTP Project Doc. No. 24590-PTF-TSP-RT-06-003, Rev. 0.

11.0 Further Reading

- Barnes S, and R Voke. 2006. *Issue Response Plan for Implementation of External Flowsheet Review Team (EFRT) Recommendations - M12, Undemonstrated Leaching Processes*. WTP Project Doc. No. 24590-WTP-PL-ENG-06-0024, Rev. 0.
- Benezeth P, DA Palmer, and DJ Wesolowski. 1997. *The Aqueous Chemistry of Aluminum. A New Approach to High-Temperature Solubility Measurements*. *Geothermics* 26(4):465-481.
- Brooks KP, PR Bredt, SK Cooley, GR Golcar, LK Jagoda, KG Rappe, and MW Urie. 2000. *Characterization, Washing, Leaching, and Filtration of AZ-102 Sludge*. PNWD-3045, Rev. 0, Battelle—Pacific Northwest Division, Richland, Washington.
- Geeting J, RT Hallen, LK Jagoda, AP Poloski, RD Scheele, and DR Weier. 2003. *Filtration, Washing, and Caustic Leaching of Hanford Tank AZ-101 Sludge*. PNWD-3206, Rev. 1, Battelle—Pacific Northwest Division, Richland, Washington.
- Geeting JGH, KP Brooks, RT Hallen, LK Jagoda, AP Poloski, DR Weier, and RD Scheele. 2002. *Filtration, Washing and Caustic Leaching of Hanford Tank AZ-101 Sludge*. WTP-RPT-043, Battelle—Pacific Northwest Division, Richland, Washington.
- Lucas L. 2006. *Hanford Waste Treatment and Immobilization Plant (WTP) Project Response Plan for Resolution of Issues Identified by the Comprehensive Review of the WTP Flowsheet and Throughput*. WTP Project Doc. No. 24590-WTP-PL-ENG-06-0008, Rev 0.
- Lumetta GJ, IE Burgeson, MJ Wagner, J Liu, and YL Chen. 1997. *Washing and Caustic Leaching of Hanford Tank Sludge: Results of FY 1997 Studies*. PNNL-11636, Pacific Northwest National Laboratory, Richland, Washington.
- Lumetta GJ, KJ Carson, LP Darnell, LR Greenwood, FV Hoopes, RL Sell, SI Sinkov, CZ Soderquist, MW Urie, and JJ Wagner. 2001. *Caustic Leaching of Hanford Tank S-110 Sludge*. PNL-13702, Pacific Northwest National Laboratory, Richland, Washington.
- Lumetta GJ, and RT Hallen. 2007. *Review of Caustic Leaching Testing With Hanford Tank Waste Sludges*. WTP-RPT-151, Rev. 0, Pacific Northwest National Laboratory, Richland, Washington.
- Packter A. 1976. “Studies on recrystallised aluminum mono-hydroxide precipitates. Kinetics of dissolution by sodium hydroxide solutions.” *Colloid and Polymer Science* 254:1024-1029.
- Rapko BM, GJ Lumetta, and MJ Wagner. 1995. *Washing and Caustic Leaching of Hanford Tank Sludges: Results of FY1995 Studies*. PNL-10712, Pacific Northwest Laboratory, Richland, Washington.
- Smith GL, and K Prindiville. 2002. *Guidelines for Performing Chemical, Physical, and Rheological Properties Measurements*. WTP Project Doc. No. 24590-WTP-GPG-RTD-001, Rev. 0.
- Smith GL. 2003. *Guideline for R&T Simulant Development, Approval, Validation, and Documentation*. WTP Project Doc. No. 24590-WTP-GPG-RTD-004, Rev. 0.

Sundar PS. 2006. *Process Development for Design of Oxidative Leaching of Hanford Wastes*. WTP Project Doc. No. 24590-PTF-TSP-RT-06-002, Rev 0.

Temer DJ, and R Villarreal. 1995. *Sludge Washing and Alkaline Leaching Tests on Actual Hanford Tank Sludge: A Status Report*. LA-UR-95-2070, Los Alamos National Laboratory, Los Alamos, New Mexico.

Temer DJ, and R Villarreal. 1996. *Sludge Washing and Alkaline Leaching Tests on Actual Hanford Tank Sludge: FY1996 Results*. LA-UR-96-2839, Los Alamos National Laboratory, Los Alamos, New Mexico.

Temer DJ, and R Villarreal. 1997. *Sludge Washing and Alkaline Leaching Tests on Actual Hanford Tank Sludge: FY1997 Results*. LA-UR-97-2889, Los Alamos National Laboratory, Los Alamos, New Mexico.

U.S. Department of Energy, Office of Environmental Management (DOE-EM). 2006. *Comprehensive Review of the Hanford Waste Treatment Plant Flowsheet and Throughput - Assessment Conducted by an Independent Team of External Experts*. WTP Project Doc. No. CCN 132846, chartered by the Hanford Waste Treatment and Immobilization Plant Project at the direction of DOE-EM, Washington DC.

U.S. Department of Energy, Office of Environmental Management (DOE-EM). 2006. *Background Information and Interim Reports for the Comprehensive Review of the Hanford Waste Treatment Plant Flowsheet and Throughput - Assessment Conducted by an Independent Team of External Experts*. WTP Project Doc. No. CCN 132847, chartered by the Hanford Waste Treatment and Immobilization Plant Project at the direction of DOE-EM, Washington DC.

Appendix A

Actual Analytical Data

Appendix A: Actual Analytical Data

Table A.1. Gibbsite Screening Test Leaching Results (PNNL ASR# 7921)

Time (hrs)	G1		G2		G3		G4		G5	
	Al (µg/mL)	Na (µg/mL)	Al (µg/mL)	Na (µg/mL)	Al (µg/mL)	Na (µg/mL)	Al (µg/mL)	Na (µg/mL)	Al (µg/mL)	Na (µg/mL)
0	---	73,500	---	72,100	---	72,500	---	71,000	[0.82]	68,500
1	3,440	77,000	3,550	73,100	3,975	72,100	2,220	69,100	929	68,100
2	3,910	73,500	3,880	72,600	3,930	72,700	2,640	69,700	1,510	69,900
4	4,670	75,700	3,990	72,200	3,860	73,200	3,170	69,400	2,140	67,700
8	5,110	75,100	4,060	73,000	4,000	72,100	3,590	70,500	2,860	68,000
24	5,180	74,300	3,940	73,400	4,030	76,700	3,950	71,800	3,580	70,000
Final	5,400	75,300	3,990	72,000	4,050	71,200	4,070	72,100	3,440	68,500

Table A.2. Al Gibbsite Matrix Test Leaching Results (SWRI SSR# 30803)

Time (hrs)	MTG-1 (mg/L)	MTG-2 (mg/L)	MTG-3 (mg/L)	MTG-4 (mg/L)	MTG-5 (mg/L)	MTG-6 (mg/L)	MTG-7 (mg/L)	MTG-8 (mg/L)	MTG-9 (mg/L)	MTG-10 (mg/L)	MTG-11 (mg/L)	MTG-12 (mg/L)	MTG-13 (mg/L)
0	<3.00	<3.00	<1.00	<1.00	<3.00	<3.00	<1.00	<1.00	7.32	<1.00	<2.00	<2.00	<2.00
1	35,500	8,370	1,770	2,920	1,610	2,970	662	174	35,600	189	4,460	3,770	4,320
2	39,800	11,300	2,320	3,320	2,230	3,820	794	237	40,400	260	5,630	4,970	5,420
4	47,100	15,300	3,120	3,660	3,090	4,690	929	322	43,600	345	6,890	6,280	6,710
8	47,000	21,200	4,090	3,900	4,220	5,720	1,090	433	45,600	459	7,980	7,740	8,040
24	48,900	27,500	6,200	4,170	7,150	7,810	1,380	686	48,900	694	9,950	10,500	10,100
Final	56,700	27,600	6,170	4,180	7,370	7,830	1,380	687	48,400	698	9,990	10,400	10,100

Table A.3. Na Gibbsite Matrix Test Leaching Results (SWRI SSR# 30803)

Time (hrs)	MTG-1 (mg/L)	MTG-2 (mg/L)	MTG-3 (mg/L)	MTG-4 (mg/L)	MTG-5 (mg/L)	MTG-6 (mg/L)	MTG-7 (mg/L)	MTG-8 (mg/L)	MTG-9 (mg/L)	MTG-10 (mg/L)	MTG-11 (mg/L)	MTG-12 (mg/L)	MTG-13 (mg/L)
0	109,000	128,000	21,700	21,800	106,000	105,000	22,000	21,900	107,000	21,600	67,100	66,500	66,800
1	102,000	116,000	21,800	22,200	104,000	104,000	22,500	22,000	99,500	21,900	65,900	66,700	66,300
2	100,000	108,000	21,800	22,000	104,000	108,000	22,000	20,900	100,000	21,900	65,700	66,600	66,300
4	110,000	106,000	22,000	22,400	105,000	105,000	22,100	22,400	99,700	21,900	66,100	66,300	67,200
8	104,000	106,000	22,100	22,800	104,000	106,000	22,200	21,100	99,400	22,000	65,800	66,200	67,100
24	103,000	108,000	22,500	22,400	104,000	106,000	22,600	21,200	101,000	21,800	66,300	66,000	66,500
Final	122,000	106,000	22,500	23,100	104,000	104,000	21,700	21,400	101,000	21,600	66,200	66,500	67,100

Sodium concentrations do not match the leaching solution concentration (1 M and 5 M) because of analytical uncertainties.

Table A.4. Blended Matrix Gibbsite Leaching Test Results (SWRI SSR# 31241 and 31334)

Time (hrs)	BSM-3		BSM-4		BSM-4a	
	Al (mg/L)	Na (mg/L)	Al (mg/L)	Na (mg/L)	Al (mg/L)	Na (mg/L)
0	6.61	120,000	5.97	117,000	6.37	97,700
1	13,000	117,000	13,000	118,000	10,700	95,100
2	13,100	117,000	13,000	119,000	11,200	99,100
4	13,000	117,000	13,200	119,000	10,900	95,900
8	13,100	119,000	13,400	121,000	10,900	95,900
24	13,300	121,000	14,400	127,000	10,900	96,100
Final	13,100	120,000	14,300	126,000	10,900	95,200

Table A.5. Nitrate Effect on Gibbsite Leaching Test Results (SWRI SSR# 31108 and 31063)

Time (days)	GNE-1a		GNE-2a		GNE-3a		GNE-4a	
	Al (mg/L)	Na (mg/L)	Al (mg/L)	Na (mg/L)	Al (mg/L)	Na (mg/L)	Al (mg/L)	Na (mg/L)
21	5,910	64,900	6,540	91,100	7,530	125,000	8,990	157,000
30	5,920	64,100	6,550	94,400	7,580	122,000	9,040	157,000
Time (days)	GNE-1b		GNE-2b		GNE-3b		GNE-4b	
	Al (mg/L)	Na (mg/L)	Al (mg/L)	Na (mg/L)	Al (mg/L)	Na (mg/L)	Al (mg/L)	Na (mg/L)
21	5,640	63,700	6,140	93,100	7,150	122,000	8,530	163,000
30	5,650	64,900	6,200	92,100	7,190	121,000	8,660	158,000
Time (days)	GNE-5a		GNE-6a		GNE-7a		GNE-8a	
	Al (mg/L)	Na (mg/L)	Al (mg/L)	Na (mg/L)	Al (mg/L)	Na (mg/L)	Al (mg/L)	Na (mg/L)
21	9,600	71,300	11,200	106,000	12,500	133,000	16,800	173,000
30	9,080	72,300	10,700	106,000	12,100	134,000	15,800	171,000
Time (days)	GNE-5b		GNE-6b		GNE-7b		GNE-8b	
	Al (mg/L)	Na (mg/L)	Al (mg/L)	Na (mg/L)	Al (mg/L)	Na (mg/L)	Al (mg/L)	Na (mg/L)
21	9,420	75,000	10,100	101,000	12,400	133,000	15,800	172,000
30	8,990	73,900	9,670	99,500	11,900	135,000	15,000	171,000

Table A.6. Aluminate Ion Effect on Gibbsite Leaching Test Results (SWRI SSR# 31421)

Time (hrs)	GAM-1		GAM-2	
	Al (mg/L)	Na (mg/L)	Al (mg/L)	Na (mg/L)
0	8,190	69,300	7,780	106,000
1	9,470	71,300	9,140	106,000
2	9,830	71,100	9,540	105,000
4	10,200	70,600	10,200	107,000
8	10,800	70,700	10,900	107,000
24	11,900	72,500	11,500	106,000
Final	11,700	70,400	12,600	115,000

Table A.7. Al Gibbsite Simulant Revision Testing Results (SWRI SRR# 33095, 33181, and 33182)

Time (hrs)	GRT-1 (mg/kg)	GRT-2 (mg/kg)	GRT-3 (mg/kg)	GRT-4 (mg/kg)	GRT-5 (mg/kg)	GRT-6 (mg/kg)	GRT-7 (mg/kg)	GRT-8 (mg/kg)	GRT-9 (mg/kg)
0	<2.20	<2.28	<4.81	<4.31	<4.57	<4.51	<4.39	<4.53	<4.75
1	1,740	821	233	3,640	3,390	2,500	2,770	2,060	1,350
2	2,500	1,440	432	3,700	3,630	2,930	3,480	2,680	1,670
4	3,110	2,160	783	3,720	3,650	3,250	3,930	3,230	2,180
8	3,610	2,960	1,220	3,750	3,600	3,290	3,850	3,630	2,370
24	3,630	3,640	1,990	3,670	3,620	3,490	3,910	3,870	2,840
Final	3,690	3,640	2,050	3,720	3,670	3,500	3,870	3,840	2,780

Table A.8. Na Gibbsite Simulant Revision Testing Results (SWRI SRR# 33095, 33181, and 33182)

Time (hrs)	GRT-1 (mg/kg)	GRT-2 (mg/kg)	GRT-3 (mg/kg)	GRT-4 (mg/kg)	GRT-5 (mg/kg)	GRT-6 (mg/kg)	GRT-7 (mg/kg)	GRT-8 (mg/kg)	GRT-9 (mg/kg)
0	95,300	58,900	21,800	97,000	62,700	22,000	97,800	61,900	21,400
1	92,400	58,600	21,300	97,300	62,200	21,300	97,000	61,600	21,600
2	94,500	58,600	21,900	97,300	61,800	22,000	96,400	61,300	21,800
4	93,500	59,200	22,600	98,700	62,200	22,400	101,000	61,000	23,900
8	93,800	62,000	22,000	101,000	61,700	21,800	98,900	61,500	22,300
24	94,900	62,100	22,300	96,800	62,100	22,000	99,100	62,800	21,800
Final	94,300	62,300	22,600	99,300	61,800	21,400	99,200	63,000	20,600

Appendix B
Testing Conditions

Appendix B: Testing Conditions

Table B.1. Gibbsite Screening Test Leaching Conditions

	G1	G2	G3	G4	G5
OH ⁻ conc. (M)	3	3	3	3	3
Leach Temp (°C)	60	60	60	60	60
Density (g/mL)	1.12	1.12	1.12	1.12	1.12
Gibbsite added (g)	8.00	8.00	8.01	8.01	8.01
Caustic soln added (g)	802.09	802.04	802.03	802.03	802.04

Table B.2.a. Gibbsite Matrix Test Leaching Conditions

	MTG-1	MTG-2	MTG-3	MTG-4	MTG-5	MTG-6	MTG-7
OH ⁻ conc. (M)	5	5	1	1	5	5	1
Leach Temp (°C)	80	80	80	80	40	40	40
Density (g/mL)	1.19	1.19	1.04	1.04	1.19	1.19	1.04
Gibbsite added (g)	111.25	55.62	18.01	9.00	48.08	24.03	7.41
Caustic soln added (g)	805.98	806.02	806.02	806.00	805.99	806.01	806.02

Table B.2.b. Gibbsite Matrix Test Leaching Conditions

	MTG-8	MTG-9	MTG-10	MTG-11	MTG-12	MTG-13
OH ⁻ conc. (M)	1	5	1	3	3	3
Leach Temp (°C)	40	80	40	60	60	60
Density (g/mL)	1.04	1.19	1.04	1.12	1.12	1.12
Gibbsite added (g)	3.70	111.25	3.70	29.29	29.28	29.28
Caustic soln added (g)	806.01	806.00	806.01	806.01	806.02	806.00

Table B.3. Blended Matrix Gibbsite Leaching Test Conditions

	BSM-3	BSM-4	BSM-4a
OH ⁻ conc. (M)	5.8	5.8	5.8
Leach Temp (°C)	100	100	100
Density (g/mL)	N/A	N/A	N/A
Gibbsite added (g)	22.73	22.73	22.72
Caustic soln added (19M) (g)	200.30	200.27	200.28
Condensate added (g)	200.66	274.97	274.98
Supernate added (g)	259.93	259.85	259.83
Sludge slurry added (g)	89.90	0	0
Sodium oxalate added (g)	0	6.50	6.50

Table B.4. Nitrate Effect on Gibbsite Leaching Test Conditions

	GNE-1a	GNE-2a	GNE-3a	GNE-4a
OH ⁻ conc. (M)	3	3	3	3
Leach Temp (°C)	25	25	25	25
Density (g/mL)	1.12	1.18	1.24	1.32
Gibbsite added (g)	21.94	21.94	21.95	21.94
Caustic soln added (g)	203.07	203.07	203.08	203.05
NO ₃ ⁻ added (g/kg soln)	0	1	2	3
	GNE-1b	GNE-2b	GNE-3b	GNE-4b
OH ⁻ conc. (M)	3	3	3	3
Leach Temp (°C)	25	25	25	25
Density (g/mL)	1.12	1.18	1.24	1.32
Gibbsite added (g)	21.95	21.94	21.94	21.94
Caustic soln added (g)	203.07	203.06	203.05	203.06
NO ₃ ⁻ added (g/kg soln)	0	1	2	3
	GNE-5a	GNE-6a	GNE-7a	GNE-8a
OH ⁻ conc. (M)	3	3	3	3
Leach Temp (°C)	100 for 8h, then 25	100 for 8h, then 25	100 for 8h, then 25	100 for 8h, then 25
Density (g/mL)	1.12	1.18	1.24	1.32
Gibbsite added (g)	21.95 + 10.97	21.93 + 10.97	21.94 + 10.97	21.94 + 10.97
Caustic soln added (g)	203.05	203.05	203.08	203.06
NO ₃ ⁻ added (g/kg soln)	0	1	2	3
	GNE-5b	GNE-6b	GNE-7b	GNE-8b
OH ⁻ conc. (M)	3	3	3	3
Leach Temp (°C)	100 for 8h, then 25	100 for 8h, then 25	100 for 8h, then 25	100 for 8h, then 25
Density (g/mL)	1.12	1.18	1.24	1.32
Gibbsite added (g)	21.94 + 10.97	21.95 + 10.97	21.94 + 10.97	21.94 + 10.97
Caustic soln added (g)	203.08	203.08	203.08	203.07
NO ₃ ⁻ added (g/kg soln)	0	1	2	3

Table B.5. Aluminate Ion Effect on Gibbsite Leaching Test Conditions

	GAM-1	GAM-2
OH ⁻ conc. (M)	3	3
Leach Temp (°C)	60	60
Density (g/mL)	1.12	1.12
Gibbsite added (g)	8.62	9.68
Caustic soln added (g)	845.02	845.01
NaAlO ₂ added (g)	21.55	21.55
Other Na salts added (g)	0	106.89

Table B.6. Gibbsite Simulant Revision Testing Conditions

	GRT-1	GRT-2	GRT-3	GRT-4	GRT-5	GRT-6	GRT-7	GRT-8	GRT-9
OH ⁻ conc. (M)	5	3	1	5	3	1	5	3	1
Leach Temp (°C)	60	60	60	60	60	60	60	60	60
Density (g/mL)	1.19	1.12	1.04	1.19	1.12	1.04	1.19	1.12	1.04
Type of Gibbsite Used	C31C	C31C	C31C	H710	H710	H710	C333	C333	C333
Gibbsite added (g)	8.00	8.00	8.00	8.00	8.00	8.00	8.00	8.00	8.00
Caustic soln added (g)	806.01	806.01	806.00	806.02	806.03	806.00	806.02	805.99	806.01

Appendix C

Gibbsite Product Specifications

Appendix C: Gibbsite Product Specifications



Global Product Data

Alumina Trihydroxides Exceptionally Pure White Hydrates

Product Information

Almatris white hydrated alumina is aluminum trihydroxide, $Al(OH)_3$, that is produced through special processing of alumina-bearing feedstocks and stringent process control systems. The result is an aluminum trihydroxide of exceptional purity and whiteness. Although aluminum trihydroxide is a dry powder, it contains a high proportion, approximately 35 percent by weight, of chemically combined water. The hydrate is a nonabrasive, low-density material with a Mohs hardness index of 2.5 - 3.5 and a specific gravity of 2.42. White hydrates are used primarily in applications where color and the absence of impurities are critical. They are halogen-free making them excellent nontoxic flame retardant/smoke suppressant fillers for plastic compounds.

Product Description

Almatris precipitates a highly pure gibbsite phase of alpha alumina trihydrate. The Almatris proprietary white stream process is designed, through chemical and recrystallization processes, to achieve near 100 percent photovolt brightness and relatively uniform particles.

C-33 and C-31C (coarse)

The precipitation process is controlled to produce two median particle sizes, Grades C-33 (50 microns) and C-31C (85 microns). Both grades have free-flowing properties.

C-333 Ground White Hydrates

A fine size grade is produced by grinding the precipitated grade to form C-333 (7 microns).

Applications

Grades C-33 and C-31C hydrates are used in the manufacture of glass, chemicals, catalysts, vitreous enamels and ceramic whitewares, and as additives in high quality pigments. These products are also used as additives and fillers in polymer systems such as electrical wire insulation and high quality cultured onyx and solid countertop surfacing material. Aluminum trihydroxides are preferred because of their good arc and track resistance, aesthetic properties, reinforcing characteristics, and performance as nontoxic smoke suppressants and flame retardants.

C-333 is a ground version of the precipitated grade. It is used in polymer formulations, toothpastes, adhesives, coatings, paper, cosmetics, waxes, and polishes.

Think alumina, think Almatris.

GP-SH/024/R05/1207/MSDS 839



Alumina Trihydroxides

Exceptionally Pure White Hydrates

Product	Aluminum Trihydroxides			Test Methods
	C-33	C-31C	C-333	
Chemical Composition (%)				
Al(OH) ₃ (min)	99.6	99.6	99.6	Difference
SiO ₂	0.003	0.003	0.003	DC Arc Optical Emission Spectrometry
Fe ₂ O ₃	0.009	0.009	0.009	
Na ₂ O (total)	0.20	0.26	0.17	
Na ₂ O (soluble)	0.008	0.008	0.026	Flame Emission Photometry
Moisture	0.08	0.08	0.26	Microwave
Physical Properties				
Loose bulk density (g/cm ³)	1.07	1.15	0.76	Modified ASTM B212-89
Packed bulk density (g/cm ³)	1.3	1.3	1.15	Modified ASTM B527-85
Refractive index	1.57	1.57	1.57	
Mohs hardness	2.5-3.5	2.5-3.5	2.5-3.5	
Density (g/cm ³)	2.42	2.42	2.42	
Surface area (m ² /g)	-	-	3.0	BET
LOI (%)	34.6	34.6	34.6	From 110-1100°C
Color	White	White	White	
Particle Size Distribution				
% on 100 Tyler mesh	0	0	-	
% on 200 Tyler mesh	8	45	0	
% on 325 Tyler mesh	60	90	1	
% through 325 Tyler mesh	40	10	99	Wet Screen
d50 (µ)	50	85	7	Sediograph 5100 or Microtrac

2003 Data - All data are based upon Almatis standard test methods, and all test methods are available upon request.
Unless stated otherwise values are typical.



Contacts for sales, technical information and application assistance

Almatis GmbH
Lyoner Straße 9
60528 Frankfurt/Germany
Phone
49 69 957 341 0
Fax
49 69 957 341 13

Almatis, Inc.
501 West Park Road
Leetsdale, PA 15056
USA
Phone (within US)
1 800 643 8771
Phone (outside US)
1 412 630 2800
Fax
1 412 630 2900

Qingdao Almatis Co., Ltd.
15F, Sunshine Tower
61 Hongkong Middle Road
Qingdao, 266071, China
Phone
86 532 8572 8035
Fax
86 532 8572 8551

Almatis Limited
Morimura Bldg.
1-3-1 Toranomom
Minato-ku, Tokyo 105-8451
Japan
Phone
81 3 3502 2371
Fax
81 3 3502 2375

Almatis Headquarters
Lyoner Straße 9
60528 Frankfurt/Germany
Phone **49 69 957 341 0**
Fax **49 69 957 341 13**

info@almatis.com
www.almatis.com

MSDS 839

Distribution

**No. of
Copies**

ONSITE

4	<u>Bechtel National, Inc.</u>	
	WTP R&T Docs (2)	H4-02
	P. S. Sundar	H4-02
	S. Barnes	H4-02
8	<u>Pacific Northwest National Laboratory</u>	
	D. E. Kurath	K3-52
	R. A. Peterson	P7-22
	D. E. Rinehart	K6-24
	R. L. Russell (3)	K6-24
	H. D. Smith	K6-24
	Project File	P7-28